

# Durham E-Theses

---

## *Model compounds related to fluoroelastomers*

Martin Salisbury

### How to cite:

---

Salisbury, Martin (1986) Model compounds related to fluoroelastomers. Doctoral thesis, Durham University.

### Use policy

---

The full-text may be used and/or reproduced, and given to third parties in any format or medium, without prior permission or charge, for personal research or study, educational, or not-for-profit purposes provided that:

- a full bibliographic reference is made to the original source
- a <https://etheses.durham.ac.uk/id/eprint/9318/> is made to the metadata record in Durham E-Theses
- the full-text is not changed in any way

The full-text must not be sold in any format or medium without the formal permission of the copyright holders.

Please consult the [full Durham E-Theses policy](#) for further details.

The copyright of this thesis rests with the author.  
No quotation from it should be published without  
his prior written consent and information derived  
from it should be acknowledged.

UNIVERSITY OF DURHAM

A THESIS

Entitled

MODEL COMPOUNDS RELATED  
TO FLUOROELASTOMERS

Submitted by

MARTIN SALISBURY, B.Sc.

(University College)

A Candidate for the Degree of Doctor of Philosophy

1986



-1. DEC. 1986

To My Late Father

ACKNOWLEDGEMENTS

I would like to thank Professor R.D. Chambers for his excellent supervision, advice and discussions throughout this work.

I would also like to thank: Dr. R.S. Matthews for his help in interpreting the n.m.r. spectra; Dr. M. Jones and Mr. V.J. McNeilly for the running and discussion of mass spectra; and Mr. T.F. Holmes for his advice about practical work.

I am also indebted to the many technical staff who assisted me: Messrs. R. Hart and G. Haswell for their expert glass-blowing; Mr. J.A. Parkinson for his help and advice with gas chromatography; Mr. D. Hunter for his help with high-pressure reactions; and Mrs. M. Cocks for analyses.

Thanks go also to Dr. Alberto Fontana (Montefluos SPA - Milan) for his liaison and discussions throughout the whole of this project.

I am also grateful to my colleagues in the laboratory who helped with ideas, and to Mrs. Marion Wilson for her hospitality and advice during the typing of this thesis.

Last, but not least, I would like to express my gratitude to my mother and family for their encouragement during the time of this research.

MEMORANDUM


The work described in this thesis was carried out at the University of Durham between October 1982 and August 1985 and is original except where stated by reference. This work has not previously been submitted, either wholly or in part, for a degree at this or any other university.

by


MARTIN SALISBURY

ABSTRACT

The aims of the research described in this thesis were to explore the chemistry of some model compounds related to fluorohydrocarbon polymers, in particular the copolymer of (I), especially to obtain definitive information about mechanisms of cross-linking and polymer degradation and to explore new approaches to cross-linking.

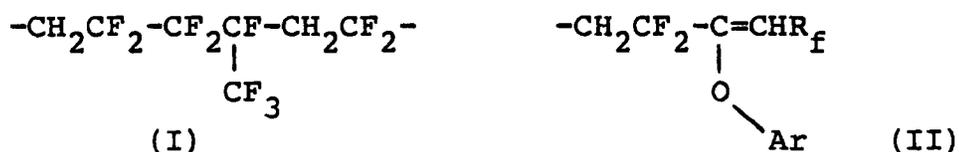


A range of model compounds of the form (III) and (IV) were synthesized and the results obtained demonstrate that aryl-ether cross-links of the form (II) are stable in the presence of various bases at elevated temperatures. This indicates that these links are not responsible for the instability of copolymers cured in this way.

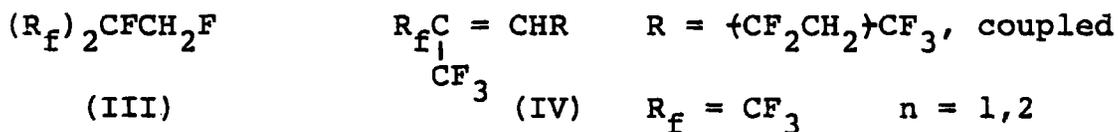


Models of the form (III) and (IV) show surprisingly low reactivity under typical curing conditions, indicating that either the polymers themselves are more reactive or reaction occurs by an unexpected mechanism.


In pursuit of the likely cross-linking mechanism it was shown that polymers of the forms (I) and  $\text{-(CF}_2\text{CH}_x\text{F}_{2-x}\text{)-}_n$ ,  $x=1,2$ , are highly susceptible to elimination of HF in the presence of Lewis acids, *e.g.*  $\text{SbF}_5$  to yield highly unsaturated materials. Model chemistry involving  $\text{SbF}_5$  resulted in novel eliminations of HF, *e.g.*



the formation of some stable long-lived carbocations, *e.g.*

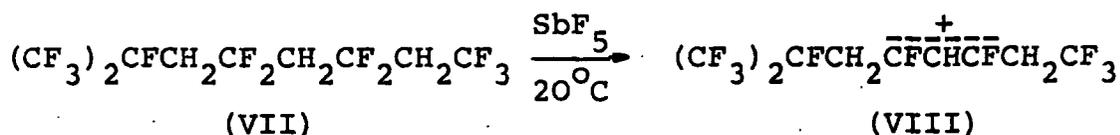


and other novel chemistry, *e.g.* a 1,5 elimination of HF

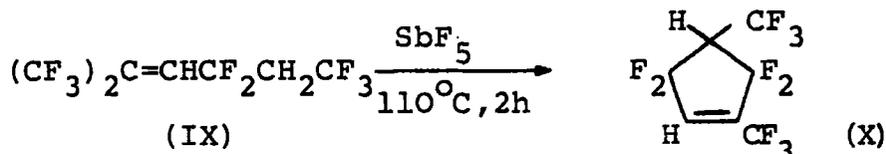


A new approach to cross-linking was also developed involving the incorporation into the copolymer (I) of crowded comonomer units, *e.g.* when copolymers containing the structures (XI) where heated radicals were found *via* homolytic cleavage to promote cross-linking:



General examination of the model compounds yielded new reactions including a route to seven-membered cyclic ethers,

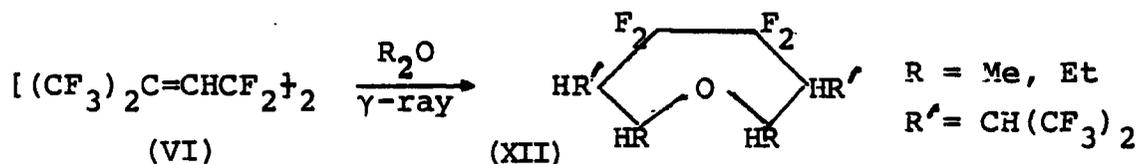

and an unexpected ring closure reaction catalysed by  $\text{NBu}_3, (\text{HF})_x$ ,

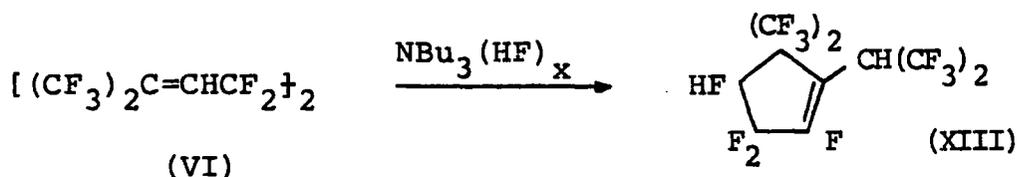

The reactivity of the models was also examined in the areas of nucleophilic attack, base-catalysed elimination of HF,

addition of 1,3-dipoles, the formation of long-lived carbanions and one-electron transfer chemistry. The results obtained considerably broaden the chemistry of this class of compound.

CONTENTS

	<u>PAGE NO.</u>
Acknowledgements	i
Memorandum	ii
ABSTRACT	iii
INTRODUCTION	1
GENERAL INTRODUCTION - ORGANOFLUORINE CHEMISTRY	2
CHAPTER ONE - FLUOROPOLYMERS	4
A. Fluoropolymers and Industry	4
B. Fluoropolymers <i>via</i> Fluorinated Alkenes	4
(i) Availability of Fluorinated Alkenes	4
(ii) The Effect of Fluorine in Free-Radical Additions	5
(iii) Mechanistic Aspects of Polymerisation	12
(iv) Polymerisation Methods	19
(v) Properties of Fluoropolymers	20
(vi) The Uses and Applications of Fluoropolymers	26
C. Miscellaneous Fluoroelastomers	26
D. Cross-linking of Copolymers of 1,1-Difluoroethene	26
(i) Introduction	26
(ii) Cross-Linking Involving Amines	31
(iii) Cross-Linking Involving Bisphenols	37
(iv) The Use of Cure-Site Comonomers	42
(v) Other Methods	45
E. Model Studies Related to Cross-Linking	47
(i) Introduction	47
(ii) Discussion of Results Obtained	48
(iii) Conclusions	55
CHAPTER TWO - SYNTHESIS AND EXAMINATION OF SATURATED MODEL COMPOUNDS	56
A. Introduction - Research Objectives	56
B. Choice of Model Compounds and Strategy	56
C. Synthesis of Model Compounds	57
(i) Synthesis of 2-Iodoheptafluoropropane	57
(ii) Telomerization Reactions	57
(iii) Coupling Reactions	60
(iv) Fluorination of the Telomer Iodides	62

	<u>PAGE NO.</u>
D. Examination of the Saturated Model Compounds	63
(i) Introduction	63
(ii) Response to Curing Agents	64
E. Attempts to Incorporate Bromine	66
F. Conclusions	66
 CHAPTER THREE - SYNTHESIS OF UNSATURATED MODELS	 68
A. Introduction	68
B. Base-Catalysed Elimination of HF	68
(i) Using KOH	68
(ii) Using Lithium Alkyls	68
(iii) Using Nitrogen Bases	69
C. Lewis-Acid Catalysed Eliminations of HF	70
(i) Use of Antimony Pentafluoride	70
(ii) Mechanistic Considerations	70
D. Other Routes to Unsaturated Models	72
(i) Synthesis of 2H-heptafluorobut-2-ene (83)	72
(ii) Reactions of (83) with Sodium Alkoxides	72
 CHAPTER FOUR - REACTIONS OF UNSATURATED MODEL COMPOUNDS	 74
A. Introduction	74
B. The Hydrolytic Stability of the Model Compounds	75
C. The Reactivity of Model Compounds containing the Group $(CF_3)_2C=CH-$	76
(i) Under Typical Cure Conditions	76
(ii) Towards Phenoxide, Hydroxide and Fluoride	77
D. Conclusions	82
(i) Relevance of Results Obtained	82
(ii) Implications for the Copolymer Systems	84
 CHAPTER FIVE - AN APPROACH TO A NEW FREE-RADICAL CROSS-LINKING PROCESS	 85
A. Introduction	85
B. Synthesis of Crowded Comonomers	87
C. Synthesis of Copolymers Incorporating the Crowded Comonomers	87
D. Vacuum Pyrolysis of $CH_2=CF_2/(CF_3)_2CFCF=CF_2$ Copolymers	92

	<u>PAGE NO.</u>
E. Differential Scanning Calorimetry Studies	95
(i) $\text{CH}_2=\text{CF}_2$ Homopolymer and $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$ Copolymer	95
(ii) $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$ Copolymers	96
(iii) $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCH}=\text{CF}_2$ Copolymer	97
(iv) $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2/(\text{CF}_3)_2\text{CFER}=\text{CF}_2$ (R=H,F) Terpolymers	97
F. Attempted Synthesis of a Comonomer to Promote Capto-Dative Free-Radical Stabilization	99
G. Conclusions	101
(i) A Summary of Results obtained	101
(ii) Implications for Cross-Linking	102
CHAPTER SIX - NOVEL CHEMISTRY INVOLVING ANTIMONY PENTAFLUORIDE	104
A. Introduction: An Unusual Discovery	104
B. Some Novel Elimination Reactions	106
(i) A Novel 1,5-Elimination of Hydrogen Fluoride	106
(ii) Cyclisation of a Saturated Fluorohydrocarbon	107
(iii) Attempts to Promote Related Inter-Molecular Reactions	108
C. The Formation of some remarkably Stable Fluorin- ated Cations and their Chemistry	109
(i) Observations	110
(ii) Interpretation of NMR Spectra	112
(iii) Reaction of a Stable Carbocation with Methanol	113
(iv) Other Reactions	115
D. Treatment of Fluorohydrocarbon Polymers with $\text{SbF}_5$ : A Route to Fluorinated Polyacetylenes	117
(i) Introduction	117
(ii) $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$ Copolymer Systems	117
(iii) Homopolymer Systems	118
E. Conclusions	120
CHAPTER SEVEN - THE GENERAL CHEMISTRY OF THE MODEL COMPOUNDS	122
A. Introduction	122

	<u>PAGE NO.</u>
B. Chemistry involving 2-(2H-hexafluoro-2-propyl)-4-hydro decafluoro-3,3-dimethylcyclopentene	122
(i) Reaction with Sodium Methoxide	123
(ii) Pyrolysis Experiments	124
(iii) Reaction of 2-(pentafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene with Caesium Fluoride, Formation of a Stable Carbanion	125
C. Chemistry involving 3,6-Dihydrohexadecafluoro-2,7-dimethylocta-2,6-diene and 2H-nonafluoro-3-methylbut-2-ene	127
(i) Free Radical Additions	127
(ii) Addition of Diazomethane	131
(iii) Attempted Metallations using Butyl Lithium	133
D. One Electron Transfer Reactions involving Tri-n-butylamine	133
(i) 2,2,4,4-Tetrahydrodecafluoro-5-methylhexane and Tri-n-butylamine	134
(ii) 1-Iodo-2,2,4,4-tetrahydroundecafluoro-5-methylhexane and Tri-n-butylamine	136
E. Further Chemistry resulting from 7-Iodo-2-hydrodecafluoro-3-methyl butane	138
(i) Synthesis of Perfluoro-2-methylbut-2-ene	138
(ii) Chemistry of Perfluoro-3-methylbut-2-ene	139
F. Chemistry of 3,6-Dihydroeicosafuoro-2,7-dimethyloctane	142
(i) Reaction with Tri-n-butylamine	142
(ii) Reaction with Caesium Fluoride	144
(iii) Pyrolysis over Potassium Fluoride	144
(iv) Reaction with Potassium Hydroxide	146
G. Chemistry of 2,4-Dihydrotetradecafluoro-5-methylhexane	147
(i) Interpretation of $^{19}\text{F}$ NMR Spectrum	147
(ii) Pyrolysis over Potassium Fluoride	149
EXPERIMENTAL SECTION	150
INSTRUMENTATION	151

PAGE NO.

CHAPTER EIGHT - EXPERIMENTAL FOR CHAPTER TWO - SYNTHESIS AND EXAMINATION OF SATURATED MODEL COMPOUNDS	153
A. Synthesis of Saturated Model Compounds	153
(i) Synthesis of Iodofluoroalkanes	153
(ii) Coupling Reactions	156
(iii) Fluorination of the Telomer Iodides	158
B. Examination of the Saturated Model Compounds	161
(i) Response to MgO and $\text{Ca(OH)}_2$	161
(ii) Response to Bisphenol AF	162
(iii) Response to Phosphonium Salts	162
(iv) Combinations of the Curing Agents	162
C. Attempts to Incorporate Bromine	164
CHAPTER NINE - EXPERIMENTAL FOR CHAPTER THREE - SYNTHESIS OF UNSATURATED MODELS	165
A. Treatment of $[\text{CF}_3]_2\text{CFCH}_2\text{CF}_2\ddagger_2$ with Bases	165
B. Reactions Involving $\text{SbF}_5$	168
C. Unsaturated Models derived from $\text{CF}_3\text{CF}=\text{CHCF}_3$	170
CHAPTER TEN - EXPERIMENTAL FOR CHAPTER FOUR - REACTIONS OF UNSATURATED MODEL COMPOUNDS	173
A. The Hydrolytic Stability of the Model Cross-Links	173
B. Reactivity of Unsaturated Models	175
CHAPTER ELEVEN - EXPERIMENTAL FOR CHAPTER FIVE - AN APPROACH TO A NEW FREE-RADICAL CROSS-LINKING PROCESS	179
A. Synthesis of Crowded Comonomers	179
B. Synthesis of Polymer Samples	179
C. Vacuum Pyrolysis of $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$ Copolymers	180
D. Differential Scanning Calorimetry Studies	183
E. Perfluoroallylfluorosulphate/Diethyl Ether Experiment	184

	<u>PAGE NO.</u>
CHAPTER TWELVE - EXPERIMENTAL FOR CHAPTER SIX - NOVEL CHEMISTRY INVOLVING ANTIMONY PENTAFLUORIDE	185
A. Cyclisation Reactions	185
B. Attempts at Related Reactions	186
C. Elimination Reactions and the Formation of Stable Carbocations	190
D. Dehydrohalogenation of Polymers by $SbF_5$	193
CHAPTER THIRTEEN - EXPERIMENTAL FOR CHAPTER SEVEN - THE GENERAL CHEMISTRY OF THE MODEL COMPOUNDS	194
A. Reactions Involving 1-(3H-hexafluoro-2-propyl-3- hydrodecafluoro-2,2-dimethylcyclopentene	194
B. Reactions involving 3,6-Dihydrohexadecafluoro-2,7- dimethylocta-2,6-diene and 2H-nonafluoro-3-methyl- but-2-ene	196
C. One Electron Transfer Reactions	199
D. Reactions involving Perfluoro-2-methylbut-2-ene	200
E. Reactions of Models derived from 1-Iodo-2-hydro- decafluoro-3-methylbutane	202
APPENDIX ONE - N.M.R. Spectra	205
APPENDIX TWO - Infra Red Spectra	222
APPENDIX THREE - Mass Spectra	231
COLLOQUIA AND CONFERENCES	277
REFERENCES	288

INTRODUCTION




## GENERAL INTRODUCTION

### ORGANOFLUORINE CHEMISTRY

Organofluorine chemistry is a particularly useful and interesting branch of organic chemistry for a number of reasons;<sup>1</sup>

(i) It is possible to replace, extensively, hydrogen in hydrocarbon compounds with fluorine, without generating steric crowding (Van der Waals radii; H 1.20Å, F 1.35Å). Therefore, in principle, a whole new organic chemistry is possible, which is entirely synthetic, based on C-F rather than C-H skeletons.

(ii) Fluorocarbon systems give rise to some very novel chemistry because of the high electronegativity of fluorine. For example, often the chemistry of functional groups is altered



In addition, the C-F chemical bond is comparatively strong (107-121 Kcal mol<sup>-1</sup> *cf.* 98 Kcal mol<sup>-1</sup> for C-H)<sup>2</sup> and this, in conjunction with its associated non-bonding electron pairs, gives rise to a well protected carbon skeleton in most highly fluorinated compounds.

(iii) A range of biologically active partially fluorinated organic compounds have wide applications in the fields of medicine, pharmacy and pest control.<sup>3,4</sup>

(iv) Organofluorine chemistry is of major interest and promise to industry<sup>5,6</sup> for the discovery of new materials

which have greater thermal and chemical resilience while at the same time exhibiting desirable physical properties, *e.g.* elasticity, low surface friction, *etc.*


Clearly, therefore, there is extensive scope for research into all of these areas for the purpose of expanding our understanding of organic chemistry<sup>7</sup> and for producing new materials and new effects that may be exploited by industry.

CHAPTER ONEFLUOROPOLYMERSI.A. Fluoropolymers and Industry



The vast advances in technology, which have been made over the last forty years, in the fields of automation,<sup>8</sup> electronics and space exploration have resulted in a high demand for materials of a very specialised nature; for example, elastomeric materials which retain their rubbery properties over a wide range of temperatures while, at the same time, are resistant to aggressive chemicals, solvents, radiation and weathering. It is in this type of role that fluoropolymers have great value.

I.B. Fluoropolymers via Fluorinated AlkenesI.B. (i) Availability of Fluorinated Alkenes

Near the end of the last century Swarts pioneered the halogen exchange reaction<sup>9</sup>



This discovery provided later workers with a route to many fluorinated alkenes<sup>10-12</sup> as exemplified below:



This and the syntheses of the other industrially important fluoroalkenes are summarised in Table 1.1.


TABLE 1.1 Syntheses of Fluoroalkenes

Alkene	Synthesis	References to other reported routes
$F_2C=CF_2$	$CF_2HCl \xrightarrow{650^\circ C} CF_2=CF_2 + HCl$	(15)
$F_2C=CFC1$	$CF_2ClCFC1_2 \xrightarrow{Zn, CH_3OH} CF_2=CFC1$	(16-18)
$FHC=CH_2$	$CH\equiv CH + HF \xrightarrow[Hg^{2+}]{500^\circ C} CHF=CH_2$	(19-21)
$F_2C=CH_2$	$CH_3CF_2Cl \xrightarrow{870^\circ C} CH_2=CF_2$	(22,23)
$CF_3CF=CF_2$	$CF_2=CF_2 \xrightarrow[steel\ tube]{750-810^\circ C} CF_2=CFCF_3$	(24,25)
$CF_3CF=CFH$	$CF_3CF=CF_2 \xrightarrow{Pd/H_2} CF_3CFHCF_2H \xrightarrow{base} CF_3CF=CFH$	(26)
$CF_3CH=CF_2$	$CF_3CFHCF_2CH_2OH \xrightarrow[(ii)\ NaOH\Delta]{(i)\ Oxidn.} CF_3CH=CF_2$	(27)

-----

I.B. (ii) The Effect of Fluorine in Free-Radical Additions

Polymerisations of the fluorinated alkenes, shown in Table 1.1 proceed *via* free radical addition mechanisms,




and this is the principle process used in industry for forming fluoropolymers.

Free-radical addition, in general, may be represented by the scheme outlined in Figure 1.1.<sup>28</sup>



This preference reflects the stability of the intermediate radical. This consideration is more important when the structure of the transition state most closely resembles the "reactants". For example, consider the separate reactions of chlorine and bromine atoms with propene. The relevant thermodynamic data for the process



is given in Table 1.2<sup>31</sup>

TABLE 1.2 Enthalpy values for  $X^{\cdot} + \text{CH}_2 = \text{CHCH}_3 \longrightarrow \text{XCH}_2\dot{\text{C}}\text{HCH}_3$

$X^{\cdot}$	$\Delta H$
Br $^{\cdot}$	-46kJ mol <sup>-1</sup>
Cl $^{\cdot}$	-109kJ mol <sup>-1</sup>

-----

The energy profiles for these reactions are shown in Figure 1.2. In the case of addition of HCl, the transition state would most closely resemble the "reactants" in structure and may therefore be represented as






Figure 1.2 Energy Profiles for  $X\cdot + CH_2 = CHCH_3 \longrightarrow XCH_2\dot{C}HCH_3$

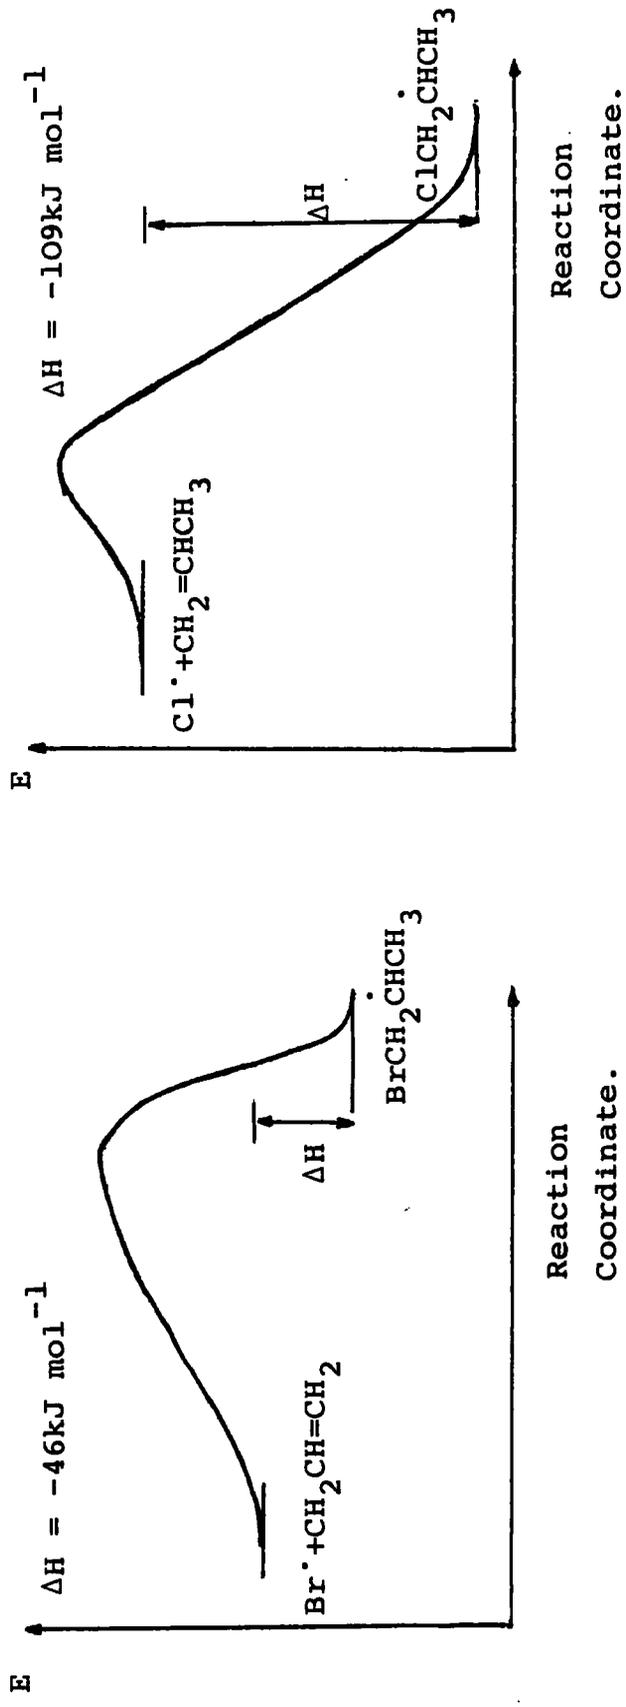


Clearly, the reactivity of this system, *i.e.* free-radical addition of HCl, does not reflect the stability of an intermediate radical. (In fact this reaction is unknown because the radical transfer step  $\text{ClCH}_2\dot{\text{C}}\text{HCH}_3 + \text{HCl} \longrightarrow \text{ClCH}_2\text{CH}_2\text{CH}_3 + \text{Cl}^\cdot$  is endothermic,  $\Delta H = +21\text{kJ mol}^{-1}$ ). In the case of free-radical addition of HBr, however, the transition state more closely resembles the "products" in structure and may be represented as



Therefore the rate of free-radical addition of HBr, which is facile, does to some extent reflect the stability of an intermediate radical.


The rate of free-radical addition is also affected by the strength of the chemical bond being formed. Consider the reactions



$$m + n = 2$$


The stability of the intermediate radical may be ignored because the odd electron resides on a  $-\text{CH}_2-$  group in each case. The activation energy and Arrhenius A factors were compared for  $m = 0, 1, 2$ .<sup>32</sup> It was found that while the Arrhenius factors remained almost constant, there was a steep increase in activation energy on going from  $m=0$  to  $m=2$ . This increase must be due to the enthalpy of bond-formation.

These observations arise from polar effects as illustrated by the reactions -





R = (i) F


(ii) H



Here, although  $\dot{C}F_3$  radicals are always more reactive than  $\dot{C}H_3$  radicals, the reaction (a) (i) is slower than the reaction (b) (i) and the reaction (b) (ii) is slower than the reaction (a) (ii). Consider the additions of thiols to trifluoroethene<sup>33</sup> (Scheme 1.2):

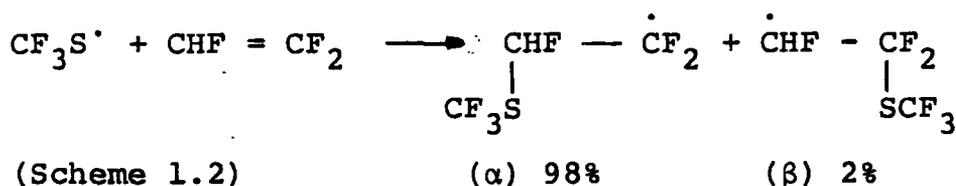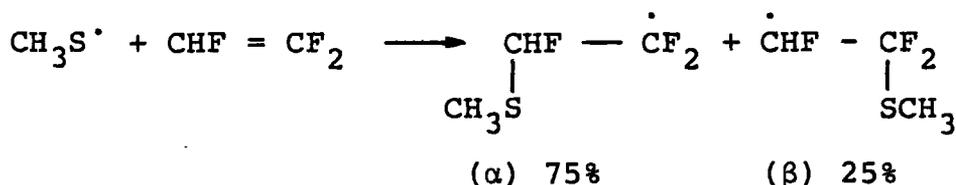


These results are rationalised in terms of the electrophilicity of the thiyl radicals and the polarity of trifluoroethene




The more electrophilic  $\dot{S}CF_3$  radical is more strongly directed towards the negatively polarised carbon whilst the  $\dot{S}CH_3$  radical, being less electrophilic, is less selective.

This trend is also observed in the addition of  $\dot{\text{C}}\text{F}_3$  and  $\dot{\text{C}}\text{H}_3$  to trifluoroethene.<sup>31</sup> However, in the series  $\dot{\text{C}}\text{F}_3$ ,  $\dot{\text{C}}\text{F}_2\text{Br}$ ,  $\dot{\text{C}}\text{FBr}_2$ ,  $\dot{\text{C}}\text{Br}_3$  there is little change in the electrophilicity of the radical and so only a small variation in the yields of the  $\alpha$ - and  $\beta$ - adducts to trifluoroethene would be expected. In fact there is a considerable lowering of reactivity at the more substituted ( $\beta$ -) end as the radical becomes more bulky.

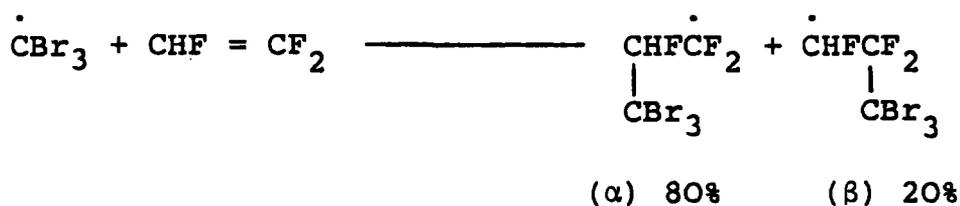

This result clearly demonstrates a steric hindrance effect due to the size of the Br atoms. This effect is even more pronounced in the series  $\dot{\text{C}}\text{F}_3$ ,  $\dot{\text{C}}\text{F}_2\text{CF}_3$ ,  $\dot{\text{C}}\text{F}(\text{CF}_3)_2$ ,  $\dot{\text{C}}(\text{CF}_3)_3$  where the yield of the  $\beta$ -adduct drops to 6%. For the straight chain perfluorocarbon radicals  $\dot{\text{C}}\text{F}_3$  to  $\dot{\text{C}}_8\text{F}_{17}$  there is, however, only a small change in selectivity which is important when considering polymerisation processes.

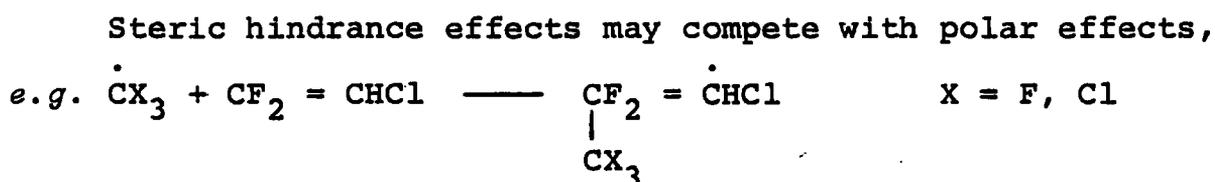


Here the electrophilic radicals  $\dot{\text{C}}\text{F}_3$  and  $\dot{\text{C}}\text{Cl}_3$  add preferentially to the positively polarised position because of steric repulsion by the large Cl atom at the negatively polarized position.

Since bond-strength, polarity, steric requirements and electrophilicity are strongly affected by the presence of fluorine in organic molecules, unusual effects are prevalent in organofluorine free-radical chemistry.

I.B. (iii) Mechanistic Aspects of Polymerisation(a) Homopolymers


The important mechanistic considerations of polymerisation of fluoroalkenes by free radical processes are identified in terms of the ground rules described above for free radical addition reactions. The key step to consider is the propagation step

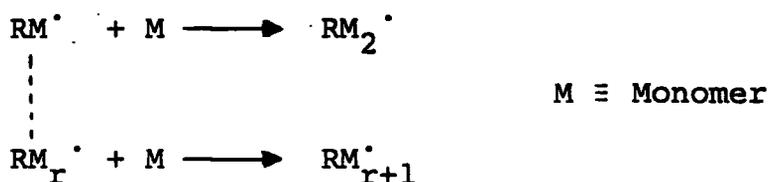

which involves the addition of polymer radicals  $\text{RM}_r^\cdot$  to the monomer unit M. The reactivity of this type of process depends mainly upon (i) polar and (ii) steric factors.

(i) Polar Effects


The rate of polymerisation is lowered by the presence of electronegative substituents. For example in the polymerisation of  $\text{CF}_2=\text{CF}_2$

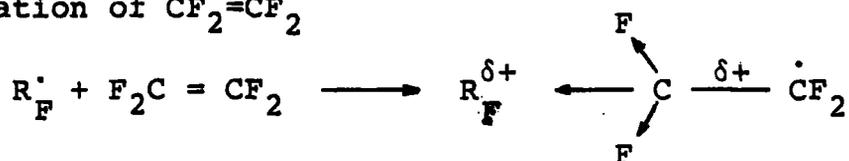

an unfavourable dipole interaction occurs due to the electronegativity of  $\text{R}_F^\cdot$  and the polar C-F bonds in  $\text{CF}_2=\text{CF}_2$ .

(ii) Steric Effects


In general the bulkier the substituents, either on the propagating radical  $\text{RCX}_2^\cdot$  or the monomer  $\text{CXY}=\text{C}$ , the greater the energy barrier towards reaction. For example, the polymerisation of 1,2-disubstituted alkenes is usually difficult




In stark contrast to this second observation is the high heat of polymerisation of  $CF_2=CF_2$  (18 Kcal mol<sup>-1</sup> greater than  $C_2H_4$ ). This is best accounted for in terms of the relief of  $\pi$ -electron repulsion in  $CF_2=CF_2$  which has a destabilising effect



$CF_3CF=CF_2$ , however, forms a homopolymer only under extreme conditions



These observations lead to the conclusion that steric considerations are unimportant when the only  $\alpha$ -substituents, on both the propagating radical  $RCX_2$  and the alkene substrate, are fluorine. In fact none of the polymerisations of  $CH_2=CHF(VF)$ ,  $CH_2=CF_2(VF_2)$  or  $CHF=CF_2(VF_3)$  (to form PVF, PVF<sub>2</sub>, PFV<sub>3</sub> resp.) are sterically hindered by the presence of fluorine substituents. Therefore in these systems polar effects are more dominant. While the rate of polymerisation falls as the number of substituents is increased, the main effect is on the regiochemistry of addition, resulting in head to tail arrangements of the monomer units. The reactions are not, however, completely regiospecific.




It would be logical to expect a thermodynamic advantage for the homopolymerisation of  $\text{CF}_2\text{CF} = \text{CF}_2$  due to the relief of  $\pi$ -non-bonding electron pair repulsions, similar to that found with  $\text{CF}_2 = \text{CF}_2$ . However this is precluded by the steric hindrance of the  $-\text{CF}_3$  group. It is useful to compare the energy profiles for these two processes with that of the homopolymerisation of  $\text{Cl}_2\text{C} = \text{CCl}_2$ , which under no conditions proceeds. These are shown in Figure 1.3. In homopolymerising  $\text{Cl}_2\text{C} = \text{CCl}_2$  steric repulsions would also occur in the resultant homopolymer to further reduce the feasibility of reaction.

Steric effects strongly determine regiochemistry in certain homopolymerisations. For example polychloro- and polybromo-trifluoroethene (PCTFE and PBTFE resp.) are 98-99% regiospecific<sup>38</sup> (*cf.*  $\text{PVF}_2$  and  $\text{PVF}_3$  due to polar effects).



Figure 1.3 Reaction Profiles for the Homopolymerisations  $\text{CF}_2=\text{CF}_2$ ,  $\text{CF}_3\text{CF}=\text{CF}_2$ ,  $\text{Cl}_2\text{C}=\text{CCl}_2$

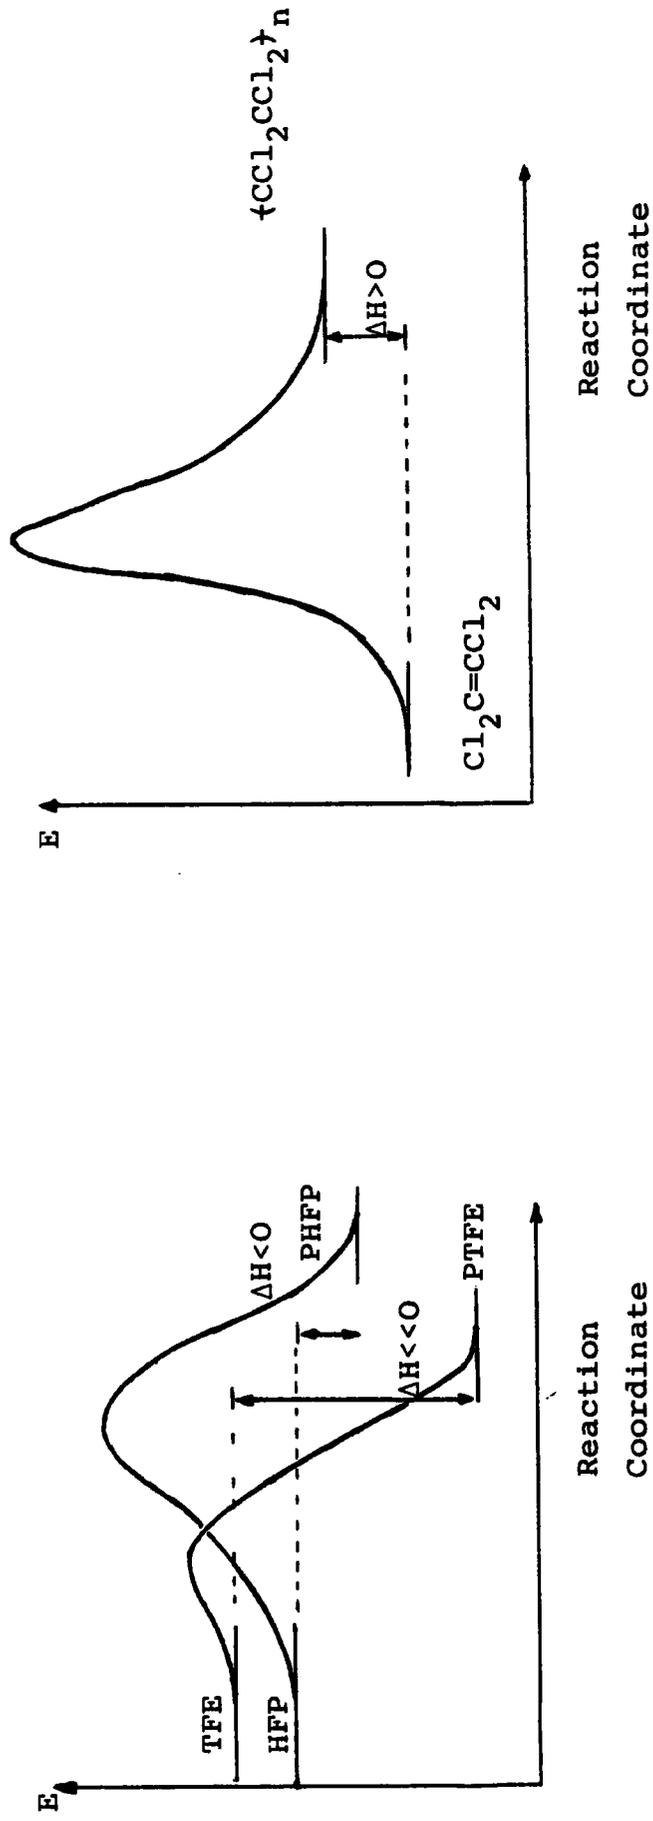


(b) Copolymers

Copolymers are produced by mixing together two or more comonomers in the presence of a free-radical initiator. Therefore an alkene which will not homopolymerise becomes useful if it can be copolymerised with one which has less steric barriers to reaction, *e.g.*  $\text{CF}_3\text{CF}=\text{CF}_2$ .

(i) Copolymers Derived from  $\text{CF}_3\text{CF}=\text{CF}_2$  and  $\text{CH}_2=\text{CF}_2$ 

The actual structure of the copolymer of  $\text{CF}_3\text{CF}=\text{CF}_2$  and  $\text{CH}_2=\text{CF}_2$  depends upon the reactivities of the comonomers and is, therefore, also subject to the factors affecting reactivity that were described above for homopolymerisation. For example, since  $\text{CF}_3\text{CF}=\text{CF}_2$  does not homopolymerise, the maximum content of  $\text{CF}_3\text{CF}=\text{CF}_2$  in the copolymer with  $\text{CH}_2=\text{CF}_2$  is 50% because it is reasonable to expect that no  $\text{CF}_3\text{CF}=\text{CF}_2$  sequences will occur. In fact, the structure



accounts for 93% of the  $\text{CF}_3\text{CF}=\text{CF}_2$  in the copolymer.<sup>39</sup> Conversely  $\text{CH}_2=\text{CF}_2$  sequences do occur due to its greater reactivity. In considering the structure of  $\text{CH}_2=\text{CF}_2$  sequences it is reasonable to assume that the regiochemistry does not differ from that of the  $\text{CH}_2=\text{CF}_2$  homopolymer and that >90% regioselectivity occurs.<sup>36</sup> Therefore the most important structural units to consider are those involving a  $\text{CF}_3\text{CF}=\text{CF}_2$  unit adjacent to a  $\text{CH}_2=\text{CF}_2$  unit.

Consider radical attack upon  $\text{CF}_3\text{CF}=\text{CF}_2$  by a polymer radical terminating in a  $-\text{CH}_2\overset{\cdot}{\text{C}}\text{F}_2$  unit. Attack upon  $\text{CF}_3\text{CF}=\text{CF}_2$




(ii) CH<sub>2</sub>=CF<sub>2</sub>/Pentafluoropropene Copolymers


1H-pentafluoropropene CF<sub>3</sub>CF=CFH and 2H-pentafluoropropene CF<sub>3</sub>CH=CF<sub>2</sub> will form copolymers with CH<sub>2</sub>=CF<sub>2</sub>. These copolymers have structures exactly analogous to the CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> copolymer.

(iii) CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>2</sub>=CFCl (CTFE)

These copolymers may contain sequences of PVF<sub>2</sub> and PCTFE because each monomer is itself able to form a homopolymer. The predominant polar effects in PVF<sub>2</sub> and steric effects in PCTFE have a strong influence upon the structure of the copolymer with the result that the copolymer, for the most part, may be represented

(iv) Terpolymers

The structural features prevailing in terpolymers incorporating CF<sub>2</sub>=CF<sub>2</sub>, e.g. the CF<sub>2</sub>=CF<sub>2</sub>/CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> system, are determined by analogy with the copolymer CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> because the incorporation of CF<sub>2</sub>=CF<sub>2</sub> does not introduce any additional polar or steric considerations. Thus the important structural units of such a terpolymer are



### I.3. (iv) Polymerisation Methods

Free-radical addition polymerisation is the principle polymerisation process employed in industrial fluorine chemistry since cationic catalysts do not promote reaction and anionic catalysts (*e.g.* lithium alkyls) react vigorously to remove fluorine. There are four main methods for the radical polymerisation of fluoroalkenes.

(i) Bulk polymerisation involves reaction of the pure monomer(s) with the initiator. This produces a very pure polymer but presents serious engineering problems due to heat dissipation and the development of hot spots.

(ii) Solution polymerisation involves mixing an inert solvent with the monomer. This overcomes the problem of heat dissipation and the need to handle viscous melts.

(iii) Suspension polymerisation involves an aqueous phase in which the monomer is suspended as droplets. The droplet size is important in determining the final physical properties of the polymer and can be controlled by the addition of suspension agents such as poly(vinyl alcohol), gelatine or water soluble cellulose derivatives.


(iv) Emulsion polymerisation employs a continuous aqueous phase which helps to dissipate heat. Small micelles in which the monomer dissolves are formed by the action of an emulsifying agent, *e.g.* sulphonate esters of long chain fatty acids. Polymerisation occurs within the micelles which swell as more monomer and initiator diffuse inside from the aqueous phase.

## I.B. (v) Properties of Fluoropolymers

### (a) Homopolymers

#### (i) Polytetrafluoroethene (PTFE)

The C-F bonds in PTFE are among the strongest known at  $115\text{Kcal mol}^{-1}$  (*c.f.*  $50\text{-}100\text{Kcal mol}^{-1}$  for most other organic single bonds). However the interactive forces between PTFE polymer chains are very small at  $0.76\text{Kcal mol}^{-1}$  (*c.f.*  $1\text{-}10\text{ Kcal mol}^{-1}$  for most organic solids). This variation in bond-strength makes PTFE a very unusual solid material.

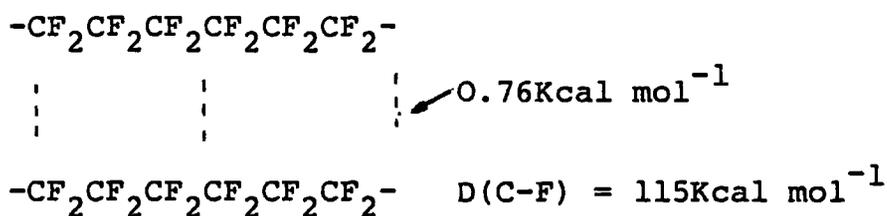

The structure of PTFE is remarkable in that the fluorine atoms are packed closely due to their size. Non-bonding electron pair repulsions between the fluorine atoms cause the polymer to twist into a helical form about its own axis (see Figure 1.4).<sup>41</sup>

The fluorine atoms in PTFE consequently shield the carbon skeleton from chemical attack with the result that PTFE has extreme chemical resilience.<sup>42</sup> Only alkali metals, chlorine trifluoride and fluorine at high temperature and pressure degrade PTFE.<sup>43</sup>

PTFE is also remarkable in that it has exceptional qualities of electrical resistivity, non-flammability, weathering,

FIGURE 1.4 THE STRUCTURES OF POLYTETRAFLUOROETHENE (PTFE) AND POLYETHENE (PE)

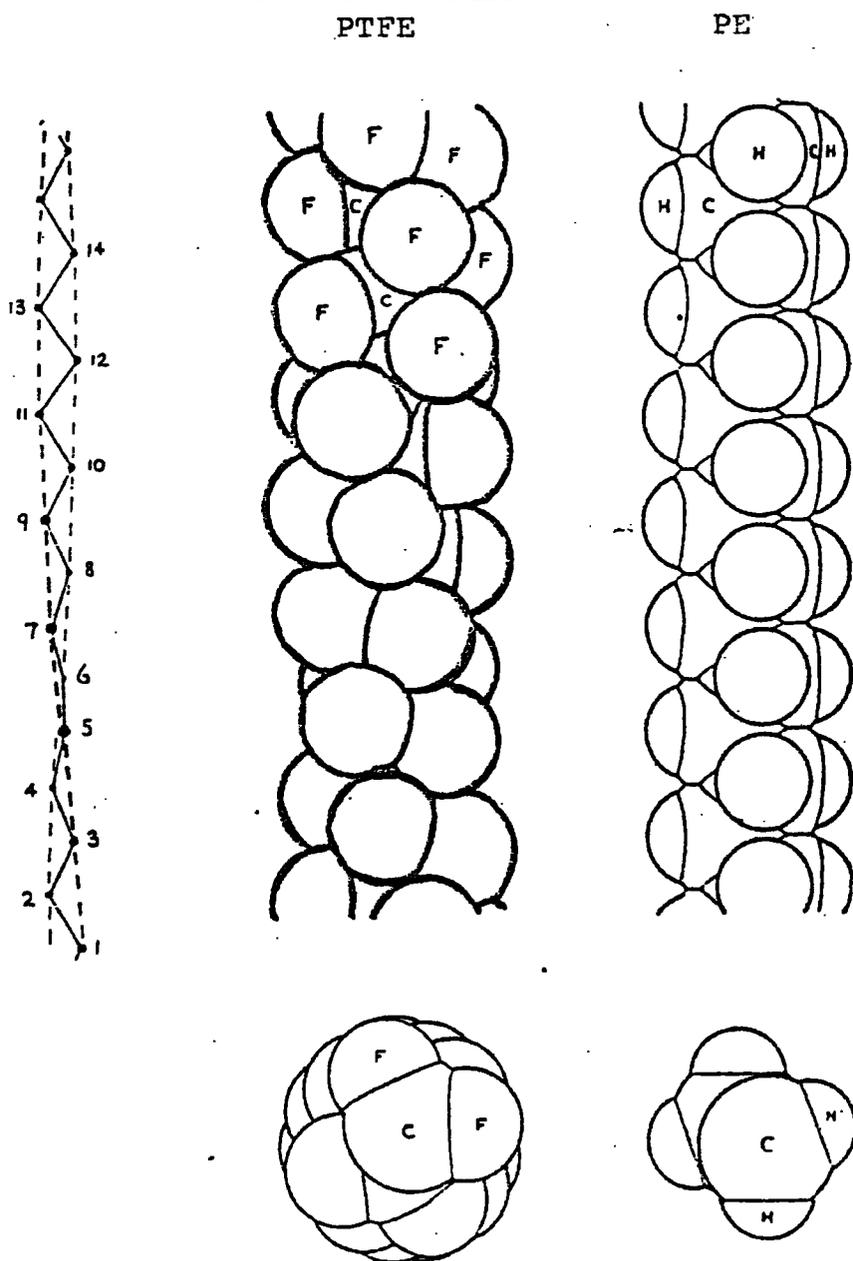


TABLE 1.3 The Properties of Some Important Homopolymers

	PCTFE	PVF	PVF <sub>2</sub>	PVF <sub>3</sub>	ALL
Structure	$\langle \text{CF}_2\text{CFCl} \rangle_n$ >98%	$\langle \text{CH}_2\text{CHF} \rangle_n$ 74%	$\langle \text{CH}_2\text{CF}_2 \rangle_n$ 90%	$\langle \text{CHF}\text{CF}_2 \rangle_n$ 85-90%	
Physical Properties:					
Optical	Thin films and annealed samples are milky and translucent (PVF films are transparent)				
Mechanical	Good creep resistance		Excellent resistance to abrasion		Good. Approach polyamides and polyesters
Melting Pt.	MPT > 202°C	MPT > 192°C	MPT 171°C		All are thermoplastic, <i>i.e.</i> soften then flow when heated
Thermal Stability in air (50% weight loss after 30 mins.)	380°C	389°C	446°C	<i>c.a.</i> 420°C	PVF <sub>n</sub> produce HF on degradation. PCTFE undergoes chain scissions.
Chemical Inertness	Excellent	Good, except to NaOH, PhNH <sub>2</sub> and NR <sub>3</sub>			Much higher than other engineering plastics.
Solvents (Resistance to swelling)	Excellent	Moderate	Poor in polar solvents	Good except (CH <sub>3</sub> ) <sub>2</sub> C=O DMF and Cyclopentanone	No better than other polyamides

low surface friction and non-adhesiveness. The main disadvantage of PTFE is that, as a dense and highly crystalline polymer, it is not viable for processes which require manipulation. The properties of the other important homopolymers are summarized in Table 1.3.

(b) Copolymers

(1)  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  Copolymers

Neither of the homopolymers  $\text{PVF}_2$  and poly(hexafluoropropene) are elastomers, *i.e.* after deformation these materials do not revert rapidly to their original dimensions. This is a very desirable property which is a characteristic of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$ ,  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CH}=\text{CF}_2$  and  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CFH}$  copolymers.

The thermal stabilities of these copolymers are high. For example at  $370^\circ\text{-}390^\circ\text{C}$  25% weight loss from  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers occurs over 2 hours depending upon composition.<sup>44</sup>

These copolymers are subjected to a curing process (or vulcanization) in order to enhance their elastomeric properties and for better service life over a wider range of temperatures. The cure introduces inter-chain crosslinks which endows the copolymer with greater rigidity. This is particularly useful at higher temperatures when elastomericity due to inter-chain entanglements is lost.

TABLE 1.4 The Chemical Resistance of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$ ,  
 $\text{CH}_2=\text{CF}_2$ /Pentafluoropropene Copolymers

Chemicals which have no effect	Chemicals which degrade
All Fuels, Oils, Lubricants, Hydraulic fluids, Chlorinated Solvents, Ozone, Mineral Acids, Steam, Aqueous Salt Solutions	Low Mol wt. Esters, Ethers and Ketones, Aldehydes, Amines, Organic Acids, Conc. Aqueous Alkali

The chemical inertness of the cured copolymers is high and this is summarized in Table 1.4.

(ii)  $\text{CH}_2=\text{CF}_2/\text{CF}_2=\text{CFCl}$  Copolymers

This elastomer has somewhat less thermal stability than the other copolymers of  $\text{CH}_2=\text{CF}_2$ . At  $350^\circ\text{C}$  25% weight loss occurs in 2 hours. This reduction in thermal stability is attributed to the fact that the C-Cl bond energy is  $81\text{Kcal mol}^{-1}$  (*c.f.*  $\Delta(\text{C-F}) = 115\text{Kcal mol}^{-1}$  in PTFE). The chemical inertness of this copolymer system is lowered towards reagents which will tend to eliminate HCl, *e.g.* amines and NaOH. Resistance to steam and mineral acids is excellent.

(iii) CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> Terpolymers

The introduction of CF<sub>2</sub>=CF<sub>2</sub> into CH<sub>2</sub>=CF<sub>2</sub> copolymers results in greater chemical and thermal stability but at the expense of physical properties at lower temperatures. For example the glass transition temperature of the raw terpolymer is -17°C whereas that of the CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> copolymer is -20°C.<sup>45</sup>

(iv) CF<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> and CF<sub>2</sub>=CF<sub>2</sub>/CF<sub>2</sub>=CFOR<sub>F</sub> Copolymers

In an effort to reduce the crystallinity of PTFE, copolymers of CF<sub>2</sub>=CF<sub>2</sub> with CF<sub>3</sub>CF=CF<sub>2</sub> are produced containing pendant -CF<sub>3</sub> groups




However this was found to introduce crowding at the tertiary sites, resulting in a reduction of thermal stability in comparison with PTFE. If, on the other hand, the -CF<sub>3</sub> group is attached to the polymer chain by an oxygen atom there is less crowding and higher thermal stability. Therefore CF<sub>2</sub>=CF<sub>2</sub> is copolymerized with perfluoromethyl vinyl ether (PFMVE).<sup>46-48</sup>



The result is a series of elastomers (PFMVE content >20%) which are melt processable<sup>5</sup> and have chemical and thermal stability approaching the excellence of PTFE.

The cross-linking of these copolymers is achieved only by incorporation of a third comonomer (Section I.D.(iv)).

$\text{CF}_3\text{OCF}=\text{CF}_2$  is not used in copolymers with  $\text{CH}_2=\text{CF}_2$  because the process

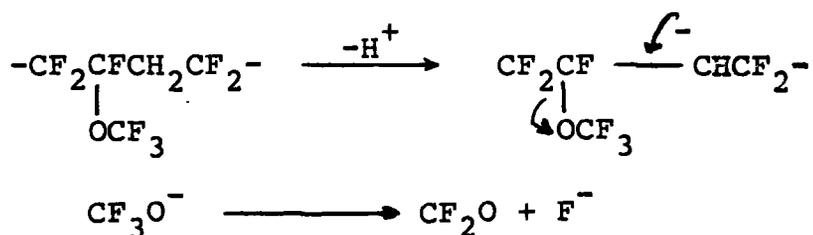

is a major pathway leading to polymer degradation.

#### I.B. (vi) The Uses and Applications of Fluoropolymers<sup>49</sup>

The applications of the copolymers described above are summarized in Table 1.5.

#### I.C. Miscellaneous Fluoroelastomers

The structure, preparation and properties of the more interesting and/or commercially successful fluoroelastomers, are summarized in Table 1.6.

#### I.D. Cross-linking of Copolymers of 1,1-Difluoroethene

##### I.D. (i) Introduction

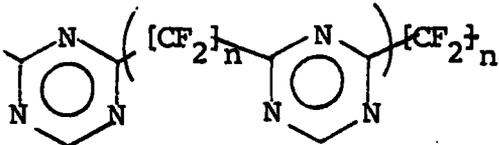
Copolymers of 1,1-difluoroethene, in the raw state, consist of long linear chain-like molecules. In this form these materials may exhibit elastomeric properties due to inter-chain entanglements, *e.g.* due to pendant  $-\text{CF}_3$  groups.

TABLE 1.5 Properties and Applications of Fluoropolymers Derived from Fluoroalkenes

Material	Properties	Uses and Applications
PTFE	High electrical resistivity. Chemical Inertness. Resistance to Weathering. Low coeff. of friction.	Almost half of the PTFE made is used in Electrical Engineering. Also used for gaskets, packings, seals, pipe linings. Solar energy systems. Cooking and Photocopying.
PCTFE	Chemical Inertness Mechanical Props and Transparency.	As PTFE (though more costly). Windows for use with cryogenic fluids. <sup>50</sup>
PVF PVF <sub>2</sub>	) Resistance to ) Sunlight. ) Processability Piezoelectric Props *	Cast into films as weather-resistant coatings for buildings. Pumps, valves, piping. Micro- phones, transducers, etc. <sup>51</sup>
HFP/VF <sub>2</sub>	Resistance to Com- pression Set. Chem- ical Inertness	Sealing applications. Also used in gas chroma- tography as a Stationary phase
TFE/PFMVE	Processability over a wide Temperature Range. Extreme Chemical Resistance	Seals, <sup>52</sup> electrical connectors, gaskets, diaphragms.

\* A piezoelectric material develops a potential difference upon deformation.

TABLE 1.6 Miscellaneous Fluoropolymers

Material	Structure and Preparation	Properties/Uses
Poly(fluoro-alkylacrylates)	$\left( \text{CH}_2 \underset{\begin{array}{c}   \\ \text{C=O} \\   \\ \text{R}_f\text{CH}_2\text{O} \end{array}}{\text{CH}} \right)_n$ (i) $\text{CH}_2=\text{CHCOOH} + \text{R}_f\text{CH}_2\text{OH} \rightarrow \text{Monomers}$ (ii) $\text{K}_2\text{S}_2\text{O}_8$ aq. emulsion polymn.	Useful temp. range -40 to +200°C. Good O <sub>3</sub> u.v. and oil resistance. Used in car industry. <sup>53</sup>
Copolymers of TFE with F-sulphonated vinyl ethers	$\left( \text{CF}_2\text{CF}_2 \right)_x \left( \text{CF}_2 \underset{\begin{array}{c}   \\ \text{CF}_2\text{-O} \\   \\ \text{CF}_3\text{CF}_2\text{SO}_2\text{F} \end{array}}{\text{CF}} \right)_y$ Monomer made by electrochem. fluorination. <sup>28</sup>	Ion selective. Used in chloro alkali cells. <sup>54</sup>
Polythiocarbonyl Fluoride	$\left( \text{CF}_2\text{S} \right)_n$ Rapid anionic polymerisation of $\text{CF}_2 = \text{S}$	Very resilient. Stable to $\text{HNO}_3$ , $\text{NaOH}$ <sup>55</sup> but degraded by amines. Non-commercial but of great chemical interest. <sup>56</sup>
Poly(F-alkylene-triazines)	 Made by condensn. of fluoro-bisamidines <sup>57-62</sup>	Thermally stable at 362°C. Stable to acids. <sup>59</sup>
Nitroso Fluoropolymers	$\left( \text{CF}_2 \underset{\begin{array}{c}   \\ \text{CF}_3 \end{array}}{\text{CF}} \text{NO} \right)_n$ Copolym. of <sup>63-68</sup> TFE/ $\text{CF}_3\text{NO}$ , 0°C	Useful low temp. properties.
Fluoro-silicone polymers	$\left[ \text{Si}(\text{CH}_2\text{CH}_2\text{R}_f)(\text{CH}_3)_2\text{O} \right]_n$	Very stable. Used in electrical applicns.


However, the temperature range of this type of effect is, in general, limited. In order to extend their elastomeric range, these copolymers are subjected to a curing process which introduces chemical bonding between the polymer molecules resulting in a stable three dimensional network.

This process is usually followed by an air-oven post-cure at elevated temperature. This second process may modify the bonding achieved in the initial cure and some sources postulate that this is the more important stage<sup>69</sup> in cross-linking.


An ideal cross-link should be a natural, stable extension of the copolymer structure so that reductions in chemical and thermal stability are minimised. Practically, however, this is rarely the case.

In general, there are two approaches to the cross-linking of  $\text{CH}_2=\text{CF}_2$  copolymers.

(i) Dehydrohalogenation of the polymer chain (in the presence of an acid-acceptor, *e.g.* MgO) yields sites of unsaturation, which are then linked chemically using a cross-linking agent of functionality 2 or greater. This type of cure most often involves polyamines and bisphenols.<sup>70</sup> For example the mechanism shown in scheme 1.3 is postulated for the curing of  $\text{CH}_2=\text{CF}_2/\text{CF}_2=\text{CFCl}$  copolymers with diamines:<sup>71</sup>

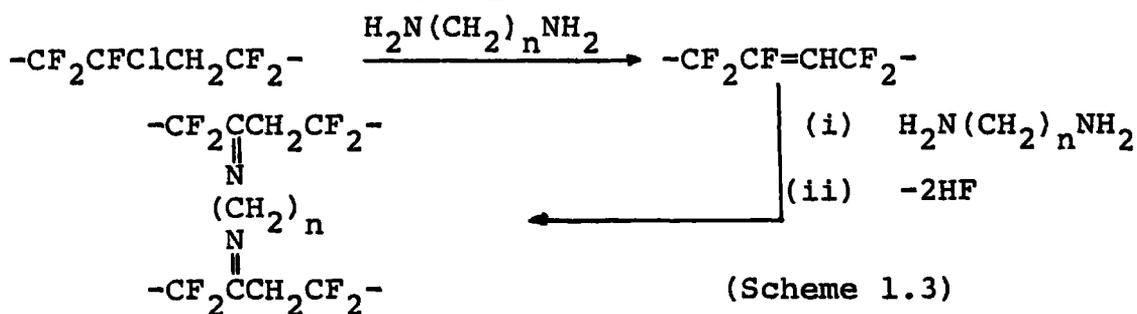

(ii) A third comonomer which itself provides the active site for cross-linking is included in the copolymerisation. For example bromotrifluoroethene (BTFE) is used as shown in scheme 1.4: <sup>72</sup>

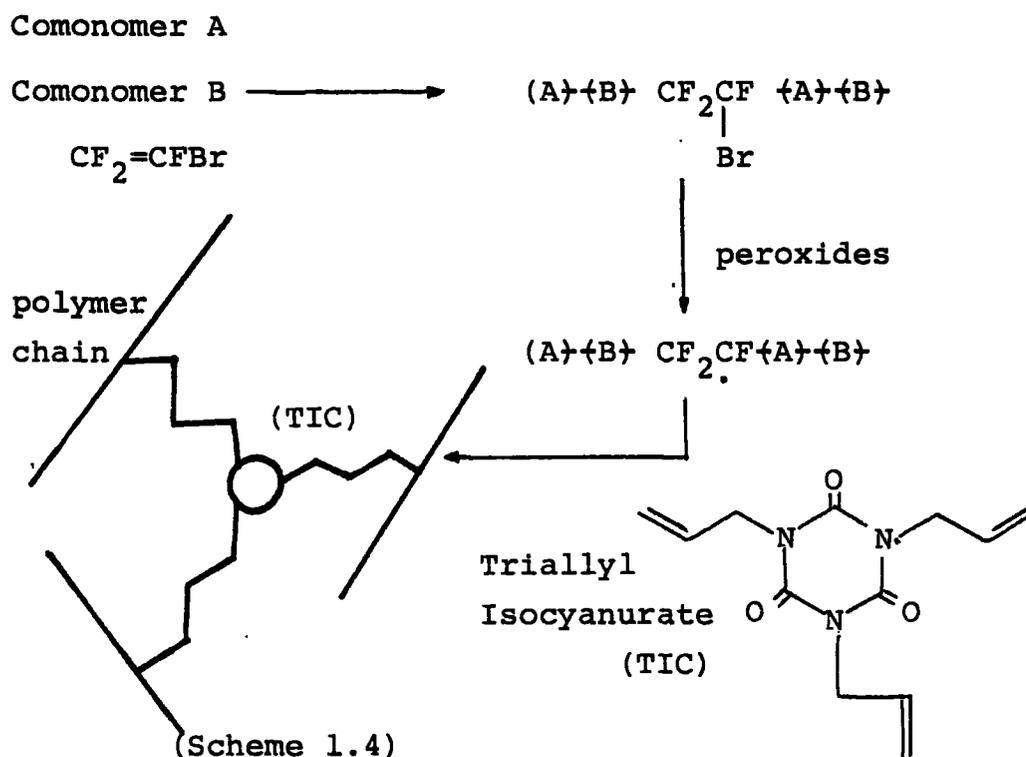

The second approach has been fully developed only recently <sup>73,74</sup> whereas a great deal of research has been directed towards a fuller understanding of the mechanisms involved in the first approach. <sup>69</sup>

Other materials included in a typical curing process are summarized in Table 1.7. The role of the acid-acceptor is not completely understood and has been the subject of detailed investigation as has the role and effect of the fillers. <sup>75-78</sup>

The properties of the cured fluoroelastomers are improved by air oven post-curing, usually at *c.a.* 230°C. For example diamine, bisphenol and peroxides vulcanizates show 50% increases in tensile strength. The post-cure also removes H<sub>2</sub>O, a biproduct of the cure.


TABLE 1.7 Cure Ingredients and Additives

Material	Approx. Amount Used (by weight)	Purpose
Raw Polymer	100	
Basic Metal Oxides, <i>e.g.</i> MgO, CaO	6-20	Absorption of HX (X=Cl, F) released during the generation of unsat. sites
Fillers, <i>e.g.</i> Carbon Black, Austin Black, Silica, Calcium Silicate	Up to 60	Improve tensile strength, increase hardness and decrease cost, but reduce low temperature performance.
Accelerators <i>e.g.</i> Crown Ethers, Poly(ethylene ether glycol)	3	Improves certain cure parameters in bisphenol cures but exact role is unknown

I.D. (ii) Cross-Linking Involving Amines(a) Mechanistic Aspects


$\text{CH}_2=\text{CF}_2/\text{CF}_2=\text{CFCl}$  copolymers are cross-linked by primary mono- and diamines and by secondary diamines at room temperature and  $50-60^\circ\text{C}$  respectively.<sup>71</sup>

The first step in the cross-linking by all amines is the removal of either HCl or HF<sup>79,80</sup>




This was verified by the isolation of amine hydrochlorides and hydrofluorides. In the case of primary diamines this step is


followed by addition of the amine and concomitant elimination of hydrogen fluoride

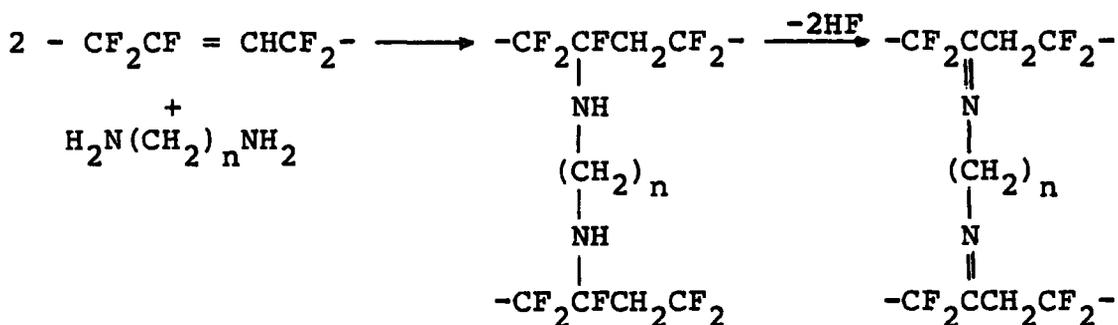

With (a) secondary diamines and (b) primary monoamines the final step clearly does not apply although dehydrofluorination of the polymer chain at the cross-link site may occur rapidly after the addition step to give cross-links of the form

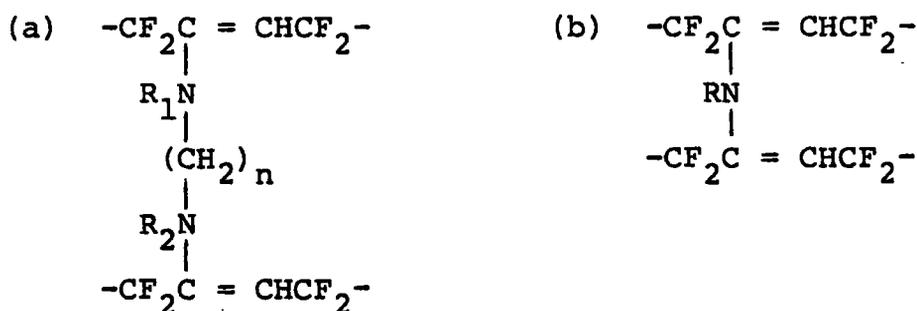


However, gelation of polymer solutions was also observed using (c) secondary monoamines ( $\text{R}_2\text{NH}$ ) at  $50\text{-}60^\circ\text{C}$  and (d) tertiary diamines ( $\text{R}_2\text{N}(\text{CH}_2)_n\text{NR}_2$ ) at  $90\text{-}100^\circ\text{C}$ . These observations would seem to indicate the involvement of quaternary ammonium salts.

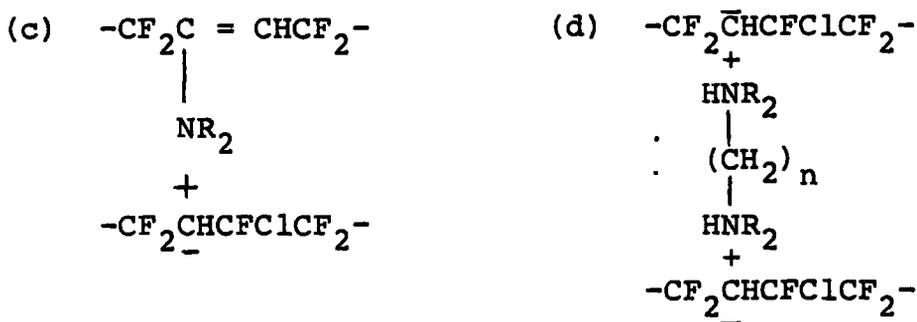




The structure (a) is the more feasible produce of nucleophilic addition because of the activating effect of the  $-\text{CF}_3$  group. The experimental observation that 4 moles of HF are eliminated per mole of cross-links formed<sup>77</sup> is further evidence supporting the structure (a) since it is much more likely to lose HF than structure (b).

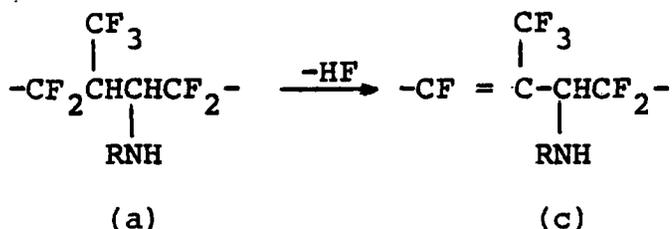

A study using  $^{19}\text{F}$  nmr spectroscopy of dehydrofluorination of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers in solution using  $n\text{Bu}_4\text{N}^+\text{OH}^-$  indicated that sites in which a  $-\text{CH}_2\text{CF}_2-$  unit is isolated between two  $-\text{CF}_2\text{CF}(\text{CF}_3)-$  units are the most easily dehydrofluorinated.<sup>49</sup>

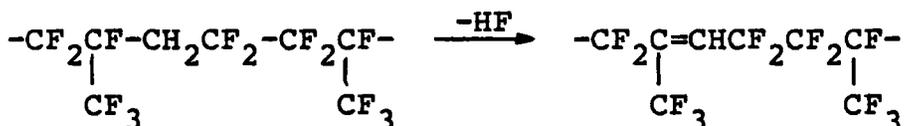


Consequently solutions of copolymers of  $\text{CF}_2=\text{CFCF}_3$  gel more quickly than those not containing  $-\text{CF}_2\text{CF}(\text{CF}_3)-$ .<sup>49</sup> This is apparent from the data shown in Table 1.8.


TABLE 1.8 Gel Rates of Certain Copolymers by  
 $\text{H}_2\text{N}(\text{CH}_2)_6\text{NH}_2$  in DMAC at 20°C

Copolymer (mol fractions)	Time to form a firm gel
$\text{CH}_2=\text{CF}_2$ (0.61) $\text{CF}_3\text{CF}=\text{CF}_2$ (0.17) $\text{CF}_2=\text{CF}_2$ (0.22)	1.22 min.
$\text{CH}_2=\text{CF}_2$ (0.78) $\text{CF}_3\text{CF}=\text{CF}_2$ (0.22)	3.75 min.
$\text{CH}_2=\text{CF}_2$ (0.74) $\text{CF}_3\text{CF}=\text{CF}_2$ (0.16) $\text{CF}_2=\text{CF}_2$ (0.10)	4.75 min.
$\text{CH}_2=\text{CF}_2$ (0.82) $\text{CF}_2=\text{CF}_2$ (0.18)	>2 hour
$\text{CH}_2=\text{CF}_2$ (1.00)	>10 days

Some sources have proposed the interaction of unsaturated sites alone to form cross-links



although it has been shown that this reaction does not occur when hydrogen is attached to the double-bond.<sup>81</sup> Alternatively a Diels-Alder mechanism has been proposed.

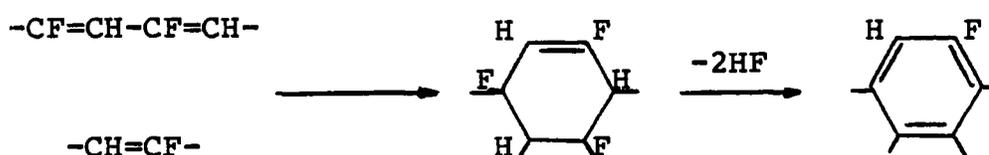


However conjugated materials failed to cross-link in the absence of amines.<sup>71</sup> Yet differential thermal analysis of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  systems treated with the acid-acceptor MgO alone indicate a certain amount of cross-linking.<sup>75</sup> Therefore reaction between unsaturated sites cannot be wholly discounted.


More definitive information from model studies should clarify the exact nature of this cross-linking process (Section I.E.) although this area of research has lapsed due to recent developments of more stable cross-linking processes.

(b) Stability Considerations

In practice amines are very reactive towards  $\text{CH}_2=\text{CF}_2$  copolymers, causing scorching. Therefore their Schiff bases are used. In order to generate the free amine water is required and this is overcome by the reactions

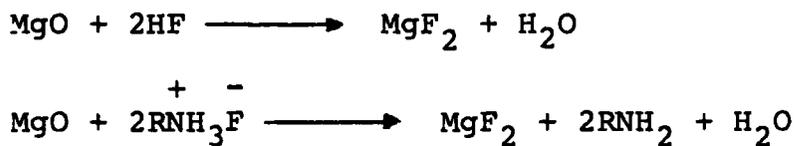

However the presence of water, particularly in the post-cure where it is slowly removed, promotes hydrolysis of the cross-links.

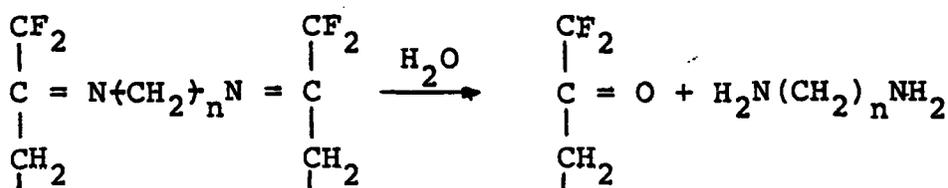


This process also occurs during the end-use of the polymer. Furthermore, unsaturated sites generated during the curing process, which have not been converted to cross-links, are susceptible to attack by aggressive reagents and therefore also lead to degradation. Consequently amine cross-linking is used for only a small percentage of the  $\text{CH}_2=\text{CF}_2$  copolymers produced.

I.D. (iii) Cross-Linking Involving Bisphenols(a) Compounding

Figure 1.9 outlines a standard cure system for a  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymer with a molar ratio 3.5:1 in favour of  $\text{CH}_2=\text{CF}_2$ .<sup>49</sup> The progress of the cure was followed using oscillating disc rheometry as shown in Figure 1.5. (This technique correlates the amount of cross-linking with the "stiffness" of the copolymer<sup>82</sup>).

FIGURE 1.5 ODR Graph of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  Copolymer Cure using Bisphenol AF

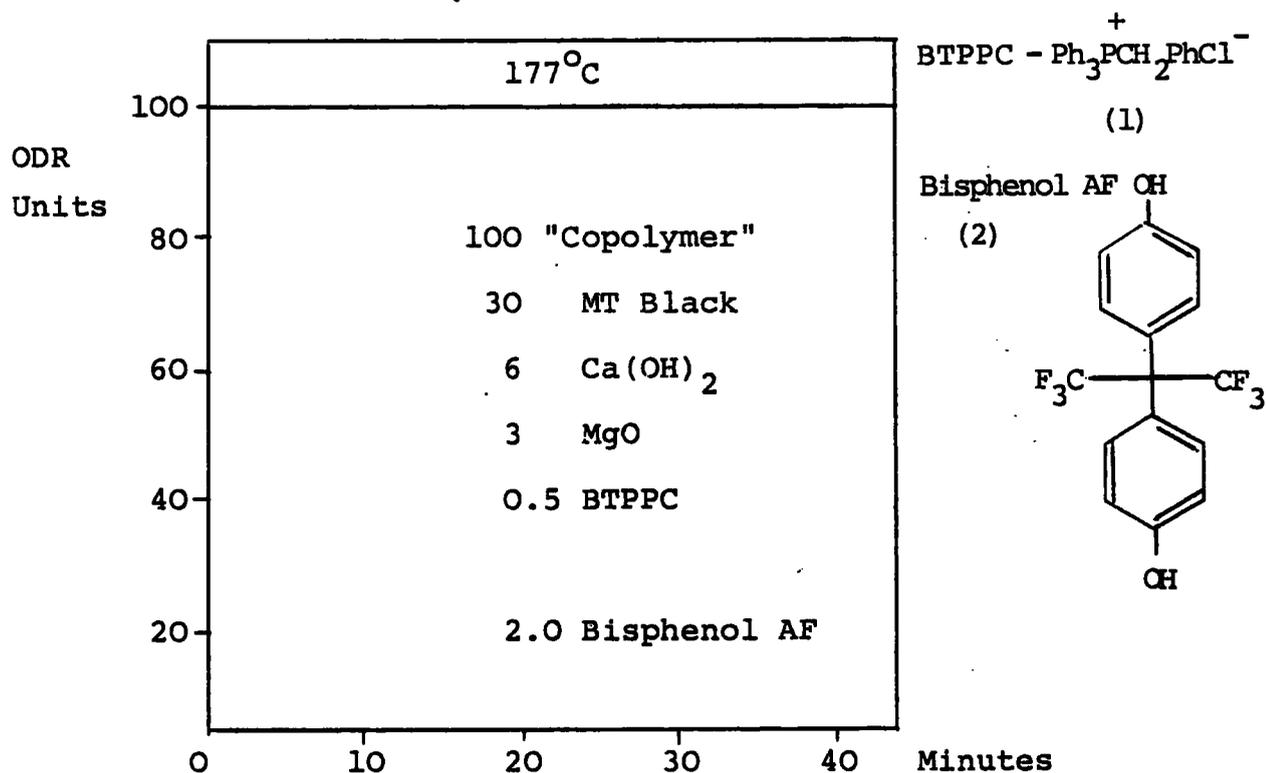


The remarkable features of this curing process are


- (i) 75% of the cure occurs within 1 minute
- (ii) No cure occurs in the absence of BTPPC (1)
- (iii) A distinct induction period of *c.a.* 5 minutes exists in which no cross-links are formed.

(b) Mechanistic Considerations

It is postulated that the bisphenol (2), on contact with the quaternary phosphonium chloride (1), forms a salt (3) with the elimination of hydrogen chloride <sup>49</sup>

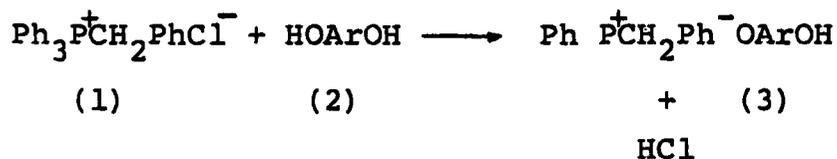

This new phosphonium salt (3) necessarily functions as both base, in eliminating HF from the saturated copolymer, and nucleophile in forming cross-links. The mechanism proposed by Smeigel is shown in scheme 1.6.

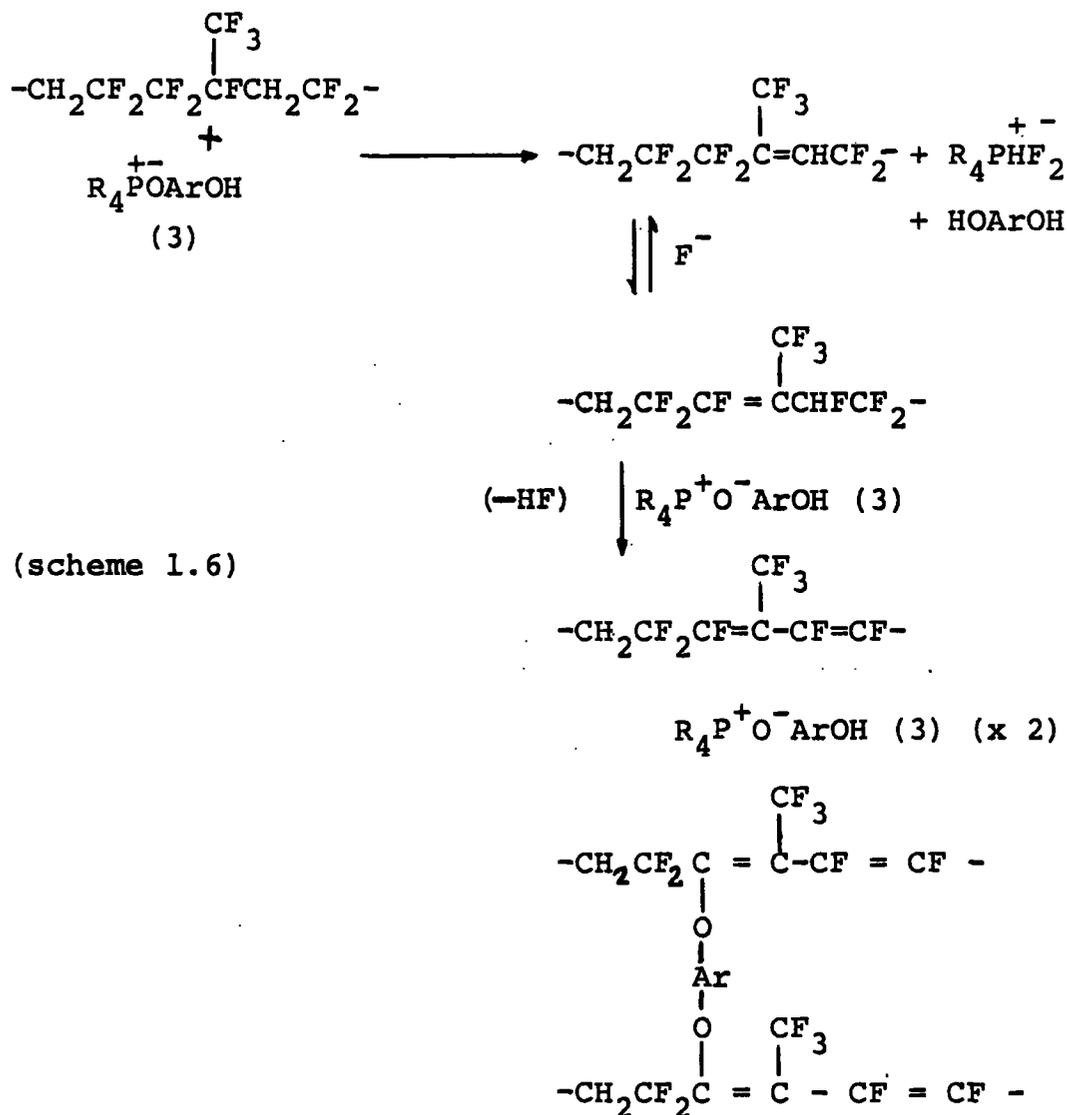


In considering the curing of VF<sub>2</sub> copolymers (and terpolymers) with HFP and TFE it is instructive to examine:

- (i) the reactivity of these systems towards base.
- (ii) the behaviour of the resultant unsaturated systems towards the bisphenolate salt (1).

(i) Reactivity Towards Base

The three systems to consider are (a) CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> (b) CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>2</sub>=CF<sub>2</sub> and (c) CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub>. <sup>19</sup>F nmr. studies have shown that the sites in (a) most sensitive to removal of HF are <sup>49</sup>





while in (b) the only such site is



Comparison of the rates of gelation of copolymers (a) and (b), of equal molar ratio CH<sub>2</sub>=CF<sub>2</sub>, showed that these sites had approximately equal reactivity. <sup>49</sup>

Consider the stability of the respective carbanions upon removing H<sup>+</sup>:

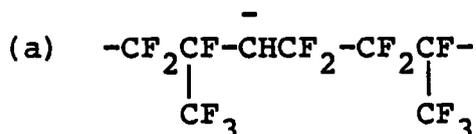





Since a fluorine atom β- to a negative charge centre has been shown to have a similar stabilizing effect to that of a -CF<sub>3</sub> group (w.r.t. hydrogen) <sup>83</sup>



then a similar reactivity would be predicted for HF elimination from each system.

However upon removal of HF from the system (a) there is more relief of crowding than in system (b)<sup>84</sup> which, together with the lower C-F bond strength of tertiary fluorine<sup>85</sup> would indicate that system (a) should be more reactive. On the whole it is therefore surprising that both systems show equal reactivity.




Consideration of the terpolymer system (c) is more complex because there are four possible environments for the -CH<sub>2</sub>- group

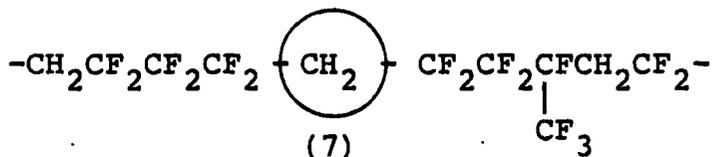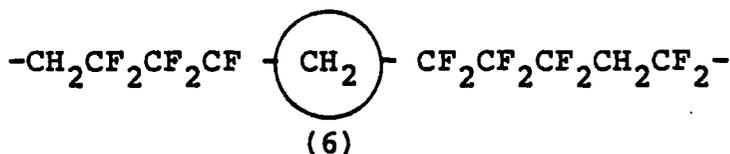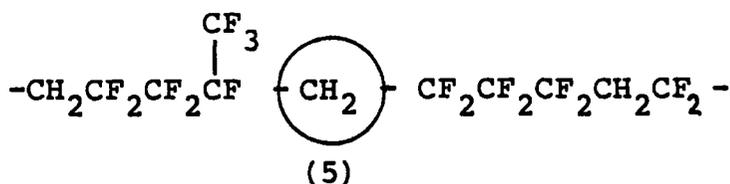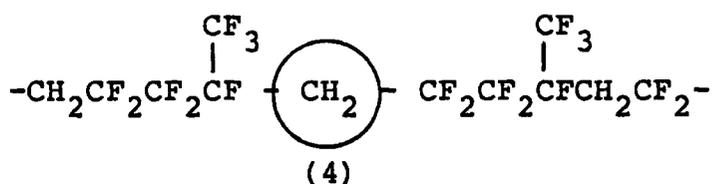


Using the earlier comparison of the reactivity of CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> copolymers with CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>2</sub>=CF<sub>2</sub> copolymers, it follows that there should be equal reactivity associated with (4) and (6) above. Since, structurally, (4) and (5) are similar and (6) and (7) are also similar, it is understandable that the terpolymer system (c) has similar reactivity towards base (compared with the copolymer systems) (a) and (b).

(ii) Reactivity of Unsaturated Systems towards the Bisphenolate Salt (3)

Again consider the systems (a)  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$   
 (b)  $\text{CH}_2=\text{CF}_2/\text{CF}_2=\text{CF}_2$  and (c)  $\text{CH}_2=\text{CF}_2/\text{CF}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$ .  
 Upon removal of HF from the base-sensitive site the relevant structures are (8), (9), (10A) and (10B) respectively:

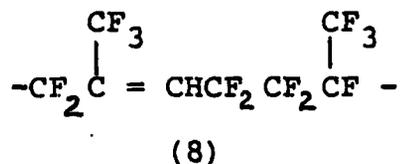


In the presence of active  $\text{F}^-$  only the structures (8) and (10A) isomerise with concomitant loss of HF to give conjugated diene systems as described earlier (Section I.D.(ii))<sup>49</sup>

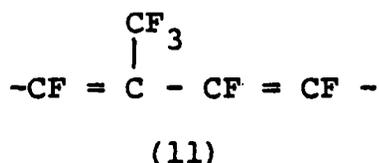

Solution studies using cyclic amidines, which remove HF but are too hindered to behave as nucleophiles, showed that the bisphenolate salt (3) reacts rapidly with the unsaturated copolymer in comparison to removing HF.<sup>49</sup> Therefore, since HF removal occurs at about the same rate, whatever the system, it is possible to predict the relative reactivities of the systems (a), (b) and (c) in terms of the rate of production of conjugated diene sites(11)(above). In system (a) all initial unsaturated sites lead to dienes whereas in (b) none




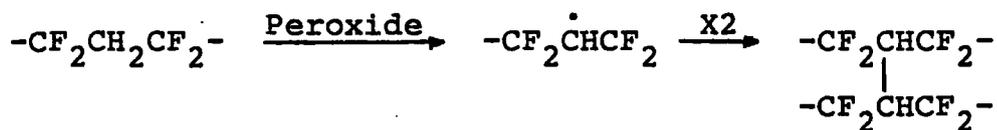

with the advantage that no heteroatom is involved in the cross-link. In practice, however, this leads to poor cure responses because of the large energy required to abstract H<sup>•</sup> and the high reactivity of the peroxides needed which causes scorching. An approach is needed, therefore, which enhances response to milder peroxides.

(b) Mechanistic Considerations



In principle the concept of incorporating a cure-site comonomer into a copolymer, in order to promote cross-linking, may be represented by scheme 1.7.

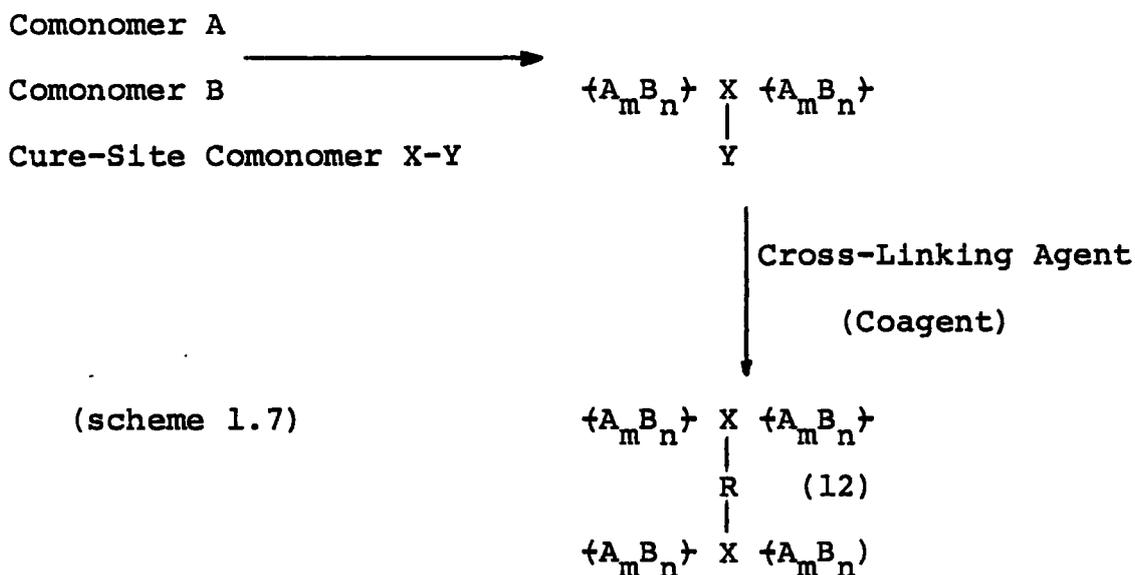

The cross-link -R- in (12) may still contain the group -X in either (a) a modified form (scheme 1.8) or (b) not at all.



functional amines at temperatures above moulding requirements whilst not affecting the performance of the final material. Examples are outlined in scheme 1.9.

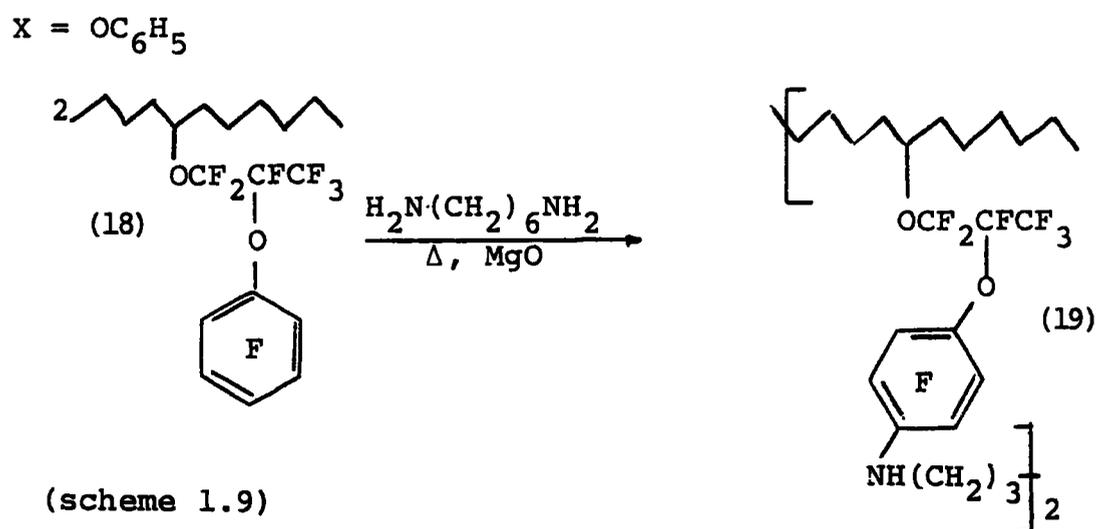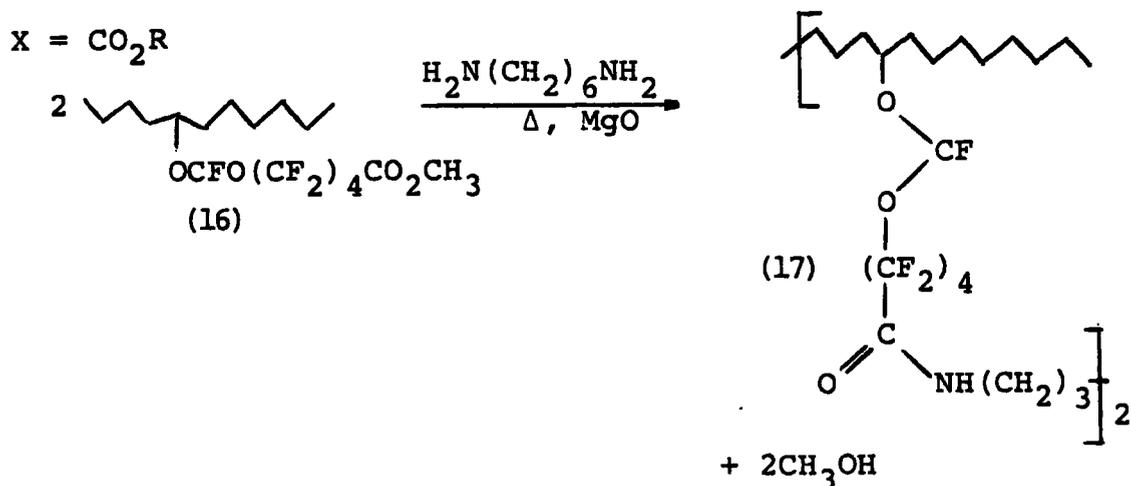

The thermal and chemical stabilities of these systems are excellent, though for X = OC<sub>6</sub>F<sub>5</sub> there is some reduction in thermal stability.


#### I.D. (v) Other Methods

There are two other important methods for cross-linking copolymers of CH<sub>2</sub>=CF<sub>2</sub>; (i) radiation techniques (ii) *via* peroxides alone. Both methods, assumed to produce carbon-carbon cross-links, have rarely attained industrial importance.

(i) Radiation Techniques

Radiation in the form of  $\alpha$ -particles, slow neutrons, X or  $\gamma$ -ray photons, liberates secondary electrons upon passing through matter (often the wall of a reaction vessel). These secondary electrons interact directly with organic molecules to form free-radicals.<sup>27</sup> Overall, therefore, the reactions can resemble those brought about by free-radical initiators.

The discovery in 1955 that irradiated PTFE gives a strong e.s.r. signal<sup>89</sup> (attributed to the polymer radical  $-\text{CF}_2\dot{\text{C}}\text{FCF}_2-$ ) prompted extensive research into the radiation treatment of fluorinated polymers. Treatment of the  $\text{VF}_2/\text{HFP}$  copolymer system with  $\beta$ -particles (low energy electrons) results in cross-linking. It is proposed that radicals formed on the copolymer backbone combine to form C-C bonds between polymer chains. This method of cross-linking (or use of cure-site comonomers) has to be used with propene/TFE copolymers, for which polyamines and polyhydroxyphenols are ineffective. Scheme 1.11 shows the mechanisms proposed for this process.<sup>90</sup>

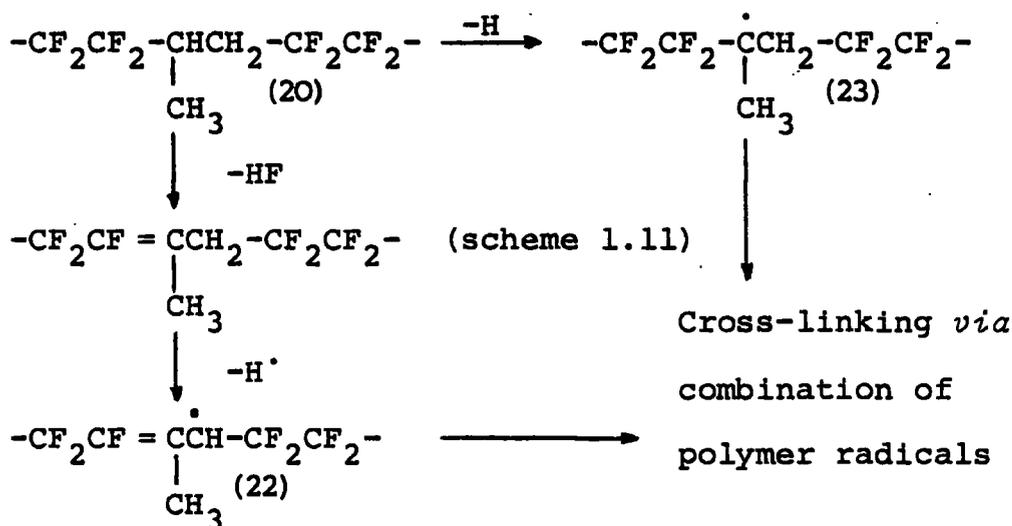


The presence of HF in the system is considered to have a stabilizing effect upon the polymer radicals formed, thus reducing the rate of cross-linking. This effect can be reduced

by the presence of MgO, Ca(OH)<sub>2</sub> or KOH.<sup>91</sup>

(ii) Peroxide Curing

The problems encountered with peroxide cures, in the absence of cure-site comonomers, have been described (Section I.D.(iv), *i.e.* highly active peroxides are required to promote the process



resulting in scorching.

However, vulcanizates of CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> and CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>2</sub>=CFCl copolymers using aromatic peroxides have been reported.<sup>92</sup> These cures, however, are generally poorer than those obtained with amines and bisphenols for two reasons:

(i) The cross-linking density is lower for peroxide formulations.

(ii) Although the degradation effect upon the polymer of peroxide cures is less than that of amine and bisphenol cures, the vulcanizates are thermally much less stable than the raw gums.

I.E. Model Studies Related to Cross-Linking

I.E. (i) Introduction


The amount of definitive information which can be obtained from solution studies about the mechanistic aspects of cross-linking is limited for two reasons:

(i) Structure determination once gelation has occurred is difficult because n.m.r. data is not attainable.

(ii) Actual polymer cures are, in general, carried out in bulk, without solvent interactions.

Model compounds containing structures closely related to those known to occur in the real systems often contain less than ten carbon atoms. The models, and their derivatives, can therefore be characterized fully using the powerful laboratory techniques available. Thus definitive information can be obtained about the chemistry most likely to occur in the real systems.

For example, in order to investigate the peroxide-induced cross-linking of  $\text{CH}_2=\text{CF}_2$  copolymers, the following model reactions were attempted, albeit unsuccessfully<sup>76</sup>

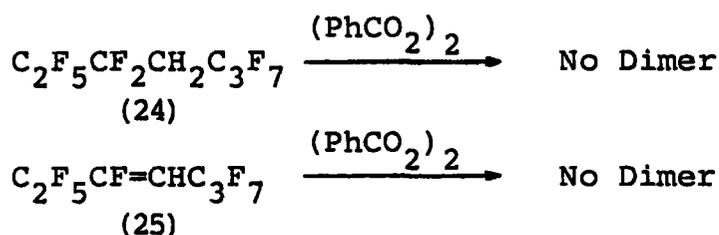


where a dimer represents a cross-link.

#### I.E. (ii) Discussion of Results Obtained

Model studies related to the cross-linking of  $\text{CH}_2=\text{CF}_2$  elastomers have been carried out in three areas which are discussed below


- (a) Amine Cross-linking.
- (b) The effect of peroxides.
- (c) Cross-linking involving  $\text{CF}_2=\text{CFBr}$
- (a) Amine Cross-Linking

Paciorek and coworkers synthesized the four model compounds (25-28) as shown in scheme 1.10.<sup>93,94</sup>

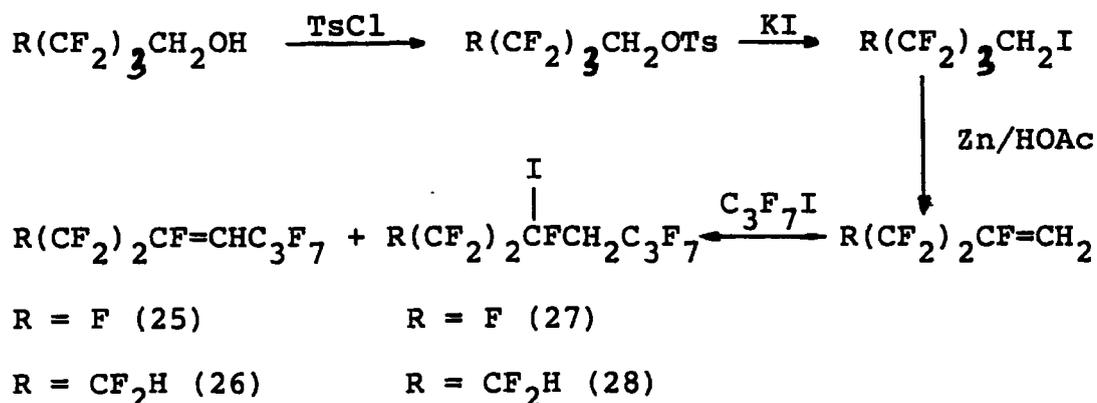


Scheme 1.10


Since the  $\text{HCF}_2$ - group is comparatively inert, these compounds resemble the copolymer system



The model (24) and the model  $\text{HCF}_2(\text{CF}_2)_2\text{CF}_2\text{CH}_2\text{C}_3\text{F}_7$  (30) were treated with  $\text{BuNH}_2$ ,  $\text{Bu}_2\text{NH}$  and  $\text{NEt}_3$  with the results that dehydrofluorination was the initial step in all cases to give (25) and (26)




(25)



(26)

Further treatment of (25) with  $\text{BuNH}_2$  resulted in a mixture of addition-elimination products as outlined in scheme 1.11.

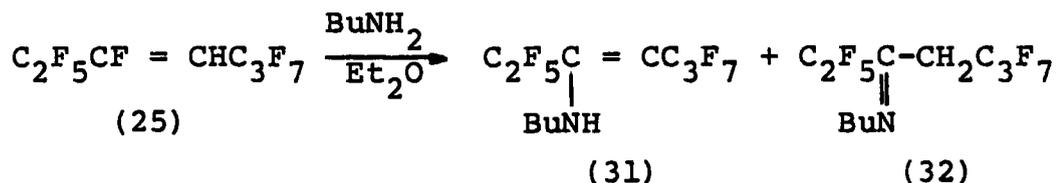


+

(scheme 1.11)




The infra-red spectrum of the conjugated model (33) resembles most closely that of the cross-linked polymer in the 5-7 $\mu$  region, which indicates that structures of the type present in (33) may be of major significance.

It is concluded, therefore, that while dehydrohalogenation is the initial step, the cross-links are formed either by addition of the amine to the unsaturated sites or by interaction of the unsaturated sites alone. In order to test the latter case, the model (25) was heated over a prolonged period but found to be unreactive.

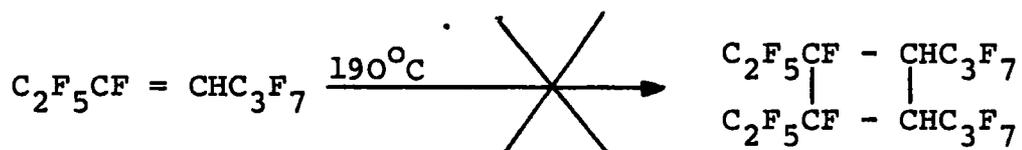


This is in agreement with the findings of Park *et al* that cyclobutane rings are not formed when hydrogen is one of the substituents<sup>95</sup> (Section I.D. (ii)). In order to produce models more closely resembling the  $\text{CH}_2=\text{CF}_2/\text{CF}_2=\text{CFCl}$  copolymer systems, the reactions outlined in scheme 1.12 were carried out involving the model (25)<sup>94</sup>

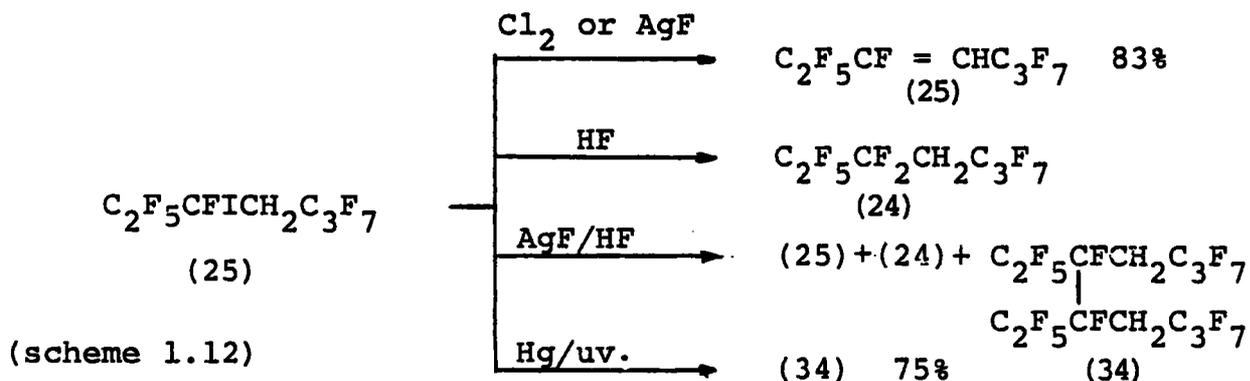

Although replacement of I with Cl was not achieved, the saturated model (24) was useful for peroxide studies. In an effort to produce a conjugated model system related to the

$\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymer, the synthesis outlined in scheme 1.13 was attempted.

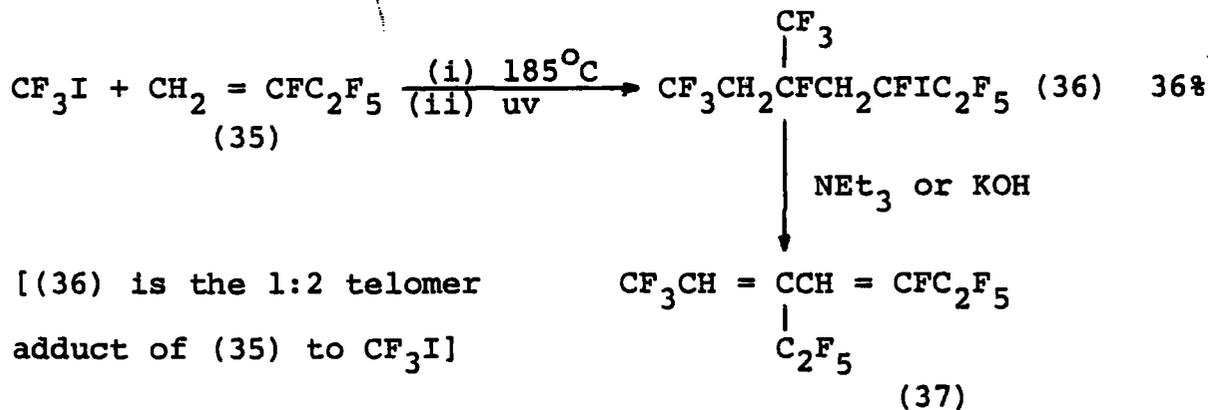

(scheme 1.13)

However no model studies involving the diene (37) have been reported.


#### (b) The Effect of Peroxides

Several mechanisms can be postulated for the peroxide cross-linking of  $\text{CH}_2=\text{CF}_2$  copolymers. Hydrogen abstraction followed by subsequent combination of polymer radicals has been discussed (Section I.D.(iv)(a)). However model studies using both  $\text{C}_2\text{F}_5\text{CF}=\text{CHC}_3\text{F}_7$  (25) and  $\text{C}_2\text{F}_5\text{CF}_2\text{CH}_2\text{C}_3\text{F}_7$  (24) with benzoyl peroxide failed to produce any dimers. Furthermore, substances known to liberate phenyl radicals ( $\text{Ph}_3\text{Sb}$ ,  $\text{Ph}_3\text{As}$ ) failed to promote reaction.<sup>76</sup> Yet benzoyl peroxide gives rise to a polymer vulcanizate far superior to that produced by  $\text{MgO}$  alone.<sup>69</sup>

It is clear therefore that cross-linking must be due to reaction of the polymer chain with benzoyl peroxide or its radicals or *via* other radicals produced during the cure. No study so far carried out has elucidated either the type of cross-link formed or the mechanism by which it is formed.

(c) Cross-Linking Involving CF<sub>2</sub>=CFBr (BTFE)

Model studies were carried out related to copolymers incorporating the cure-site comonomer CF<sub>2</sub>=CFBr<sup>73,74</sup> (Section I.D.(i) Scheme 1.4) in order to elucidate the mechanism involved and the final structure of the cross-linked network. The work was based partly on e.s.r. data because it involved production of the model perfluoroalkyl radical (37).

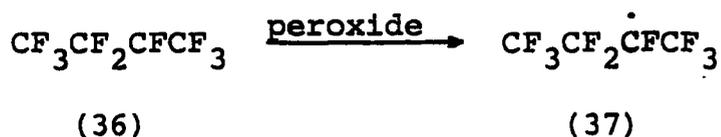


The study of fluorinated alkyl radicals has been well developed<sup>96,98</sup> and therefore provides a powerful tool for this type of study.

2-Bromooctafluorobutane, a model for the pendant Br atoms of copolymers incorporating CF<sub>2</sub>=CFBr, was treated initially with di-t-butyl peroxide in cyclopropane. The resulting solution gave an intense e.s.r. signal due to the production of the radical (37).

It is postulated that, after β-scission of the radical (38)



abstraction of Br is achieved by the resulting  $\dot{\text{C}}\text{H}_3$  radicals

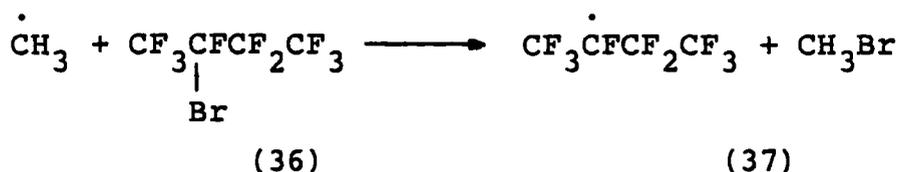


However when the volatile materials from the actual polymer cure were analysed, very little CH<sub>3</sub>Br was detected (Table 1.9).

TABLE 1.9 Volatile Products from Cure Involving CF<sub>2</sub>=CFBr

Product	Amount Generated (relative)
(CH <sub>3</sub> ) <sub>2</sub> C=O	100
(CH <sub>3</sub> ) <sub>3</sub> COH	8.1
CH <sub>3</sub> Br	1.9
CH <sub>4</sub>	28.7






While the relative proportion of acetone to t-butanol is in accordance with  $\beta$ -scission of the radical, (38) the relatively low amounts of CH<sub>3</sub>Br and CH<sub>4</sub> produced have been explained in terms of the rapid addition of  $\dot{\text{C}}\text{H}_3$  radicals to the radical trap triallylisocyanurate (TIC)(39) (Scheme 1.14).

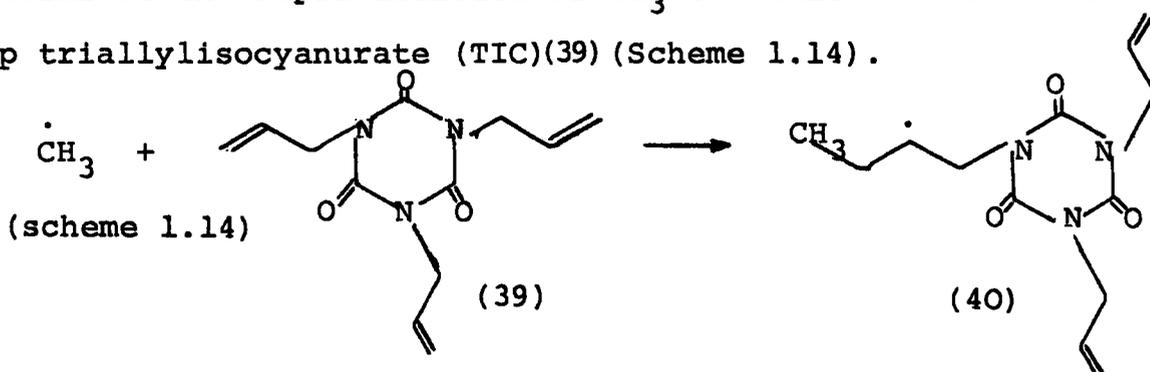



Abstraction of Br $\cdot$  from the polymer is thought mainly to be by the radical, (40) with the polymer radicals (resulting from abstraction of Br $\cdot$ ) then adding across the double bonds of TIC to give a cross-linked network (Scheme 1.15).

The mechanism may be viewed as a chain reaction. The driving force during the propagation step appears to be the transfer of Br $\cdot$  from the electron-poor fluoropolymer to the electron-rich hydrocarbon radical.

## Initiation

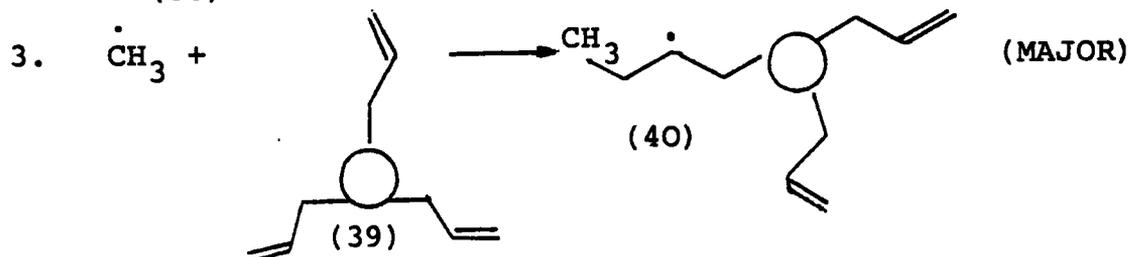

## Propagation

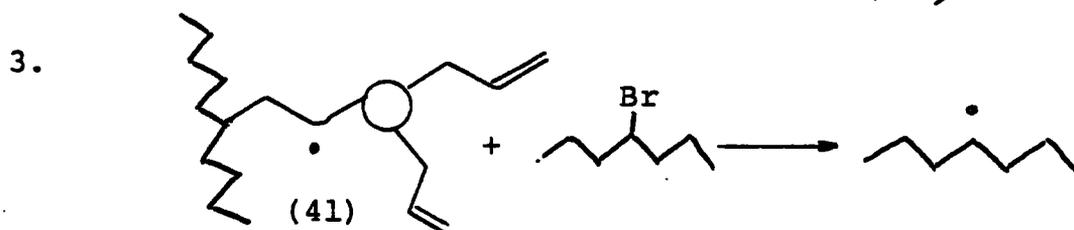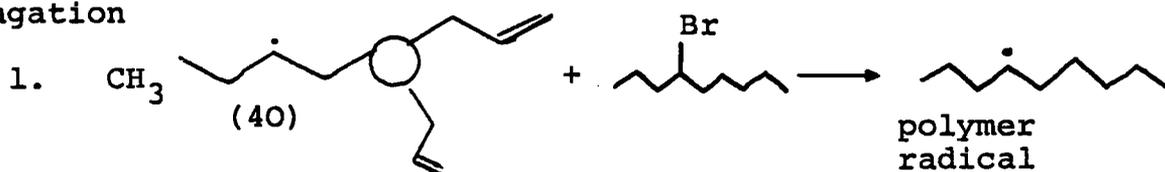

(scheme 1.15)

I.E. (iii) Conclusions

The mechanisms involved in the cross-linking by amines is well understood. However it is thought that post-cure heating of the cross-linked polymers results in the formation of a certain amount of new cross-links, the nature of which is not fully understood. There have been no model studies directed towards investigating this effect.

The bisphenol cross-linking process has not been studied using model systems. Such a study could give more information as to the significance of post-cure heating and might also verify the postulates of Smeigel<sup>49</sup> (Section I.D.(iii)). Furthermore, model studies should be carried out to establish the stability of bisphenol cross-links.

While model studies could give more definitive information about the other systems discussed above, their excellent physical properties and stability have not yet necessitated this type of investigation.


## CHAPTER TWO

SYNTHESIS AND EXAMINATION OF  
SATURATED MODEL COMPOUNDS

2A. Introduction - Research Objectives

The objectives of this research are to synthesize and explore the chemistry of model compounds related to the cross-linking of copolymers of  $\text{CH}_2=\text{CF}_2$  and  $\text{CF}_3\text{CF}=\text{CF}_2$ .




Initially this involves an investigation into the mechanism of cross-linking involving bisphenol AF (2) and the stability of such cross-links.

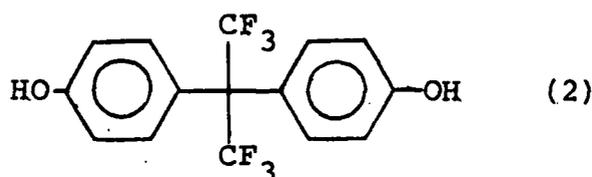


The general chemistry of the model compounds is investigated both to provide a broader background as to the reactivity of the copolymer systems and an opportunity to explore some novel reactions of fluorohydrocarbon systems.

2B. Choice of Model Compounds and Strategy


The important structural features of the  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymer system are the following - <sup>39,80</sup>



Model compounds of the form <sup>99-102</sup>



contain all of these structures and may be obtained in good yields, *via* two-step syntheses, from perfluoroiodoalkanes. This approach is outlined in scheme 2.1.

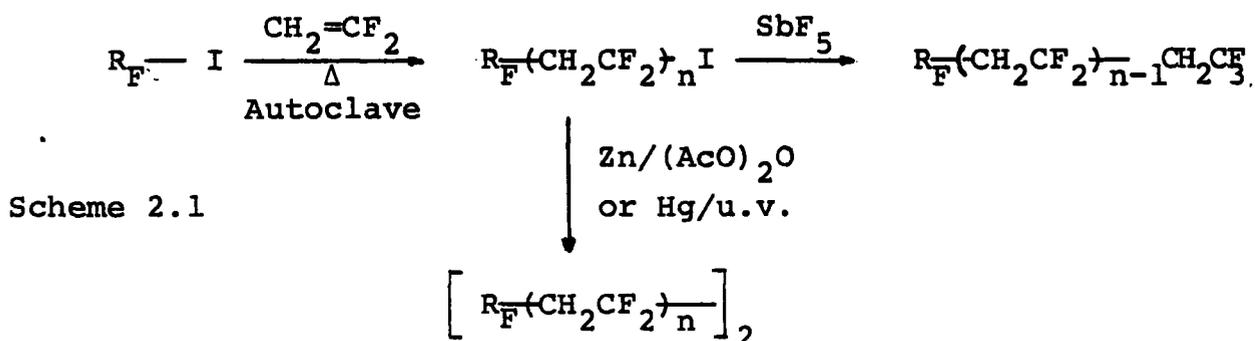


These reactions and the synthesis of  $(\text{CF}_3)_2\text{CFI}$  (44) are discussed below.

## 2C. Synthesis of Model Compounds

### 2C (i) Synthesis of 2-Iodoheptafluoropropane (44)

There are many reports in the literature about the synthesis and chemistry of perfluoroiodoalkanes.<sup>103-107</sup>



2-Iodoheptafluoropropane  $(\text{CF}_3)_2\text{CFI}$  (44) was prepared in excellent yields using the method of Chambers *et al.* This involves the addition of "I-F" to  $\text{CF}_3\text{CF}=\text{CF}_2$  under autogenous pressure<sup>108</sup>

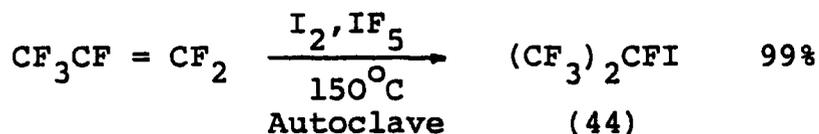

2C (ii) Telomerization Reactions <sup>109,110</sup>

(a) (CF<sub>3</sub>)<sub>2</sub>CFI/CH<sub>2</sub>=CF<sub>2</sub> Telomers <sup>101</sup>

When (CF<sub>3</sub>)<sub>2</sub>CFI (44) is used as a chain transfer agent (*e.g.* in the reaction with CH<sub>2</sub>=CF<sub>2</sub>, Scheme 2.2) it is a useful source of tertiary fluorine.

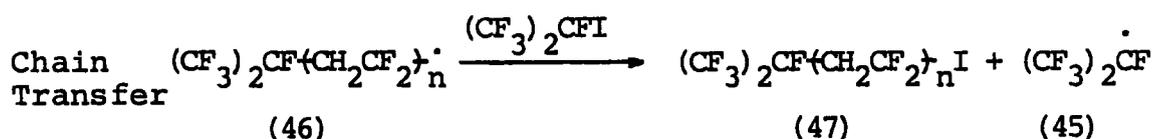

Scheme 2.2

The reactions were carried out in an autoclave without free-radical initiators at 185°C for 24h. The maximum yield of 2H, 2H-1-iodononafluoro-3-methylbutane (n=1), (CF<sub>3</sub>)<sub>2</sub>CFCH<sub>2</sub>CF<sub>2</sub>I (48) was 75% using a 1:1 molar ratio of CH<sub>2</sub>=CF<sub>2</sub> to (44).

In order to increase the yields of the higher telomers (n>1) the proportion of CH<sub>2</sub>=CF<sub>2</sub> was raised and the reaction carried out at 220°C for 36h. The results are shown in Table 2.1.

TABLE 2.1 The Yields of Higher Telomers. n>2.




Ratio of Reactants	Approx. % Composition of (47)				
	n=1	n=2	n=3	n=4	n=5
(CF <sub>3</sub> ) <sub>2</sub> CFI : CH <sub>2</sub> =CF <sub>2</sub> 1 : 3	5	30	30	20	10

These results are in accordance with those of Chambers *et al.* <sup>101</sup>




2C (iii) Coupling Reactions(a) Introduction

The coupling of fluoriodoalkanes has been achieved using mercury and ultra-violet light. For example

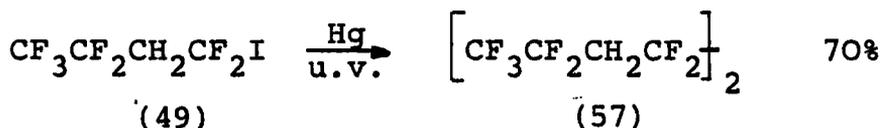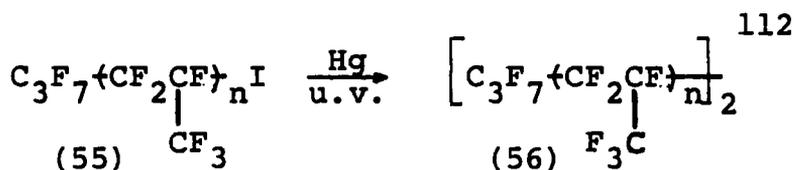
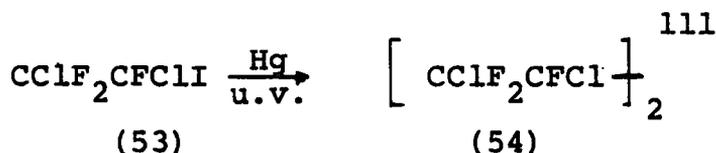


These reactions are believed to proceed the formation of the mercurials  $\text{R}_F\text{HgI}$  which decompose upon further irradiation to give the coupled products  $\text{R}_F\text{-R}_F$ .

Fluoriodoalkanes are also coupled by reaction with zinc in dioxane<sup>113</sup> or in  $(\text{CH}_3\text{CO})_2\text{O}/\text{CH}_2\text{Cl}_2$ .<sup>114</sup> For example Henne and coworkers report the following

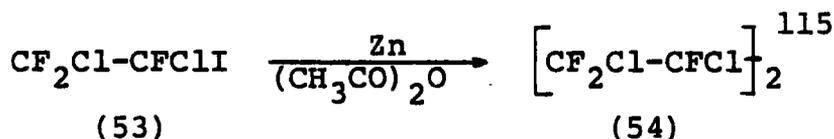


However<sup>114</sup> the iodide (58) did not couple.

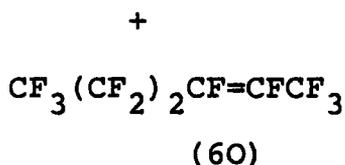

There appears therefore to be a degree of uncertainty when the  $(\text{CH}_3\text{CO})_2\text{O}$ ,  $\text{Zn}/\text{CH}_2\text{Cl}_2$  system is used.

(b)  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{I}$  (48)


Chambers *et al* observed the following<sup>101</sup>

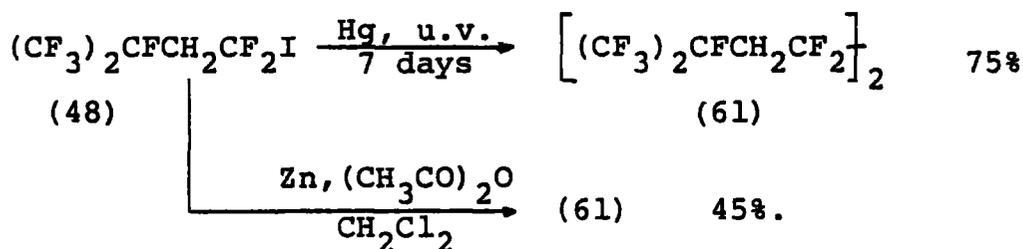

During the course of the present work it was found that 80% isolated yields of the coupled product (61) could be obtained when  $\text{CH}_2\text{Cl}_2$  was excluded and the reaction carried out at  $50^\circ\text{C}$ . Vacuum-line techniques were used to purify the product.


(c)  $(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_2\text{I}$  (62)

When (62) was treated with  $\text{Zn}$ ,  $(\text{CH}_3\text{CO})_2\text{O}$  at  $50^\circ\text{C}$  only 40% yields of the coupled model (63) could be obtained.

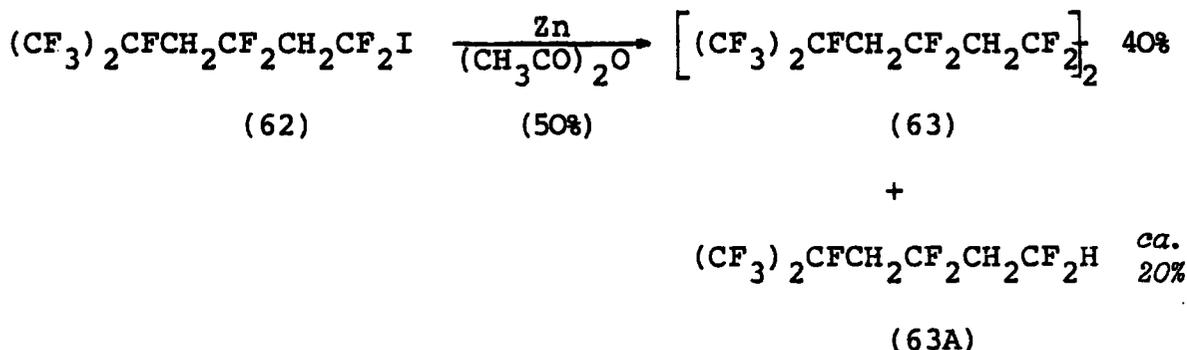

(d)  $\text{CF}_3\text{CF}_2\text{CH}_2\text{CF}_2\text{I}$  (49) and  $(\text{CF}_3)_2\text{CFCFHC}_2\text{F}_2\text{I}$  (50)





2H,2H-1-iodoheptafluorobutane (49) and 2H-1-iododecafluoro-3-methylbutane (50) were both coupled in excellent yields using the  $\text{Hg}/\text{u.v.}$  method.

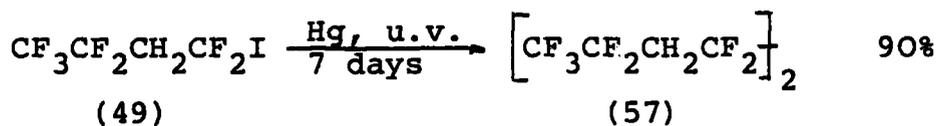

## 2C. (iv) Fluorination of the Telomer Iodides

### (a) Introduction

The C-I bond of iodofluoroalkanes may be converted to a C-F bond by reaction with  $\text{SbF}_3\text{Cl}_2$ ,<sup>116</sup>  $\text{HF}$ ,<sup>94</sup>  $\text{CoF}_3$ <sup>112</sup> and  $\text{Hg}_2\text{F}_2$ <sup>117</sup> as exemplified below

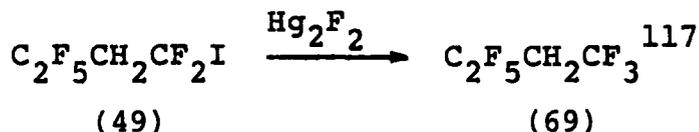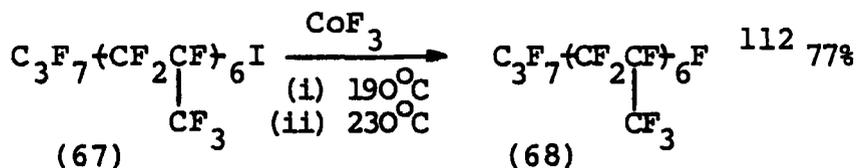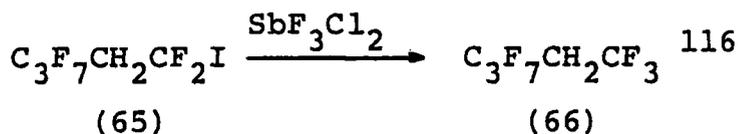


$\text{SbF}_5$  has also been used for similar reactions<sup>118</sup> and was found to work very well at  $0^\circ\text{C}$  with the fluorinations described below.

### (b) $(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_n\text{I}$ . Telomers (n=1-5)


The telomer iodides  $(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_n\text{I}$  (n=1-5) were each fluorinated using  $\text{SbF}_5$  at  $0^\circ\text{C}$  in  $\text{CF}_2\text{ClCFCl}_2$  to yield the

fluorohydrocarbons  $(CF_3)_2CF(CH_2CF_2)_nF$  in good yields.


In an earlier experiment the iodide (62) was sealed with a 2:1 excess of  $SbF_5$  in an evacuated tube. The fluorination reaction is exothermic and caused the temperature to exceed  $100^\circ C$  resulting in an unexpected product (71).

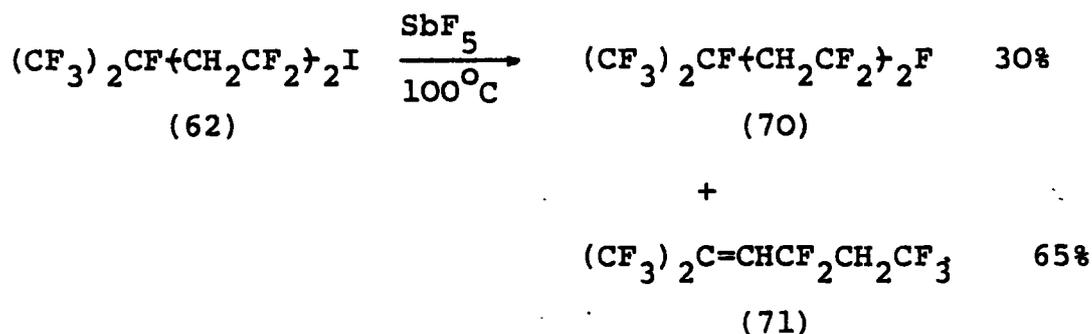

This was rationalized as a Lewis acid catalysed elimination of HF and is discussed in Chapter Three, Section C.



Fluorination of (52) was also achieved using  $SbF_5$  at  $0^\circ C$  in  $CF_2ClCFCl_2$  to give the diastereomer mixture (72)

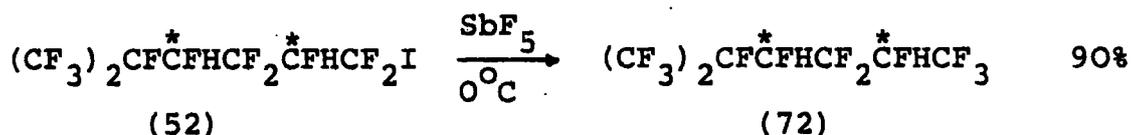


## 2D. Examination of the Saturated Model Compounds

### 2D (i) Introduction


The ingredients used in a typical bisphenol cure of  $CH_2=CF_2/CF_3CF=CF_2$  copolymers were outlined in Chapter One, ID(iii).<sup>49</sup> In order to discover the mechanism of the bisphenol cure each saturated model was heated to the cure temperature  $177^\circ C$  (and higher, for extended times with a variety of the curing agents).

2D (ii) Response to the Curing Agents(a) Inorganic Acid-Acceptors MgO, Ca(OH)<sub>2</sub>


Treatment of the models (70), (61) and (63) with MgO and Ca(OH)<sub>2</sub> at 177°C resulted in only 1-2% unsaturation, (Scheme 2.2).

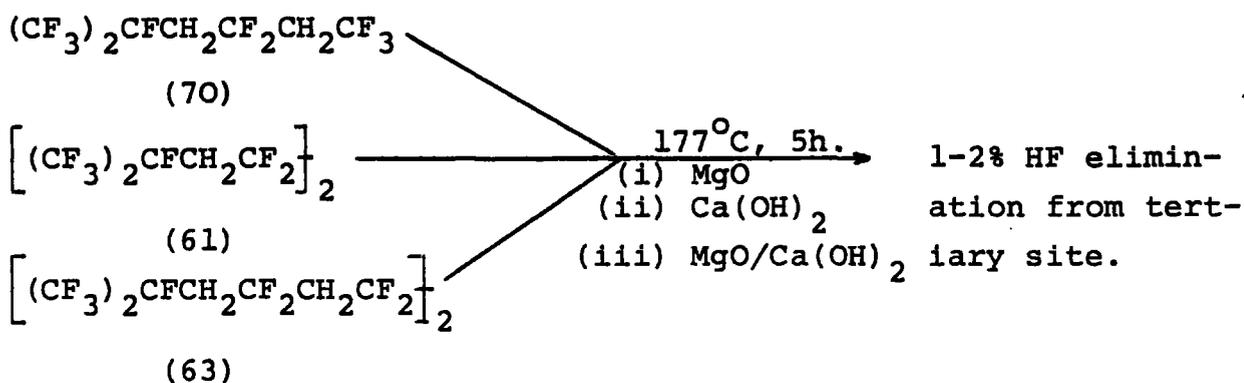


Elimination of HF occurred preferentially at tertiary sites to yield products of the form (in low yields)

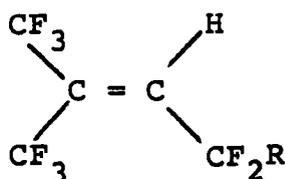

which are easily identified by <sup>19</sup>F, <sup>1</sup>H nmr spectroscopy. This supports the postulate of Smeigel that the sensitive site in CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> copolymers is

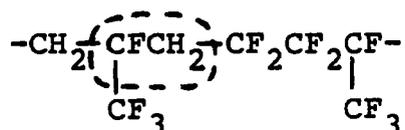(b) Bisphenol AF

When the model (61) was treated with bisphenol AF (2) at 200°C for 3h. there was no reaction.

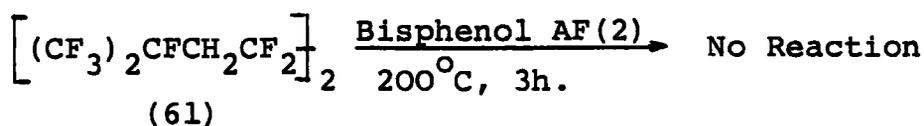


(c) Phosphonium Accelerators

When the model (61) was treated with

(i) Tetraphenylphosphonium Chloride,  $\text{Ph}_4\text{P}^+\text{Cl}^-$

(ii) Benzyltriphenylphosphonium Chloride,  $\text{Ph}_3(\text{PhCH}_2)\text{P}^+\text{Cl}^-$

at  $190^\circ\text{C}$  for 18h. there was no reaction.

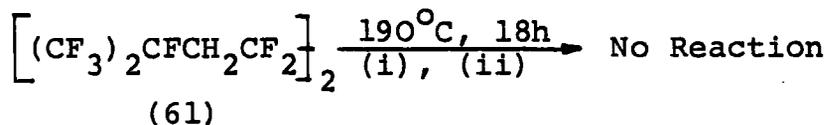

(d) Combinations of the Curing Agents

Table 2.2 summarizes the experiments which were carried out. The temperature in each case was  $177^\circ\text{C}$  unless stated, and maintained over 5h., with the reactants stirred or shaken in sealed tubes. In each case there was no reaction.



TABLE 2.2 Combinations of the Curing Agents

Models	Curing Agents
$\left[ (\text{CF}_3)_2\text{CFCH}_2\text{CF}_2 \right]_2$ (61)	Bisphenol Af, $\text{Ca}(\text{OH})_2$ , MgO
$\left[ (\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_2 \right]_2$ (63)	Bisphenol Af, $\text{Ca}(\text{OH})_2$ , MgO
$\left[ (\text{CF}_3)_2\text{CFCH}_2\text{CF}_2 \right]_2$ (61)	Bisphenol Af $\text{PPh}_4^+ \text{Cl}^-$ $190^\circ$ , 18h.
$\left[ (\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_2 \right]_2$ (63)	
$(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2$   $2$ (61)	Bisphenol Af, MgO, $\text{Ca}(\text{OH})_2$ , $\text{PPh}_4^+ \text{Cl}^-$



- (i) The copolymer system, for reasons which are not clear, is much more reactive than the models (61), (63) and (70) despite the exactly analogous structural features,
- (ii) Very little unsaturation is involved in the curing process.

In the first case the presence in the copolymer cures of significant levels of impurities (*e.g.*  $F^-$ ) or structural irregularities, *e.g.* (73) or (74) may be important

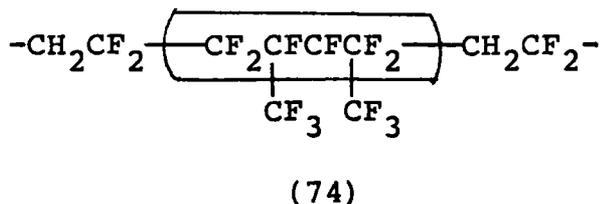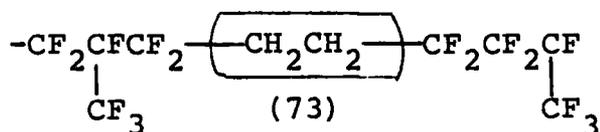

Model reactions involving unsaturated sites is discussed in Chapter Four.

CHAPTER THREE

SYNTHESIS OF UNSATURATED MODELS

3A. Introduction

Elimination of HF from saturated fluorohydrocarbons provides a general route to unsaturated model compounds.<sup>90,100</sup> The systems  $(CF_3)_2CFCH_2CF_2R$ , [R=F (66), R=CH<sub>2</sub>CF<sub>3</sub> (70) and R = -coupled (61)] were investigated.

3B. Base-Catalysed Elimination of HF

3B.(i) Using KOH<sup>100</sup>

Treatment of  $[(CF_3)_2CFCH_2CF_2]_2$ , (61) with KOH at 80°C without a solvent caused tarring, although ca. 5% removal of HF occurred. Elimination occurred preferentially at tertiary sites, since the <sup>19</sup>F nmr spectrum showed clearly the presence of the  $(CF_3)_2C=$  group.<sup>124,125</sup> However both refluxing (61) over KOH at 130°C and passing the vapour of (61) in N<sub>2</sub> through KOH at 180°C resulted in extensive decomposition and tar.


3B. (ii) Using Lithium Alkyls

Treatment of  $[(CF_3)_2CFCH_2CF_2]_2$ , (61) with (i) CH<sub>3</sub>Li and (ii) <sup>n</sup>C<sub>4</sub>H<sub>9</sub>Li at -78°C resulted in vigorous decomposition.

It was concluded that the lithium alkyls were acting as powerful nucleophiles to any unsaturated sites despite the fact that the lithiation of hydrofluoroalkenes is well known.<sup>126</sup>

B. (iii) Using Nitrogen Bases

Treatment of  $[(CF_3)_2CFCH_2CF_2]_2$ , (61) with  $(C_4H_9)_3N$  at  $110^\circ C$  resulted in the single cyclic product 1-(2H-hexafluoroisopropyl)-3-hydrodecafluoro-2,2-dimethylcyclopentene, (79).<sup>100</sup> The most likely mechanism for this reaction is shown in Scheme 3.1.

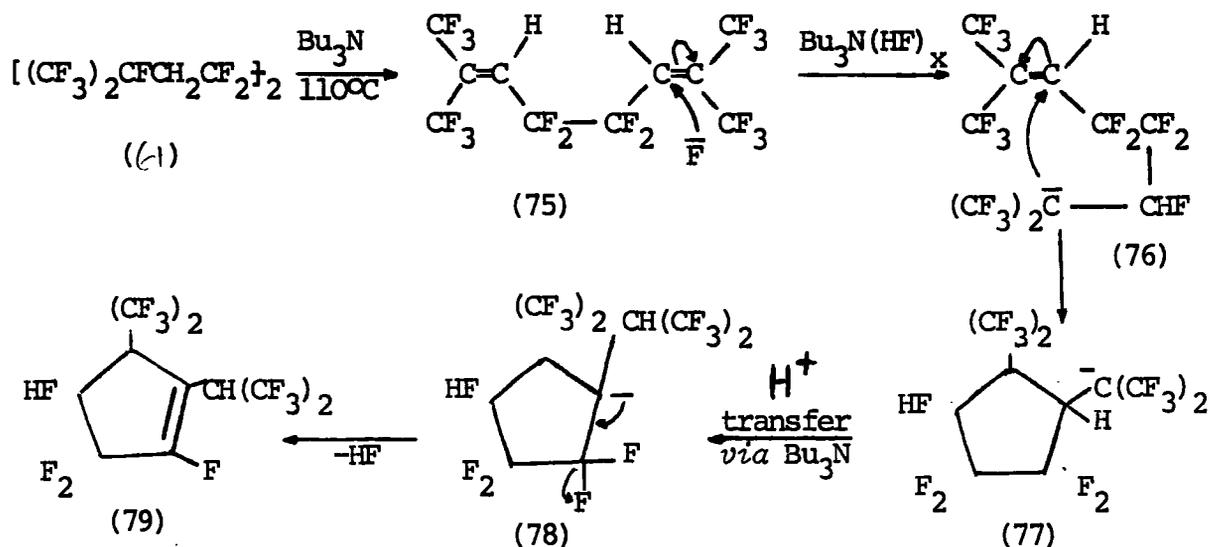

Scheme 3.1

The cyclisation step to produce the intermediate (77) is surprising in view of the steric crowding of the system<sup>127</sup> and provides evidence that large amine hydrofluorides are a source of active  $F^-$ .<sup>128,129</sup> When the reaction was repeated under milder conditions ( $NBu_3$ ,  $100^\circ C$ , 1h) the monoalkene  $(CF_3)_2C=CHCF_2CF_2CH_2CF_2CF_3$ , (80) together with (79) were the only products.


Further chemistry of the product (79) is discussed in Chapter Seven.

When the saturated model  $[(CF_3)_2CFCH_2CF_2]_2$ , (61) was treated with the hindered nitrogen base lithium diisopropylamide (L.D.A.),  $[(CH_3)_2CH]_2NLi$  at  $-78^\circ C$  there was vigorous tarring.




However rarely have Lewis acids been used to form alkenes (*e.g.* biproducts during Friedel-Crafts reactions<sup>131</sup>). The use of  $\text{SbF}_5$  to form fluorinated alkenes is therefore of great interest since, (a) the yields obtained were quantitative and (b) the resulting fluoroalkenes are quite stable to further attack, (*cf.* with  $\text{NBU}_3$  the diene (75) is cyclised by a nucleophilic process).

It is expected that the acid-catalysed route is concerted since the production of an intermediate carbocation (82) would be unlikely due to the presence of  $-\text{CF}_3$  groups at the charge-centre (Scheme 3.2), *e.g.*

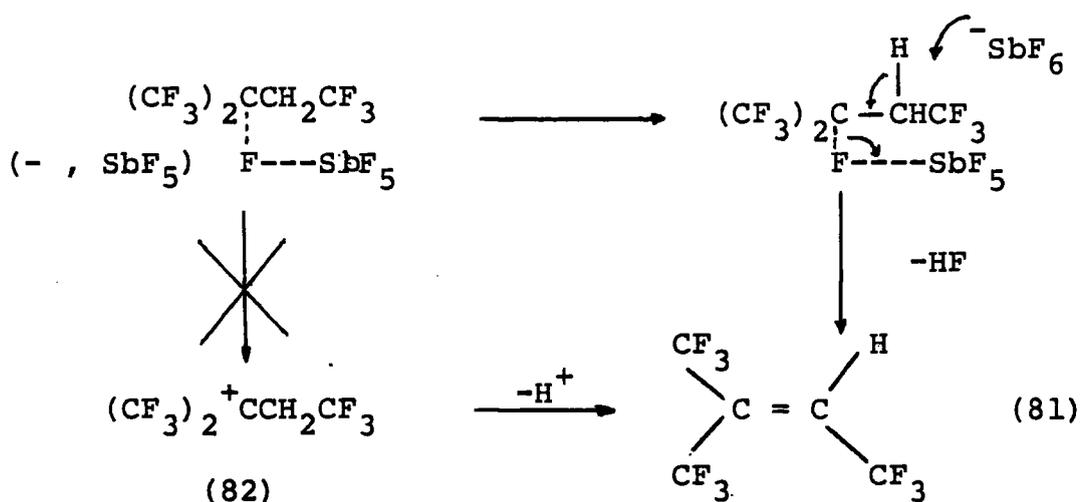

In order to determine whether the presence of superacid  $\text{SbF}_5, \text{HF}$  (a strong protic acid) was not responsible, the model  $[(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2]_2$ , (61) was treated with a solution of  $\text{SbF}_5$  in excess  $\text{HF}$  under autogenous pressure at  $120^\circ\text{C}$ . Only a trace of unsaturation resulted (*cf.* Quant. using  $\text{SbF}_5$ ).

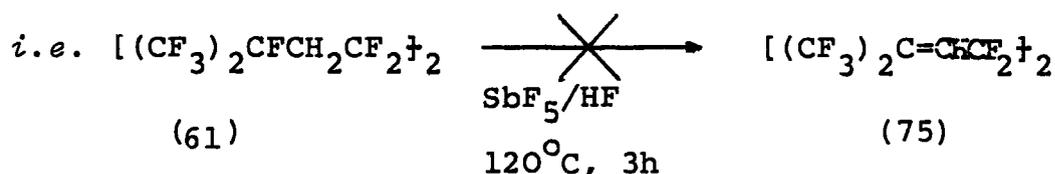


Furthermore the rates of the elimination reactions involving  $\text{SbF}_5$  did not increase as they proceeded (monitored using  $^{19}\text{F}$

nmr. techniques) which would be expected if  $\text{SbF}_5 \cdot \text{HF}$  was responsible, and when a deficiency of  $\text{SbF}_5$  was used, the reactions did not go to completion.

### 3D. Other Routes to Unsaturated Models


#### 3D. (i) Synthesis of 2H-heptafluorobut-2-ene (83)

$\text{CF}_3\text{CF}=\text{CHCF}_3$ , (83) was synthesized in good yield using the reaction<sup>132,133</sup>

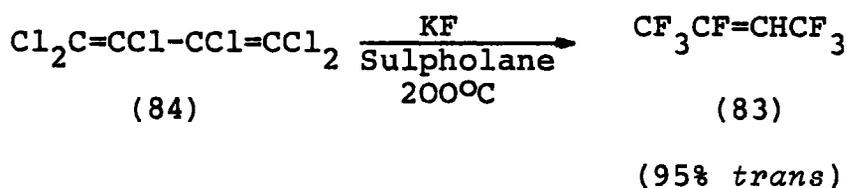

#### 3D. (ii) Reactions of (83) with Sodium Alkoxides

A series of model compounds, which relate to the proposed structure of the bisphenol-cured  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers,<sup>49</sup> were synthesized by nucleophilic displacement of vinyl fluorine from (83) by the sodium alkoxides  $\text{Na}^+\text{Ro}^-$  ( $\text{R}=\text{Ph}$ ,  $\text{CH}_3$ ,  $\text{CH}_2\text{CH}_3$ ).



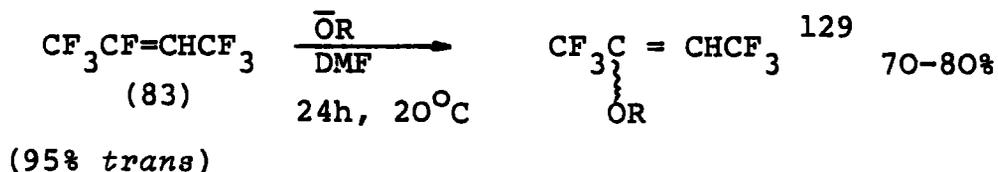


$\text{R} = \text{Ph}$ , 75% trans, (85)

$\text{R} = \text{CH}_3$ , 95% trans, (86)

$\text{R} = \text{CH}_2\text{CH}_3$ , 95% trans, (87)

The model (83) was also treated with bisphenol AF (2) in DMF in the presence of  $\text{K}_2\text{CO}_3$  to form the model cross-link (88).

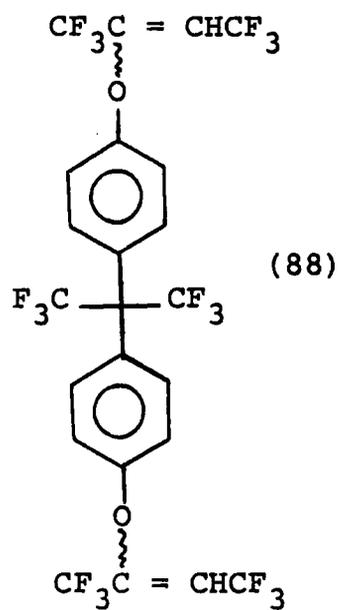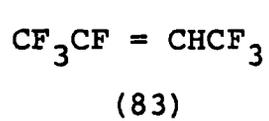

85% *trans, trans*


## CHAPTER FOUR

REACTIONS OF UNSATURATEDMODEL COMPOUNDS4A. Introduction

Copolymers of  $\text{CF}_3\text{CF}=\text{CF}_2$  and  $\text{CH}_2=\text{CF}_2$  cured with bisphenol AF are degraded when subjected to hydrolytic conditions (*e.g.* steam, aqueous alkali) and amines over a prolonged period.<sup>26</sup> This proves a serious disadvantage when these materials are employed in coolant systems.


At the outset of this research the reasons for this instability were by no means clear and it was believed that the bisphenol cross-link was the source of the instability.<sup>26</sup> However a definitive study of this problem had not been carried out despite much speculation.

A study of the unsaturated model systems was therefore carried out in order to establish the reactivity of the bisphenol cross-links (89) and other unsaturated systems related to the  $\text{CF}_3\text{CF}=\text{CF}_2/\text{CH}_2=\text{CF}_2$  copolymer system.

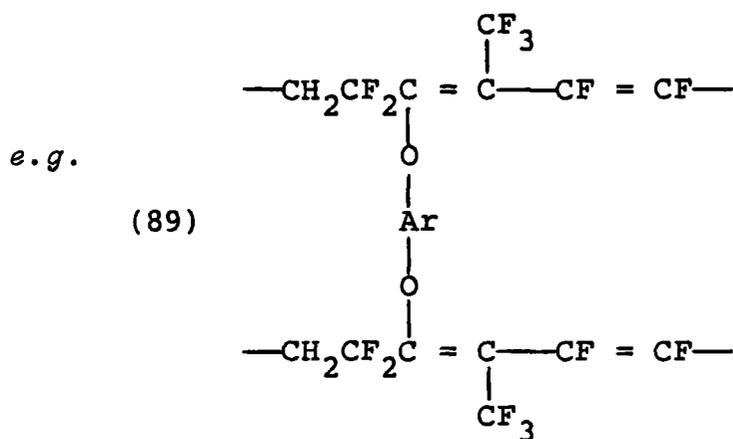


#### 4B. The Hydrolytic Stability of the Model Compounds

The stabilities of 2H-3-phenoxyhexafluorobut-2-ene (85) and 2,2-bis-(4-[2H-hexafluorobut-2-en-oxy-phenol) hexafluorobutane (88) were investigated in the presence of hot water, succinimide and amines.



(85)

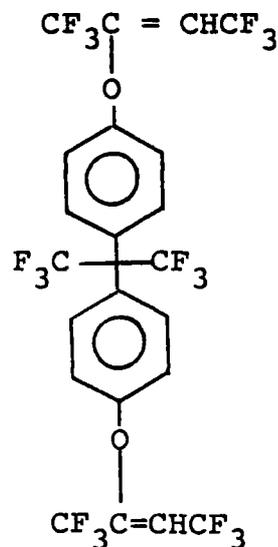

(88)

The conditions employed in the tests were very aggressive and carried out in sealed tubes. Reagents and conditions are summarized in Table 4.1. The systems involving the solvent N,N-dimethylformamide (DMF) were homogeneous whereas those involving steam, inorganic acid acceptors (MgO, Ca(OH)<sub>2</sub>) and KOH were heterogeneous.

In each case there was no detectable chemical change in the models (85) and (88). We have therefore been unable to demonstrate any hydrolytic instability attributable to the bisphenol cross-link.

Consequently unsaturated sites generated in the copolymer system which remain unconverted to cross-links may contribute to the lower stability. Therefore the reactivity of the unsaturated model compounds was examined.

TABLE 4.1 The Hydrolytic Stability of Model Aryl-Ether Cross-links

Model System(s)	Conditions
(85), (88)	30% Aqueous KOH 100°C, 3h
(85), (88)	MgO, Ca(OH) <sub>2</sub> 177°C, 3h
(88)	H <sub>2</sub> O 250°C, 60h
(88)	5% Succinimide DMF 140°C, 36h
(88)	5% NEt <sub>3</sub> DMF 140°C, 60h
(88)	5% PhNH <sub>2</sub> DMF 140°C, 60h

-----

4C. The Reactivity of Model Compounds containing the Group (CF<sub>3</sub>)<sub>2</sub>C=CH-

(i) Under Typical Cure Conditions

The unsaturated model (CF<sub>3</sub>)<sub>2</sub>C=CHCF<sub>2</sub>CH<sub>2</sub>CF<sub>3</sub>, (71) was subjected to conditions typical of the bisphenol curing process.<sup>49</sup> These are summarized in Table 4.2.

TABLE 4.2 Reactivity of  $(CF_3)_2C=CHCF_2CH_2CF_3$  (71)  
under Typical Cure Conditions

Components	Conditions
(71) MgO, Ca(OH) <sub>2</sub> PPh <sub>4</sub> <sup>+</sup> Cl <sup>-</sup> , PhOH	180°C, 24h
(71) MgO, Ca(OH) <sub>2</sub> PhOH	180°C, 24h
(71) MgO, Ca(OH) <sub>2</sub> Bisphenol AF(2) PPh <sub>4</sub> <sup>+</sup> Cl <sup>-</sup>	200°C, 18h

-----


The model (71) was unchanged under these conditions even over the prolonged periods shown. This stability is very remarkable in the light of the extreme reactivity towards nucleophiles of these model compounds described below.

4C. (ii) Towards Phenoxide, Hydroxide and Fluoride

(a)  $(CF_3)_2C=CHCF_3$


When 2H-nonafluoro-3-methylbut-2-ene (81) was treated with PhOH in CH<sub>3</sub>CN at 20°C in the presence of base (K<sub>2</sub>CO<sub>3</sub>) the single nucleophilic adduct 2-phenoxy-2H,3H,3-trifluoro-

methylhexafluorobutane (90) was obtained in good yield.

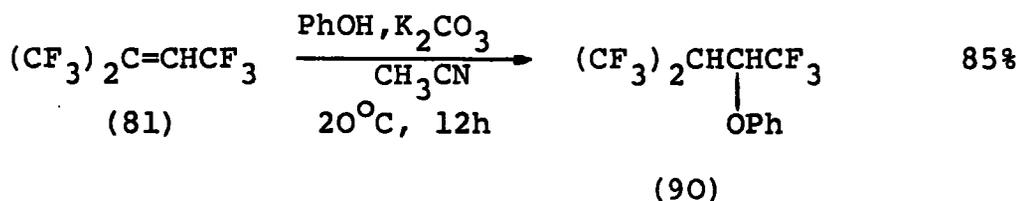


This result demonstrates that this type of unsaturated site is highly susceptible to nucleophilic attack under very mild conditions.

In complete contrast however the model (81) was wholly unchanged when treated with solid powdered KOH at 190°C for 12h. When treated with CsF in sulpholane at 100°C for 2h there was also no chemical change.

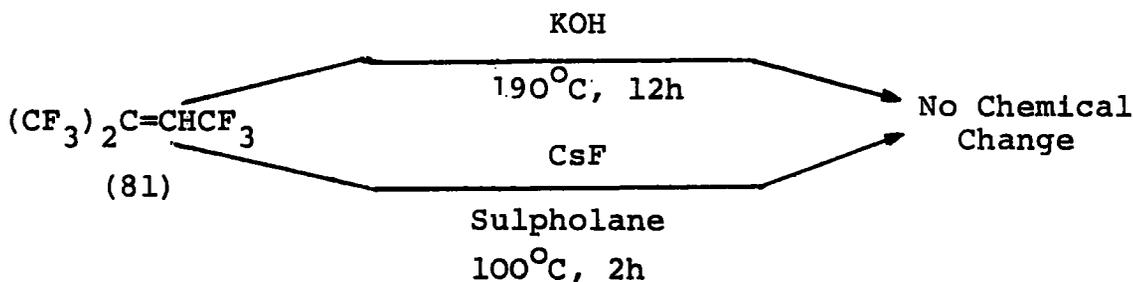


When the model 2,7-bistrifluoromethyl-3,6-dihydrodecafluoroocta-2,7-diene (75) was treated with CsF in tetraglyme at 100°C the cyclopentene derivative (79) was obtained as the only product.

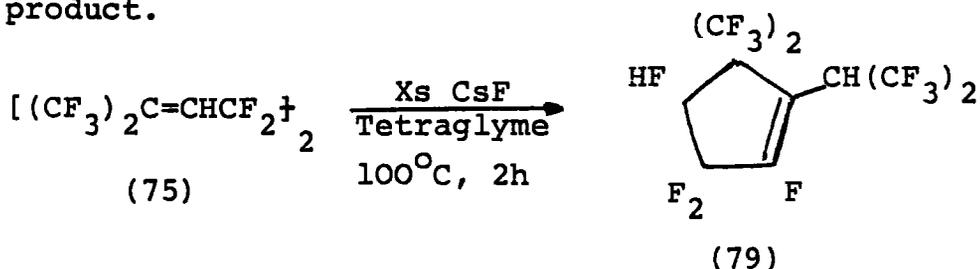


The product (79) is identical to that which was obtained when the saturated model  $[(CF_3)_2CFCH_2CF_2]_2$  (61) was treated with  $NBu_3$ . This result is particularly important because it again demonstrates the susceptibility of this type of unsaturated site to nucleophilic attack. Furthermore, however, it provides support for the mechanism proposed for the reaction involving the saturated model (61) and  $NBu_3$  (Scheme 3.1) which suggests that  $NBu_3(HF)_x$  is a source of active fluoride ion. This is particularly apparent since the cyclisation step is achieved in each reaction over the same period of time (2h,  $100^\circ C$ ) even though excess  $CsF$  was used in the reaction involving (75).

Treatment of  $[(CF_3)_2C=CHCF_2]_2$  (75) with  $PhOH$  (3:1 excess), again under very mild conditions ( $K_2CO_3$ ,  $20^\circ C$ ), resulted in a complex mixture of products which were not separable. Analysis by  $^1H$  and  $^{19}F$  nmr techniques <sup>134</sup> showed the presence of unsaturated products containing vinyl fluorine <sup>135</sup> as well as saturated products. Analysis by mass spectrometry using capillary column gas chromatography showed that the products included nucleophilic diadducts (Molecular weight 614) as well as products from nucleophilic substitution.

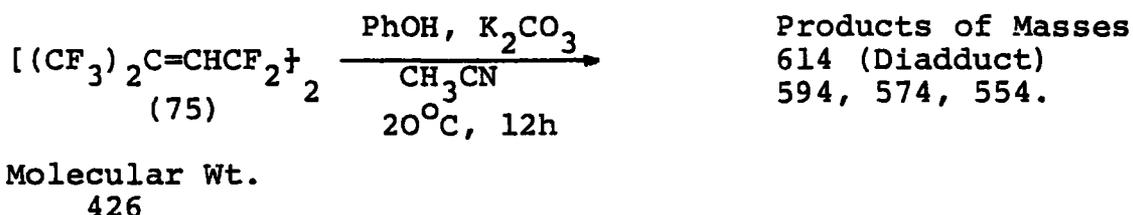


At the time of writing these products had not been fully characterized but further work in the laboratory is proceeding.


This result again demonstrates a high susceptibility to nucleophilic attack associated with the models.



When 2H,2H,4H-undecafluoro-5-methylhex-4-ene (71) was treated with PhOH under very mild conditions, identical to those used for (75) and (81) above, the unusual products (91A) and (91B) were obtained.

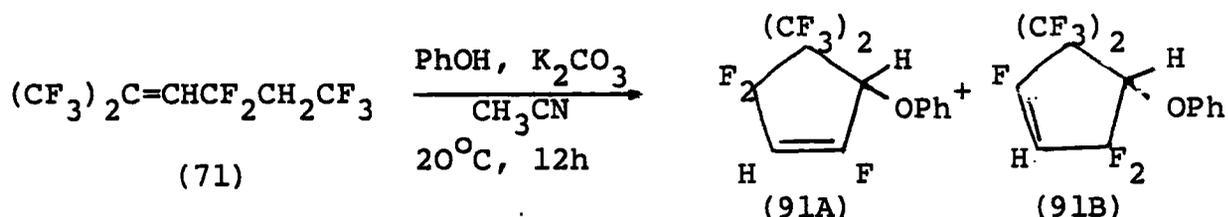


This result presents an interesting mechanistic problem, which may be very relevant to the cross-linking process. The pathway proposed for this reaction is outlined in Scheme 4.1.

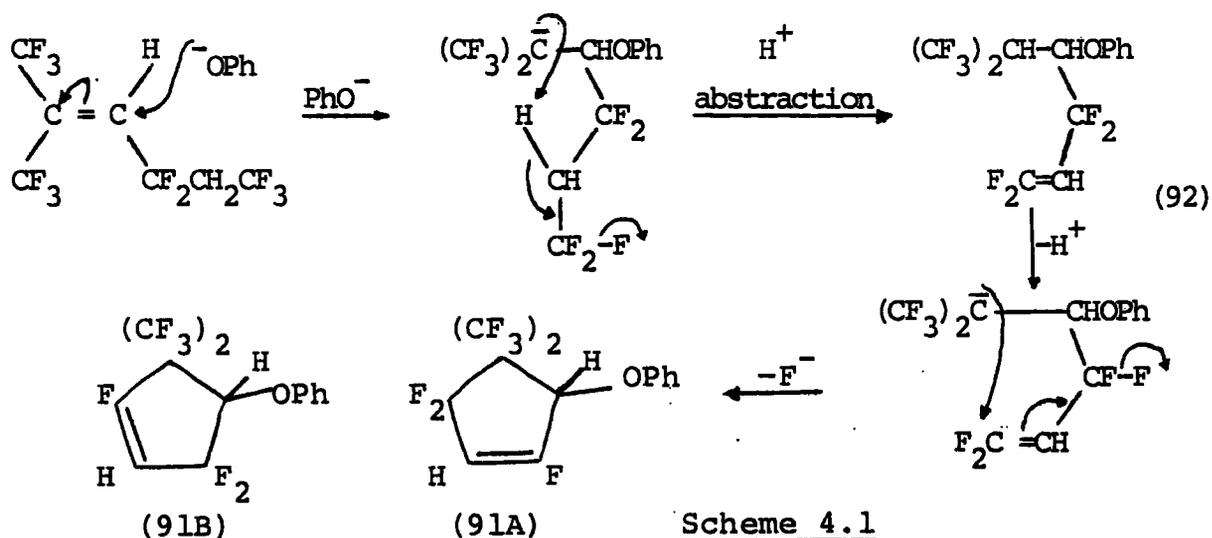

When this type of process is considered in the context of the copolymer system the analogous intramolecular abstraction of  $\text{H}^+$  by a copolymer anion (93) could give rise to further unsaturated sites of the form (94) as exemplified by Scheme 4.2.


## Scheme 4.2

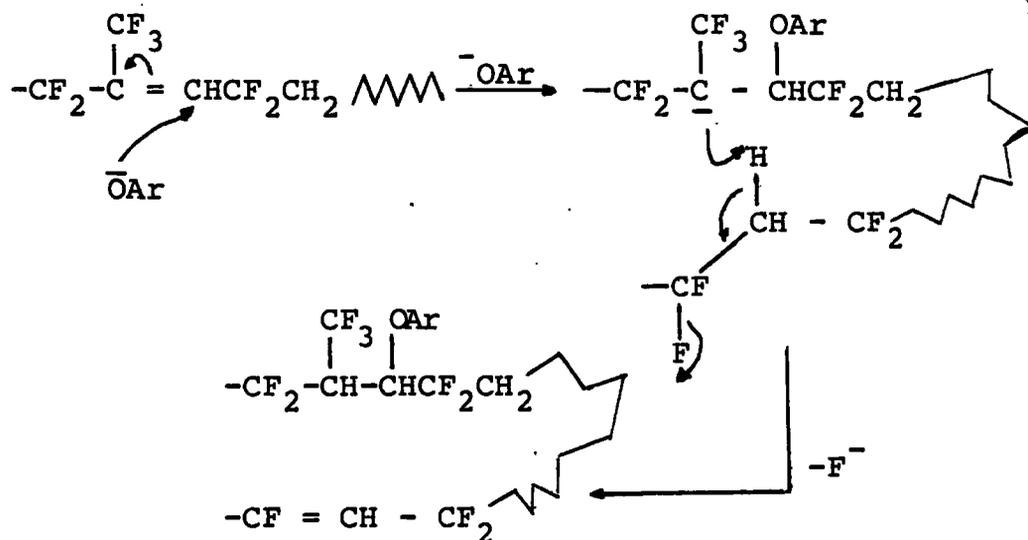

(94)

Alternatively abstraction of  $H^+$  could possibly take place between copolymer chains if they were in suitably close proximity in the solid.

In stark contrast the model (71) was found to be completely unchanged by CsF and KOH under very forcing conditions.


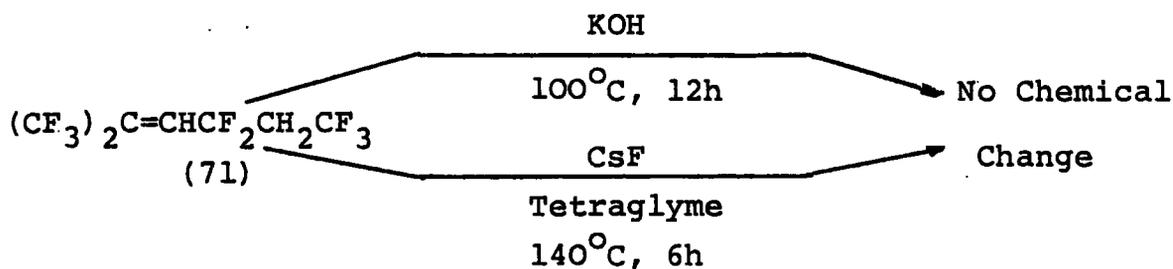


Only after 72h at 150°C did some tarring of (71) occur in the presence of KOH.

The stability of (71) in the presence of CsF at 140°C is very surprising for two reasons:

- (i) The high reactivity of (71) to PhOH under mild conditions.
- (ii) The cyclisation of  $[(CF_3)_2C=CHCF_2]_2$  (75) in the presence of CsF at 100°C indicates that (71) might also be susceptible to attack.

However the expected derivatives (95) and (96) (by analogy to Scheme 4.1) were not obtained.



#### 4D. Conclusions


##### (i) Relevance of Results Obtained

##### Summary

The important observations are summarized by points

(a)-(f):

- (a) The model aryl-ether cross-links (85) and (88) are stable under extremely aggressive conditions.
- (b) Under typical cure conditions <sup>49</sup> the model  $(CF_3)_2C=CHCF_2CH_2CF_3$  (71) showed no tendency to react with bisphenol AF.
- (c) Under very forcing conditions the models (71) and  $(CF_3)_2C=CHCF_3$  (81) were unchanged in the presence of KOH (no solvent) and CsF (solvent).
- (d) In complete contrast the models (71), (81) and  $[CF_3)_2C=CHCF_2]_2$  (75) undergo nucleophilic attack in the presence of PhOH (with solvent) under very mild conditions.
- (e) The reaction of (71) with PhOH clearly demonstrates the feasibility of  $H^+$  abstractions from saturated sites in the copolymer *via* carbanionic sites, *e.g.*:

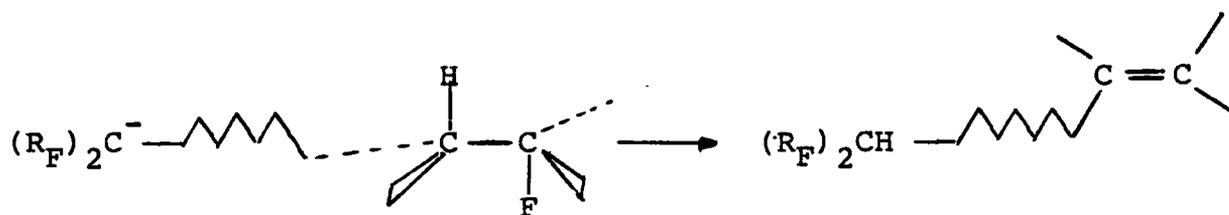


(This may be an intramolecular or intermolecular process).

(f) The model (75) is susceptible to nucleophilic attack by  $F^-$  (with solvent).


### Remarks

It was shown in Chapter Two that elimination of HF by base occurs preferentially at tertiary sites resulting in double bonds of the form (97)

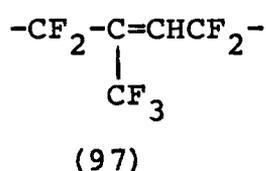

We have now shown that this structure is highly susceptible to nucleophilic attack under mild conditions.

It is worth emphasizing that no products were obtained from nucleophilic attack which involve allylic displacement of  $F^-$  (Scheme 4.3) as postulated by Schneigel for the copolymer.<sup>49</sup>

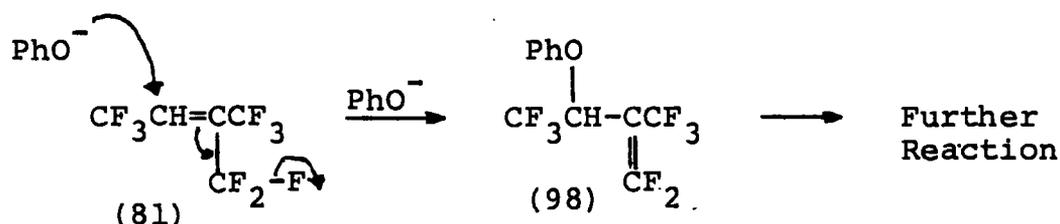

Scheme 4.3

The unsaturated models, however, show surprising resistance to KOH although this may be due to a lack of phase contact in this system.

4D. (ii) Implications for the Copolymer Systems

The stability of the model cross-links (85) and (88) demonstrate clearly that the aryl-ether cross-link (89) in the bisphenol cured copolymer is not the source of instability in this system.

The high susceptibility of the unsaturated models to nucleophilic attack demonstrates that residual unsaturated sites in the cured copolymer will be a source of instability in hydrolytically aggressive environments. Furthermore the number of residual sites may be higher than expected due to  $H^+$  abstraction processes as outlined in Scheme 4.2. Therefore any cross-linking process which employs nucleophilic attack under basic conditions results in a loss of stability under hydrolytically aggressive conditions.

We have now put on a firm basis the reactivity of copolymer sites which previously was a source of much speculation.

Further work in this area is currently being conducted in the laboratory.

## CHAPTER FIVE


AN APPROACH TO A NEW FREE-RADICALCROSS-LINKING PROCESS

In the previous chapter it was shown that the cross-linking of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers using bisnucleophiles, *e.g.* bisphenol AF (2) results in a considerable reduction of the chemical stability of the system. In this chapter an entirely novel approach to cross-linking is discussed. This approach involves the production of free-radical sites in the copolymer promoted by the incorporation of special sterically crowded comonomers.


5A Introduction

In Chapter One (Scheme 1.4) the use of bromine-containing comonomers was shown to promote cross-linking *via* scission of pendant polymer C-Br bonds and reaction of the subsequent polymer radical sites with the coagent triallyl isocyanurate (TIC). 72-74

However, the use of bromine containing comonomers does result in some inhibition of the copolymerisation process<sup>26</sup> (Scheme 5.1) and loss of active C-Br sites:

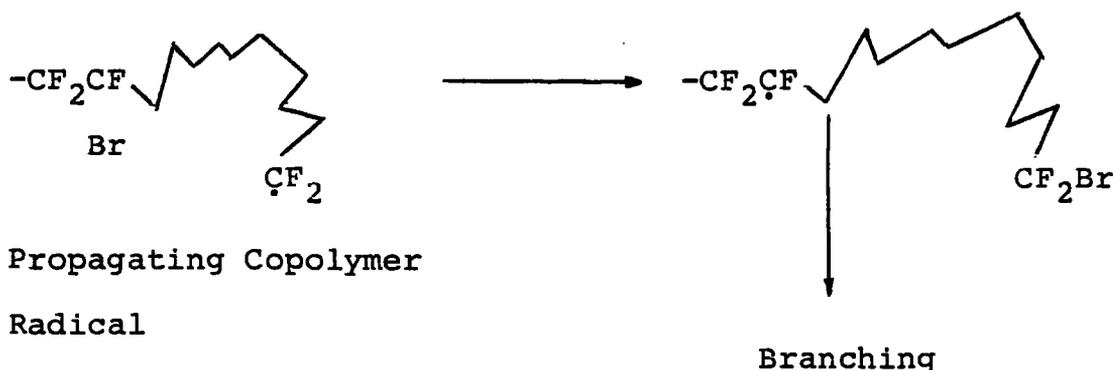Scheme 5.1

Our objective therefore was to synthesize copolymers which did not involve the incorporation of C-Br bonds but which, on heating, gave rise to copolymer radical sites. These sites would be active towards cross-linking in the presence of a suitable coagent (*e.g.* TIC). This objective was achieved by incorporating into the polymer system a varying amount of a third comonomer containing a large, sterically demanding vinyl group. In general this approach is illustrated by Scheme 5.2.

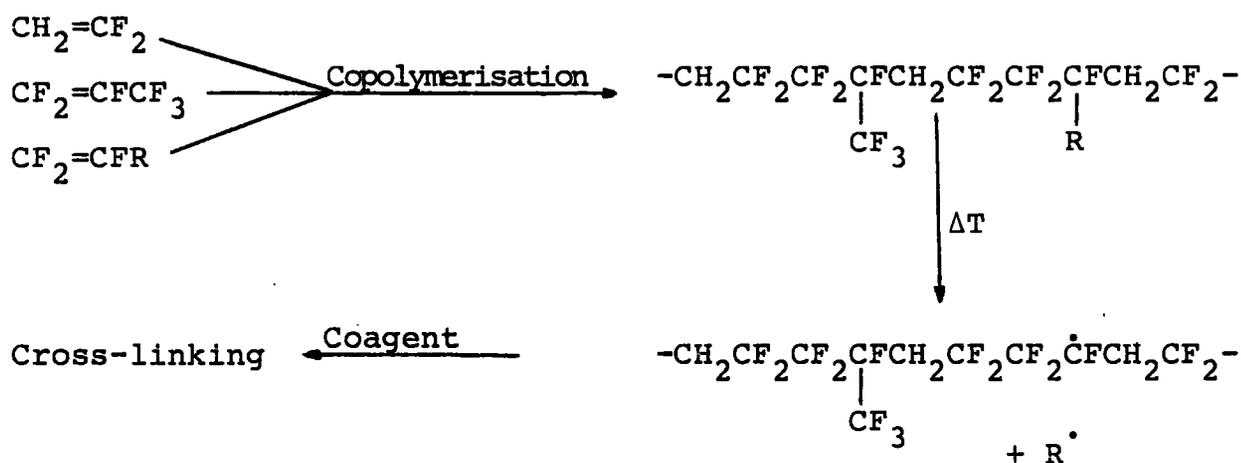


Scheme 5.2

When the group R is large the bond C-R in the copolymer is considerably weakened due to steric crowding and on heating undergoes facile thermolysis giving rise to copolymer radical sites.


We have successfully synthesized and made a preliminary study of copolymer systems incorporating sterically crowded comonomers using vacuum pyrolysis and differential scanning calorimetric techniques.

## 5B Synthesis of Crowded Comonomers

The two crowded alkenes chosen for study initially were 2H-nonafluoro-3-methylbut-1-ene (99) and perfluoro-3-methylbut-1-ene (100).

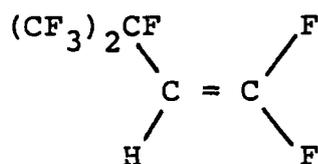


(99)

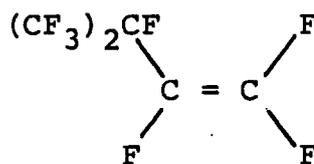

(100)

The syntheses of the alkenes (99) and (100) were achieved in excellent yields using the routes outlined in Scheme 5.3.

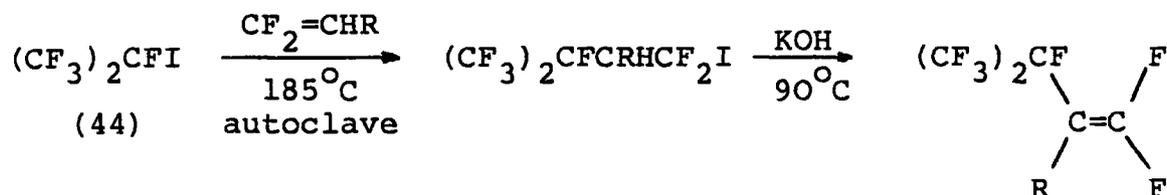

R = H (99) (quant.)

R = F (100) (quant.)<sup>136</sup>

Scheme 5.3

The alkenes (99) and (100) are low-boiling liquids (b.pts. 30°C and 32°C resp.) and easily stored and handled using vacuum-line techniques. These properties render them particularly suited to copolymerisation with CH<sub>2</sub>=CF<sub>2</sub> and CF<sub>3</sub>CF=CF<sub>2</sub> in sealed glass ampoules in the presence of γ-radiation.

## 5C Synthesis of Copolymers Incorporating the Crowded Comonomers

The copolymerisations described below were carried out (in sealed evacuated glass tubes) in the presence of a <sup>60</sup>Co γ-source. This method of initiation is advantageous


because it excludes impurities, *e.g.* initiators, H<sub>2</sub>O *etc.* which remain in the copolymer when aqueous emulsion methods are used.<sup>5,6</sup> Good samples of pure copolymers were therefore easily obtained using this technique.

(i) CH<sub>2</sub>=CF<sub>2</sub> Homopolymer

Samples of poly-1,1-difluoroethene were obtained after  $\gamma$ -irradiation of CH<sub>2</sub>=CF<sub>2</sub> for 3 days at 20°C.

(ii) CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> Copolymers

When a 1:1 molar mixture of CH<sub>2</sub>=CF<sub>2</sub> and CF<sub>3</sub>CF=CF<sub>2</sub> was irradiated for 3 days at 20°C a copolymer was obtained which was determined using <sup>19</sup>F nmr studies (in solution in DMAC) to have molar composition 70:30 in favour of CH<sub>2</sub>=CF<sub>2</sub>. Analysis of the spectra showed that the structure

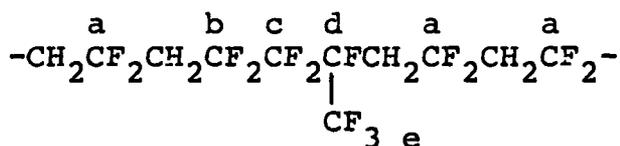


accounts for >95% of the CF<sub>3</sub>CF=CF<sub>2</sub> monomer units, which result is in agreement with the findings of Ferguson.<sup>39</sup> The <sup>19</sup>F nmr data are summarized in Table 5.1 relating to the above structure. Assignment of these chemical shift data was greatly facilitated by using that of model compounds which contained similar structures (see Appendix).

TABLE 5.1  $^{19}\text{F}$  nmr Data for 70:30  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  Copolymer $\delta$   $\text{CFCl}_3$  0 ppm.

Chemical Shift ppm.	Relative Intensity	Assignment
- 75.9	9	e $-\text{CF}_3$
- 94.0	10	a $-\text{CF}_2$
-109.5	4	b $-\text{CF}_2$
-118.1	6	c $-\text{CF}_2$
-183.8	3	d $-\text{CF}$

(iii)  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCH}=\text{CF}_2$  Copolymers

When a 3:2 molar mixture of  $\text{CH}_2=\text{CF}_2$  and  $(\text{CF}_3)_2\text{CFCH}=\text{CF}_2$  (99) respectively was irradiated at  $20^\circ\text{C}$  for 24 hours a copolymer was obtained which gave a surprisingly complex  $^{19}\text{F}$  nmr spectrum (in solution in DMAC). It is clear from resonances observed in the range -60 to -75 ppm that incorporation of the comonomer (99) had taken place, however, the structure of the resulting copolymer is not (101) as expected, but a complex mixture of structures



(101)

which could not be resolved using nmr techniques.

(iv)  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  Copolymers


A range of copolymers of  $\text{CH}_2=\text{CF}_2$  and the crowded comonomer  $(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  (100) were synthesized which varied

in composition. These are summarized in Table 5.2. The percentage incorporation of the comonomer (100) by moles was determined by  $^{19}\text{F}$  nmr spectral analysis (in solution in DMAC).

TABLE 5.2 Molar Compositions of Copolymers of  
 $\text{CH}_2=\text{CF}_2 / (\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  (100)

Molar Ratio of Comonomer Mixture		Conditions ( $\gamma$ -Irradiation)	% Molar Incorporation of (100)
$\text{CH}_2=\text{CF}_2 : (\text{CF}_3)_2\text{CFCF}=\text{CF}_2$			
9	1	72h, 20°C	7%
8	3	72h, 20°C	10%
9	6	168h, 20°C	17%

The  $^{19}\text{F}$  nmr spectra were consistent with the structure (102) accounting for >98% of the comonomer (100).

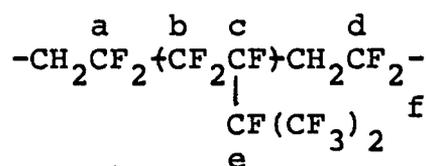

(102)

However it is notable that the chemical shifts of the  $^{19}\text{F}$  atoms present in the structure (102) are moved to lower field as the % incorporation of the crowded comonomer (100) increases. This trend is summarized in Table 5.3.

This trend could be correlated with chronic steric repulsion resulting in a weakening of the structure (102) and a perturbation of the electron density. This effect could result in a deshielding of certain  $^{19}\text{F}$  nuclei. In the more crowded case there is evidence for restricted

TABLE 5.3 The Dependence of Chemical Shift Data from  
CH<sub>2</sub>=CF<sub>2</sub>/(CF<sub>3</sub>)<sub>2</sub>CF=CF<sub>2</sub> Copolymers upon  
Composition

$\delta$  CFC1<sub>3</sub> 0 ppm

Chemical Shifts/ppm			Assignment
Molar % (100)	7	17	
	- 72.6	- 67.6, -69.6	f -CF <sub>3</sub> 's
	- 91.4	- 91.4	d -CF <sub>2</sub>
	-108.2	-109.5	a -CF <sub>2</sub>
	-116.0	-111.8	b -CF <sub>2</sub>
	-186.6	-173.6	e -CF
	-197.0	-180.8	c -CF

rotation about the CF-CF(CF<sub>3</sub>)<sub>2</sub> bond since the -CF<sub>3</sub> groups are inequivalent.

(v) Terpolymer Systems

Terpolymers of CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> and (CF<sub>3</sub>)<sub>2</sub>CF=CF<sub>2</sub> (R=H(99), R=F(100)) were also synthesized using  $\gamma$ -irradiation. The resulting terpolymer compositions, as estimated by <sup>19</sup>F nmr techniques are summarized in Table 5.4.


TABLE 5.4 Terpolymer Compositions

Molar Ratio of Comonomers			Conditions	% Molar Composition of Terpolymers					
CH <sub>2</sub> =CF <sub>2</sub>	CF <sub>3</sub> CF=CF <sub>2</sub>	C <sub>3</sub> F <sub>7</sub> CR=CF <sub>3</sub>		CH <sub>2</sub> =CF <sub>2</sub>	CF <sub>3</sub> CF=CF <sub>2</sub>	<sup>1</sup> C <sub>3</sub> F <sub>7</sub> CR=CF <sub>2</sub>			
R=H	4	:	3	:	2	72h	70	27	ca. 3
R=F	6	:	4	:	1	20°C	85	14	ca. 1

5D Vacuum Pyrolysis of  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  Copolymers

The thermal decomposition of copolymers of  $\text{CH}_2=\text{CF}_2$  and  $(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  (100) shown in Table 5.2 were studied over the temperature range  $20^\circ\text{-}220^\circ\text{C}$ . Volatile decomposition products were collected in liquid-air-cooled traps using vacuum line techniques. In this way definitive information about the ease of fragmentation of these materials in relation to steric strain was obtained.

When the copolymer containing 7% molar concentration of the structure (102) was heated to  $90^\circ\text{C}$  under vacuum a bright orange-red colouration appeared in the cold-trap.




(102)

After prolonged heating at  $120^\circ\text{C}$  the contents of the cold-trap were examined. This consisted of the single product perfluoro-2,3-dimethylbutane (103) and provides clear evidence for the production of the free-radical  $(\text{CF}_3)_2\text{CF}^\cdot$ .




(103)

When a portion of the copolymer residue was redissolved in DMAC a  $^{19}\text{F}$  nmr spectrum was obtained which showed that the % molar concentration of the structure (102) had fallen to 5.8%. Further heating of the copolymer residue resulted in a further reduction to 3.8%. This result demonstrates clearly that selective homolytic cleavage takes place in the copolymer as follows:

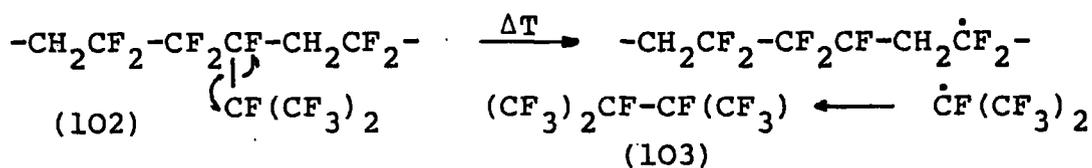

On further heating of the copolymer to 220°C a high-boiling liquid mixture was obtained which contained -CH<sub>2</sub>- groups (<sup>1</sup>H nmr). This provides evidence that at higher temperatures the bond-cleavage is less selective (Scheme 5.4).

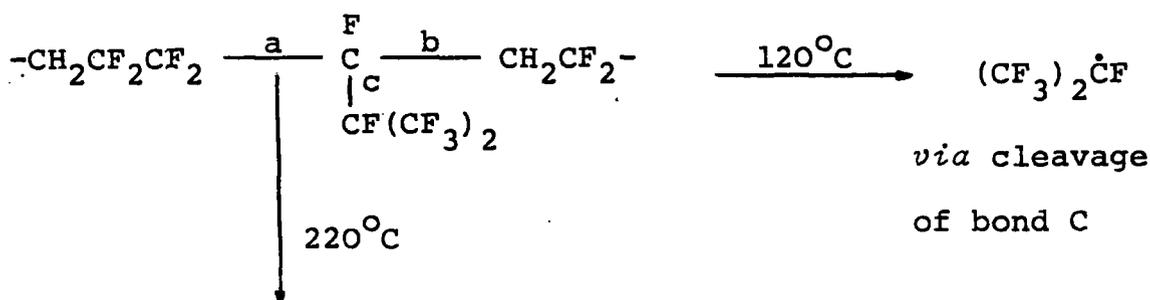

Compounds containing

Scheme 5.4


C, H, F *via* cleavage

of bonds a, b and c.

When the copolymer containing 17% molar concentration of the structure (102) was heated at 90°C for 6h a complex mixture of products was obtained containing C, F and H. These products were analysed by mass-spectrometry using capillary column gas chromatography. 140 products were resolved of mass-range 200-700 mass units. Using the approximate empirical formula C<sub>n</sub>F<sub>2n</sub> it is possible to estimate the number of carbon atoms in each product. The distribution of carbon numbers is represented in Figure 5.1.

It is notable that products containing 5 and 7 carbon atoms are preferred. This is easily rationalized by considering the structure of the copolymer. It may be assumed that no two (CF<sub>3</sub>)<sub>2</sub>CFCF=CF<sub>2</sub> (100) can occur consecutively on

FIGURE 5.1 Approximate Molecular Weight Distribution of the Thermal Decomposition Products of  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CF}=\text{CF}_2$  (17%) Copolymer

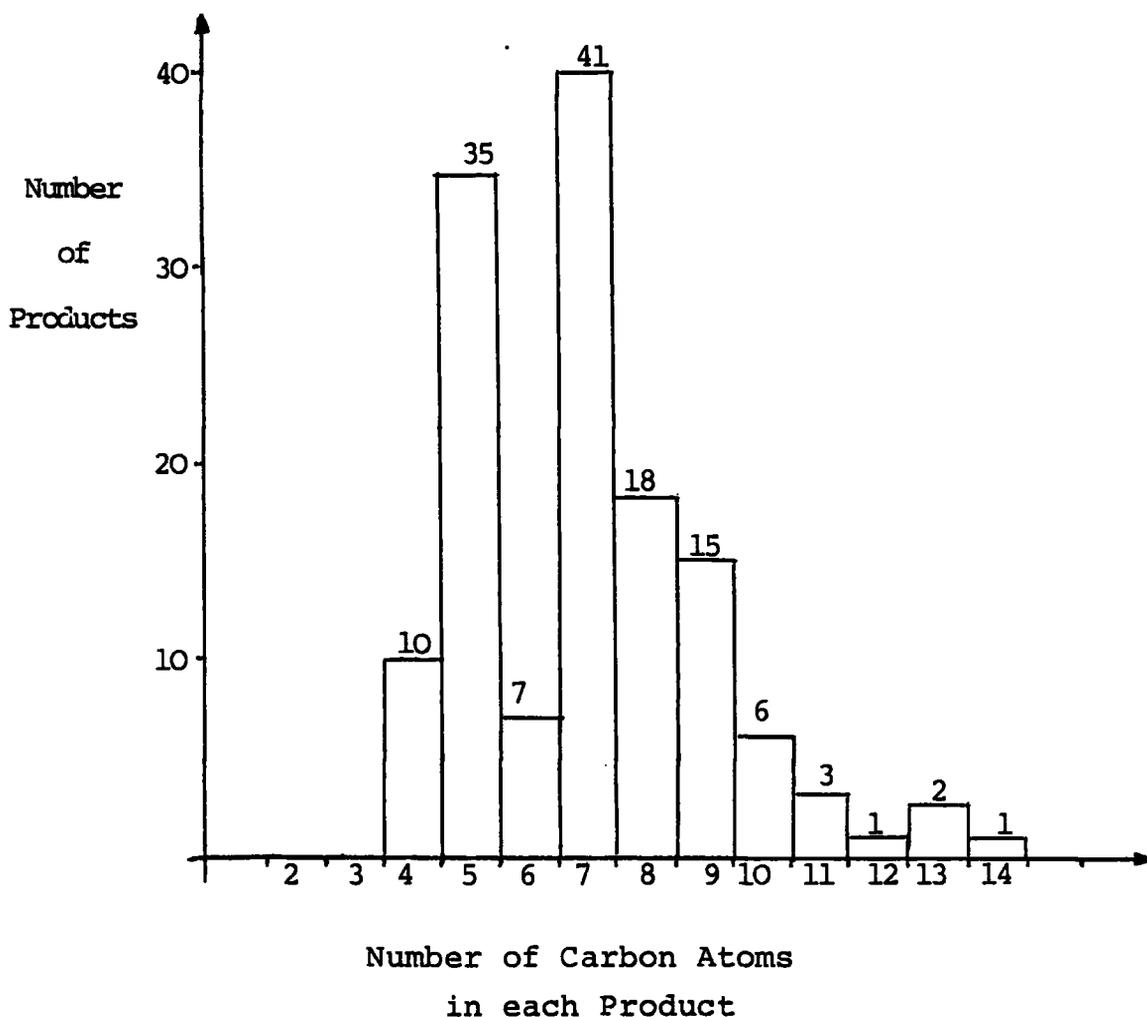

-----

the basis that if  $\text{CF}_3\text{CF}=\text{CF}_2$  does not homopolymerise easily<sup>34</sup> due to steric effects (see Chapter One) then it is even less feasible that (100) will do so. Therefore the shortest product fragments from thermal bond-scission will contain either 5 or 7 carbon atoms as shown by Scheme 5.5.



copolymer of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  containing 30%  $\text{CF}_3\text{CF}=\text{CF}_2$  did not exhibit any exothermic behaviour below  $330^\circ\text{C}$ . Above this temperature a steady exotherm of increasing magnitude occurred which was attributed to decomposition.

(ii)  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  Copolymers

A sample of the  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  (100) copolymer containing 7% molar concentration of (100) was studied using DSC techniques over the temperature range  $20^\circ\text{C}$ - $330^\circ\text{C}$ . A sharp endothermic melting point was observed at  $174^\circ\text{C}$  which was reversible and became sharper on cooling and repeating the experiment. However when the copolymer was heated over the temperature range  $280^\circ\text{C}$ - $330^\circ\text{C}$  an exothermic process occurred which was not reversible. Furthermore on cooling to  $20^\circ\text{C}$  and repeating over the full temperature range no melting point was observed. When the cooled residue was examined it had become brittle and dark brown in appearance in contrast to the soft white plastic appearance of the starting material. These observations are consistent with the formation of a cross-linked network following bond-breaking at the weak sterically crowded sites.


When the copolymer with 17% incorporation of the crowded comonomer (100) was examined a steady and increasing exotherm was observed over the temperature range  $90^\circ\text{C}$ - $200^\circ\text{C}$ . No melting point was observed. This result is again best explained by exothermic cross-link formation, the rate of which increases with the applied temperature.

5E (iii)  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCH}=\text{CF}_2$  Copolymer

When a sample of a  $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCH}=\text{CF}_2$  (99) copolymer containing 5% of the crowded comonomer (99) was studied over the temperature range  $20^\circ\text{C}$ - $200^\circ\text{C}$  a weak exotherm was observed between  $110^\circ$  and  $150^\circ\text{C}$ .

(iv)  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2/(\text{CF}_3)_2\text{CR}=\text{CF}_2$ , (R=H,F) Terpolymers

A sample of a  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2/(\text{CF}_3)_2\text{CFCH}=\text{CF}_2$  (99) containing respective mole-fractions 70%/25%/5% showed clear exotherms at  $140^\circ\text{C}$  and  $170^\circ\text{C}$ . Another sample of this system, of similar composition, was synthesized and studied by Dr. Alberto Fontana (Montefluos SPA). This sample underwent a clear exothermic process at  $165^\circ\text{C}$ <sup>137</sup> as shown by Figure 5.2. When the terpolymer system  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$  (100) of molar composition 85%/14%/1% respectively was examined a weak exothermic feature was observed at  $175^\circ\text{C}$ .

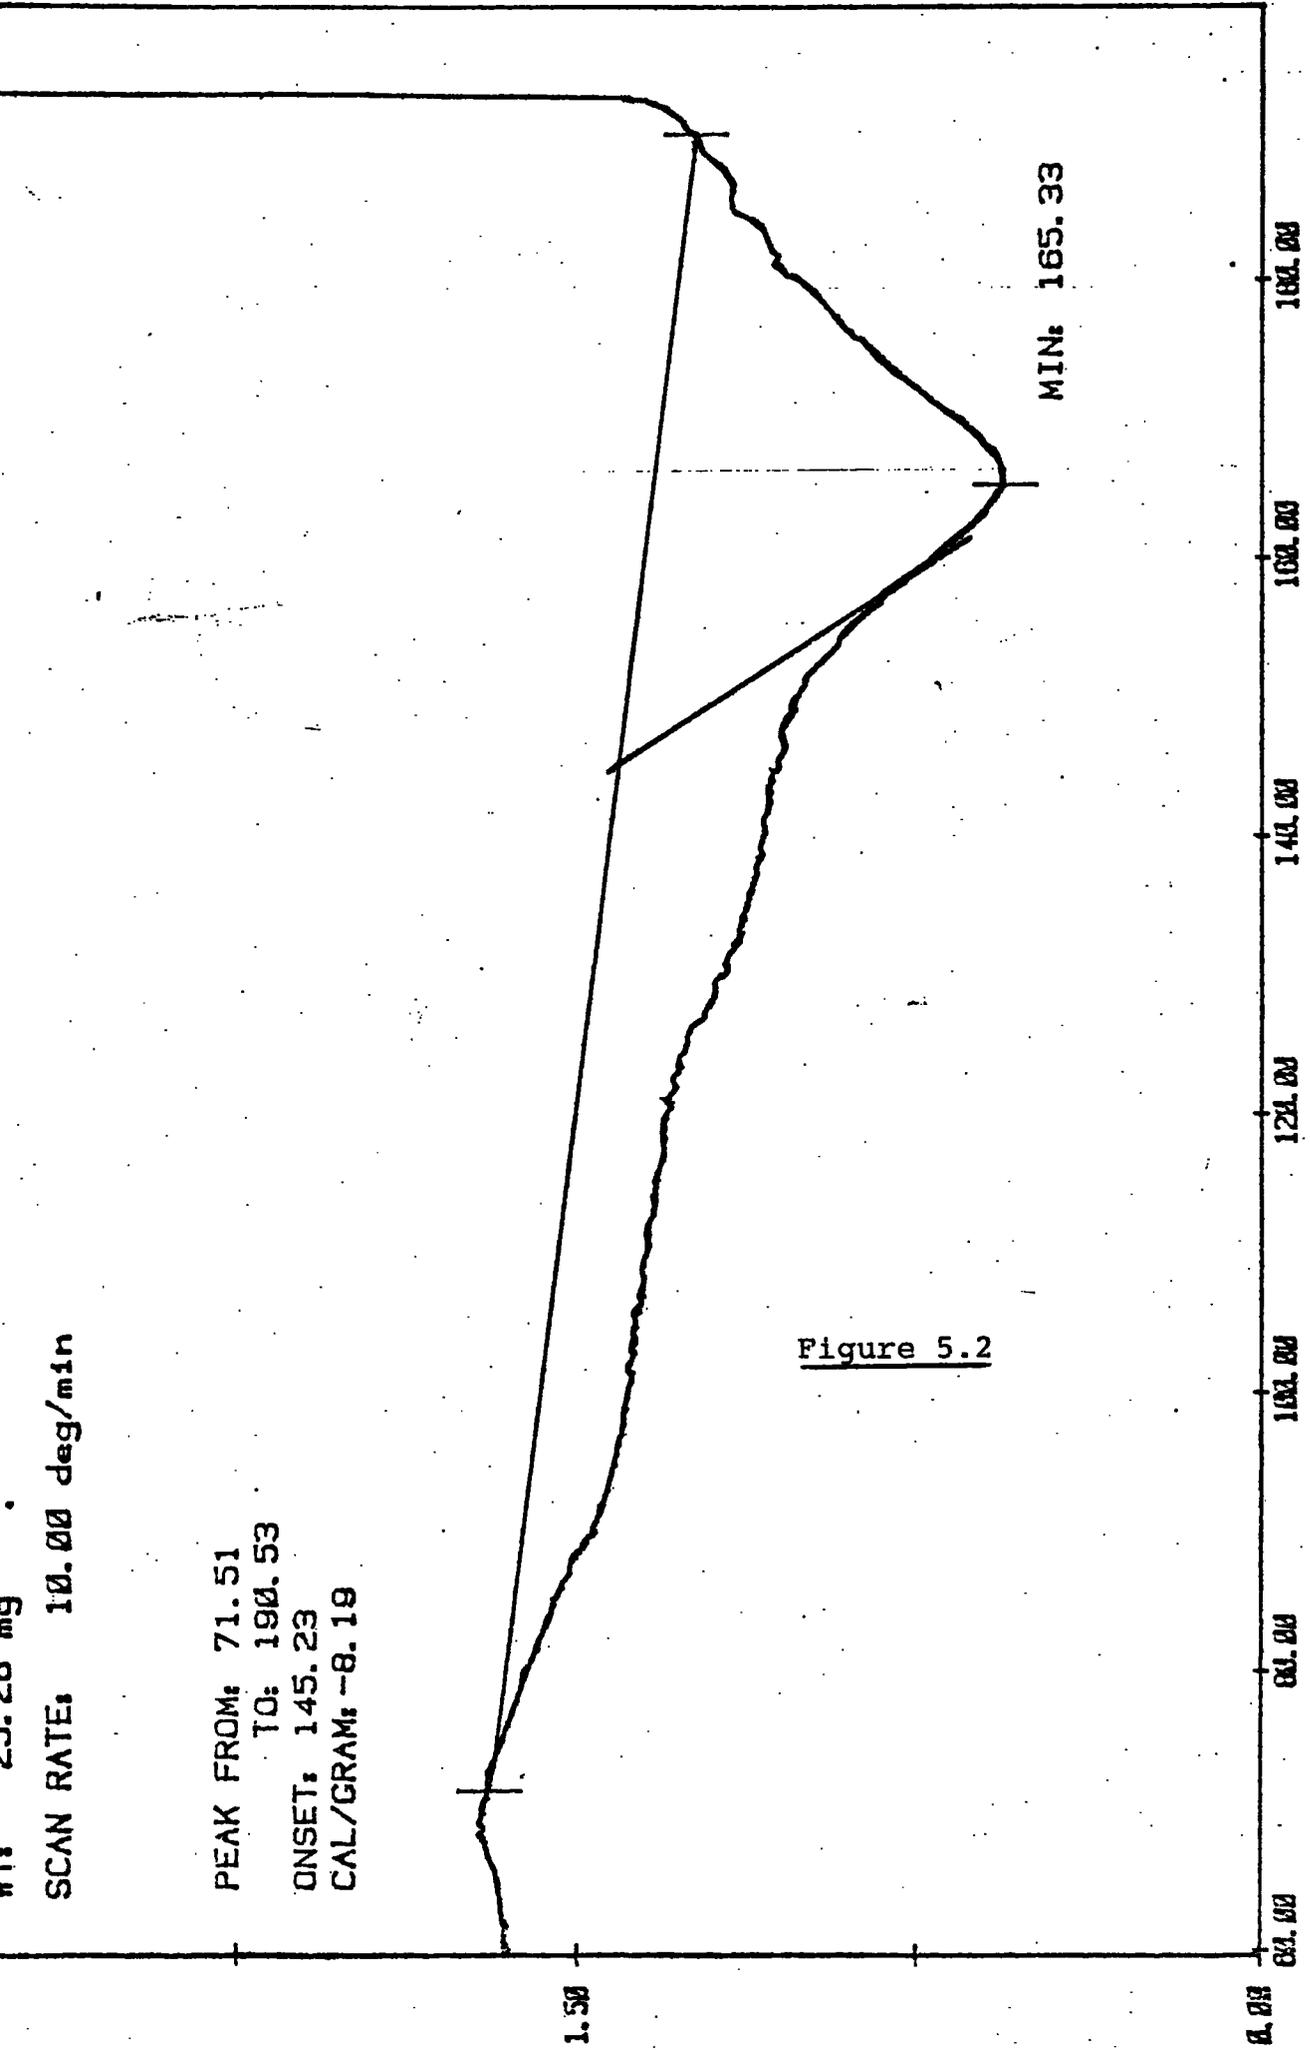

SCAN RATE: 10.00 deg/min

PEAK FROM: 71.51  
TO: 190.53  
ONSET: 145.23  
CAL/GRAM: -8.18

Figure 5.2

DSC

TEMPERATURE (C)


CRAFI FILE: M0GGI.DA  
DATE: 84/01/27 TIME: 09:18

ENDO

MCAL/SEC




The synthesis of the alkene (106) was however not successful using the approach outlined in Scheme 5.6, the only products isolated from the reaction between  $(C_2H_5)_2O$  and (104) being (107), (108) and (109) as shown in Scheme 5.8.

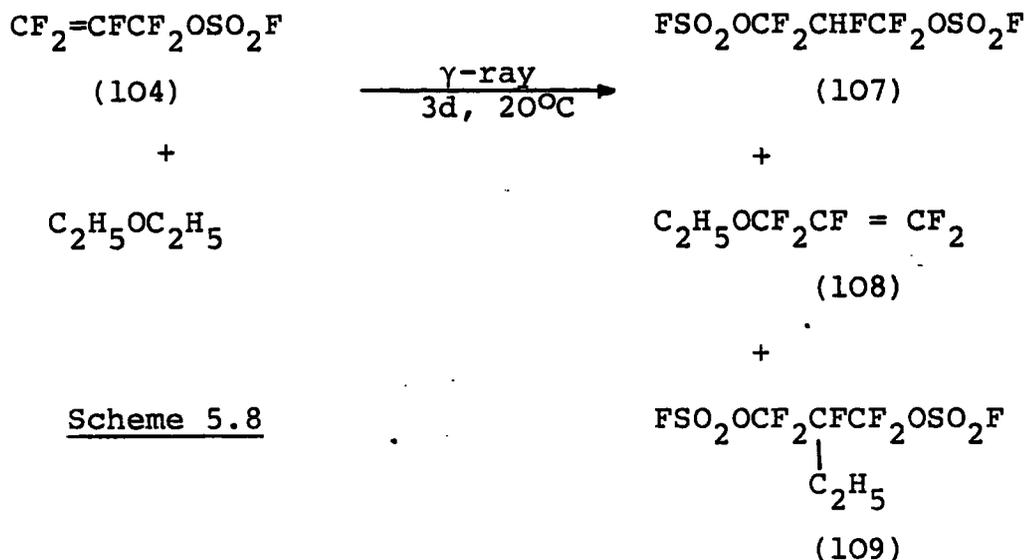

Scheme 5.8

The products (107-109) are rationalized by the ionic processes outlined in Scheme 5.9.

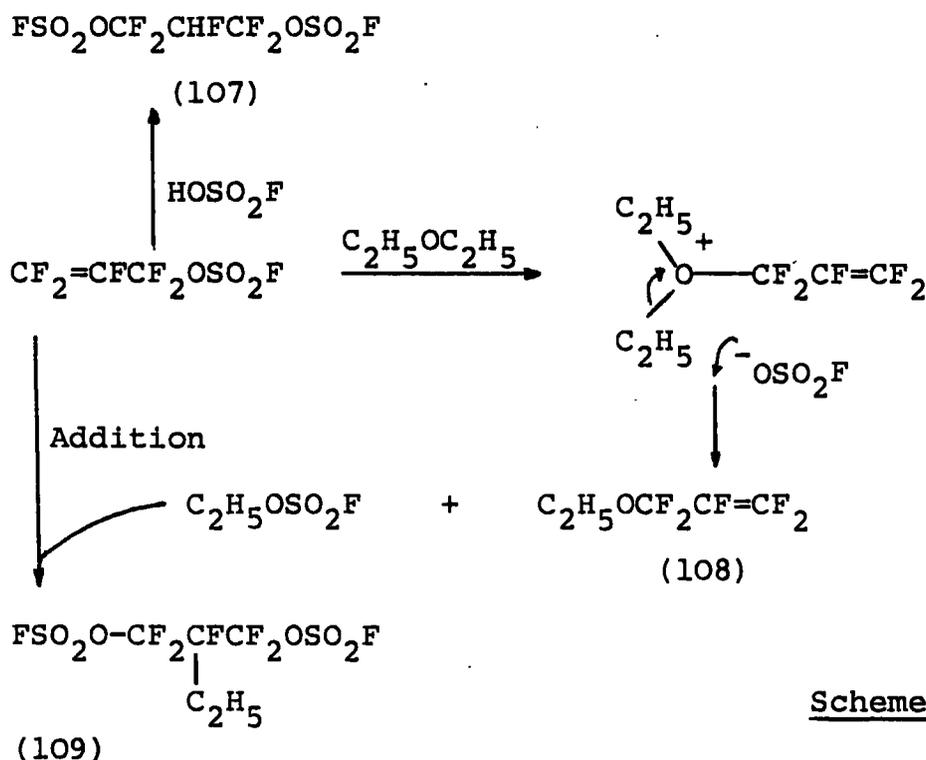


Scheme 5.9

This approach was not further developed.

5G Conclusions(i) A summary of Results obtained

- (a) The comonomers  $(CF_3)_2CFCH=CF_2$  (99) and  $(CF_3)_2CFCF=CF_2$  (100) are easily synthesized in excellent yields from available precursors and are easily handled using vacuum-line techniques.
- (b) These crowded comonomers are each easily incorporated into the  $CH_2=CF_2$  and  $CH_2=CF_2/(CF_3)_2CFCF=CF_2$  polymer system using  $\gamma$ -ray initiation. Furthermore the amount of incorporation can be controlled to a large extent by varying the proportions of the comonomers used.
- (c) When  $CH_2=CF_2/(CF_3)_2CFCF=CF_2$  (100) copolymers are heated bond-scissions occur due to steric overcrowding. At  $120^\circ C$  this process occurs selectively for 7% incorporation of (100) to give  $\dot{C}F(CF_3)_2$  and polymer radicals.

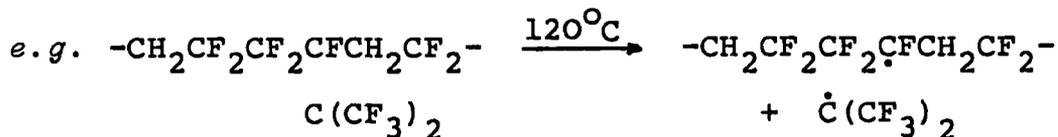

At higher temperatures, *e.g.*  $220^\circ C$  bond-scissions occur less selectively and fragmentation of the polymer backbone takes place. When the concentration of the comonomer was increased to 17% the temperature at which bond-scission occurred was lower *ca.*  $90^\circ C$  and, from analysis of the products of decomposition, appeared to be completely non-selective involving fragmentation of the polymer backbone.

- (d) When differential scanning calorimetric (DSC) methods were used to study the thermal behaviour of  $CH_2=CF_2$




and  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers incorporating the special comonomers (99) and (100), exothermic processes were identified which did not occur when the special comonomers were excluded. The DSC study of the  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2/(\text{CF}_3)_2\text{CFCH}=\text{CF}_2$  (99) was particularly promising, showing clear exothermic non-reversible processes between  $140^\circ\text{C}$  and  $170^\circ\text{C}$ .

(ii) Implications for Cross-Linking

The results discussed in this chapter provide an excellent basis for an entirely novel approach to the cross-linking of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers. In principle this approach involves the inclusion into the copolymerisation mixture of a special third comonomer alkene containing a large sterically demanding group. The resulting polymer therefore contains built-in sites of instability due to steric crowding which may undergo thermolysis to give polymer radical sites. Cross-linking may then take place *via* combination of these radical sites with a suitable coagent (*e.g.* TIC). We have demonstrated that the generation of polymer radicals by this approach is very feasible (Scheme 5.2).

Research is also currently being carried out in order to synthesize comonomers containing sterically crowded sites which are remote from the site of copolymerisation. This study will also be extended to include non-fluorinated crowded comonomers. This approach is illustrated by Scheme 5.10.

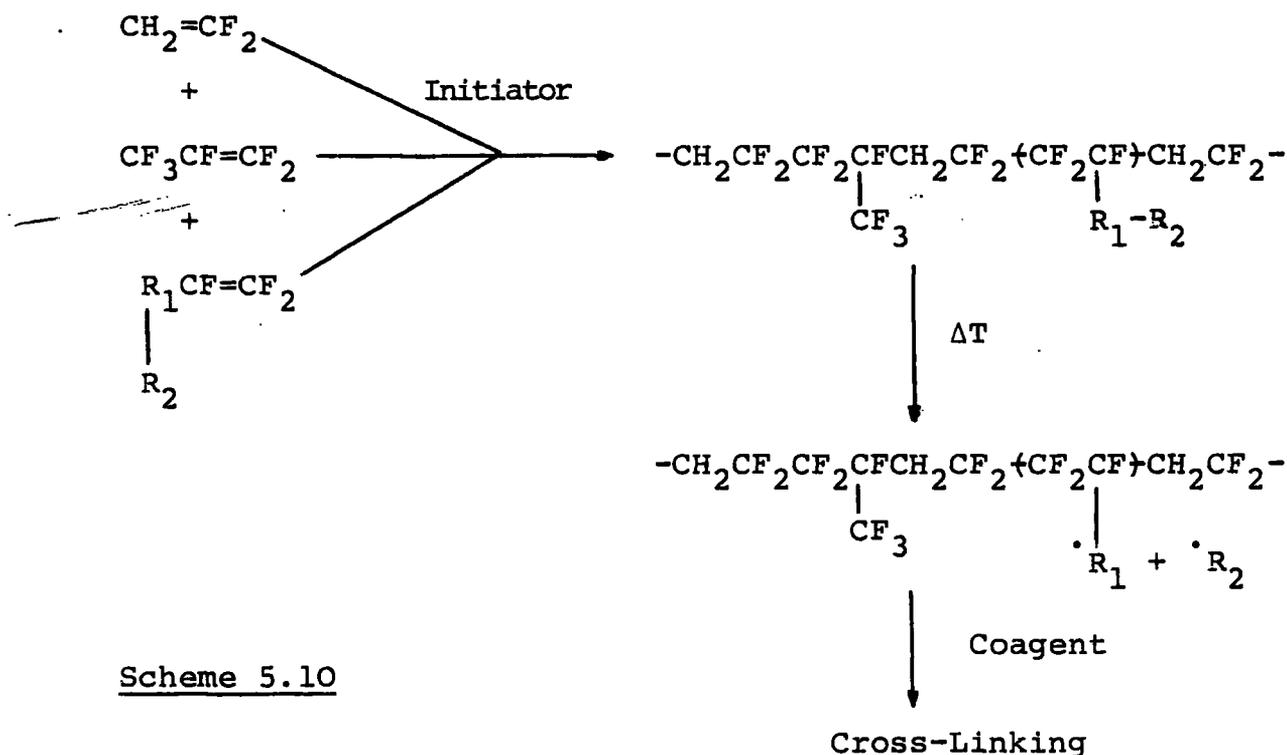

Scheme 5.10

Here the incorporation into the copolymerisation mixture of an alkene containing a group  $\text{R}_2$  which is sterically demanding, *e.g.*  $(\text{CF}_3)_2\text{CF}-$ , results in a weakening of the bond  $\text{R}_1\text{-R}_2$  in the copolymer and facile thermal homolytic cleavage to form radical sites remote from the polymer backbone. Cross-linking achieved using this approach should result in very little loss of chemical and thermal stability in comparison with the raw  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymer.

Thus we have provided an alternative approach to the curing of  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers not involving dehydrohalogenation, which we now believe to be a major source of instability generated during the bisphenol cure.



## CHAPTER SIX

NOVEL CHEMISTRY INVOLVING ANTIMONY PENTAFLUORIDE

During investigations into the general chemistry of the model compounds related to  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers it became clear at an early stage that treatment with antimony pentafluoride in many cases resulted in reactions which were both fundamentally novel in nature and had potential relevance to fluoropolymers. Therefore the chemistry of these systems was pursued and developed providing the content of this chapter.

6A Introduction: An Unusual Discovery

In Chapter Three the elimination of HF from the saturated model  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (70) in the presence of  $\text{SbF}_5$  to give  $(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CH}_2\text{CF}_3$  (71) was discussed. This reaction represents a Lewis acid-catalysed elimination process of a kind, which to our knowledge, has not previously been exploited. This reaction, together with the following are essentially quantitative and, in principle, provides a simple route to fluoroalkenes and polyenes.

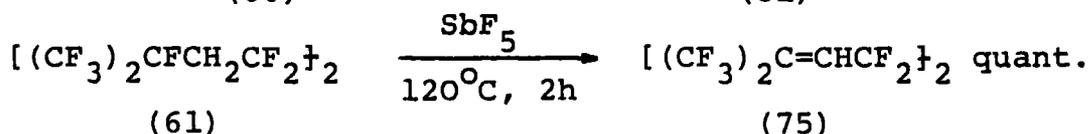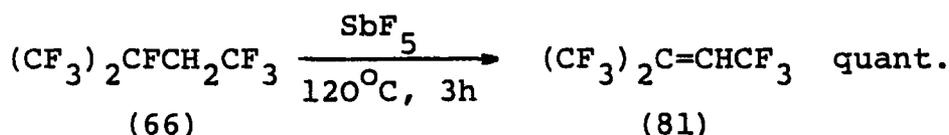


The general mechanism proposed for this process is as follows:




Therefore in order to investigate the feasibility of further elimination of HF from fluorohydroalkenes to form fluoroallenes or fluoroalkynes, the unsaturated models  $(CF_3)_2CFCH=CF_2$  (99) and  $CF_3CH=CFCF_3$  (83) were treated with  $SbF_5$ .


When (83) was heated with  $SbF_5$  in a sealed system at  $120^\circ C$  for 12h a small amount of HF elimination occurred to give  $CF_3C\equiv CCF_3$  (108) which was identified by mass spectrometry and  $^{19}F$  nmr techniques

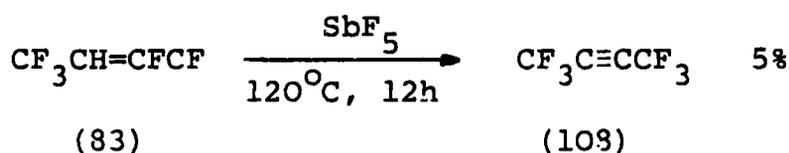

This observation demonstrates that complexation of  $SbF_5$  to vinyl fluorine can result in elimination to give alkynes:

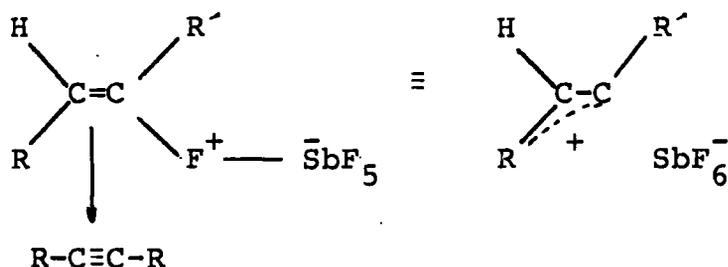


When  $(CF_3)_2CFCH=CF_2$  (99) was treated at  $20^\circ C$  with  $SbF_5$ , quantitative isomerisation to the product  $(CF_3)_2C=CHCF_3$  (81) occurred over *ca.* 10 min and no elimination products were obtained. This observation is readily explained by the strong complexation of  $SbF_5$  to the tertiary fluorine atom of (99). Subsequent isomerisation of the C=C bond in the presence of  $\bar{S}bF_6^-$  is then preferable to elimination of a molecule of HF:

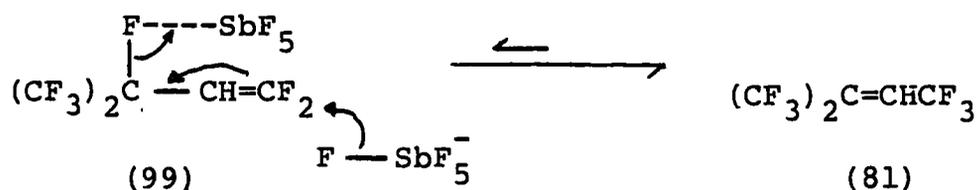


6B Some Novel Elimination Reactions(i) A Novel 1,5-Elimination of Hydrogen Fluoride

When the unsaturated model  $(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CH}_2\text{CF}_3$  (71) was treated with  $\text{SbF}_5$  at  $110^\circ\text{C}$  for 2h, the product 1H-2,4-bistrifluoromethyl-4H-tetrafluorocyclopentene (109) was obtained in good yield:

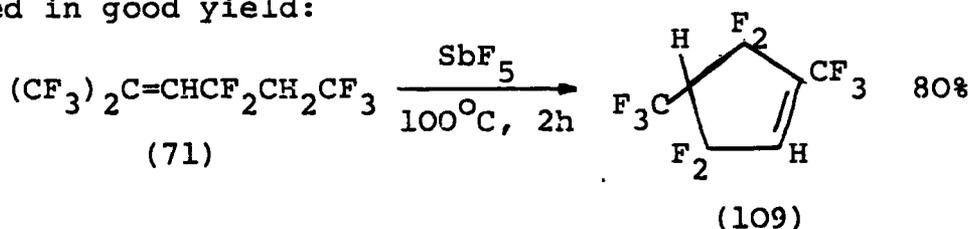

Other products were not characterized.

This reaction represents an entirely novel intramolecular 1,5-elimination of HF. The mechanism proposed for this reaction is shown in Scheme 6.1.

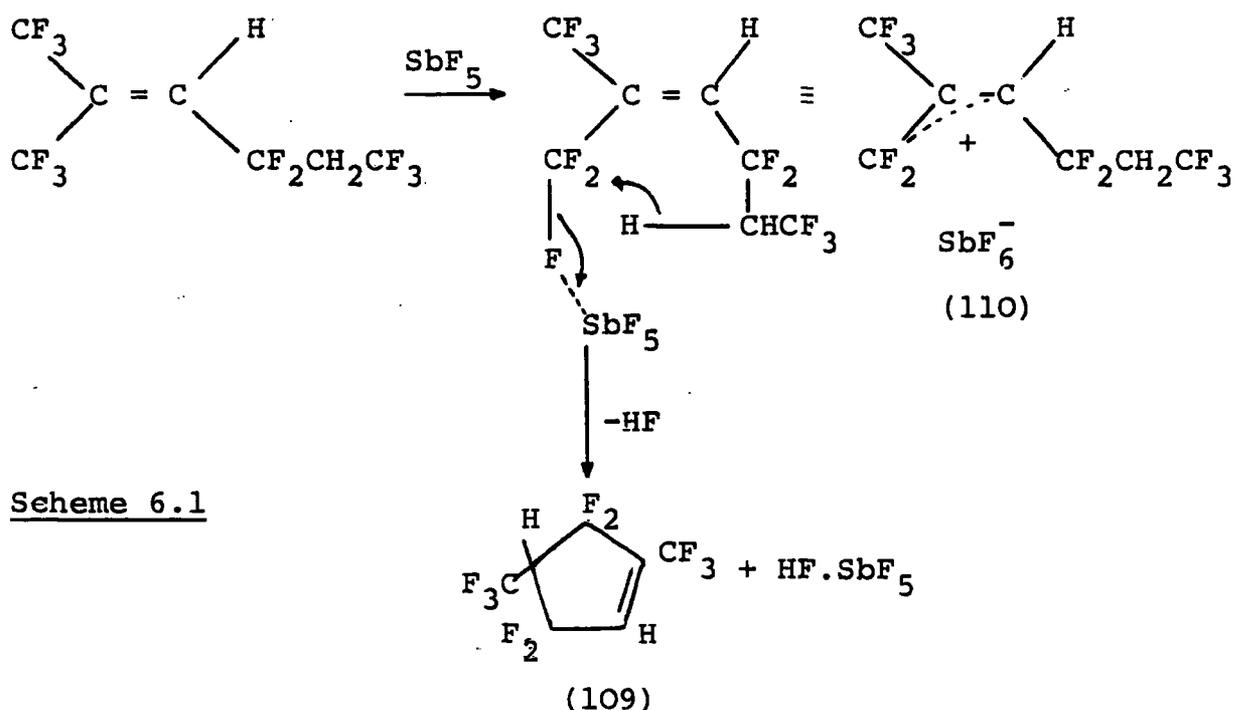


This mechanism involves nucleophilic attack by a saturated C-H bond on a saturated C-F bond complexed to  $\text{SbF}_5$  and has not previously been reported. This result therefore repres-


ents an area of potentially fundamental interest to mechanistic organic chemistry.

### 6B (ii) Cyclisation of a Saturated Fluorohydrocarbon

When the saturated model compound  $(\text{CF}_3\text{CF}_2\text{CH}_2\text{CF}_2)_2$  (57) was treated with  $\text{SbF}_5$  at  $110^\circ\text{C}$  for 2h the product 1H-2-trifluoromethyl-3H-3-pentafluoroethyltetrafluorocyclopentene (111) was obtained in excellent yield.

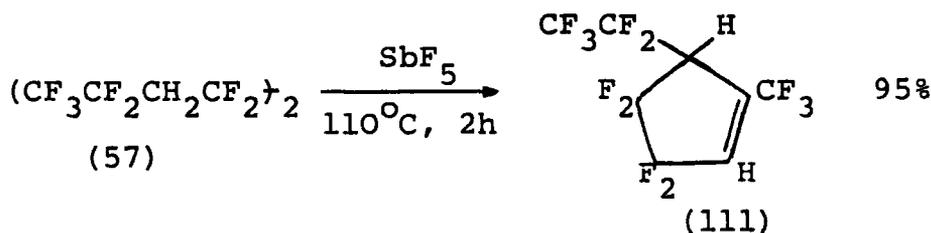


The mechanism proposed for this reaction involves again the nucleophilic attack by a saturated C-H bond at a saturated C-F bond. This pathway is illustrated by Scheme 6.2.

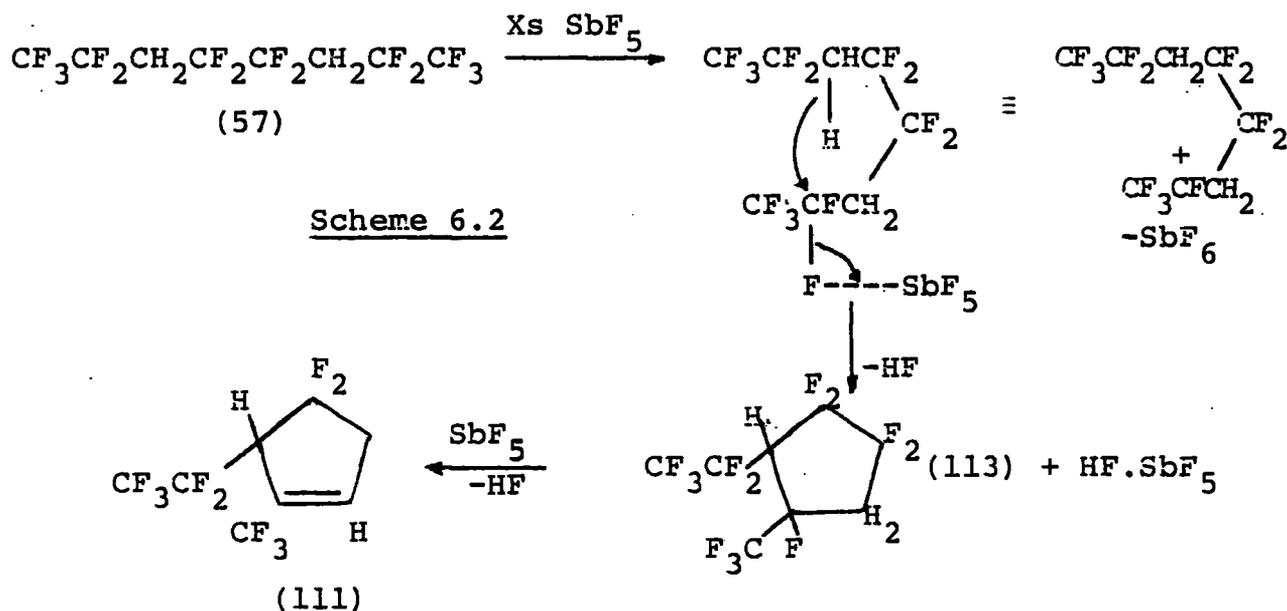


The saturated cyclic intermediate (113) could not be isolated or observed by  $^{19}\text{F}$  nmr spectroscopy and it was concluded that, under the conditions employed, the final elimination step to give the product (111) takes place very rapidly.


In an attempt to reproduce this reaction mechanism the model compound  ${}^n\text{C}_8\text{F}_{17}\text{CH}_2\text{CF}_3$  (116) was synthesized using the route outlined below:

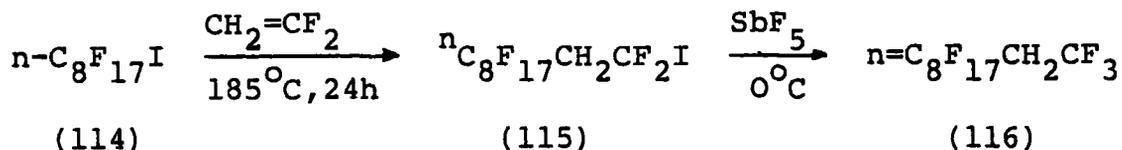

If the model (116) cyclised in the presence of  $\text{SbF}_5$  it would support the mechanism proposed in Scheme 6.2, and indicate the preferred ring size for the process. However no reaction between (116) and  $\text{SbF}_5$  occurred below  $190^\circ\text{C}$ . After 12h at this temperature the following products were identified:

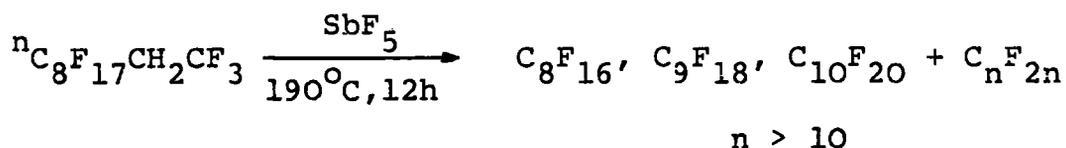



These products suggest that fragmentation processes have taken place, however so far we are unable to advance a satisfactory explanation for the formation of these products. It would appear that dehydrofluorination has taken place as expected, but the overall substitutions of F for H in each product suggest that  $\text{SbF}_5$  is acting as a fluorinating agent towards the resulting alkenes, which is a known process.<sup>138</sup>



### (iii) Attempts to Promote Related Inter-Molecular Reactions

In order to determine whether the mechanisms proposed for the above two intramolecular reactions (Schemes 6.1 and 6.2) could be extended to include intermolecular processes the systems outlined in Table 6.1 were investigated.

TABLE 6.1 Intermolecular Systems Related to Observed Intramolecular Displacement of C-F by C-H

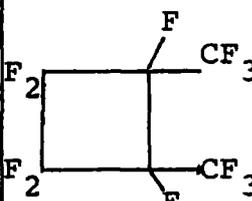
C-F Substrate	C - H Nucleophile	Conditions
 <p>(118)</p>	$\text{CF}_3\text{CF}_2\text{CH}_2\text{CF}_3$	Xs $\text{SbF}_5$ , $150^\circ\text{C}$ , 12h
$(\text{CF}_3)_2\text{CF}-\text{CF}(\text{CF}_3)_2$ (103)	$\text{CF}_3\text{CF}_2\text{CH}_2\text{CF}_3$ (119)	Xs $\text{SbF}_5$ , $180^\circ\text{C}$ , 12h
$(\text{CF}_3)_2\text{C}=\text{CHCF}_3$ (81)	$\text{CF}_3\text{CF}_2\text{CH}_2\text{CF}_3$ (119)	Xs $\text{SbF}_5$ , $150^\circ\text{C}$ , 12h
$(\text{CF}_3)_2\text{C}=\text{CHCF}_3$ (81)		Xs $\text{SbF}_5$ , $-78^\circ\text{C}$ , 2h

In each case, however, no chemical change took place. Furthermore variable temperature  $^{19}\text{F}$  nmr studies of the systems  $\text{SbF}_5/(118)$  and  $\text{SbF}_5/(81)$  over the range  $-70^\circ\text{C}$  to  $+100^\circ\text{C}$  showed no occurrence of stable complexes or ions.

#### 6C The Formation of Some Remarkably Stable Fluorinated Cations and their Chemistry


The results discussed so far show clearly that elimination of HF from simple fluorohydrocarbon systems, *e.g.*  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (70) is achieved easily in the presence of  $\text{SbF}_5$  to form the corresponding mono- and di-alkenes *e.g.*

$(CF_3)_2C=CHCF_2CH_2CF_2$  (71). A study was therefore carried out involving the higher homologues  $(CF_3)_2CF(CH_2CF_2)_nF$  [ $n=3$  (120),  $n=4$  (121)]. These models were synthesized as follows (Scheme 6.3):

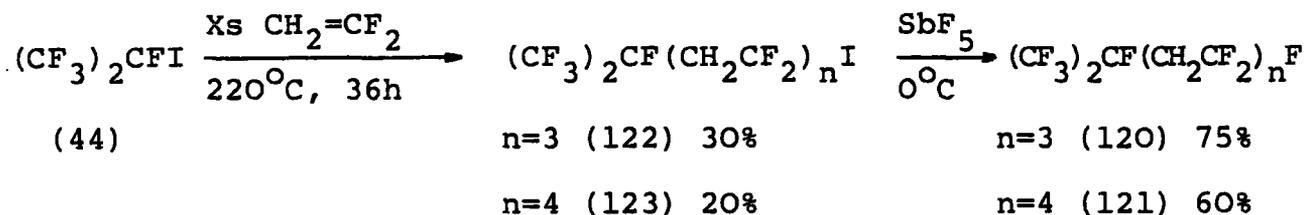


(i) Observations

It was expected that, after preferential elimination of HF from the tertiary sites of (120) and (121) to yield alkenes of the form (124)





further removal of HF from the allylic sites of (124,  $n=3,4$ ) would be favoured since removal of  $F^-$  by  $SbF_5$  from these sites would result in carbocations stabilized by the double bond (Scheme 6.4).

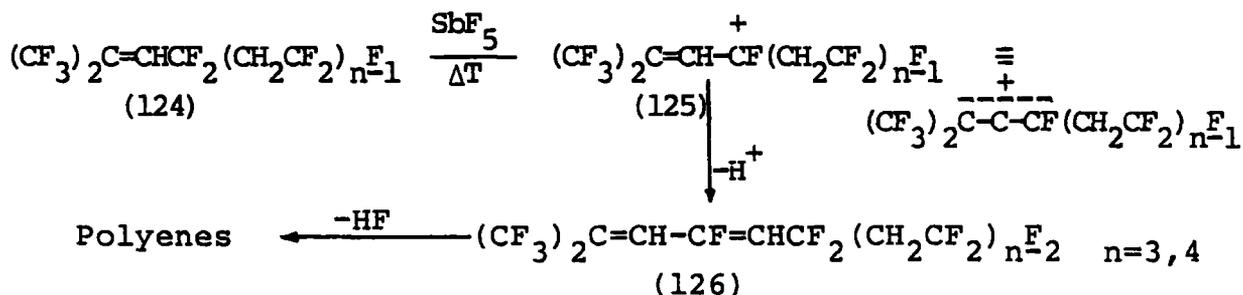

Scheme 6.4

However when the saturated models (120) and (121) were dissolved in 5:1 excess  $SbF_5$  at  $20^\circ C$  the remarkably stable fluorinated carbocations (127) and (128) were formed in quantitative yields.

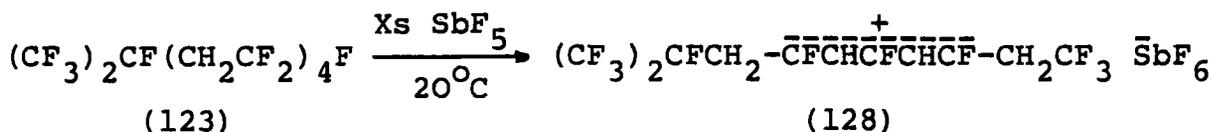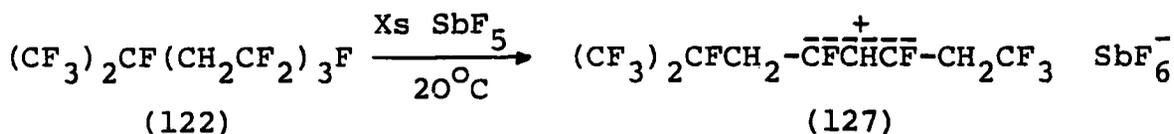


These carbocations persist over several weeks and, using  $^{19}\text{F}$  nmr techniques, no chemical change is observed over this period of time. It is also remarkable that elimination of HF in each case occurred from  $-\text{CH}_2\text{CF}_2-$  sites and under extremely mild conditions ( $20^\circ\text{C}$ ) prior to the formation of the allylic cations (127) and (128). This is in stark contrast to the observed reactivity of the smaller homologues ( $n = 1,2$ ) towards  $\text{SbF}_5$ . The range of reactivity of the saturated model systems is now summarized fully in Table 6.2.

TABLE 6.2 Comparison of the Reactivity of the Saturated Models towards  $\text{SbF}_5$

Model Compound	Preferred Site for elimination	Conditions employed	Products
$(\text{CF}_3)_2\text{CFCH}_2\text{CF}_3$ (66)	$\diagup\text{CFCH}_2-$	$120^\circ\text{C}$ , 3h	$(\text{CF}_3)_2\text{C}=\text{CHCF}_3$ (81)
$[(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2]_2$ (61)	$\diagup\text{CFCH}_2-$	$120^\circ\text{C}$ , 2h	$[(\text{CF}_3)_2\text{C}=\text{CHCF}_2]_2$ (75)
$(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_2\text{F}$ (70)	$\diagup\text{CFCH}_2-$	$40^\circ\text{C}$ , $1/3\text{h}$	$(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CH}_2\text{CF}_3$ (71)
$(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_3\text{F}$ (120)	$-\text{CF}_2\text{CH}_2-$	$20^\circ\text{C}$ , Inst.	$(\text{CF}_3)_2\text{CFCH}_2-\overset{+}{\text{CFCHCF}}-\text{CH}_2\text{CF}_3$ (127)
$(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_4\text{F}$ (121)	$-\text{CF}_2\text{CH}_2-$	$20^\circ\text{C}$ , Inst.	$(\text{CF}_3)_2\text{CFCH}_2-\overset{+}{\text{CFCHCFCHCF}}-\text{CH}_2\text{CF}_3$ (128)

Using the above data the following trend in the reactivity of the models (66), (61) and (70) towards elimination of HF from the tertiary site is apparent.



Clearly the order of reactivity is determined by the electron withdrawing ability of the group R. However the extreme reactivity of the higher homologues (120) and (121) towards elimination from secondary sites  $\text{-CF}_2\text{CH}_2\text{-}$  is not explained.

#### 6C (ii) Interpretation of NMR Spectra

The  $^{19}\text{F}$ ,  $^1\text{H}$  and  $^{13}\text{C}$  nmr spectra of the cations (127) and (128) were recorded in solution in  $\text{SbF}_5$  at  $20^\circ\text{C}$ . With reference to the many reports in the literature of stable fluorinated carbocations<sup>139-144</sup> and  $^{19}\text{F}$  nmr studies involving  $\text{SbF}_5$ ,<sup>144</sup> the carbocations (127) and (128) were easily characterized. The important  $^{19}\text{F}$  and  $^1\text{H}$  nmr data are shown in Table 6.3. (See Appendix for full analysis including  $^{13}\text{C}$  data)

TABLE 6.3 Diagnostic Resonances in  $^1\text{H}$ ,  $^{19}\text{F}$  nmr Spectra of the Cations (127) and (128)


Cation	$^1\text{H}$ shifts/ppm TMS $\delta$ 0.0	$^{19}\text{F}$ shifts/ppm $\text{CFCl}_3$ $\delta$ 0.0
$(\text{CF}_3)_2\text{CFCH}_2\text{CFCH}^+\text{CFCH}_2\text{CF}_3$ a    b c    d e f g    h (127)	-4.5 to -5.0 c, g -8.2            e	-180.5 b - 76.9 a - 61.4 h + 68.1 d, f
$(\text{CF}_3)_2\text{CFCH}_2\text{CFCH}^+\text{CFCHCFCH}_2\text{CF}_3$ a    b c    d e f g h i    j	-4.0 to -4.5 c, i -6.5 to -7.0 e, g	-181.0 b - 76.9 a - 62.4 j + 7.0 to 0 d, f, h

Recording these spectra at +20°C gives rise to considerable broadening of the resonances due to exchanging processes. Current studies are taking place in order to obtain data from spectra run on solutions of (127) and (128) in  $\text{SbF}_5/\text{SO}_2\text{ClF}$  at -80°C. The  $^{19}\text{F}$  nmr resonances observed at +68.1 ppm for the cation (127) are consistent with extensive deshielding expected for nuclei close to the positive charge centre. It is notable that the corresponding  $^{19}\text{F}$  nuclei in the cation (128) are deshielded to a lesser extent ( $\delta$  +7 to 0 ppm) due to greater delocalization of formal charge. The same trend is also observed for the  $^1\text{H}$  nuclei of (127) and (128) near to the charge centre which came into resonance at -8.2 and -6.5 to -7.0 ppm respectively.

Further confirmation of the production of the cation (127) was obtained by the quenching experiments described below.

(iii) Reaction of the Stable Carbocation (127) with Methanol


A solution of the carbocation (127) in  $\text{SbF}_5$  was quenched with excess methanol at -78°C. The major product (65%) isolated was the  $\alpha,\beta$ -unsaturated ketone (129)

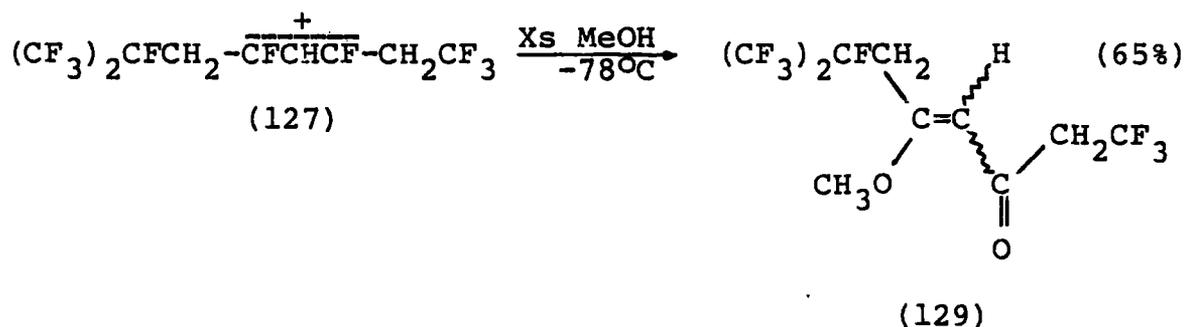


The structure of the product (129) was determined by mass spectrometry ( $M^+$  350), infra-red spectrophotometry (strong

bands  $1600\text{ cm}^{-1}$  and  $1700\text{ cm}^{-1}$  characteristic of conjugated unsaturated ketone) and the  $^1\text{H}$  and  $^{19}\text{F}$  nmr data summarized in Table 6.4.


TABLE 6.4  $^1\text{H}$  and  $^{19}\text{F}$  nmr Data for Structure  
Confirmation of the Product (129)

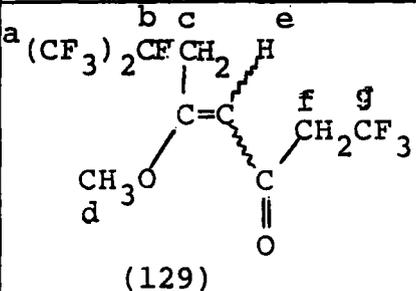Structure	$^1\text{H}$ shifts/ppm TMS $\delta$ 0	$^{19}\text{F}$ shifts/ppm $\text{CFCl}_3$ $\delta$ 0
 <p>(129)</p>	<p>-3.2 (q) f</p> <p>-3.6 (s) d</p> <p>-5.6 (s) e</p>	<p>-65.0 (t) g</p> <p>-78.5 (d) a</p> <p>-182.8 (m) b</p>

The structure of (129) was finally uniquely determined by mass-spectrometry due to the high intensity peak of 111 mass units arising from the fragment (130)

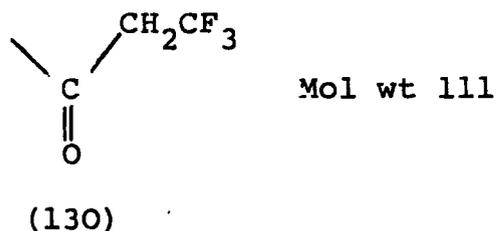


This observation distinguishes the product from the possible isomer (129a)

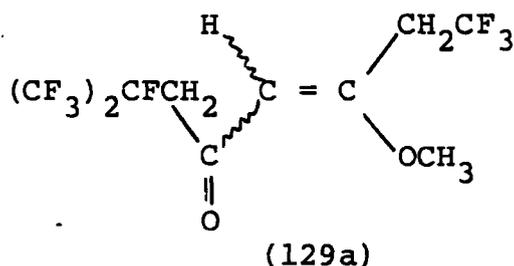

The simple mechanistic pathway outlined in Scheme 6.5 for the quenching of the cation (127) with methanol to give (129) therefore provides further support for the structure of (127).



An attempt was made using vacuum-line techniques to isolate polyenes from a solution of the cation (128) in  $\text{SbF}_5$  as outlined in Scheme 6.6.

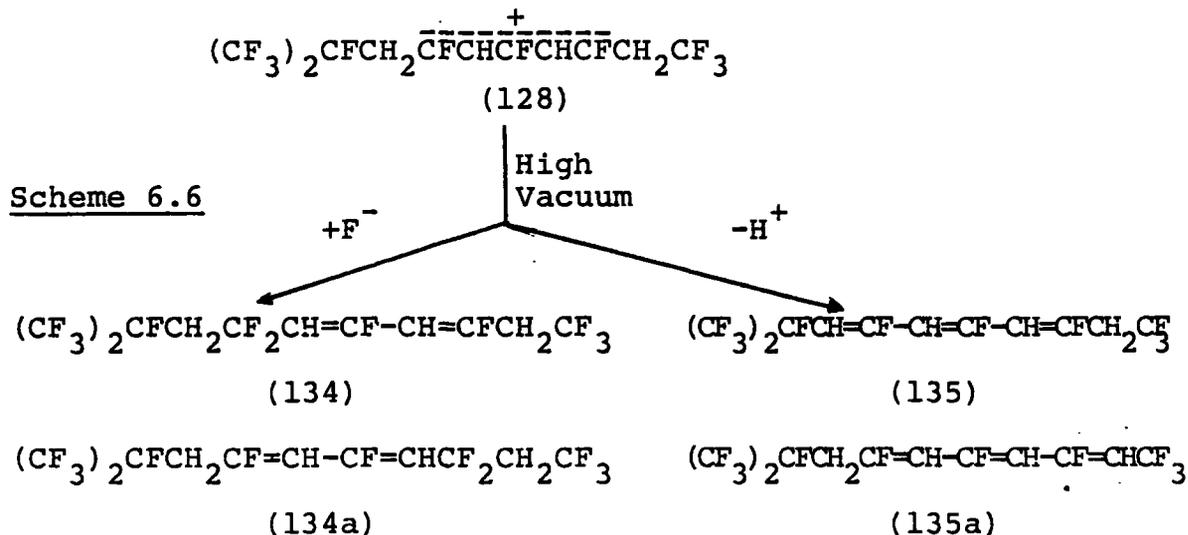


The separation of product material from the solution of (128) in  $\text{SbF}_5$  was achieved by vacuum transfer onto dry  $\text{NaF}$  and subsequent molecular distillation under high vacuum ( $10^{-5}$  torr) from the  $\text{NaF}/\text{NaSbF}_6$  residue. However the products obtained were not the expected polyenes as outlined in Scheme 6.6, but a complex mixture of lower molecular weight materials. It is thought that decomposition may have been promoted by  $\text{NaF}$ .

The reactivities of the fluorohydrocarbons  $(\text{CF}_3)_2\text{CF}(\text{CHFCF}_2)_n\text{R}$  [ $\text{R}=\text{F}$   $n=2$  (72)  $n=3$  (136) and  $\text{R}=\text{-coupled}$   $n=1$  (64)] towards  $\text{SbF}_5$  were investigated in an attempt to produce the corresponding mono- and di-alkenes. It is remarkable however that these compounds showed no susceptibility to Lewis acid catalyzed elimination of  $\text{HF}$  at  $150^\circ\text{C}$  over a period of 6h. This is in complete contrast to the extreme susceptibility of the compounds containing the structures  $\text{>CFCH}_2\text{-}$  and  $\text{-CH}_2(\text{CF}_2\text{CH}_2)_n\text{CF}_2\text{-}$  discussed earlier.

6D Treatment of Fluorohydrocarbon Polymers with SbF<sub>5</sub>:  
A Route to Fluorinated Polyacetylenes

(i) Introduction

The results described in this chapter have demonstrated clearly that model compounds related to CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> copolymers and the CH<sub>2</sub>=CF<sub>2</sub> homopolymer are highly susceptible to elimination of HF in the presence of the powerful Lewis-acid SbF<sub>5</sub>. Furthermore the resulting unsaturated systems are stable to SbF<sub>5</sub> under the conditions used to promote elimination. In principle therefore this property should also extend to the polymer systems themselves where extensive elimination of HF would lead to highly unsaturated polymers. Indeed, in the case of poly,1,1-difluoroethene, {CH<sub>2</sub>CF<sub>2</sub>}<sub>n</sub>, this process could result in a potentially conducting polymer (137)

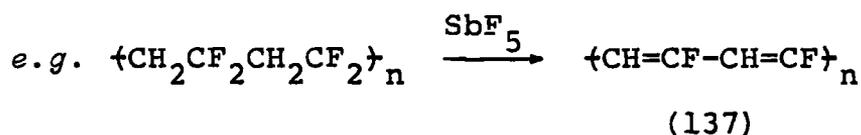

A study of the reactivity of a series of polymer systems towards SbF<sub>5</sub> was therefore carried out.

(ii) CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> Copolymer Systems


When a sample of finely divided CH<sub>2</sub>=CF<sub>2</sub>/CF<sub>3</sub>CF=CF<sub>2</sub> copolymer (70:30) was exposed to SbF<sub>5</sub> vapour over a prolonged period using vacuum-line techniques, an intensely coloured powder was obtained. Analysis of this material was examined using advanced infra-red techniques (Nicolet 60 SX photo-acoustic infra-red spectrophotometer, which does not require any modification of the material for sampling) a broad intense - band



A novel approach to the synthesis of this material was therefore undertaken using Lewis-acid catalysed elimination of HF from saturated precursors in the presence of  $\text{SbF}_5$ .

(a) Polychloroethene

When a thin film of polychloroethene (PVC) was exposed to  $\text{SbF}_5$  an instantaneous and intense colouration occurred. Ultrasonic infra-red studies of the resulting material in the absence of air yielded a spectrum which was altogether different from that of PVC. Furthermore on exposure to air the infra-red spectrum obtained was wholly changed and contained a strong band at  $1700 \text{ cm}^{-1}$  indicative of C=O functionality. When a solid-state  $^1\text{H}$  nmr spectrum was obtained on the unoxidized material a single resonance was observed at *ca.*  $-6.3 \text{ ppm}$  ( $\delta$  TMS  $0 \text{ ppm}$ ). These observations are consistent with extensive elimination of HCl by  $\text{SbF}_5$  resulting in a material which we believe to be a polyconjugated system (140) doped with  $\text{SbF}_5$ .

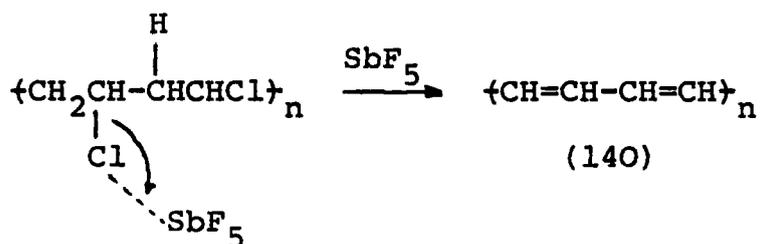


(b) Poly-1,1-difluoroethene and Polytrifluoroethene


When a thin film of poly-1,1-difluoroethene was exposed to  $\text{SbF}_5$  vapour an intensely coloured material was obtained. Infra-red studies of this product showed a strong bond in the region *ca.*  $1600\text{-}1700 \text{ cm}^{-1}$  which is indicative of extensive unsaturation. However when a thin film of polytrifluoro-

ethene was treated under identical conditions the film became coloured only slowly. The film was then further treated with liquid  $\text{SbF}_5$  at  $60^\circ\text{C}$  whereupon a strong colouration was achieved. Infra-red studies of this material again showed evidence of unsaturation.

These results clearly demonstrate a successful new approach to highly unsaturated polymer systems. From the results obtained using the model systems it is reasonable to assume that the polymers after treatment with  $\text{SbF}_5$  contain residual charged sites, *e.g.* of the form (142)

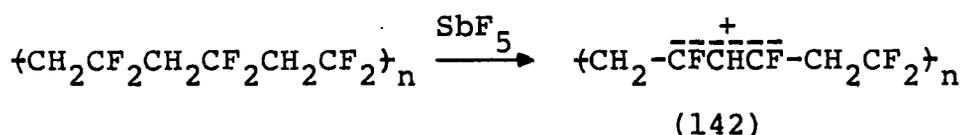

Therefore, in principle, functionalisation of the saturated polymers is now possible using, for example, (i)  $\text{SbF}_5$ , (ii)  $\text{MeOH}$  resulting in materials of great potential for industrial applications, *e.g.* :

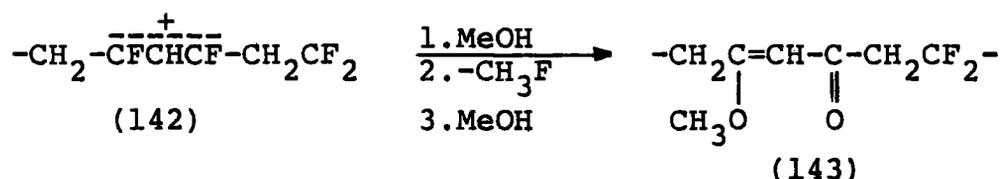

Further studies of these systems are currently being developed.

## 6E Conclusions

We have shown that Lewis-acid catalyzed eliminations of HF from fluorohydrocarbon systems by  $\text{SbF}_5$  provides an excellent and entirely novel route to fluorinated mono- and di-enes and a potential route to fluorinated polyenes. Furthermore treatment of the unsaturated products with  $\text{SbF}_5$

under more forcing conditions can lead to some highly unusual reactions which are of fundamental importance to organic chemistry in their own right.

When this approach is applied to fluorohydrocarbon polymer systems it is clear from model studies that extensive elimination of HF can occur to yield highly unsaturated and potentially conducting polymers, *e.g.* systems related to polyacetylene, polymonofluoroacetylene and polydifluoroacetylene most probably containing stable charged sites.

It is also probable that these sites can be functionalized, *e.g.* with methanol to yield new materials for industry.

## CHAPTER SEVEN


THE GENERAL CHEMISTRY OF THE MODEL COMPOUNDS7A Introduction

The objectives of this research include primarily the discovery of definitive information about the chemistry involved in the cross-linking of  $\text{CH}_2=\text{CH}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers. The results obtained in this area have been discussed in detail together with their implications in Chapters Two to Five. In the previous chapter it was shown that the model chemistry performed in achieving these results gave rise to some highly novel and fundamentally important chemistry involving antimony pentafluoride.

Therefore in order to extend our understanding of the chemistry of these systems a wider variety of experiments was carried out in some of the more important areas, *e.g.* nucleophilic attack, free-radical addition, addition of 1,3-dipoles and the formation of some stable long-lived carbanions, *etc.* The results of this study are discussed in this chapter.


7B Chemistry Involving 2-(2H-hexafluoro-2-propyl)-4-hydro decafluoro-3,3-dimethylcyclopentene (79)

The cyclopentene derivative (79) was obtained in quantitative yield by the following reaction (Ch.3B(iii))

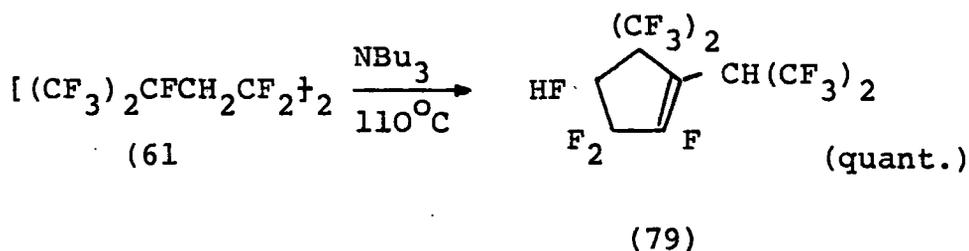

7B(i) Reaction with Sodium Methoxide

When the cyclic product (79) was treated with sodium methoxide in methanol using very mild conditions a mixture of two components was obtained and separated using preparative scale gas chromatography. The components were identified as starting material (79) and the *trans*-methoxy-derivative (146) in 70% yield:

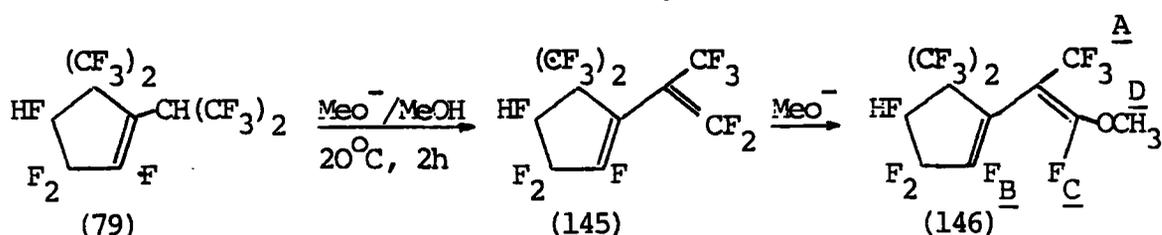


The structure of the product was established using <sup>19</sup>F and <sup>1</sup>H nmr spectroscopy wherein the chemical shifts and coupling of the ring atoms resemble strongly those of the established compound (79). In addition the <sup>19</sup>F nmr spectrum of (146) contained resonances at -57.8 ppm (3 F, s, A-CF<sub>3</sub>), -71.0 ppm (1 F, d, J 12.5, C-F) and -119.8 ppm (1 F, d, J BC 12.5, B-F) and the <sup>1</sup>H nmr spectrum showed a resonance at -3.8 ppm (3 H, s, D-OCH<sub>3</sub>). The *trans*-stereochemistry was indicated by the large through-space coupling between the F-atoms B and C. Infra-red spectrophotometry showed an intense broad absorption (ν<sub>max</sub> 1650 cm<sup>-1</sup>) which is characteristic of a conjugated diene. Mass spectrometry gave a strong molecular ion peak at 418 mass units.

This result demonstrates that the hydrogen atom of the hexafluoro-2-propyl group, -CH(CF<sub>3</sub>)<sub>2</sub>, of (79) is the selectivity base-sensitive site of this molecule in preference

to the ring hydrogen. However when (79) was treated separately with  $D_2O$ ,  $(CD_3)_2C=O$  and  $CH_3OD$ , and the  $^1H$  spectrum of each system recorded, there was no decrease in the intensity of the  $-CH(CF_3)_2$   $^1H$  resonance ( $\delta-4.25$  ppm) indicating that no H/D exchange had taken place.

### (ii) Pyrolysis Experiments

The result described above indicated that production of the conjugated diene (145) by base-catalysed elimination of HF from (79) in solution is not feasible due to subsequent nucleophilic attack at the  $=CF_2$  group of this molecule. Therefore the compound (79) was passed through a pyrolysis tube containing hot potassium fluoride using vacuum-line techniques. When the temperature of the KF was  $300^\circ C$  conversion to the diene (145) was achieved in 45% yield.

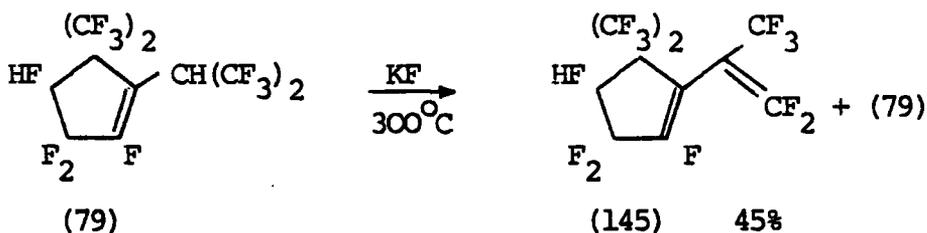


Some decomposition (*ca.* 15%) occurred in the pyrolysis tube.

In an attempt to promote "cracking" processes the cyclo-pentene derivative (79) was passed over hot iron at temperatures ranging from  $300^\circ C$ , which resulted in no chemical change, to  $500^\circ C$  which caused total decomposition.

(iii) Reaction of 2-(pentafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (145) with Cesium Fluoride; Formation of a Stable Carbanion

When the diene (145) was added to a solution of CsF in tetraglyme an intense red colouration was observed. The immediate  $^{19}\text{F}$  nmr spectrum of the resulting system showed complete change from that of the starting material (145). Most notably a new resonance signal appeared at  $\delta_{\text{F}} -45.5$  ppm which is indicative of the formation of the carbanion (147) <sup>148</sup>

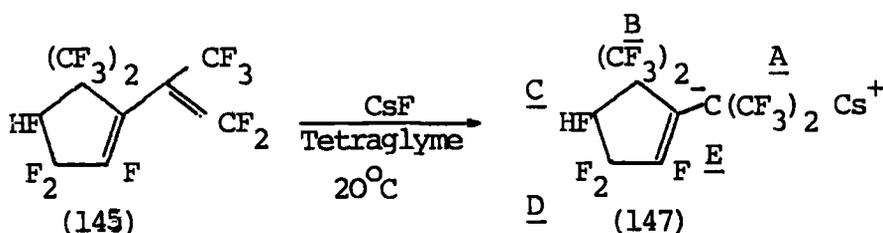

The  $^{19}\text{F}$  nmr data recorded for the anion (147) is summarized in Table 7.1. After a period of several hours the  $^{19}\text{F}$  nmr spectrum of the solution became complex and the low-field resonance (-45.5 ppm) associated with the anion (147) vanished.


TABLE 7.1  $^{19}\text{F}$  NMR Data for the Stable Carbanion (147)

$\delta$   $\text{CFCl}_3$  0 ppm.

Chemical Shift/ppm	Intensity	Assignment
-45.5	6	<u>A</u> -CF <sub>3</sub>
-61.0, -62.4	6	<u>B</u> -CF <sub>3</sub>
-109.0	1	<u>E</u> -CF
-122.6	2	<u>D</u> -CF <sub>2</sub> <sup>-</sup>
-210.8	I	<u>C</u> -CF-

This observation indicates that decomposition of the anion occurs over this period. On repeating this experiment an attempt was made to trap the anion (147) using  $\text{Br}_2$ . After the addition of  $\text{Br}_2$  the resultant solution was added to water and a fluorocarbon layer was recovered which was resolved into 2 components of highest masses 426 and 487 using analytical gas chromatography/mass spectroscopy. The lower molecular weight component was deduced to be (79) by  $^1\text{H}$  nmr spectroscopy ( $\delta_{\text{H}}\text{-CH}(\text{CF}_3)_2$  -4.25 ppm, sept). The higher molecular weight product was not, however, isolable using preparative scale gas chromatography due to thermal decomposition (attributable to the longer retention times experienced with this technique). The mass spectrum obtained from the resolved product mixture, however, provides sufficient evidence for production of the bromo-derivative (148) *via* successful trapping of the carbanion (147). This evidence is summarized as follows:

- (i)  $\text{M}^+$  -19, 487 observed.
- (ii)  $\text{M}+2$  Monobromosubstituted pattern observed.
- (iii) High intensity peaks which correspond to loss of  $-\text{CF}_3$  (69) and  $-\text{Br}$  (79,81) from the sterically crowded  $-\text{CBr}(\text{CF}_3)_2$  group<sup>148</sup> of (148).

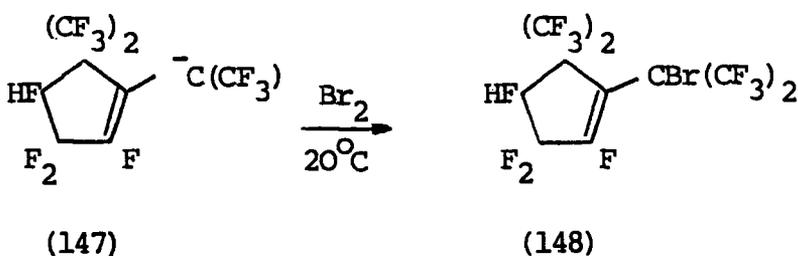


7C Chemistry involving 3,6-Dihydrohexadecafluoro-2,7-dimethylocta-2,6-diene (75) and 2H-nonafluoro-3-methylbut-2-ene (81)

$[(CF_3)_2C=CHCF_2]_2$  (75) was synthesized in excellent yields by the reaction of  $[CF_3)_2CFCH_2CF_2]_2$  (61) with  $SbF_5$  at  $120^\circ C$ , and  $(CF_3)_2C=CHCF_3$  (81) by reaction of  $(CF_3)_2CFCH_2CF_3$  (66) with  $SbF_5$  at  $130^\circ C$ . The reactivities of (75) and (81) towards  $F^-$ ,  $\bar{O}H$  and  $PhO^-$  have been discussed in Chapter Four.


(i) Free-Radical Additions

When the diene  $[(CF_3)_2C=CHCF_2]_2$  (75) was irradiated with  $\gamma$ -rays in the presence of diethyl ether (2:1 excess) a mixture of the product (149) and involatile material was obtained. The oxepane derivative (149) was isolated as an isomeric mixture.

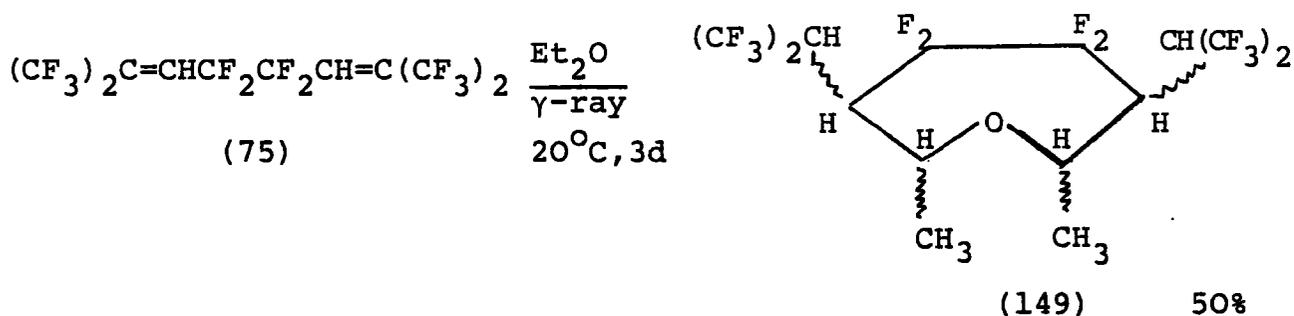


The structure of the product (149) was determined using mass spectrometry ( $M^+$  500), infra-red and raman spectrophotometry ( $\nu_{C=C}$  absent) and nmr spectroscopy (see Appendix).


When the diene (75) was treated with dimethyl ether (1:1) in the presence of  $\gamma$ -rays the product (150) was obtained in good yield.

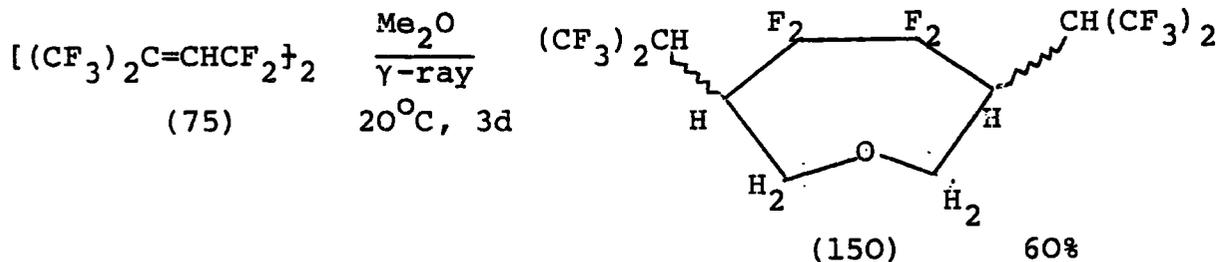

The structure of the product (150) was determined using mass spectrometry ( $M^+$  472 and loss of  $-\text{CH}(\text{CF}_3)_2$  fragment of mol.wt. 151) and infra-red spectrophotometry ( $\nu_{\text{C}=\text{C}}$  absent). The  $^{19}\text{F}$  nmr spectrum recorded for the product (150) was consistent with the presence of two isomeric forms (150A) and (150B):

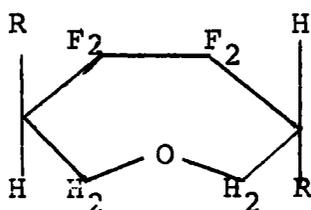

(150A)  
transoid

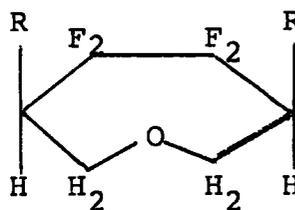


(150B)  
cisoid




The transoidal isomer (150A) comprises a pair of enantiomers which are nmr equivalent. The  $^{19}\text{F}$  nmr spectrum is, however, further complicated by the prochirality of the  $-\text{CF}_3$  groups which results in two separate resonances for each  $-\text{CF}_3$  group. Full assignment of the chemical shift data has consequently not been achieved, however the available data is summarized in Table 7.2.



The addition of ethers to (75) is facilitated by the electrophilic nature of this molecule (see Chapter I.B(ii)). Therefore hexachlorobuta-1,3-diene (151) was irradiated by a  $^{60}\text{Co}$   $\gamma$ -source in the presence of diethyl ether in order to investigate whether perchloroalkenes are active towards free-radical attack. However after 3 days at  $20^\circ\text{C}$  no chemical change had occurred.

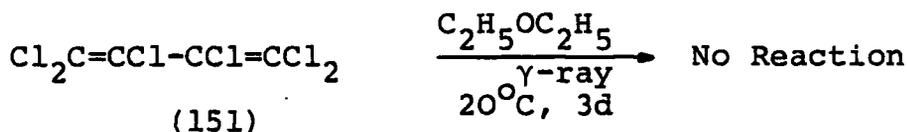

When a 1:1 molar ratio mixture of (75) and MeOH was irradiated by  $\gamma$ -rays the solid monoadduct (152) was obtained in moderate yield.

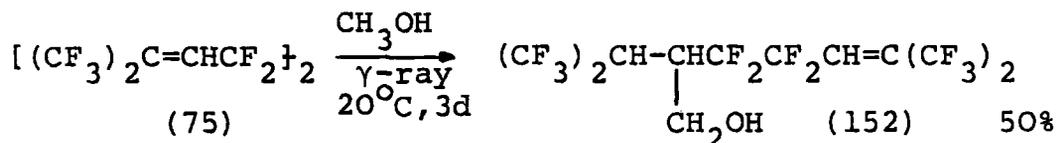


The structure of (152) was established using mass spectrometry ( $M^+$  458) and infra-red spectrophotometry ( $\nu_{\text{C}=\text{C}}$   $1695\text{ cm}^{-1}$  weak,  $\nu_{\text{OH}}$   $3600-3000\text{ cm}^{-1}$  broad strong).  $^{19}\text{F}$  and  $^1\text{H}$  nmr data summarized in the Appendix.

These simple addition reactions demonstrate clearly that the unsaturated model compounds are highly susceptible to free-radical attack by species of the form  $\text{RO}\dot{\text{C}}\text{H R}$ . Contrastingly, no addition of  $\text{Br}_2$  to the diene (75) was achieved under very forcing conditions, *i.e.*  $300^\circ\text{C}$ , 3d in the presence of  $\gamma$ -radiation.

(ii) Addition of Diazomethane

The addition of the 1,3-dipole diazomethane  $\text{CH}_2\text{N}_2$  to fluorinated alkenes has been the subject of much study.<sup>150,151</sup> Therefore this reaction was investigated using the novel unsaturated systems which we have produced. Diazomethane was synthesized in the laboratory using the method of Boer and Backer.<sup>152</sup>

Treatment of (75) with diazomethane in ether gave the di- $\Delta^1$ -pyrazoline derivative (153)

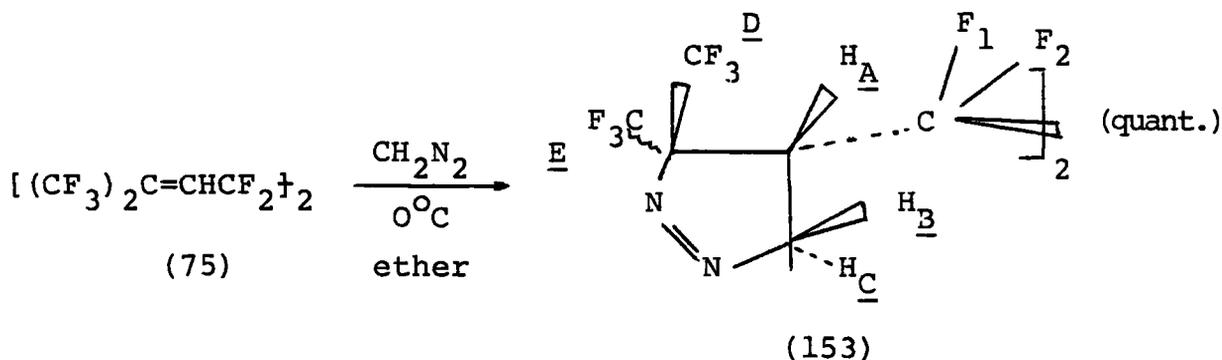

No  $\Delta^2$ -pyrazoline derivatives were obtained in contrast to the observations of Bryce *et al.*<sup>151</sup>

The structure of the product (153) was established using mass spectrometry (diadduct  $\text{M}^+$  510 with rapid loss of 28 and 56 due to  $-\text{N}=\text{N}-$ ) infra-red spectrophotometry ( $\nu_{\text{C}=\text{N}}$  ( $\Delta^2-$ ) absent,  $\nu_{\text{N}-\text{H}}$  ( $\Delta^2-$ ) absent) and the  $^1\text{H}$  and  $^{19}\text{F}$  nmr data summarized in Table 7.3.

The regiochemistry of addition was deduced by noting the coupling between the *cis* hydrogen atoms  $\text{H}_\text{A}$  and  $\text{H}_\text{B}$  ( $J=9\text{Hz}$ ). This is in accordance with the postulate of Bryce *et al.* that the addition mechanism has an appreciable degree of nucleophilic character since the expected site for nucleophilic attack is at the carbon bearing hydrogen:

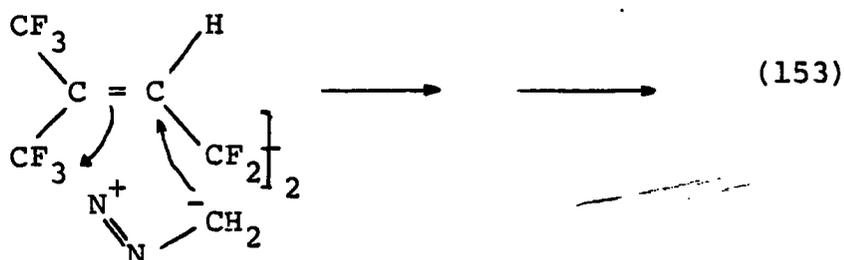


TABLE 7.3 NMR Data for Identification of Di- $\Delta^1$ -pyrazoline(153)


$^1\text{H}$  Data  $\delta$  TMS 0 ppm.

Shift/ppm	Coupling	Intensity	Assignment
-3.2	d,d,d $J_{AB} = 9\text{Hz}$ $J_{AC} = 9\text{Hz}$ $J_{AF_1} = 9\text{Hz}$	1	$\text{H}_A$
-4.4	) AB,d $J_{BC} = 18\text{Hz}$ ) $J_{BA} = 9\text{Hz}$	2	$\text{H}_B, \text{H}_C$
-5.3	) $J_{CA} = 9\text{Hz}$		

$^{19}\text{F}$  Data  $\delta$   $\text{CFCl}_3$  0 ppm.

-65.0	M	3	)
-69.0	M	3	) - $\text{CF}_3$ D, E
-109.7	AB $J_{F_1 F_2} = 280\text{Hz}$	2	- $\text{CF}_2$ - $\text{F}_1 \text{F}_2$


When the monoalkene (81) was treated with  $\text{CH}_2\text{N}_2$  at  $0^\circ\text{C}$  in ether a mixture of the  $\Delta^1$  (154) and  $\Delta^2$ - (155) pyrazoline derivatives was obtained in the ratio 3:5.

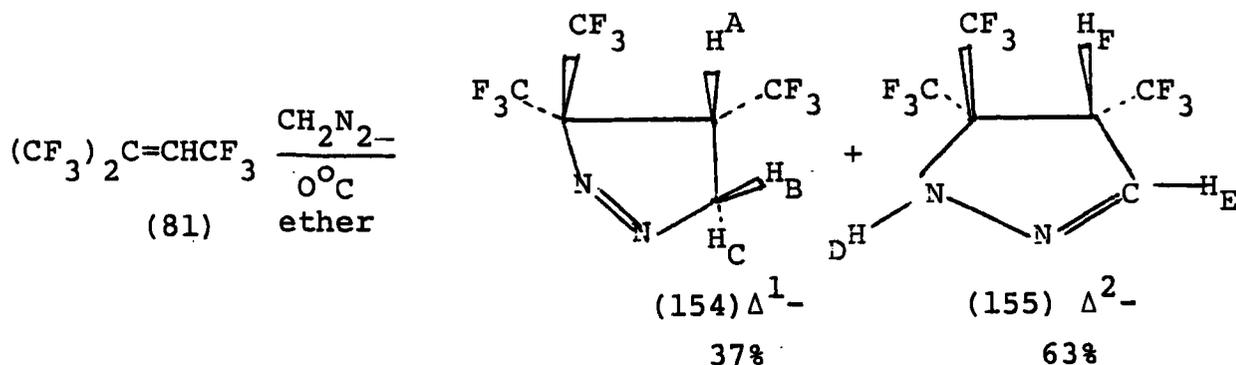

The product mixture was resolved using analytical scale gas chromatography/mass spectrometry ( $M^+$  274 for each component) and characterized using  $^1H$  nmr ( $\delta H_B, H_C$  (154) -4.8 ppm,  $\delta H_D$  (155) -7.8 ppm,  $\delta H_E$  (155) -6.6 ppm). The regiochemistry of addition was determined for the  $\Delta^1$ -isomer (154) by the observation of the coupling constant  $J_{AB} = 25\text{Hz}$  and for the  $\Delta^2$ -isomer (155) by the loss of the fragment  $-C(CF_3)_2NH-$  ( $M^+$  164 18% of base peak) in the mass spectrum of (155).

(iii) Attempted Metallations using Butyl Lithium

Hahnfield and Burton reported successful lithiation of a range of fluoroalkenes at vinyl hydrogen sites using solutions of butyl lithium in THF at  $-90^\circ\text{C}$ .<sup>126</sup> However when the alkenes  $[(CF_3)_2C=CHCF_2]_2$  (75) and  $(CF_3)_2C=CHCF_3$  (81) were treated with BuLi under these conditions only complex mixtures of nucleophilic products were obtained in low yield with considerable tarring.

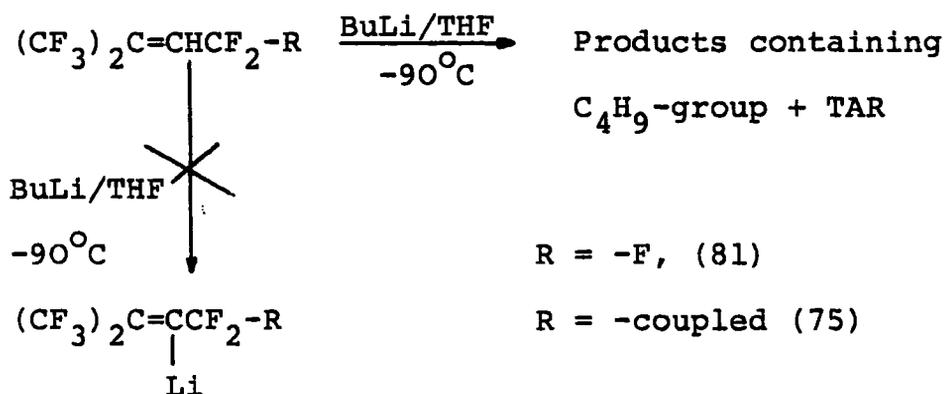


7D One Electron Transfer Reactions involving Tri-n-butylamine

One electron-transfer is now well established as a common occurrence in mechanism and may, in most general terms, be expressed<sup>153</sup>




In the case of  $(\text{Bu})_3\text{N}$  reduction of double bonds is feasible *via* one electron transfer, particularly if the double bond has electron-withdrawing substituents. This process is expressed generally by Scheme 7.2 which will be used to explain the results described thereafter.

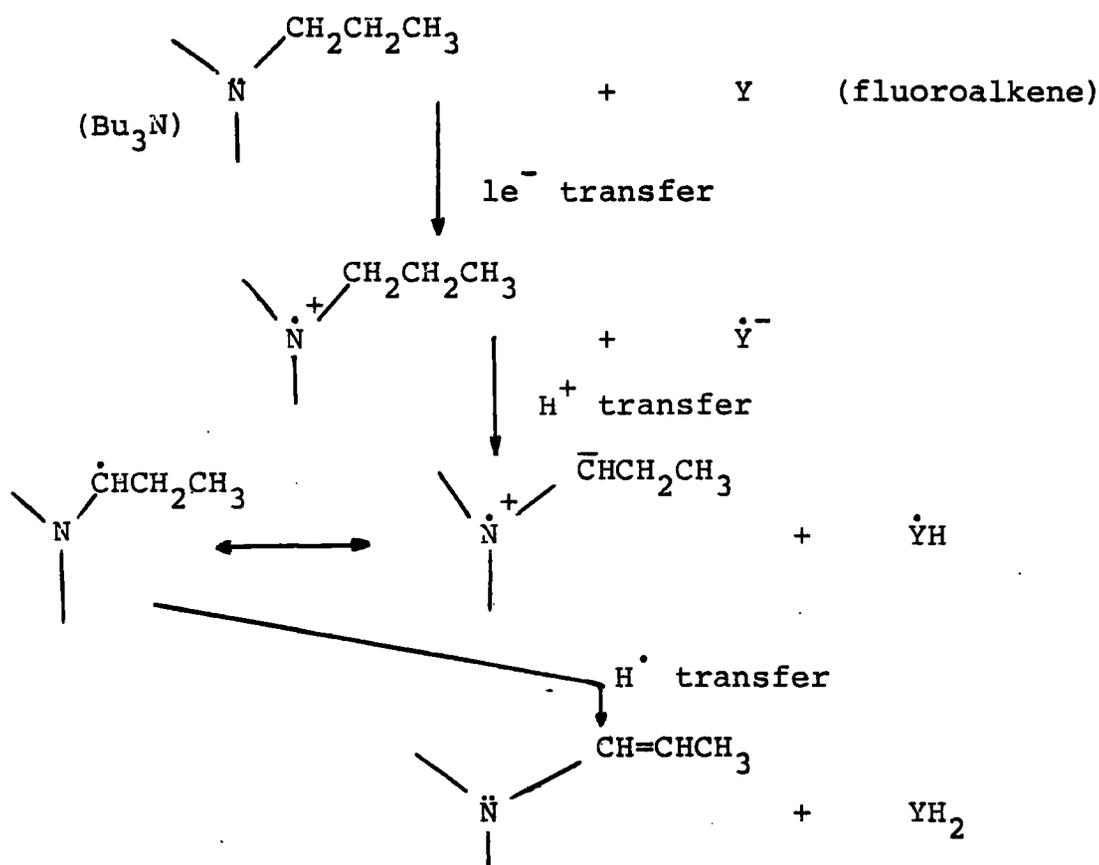

Scheme 7.2


7D (i) 2,2,4,4-Tetrahydrodecafluoro-5-methylhexane (70) and Tri-n-butylamine

When  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (70) was treated with  $\text{NBu}_3$  at  $60^\circ\text{C}$  for 72h in the presence of ultra-violet light there was 40% conversion to the reduced product (156).

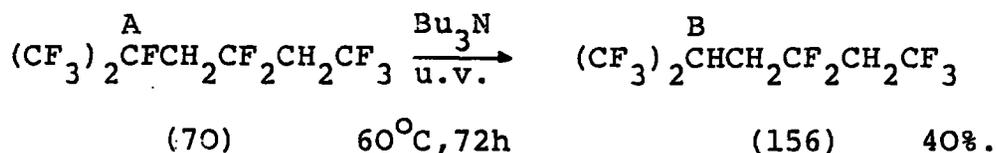

The structure of the product (156) was determined using mass spectrometry ( $M^+$  298),  $^1\text{H}$  nmr ( $\delta\text{H}_\text{B}$  sept -3.0 ppm) and  $^{19}\text{F}$  nmr spectroscopy ( $\delta\text{F}_\text{A}$  absent).

The above result is explained by the following mechanism (Scheme 7.3) which uses the reduction process described earlier.

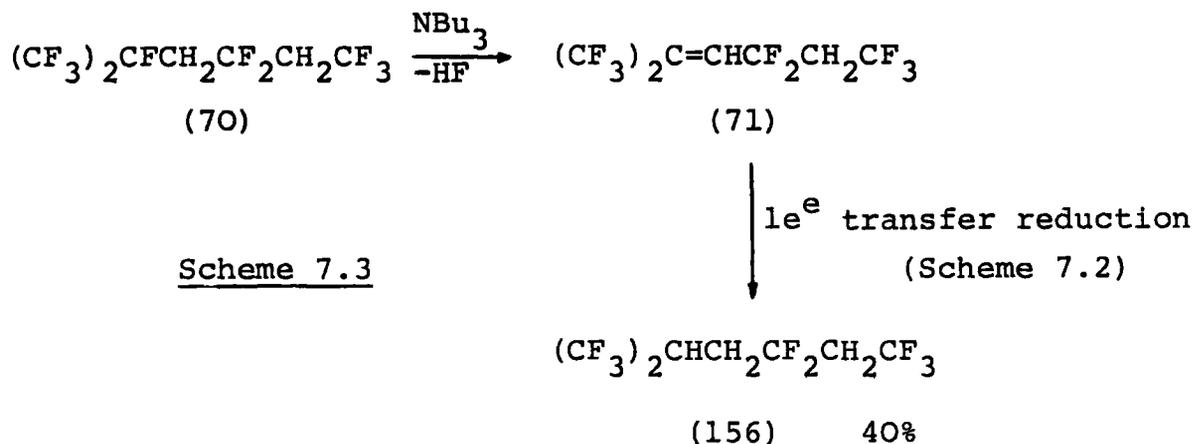

In order to verify the second step of this mechanism the unsaturated model (71) was treated separately with  $\text{Bu}_3\text{N}$  under the following conditions:


- (i) UV  $60^\circ\text{C}$ , 72h (photochemical)
- (ii)  $130^\circ\text{C}$ , 12h (thermal)

In each case a good yield of the reduced product

$(\text{CF}_3)_2\text{CHCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (156) was obtained ((i) 50% (ii) 90%).


We have therefore established that structures of the form  $-\text{CF}(\text{CF}_3)\text{CH}_2-$ , as are present in  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  copolymers, are susceptible to reduction in the presence of large tertiary amines at elevated temperatures. The reduction process comprises two separate steps which are (i) dehydrofluorination (ii) 1 electron transfer at the resultant  $-\text{C}(\text{CF}_3)=\text{CH}-$  site and concomitant reduction to give  $-\text{CH}(\text{CF}_3)_2\text{CH}_2-$ . It is therefore highly likely that these reduced structures are

present in  $\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2$  which have come into contact with amines at elevated temperatures and that they are contributors to the overall susceptibility of these copolymers to amines:

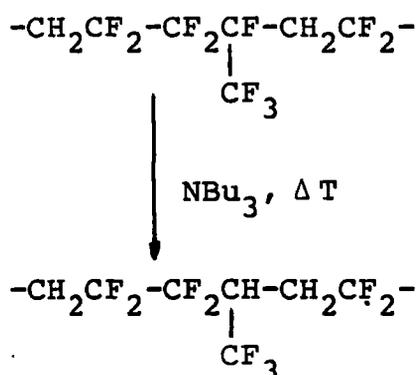


(ii) 1-Iodo-2,2,4,4-tetrahydroundecafluoro-5-methylhexane(62) and Tri-n-butylamine

When the telomer iodide  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_2\text{I}$  (62) was treated with  $\text{NBu}_3$  (2:1 excess) at  $120^\circ\text{C}$  for 12h four products were obtained in moderate yields. These products were isolated using preparative scale gas chromatography and are shown below (Scheme 7.4).

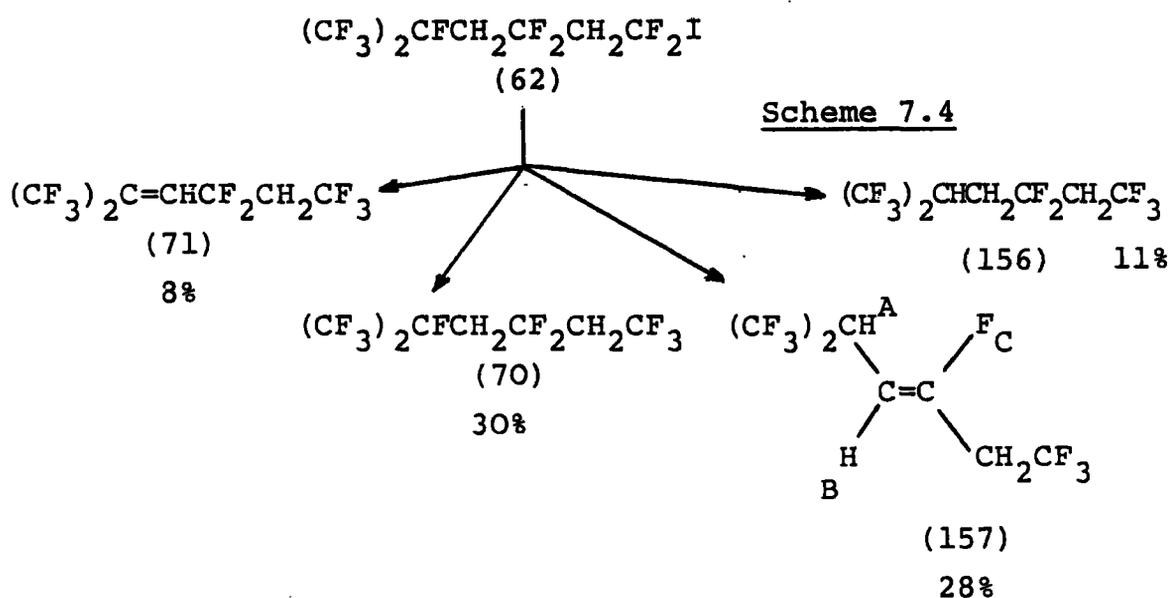


The structure of the product (157) was determined using mass spectrometry ( $M^+$  278), infra-red spectrophotometry ( $\nu_{\text{C}=\text{C}}$

1650  $\text{cm}^{-1}$  weak),  $^1\text{H}$  and  $^{19}\text{F}$  nmr spectroscopy in which the coupling constant of the vinyl  $\text{H}_\text{B}$  ( $\delta$  -4.9 ppm) and vinyl  $\text{F}_\text{C}$  ( $\delta$  -100.0 ppm) was observed to be 30 Hz which is characteristic of a *trans* H,F system. The  $\text{H}_\text{A}$  atom was observed at  $\delta$  -4.0 ppm as a septet ( $J=6$  Hz). Clearly conversion of the  $-\text{CH}_2\text{CF}_2\text{I}$  group of (62) to  $-\text{CH}_2\text{CF}_3$  has occurred in each case. However this conversion cannot occur primarily because there is no source of fluorine until appreciable elimination of HF from (62) has occurred. Therefore the first step in the mechanism must be elimination of HI by the amine acting as a base, which is a known reaction.<sup>100,115</sup>

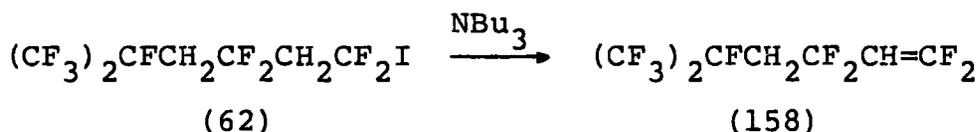


Elimination of HF from (158) at the tertiary site is then expected under the conditions employed ( $120^\circ\text{C}$ ). However any  $(\text{Bu})_3\text{N}\cdot\text{HF}$  thus generated, being a source of active fluoride ion (Chapter Three B(iii)), is expected to react rapidly with the terminal  $=\text{CF}_2$  group of (158) resulting in addition of HF to give (70) and (71)

*i.e.*

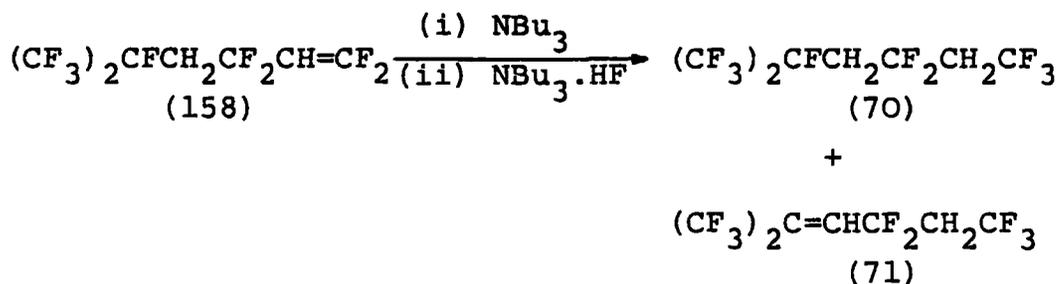

At some stage during the equilibration of the system the diene (159) is likely to be produced by removal of HF from (158). In the presence of  $\text{F}^-$  (159) can undergo isomerisation to give the conjugated diene (160) which, on reduction by

NBu<sub>3</sub> involving one electron transfer and subsequent base catalysed isomerisation, provides a route to the product (157) as outlined in Scheme 7.5.

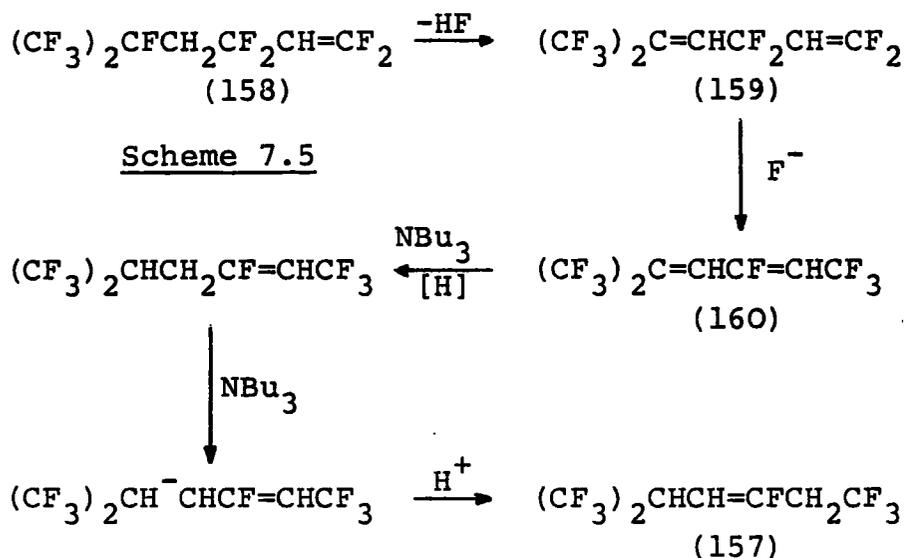

The product (156) arises simply from reduction of (71) by NBu<sub>3</sub> as previously described.


The products obtained provide further evidence for the one-electron reduction process described earlier.

#### 7E Further Chemistry resulting from 7-Iodo-2-hydrodecafluoro-3-methyl butane (50)

The synthesis of (CF<sub>3</sub>)<sub>2</sub>CFCHF<sub>2</sub>I (50) was described in Chapter Two C.

##### (i) Synthesis of Perfluoro-2-methylbut-2-ene (161)

Perfluoro-2-methylbut-2-ene (CF<sub>3</sub>)<sub>2</sub>C=CF<sub>2</sub> (161) synthesized in excellent yields using the approach outlined below (Scheme 7.6).

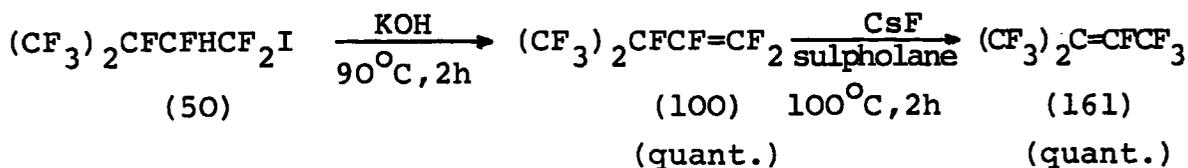


Scheme 7.6

Both reactions were carried out using sealed glass ampoules.

(ii) Chemistry of Perfluoro-3-methylbut-2-ene (161)

When the monoalkene (161) was treated with excess neutral methanol at 20°C a mixture of two products was obtained which were identified as (162) and (163) in approximately 1:1 ratio.

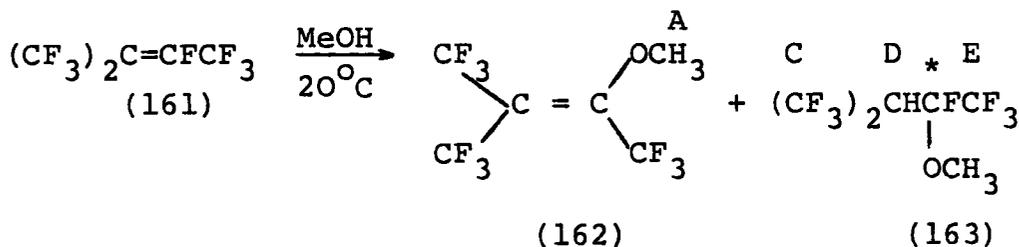

The structure of the product (162) was established using the following data:


- (i)  $M^+$  262 corresponding to addition of MeOH with loss of HF
- (ii)  $\delta_{3\text{H}}$  -OCH<sub>3</sub> at -4.0 ppm together with vinyl -CF<sub>3</sub> groups at  $\delta_{6\text{F}}$  -60 to -64 ppm.

while the structure of (163) was deduced using the data:

- (i)  $M^+$  282, *i.e.* 1:1 MeOH adduct
- (ii)  $\delta_{3\text{H}}$  -OCH<sub>3</sub> at -3.7 ppm,  $\delta_{\text{H}}$  -CH(CF<sub>3</sub>)<sub>2</sub> at -3.6 ppm (septet) and  $\delta_{\text{F}}$  -128.3 ppm (tertiary fluorine),  $\delta_{6\text{F}}$  -60.0 and -64.7 ppm (prochiral) attributable to the -CH(CF<sub>3</sub>)<sub>2</sub> group.


This result demonstrates that the perfluoroalkene (161) is exceedingly susceptible to nucleophilic attack and merits comparison with perfluorobut-2-ene  $(\text{CF}_3)_2\text{C}=\text{CF}_2$  which is also attacked by neutral MeOH.<sup>83</sup> Removal of HF from (163) to give the second product (162) is facilitated by the seven fluorine atoms  $\beta$ -to the proton D -CH of (164), which results in enhanced acidity,<sup>83</sup> together with relief of steric crowding.

When  $(\text{CF}_3)_2\text{C}=\text{CFCF}_3$  (161) was treated with  $\text{CH}_2\text{N}_2$  at  $0^\circ\text{C}$  in ether instantaneous addition occurred and the product (164) was isolated.

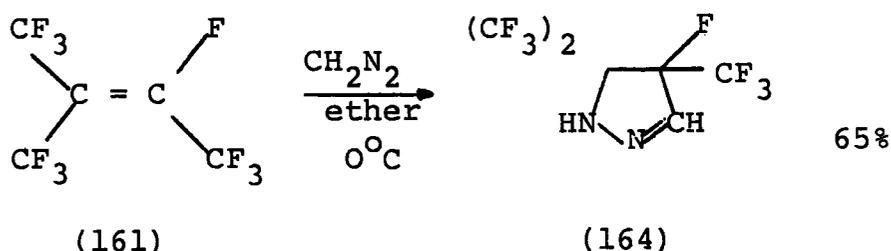

The regiochemistry of addition was determined using mass spectrometry in which the fragment  $-\text{NHC}(\text{CF}_3)_2^-$  ( $\text{M}^+$  165) occurs. This fragment can only arise from the regio adduct shown. The product (164) was further identified as the  $\Delta^2$ -pyrazoline derivative using  $^1\text{H}$  nmr spectroscopy ( $\delta$  TMS 0 ppm,  $\delta$  -NH -7.4 ppm,  $\delta$  -CH -6.8 ppm).

When (161) was stirred with excess CsF in tetra-  
glyme a dark red solution was obtained. The  $^{19}\text{F}$  nmr spect-  
rum recorded using this solution is consistent with the  
formation of the carbanion (165).

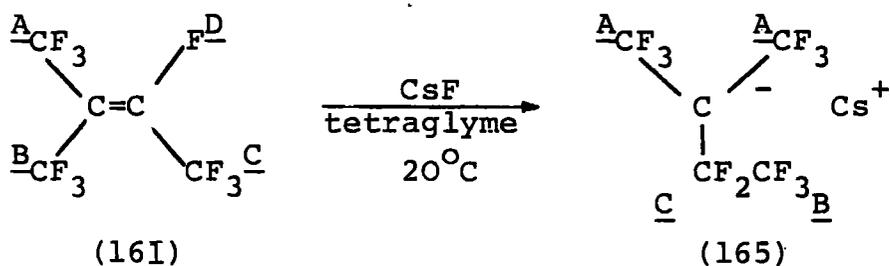

The  $^{19}\text{F}$  nmr data recorded for the carbanion (165) are summarized in Table 7.4 together with that for the alkene (161).

TABLE 7.4  $^{19}\text{F}$  nmr Data recorded for the Alkene (161) and Carbanion (165)

$\delta$   $\text{CFCl}_3$  0 ppm. (165) Carbanion

Shift/ppm.	Intensity	Assignment
-42.0	6	A $-\text{CF}_3$ 's
-85.7	3	B $-\text{CF}_3$
-95.0	2	C $-\text{CF}_2$

(161) Alkene

Shift/ppm.	Intensity	Assignment
-60.4	3	<u>A</u> $-\text{CF}_3$
-61.7	3	<u>B</u> $-\text{CF}_3$
-69.0	3	<u>C</u> $-\text{CF}_3$
-100.3	1	<u>D</u> $-\text{CF}$

When a mixture of (161) with diethyl ether (1:1) was irradiated by  $\gamma$ -rays no chemical change occurred after 72h. This is in contrast to the facile addition of diethyl ether to the diene (75) and is most feasibly explained in terms of steric repulsion.



The products (168) and (169) were identified using the  $^{19}\text{F}$  nmr spectroscopy data shown in Tables 7.5 and 7.6.

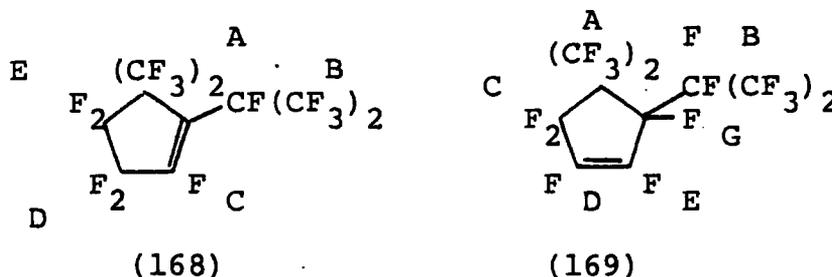


TABLE 7.5  $^{19}\text{F}$  NMR Data used for identification of (168)

$\delta$   $\text{CFCl}_3$  0 ppm.

Shift/ppm.	Intensity	Assignment
-65.7	6	A $-\text{CF}_3$
-75.7	6	B $-\text{CF}_3$
-107.3	1	C $-\text{CF}$
-122.3	4	D,E $-\text{CF}_2$
-181.2	1	F $-\text{CF}$

The intermediate cyclic olefin (167) was not isolated. This result is somewhat surprising because (167) is the least sterically crowded molecule shown in the scheme and should be the thermodynamically favoured product.

TABLE 7.6  $^{19}\text{F}$  NMR Data used for identification of (168)

$\delta$   $\text{CFCl}_3$  0 ppm.


Shift/ppm.	Intensity	Assignment
-74.6	6	A $-\text{CF}_3$
-74.8, -77.8	6	B $-\text{CF}_3$ (prochiral)
-118.6	2	C $-\text{CF}_2$
-122.2, -124.4	2	D,E $-\text{CF}$
-188.1, -188.5	2	F,G $-\text{CF}$

Excellent molecular ion peaks ( $M^-$  462) were obtained for each of the isomers (168) and (169) using negative ion mass spectrometry.<sup>154</sup>

(ii) Reaction with Cesium Fluoride

In order to determine the preferred thermodynamic product from the reaction between  $\text{NBU}_3$  and  $[(\text{CF}_3)_2\text{CFCFHCF}_2]_2$  (64) an experiment was tried using  $\text{CsF}$  alone under forcing conditions. At elevated temperatures  $\text{CsF}$  acts as a base towards acidic protons<sup>149</sup> and therefore should behave entirely analogously to  $\text{NBU}_3$ .

When  $[(\text{CF}_3)_2\text{CFCFHCF}_2]_2$  (64) was stirred at  $140^\circ\text{C}$  in a solution of  $\text{CsF}$  in sulpholane, and the reaction followed using  $^{19}\text{F}$  nmr techniques, complete conversion to the cyclic product (168) was observed after 3h.

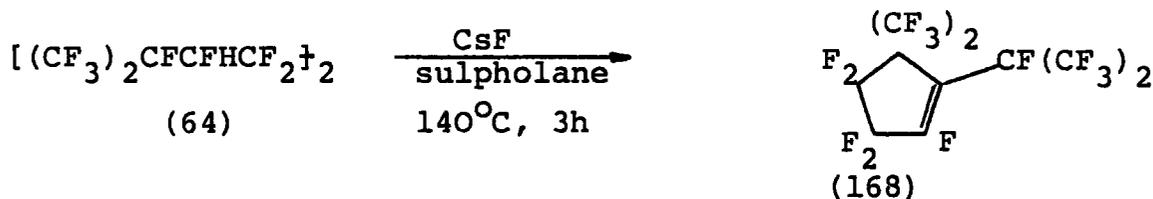

The isomers (167) and (169) were not present in detectable amount (<1% by nmr).


(iii) Pyrolysis over Potassium Fluoride

In an attempt to isolate acyclic alkenes *via* removal of  $\text{HF}$  from  $[(\text{CF}_3)_2\text{CFCFHCF}_2]_2$  (64) this compound was passed over hot  $\text{KF}$  using vacuum-line techniques. The experiment was conducted over a range of temperatures as outlined in Table 7.7 together with the products obtained.

TABLE 7.7 Products obtained from the Pyrolysis of  
 $[(CF_3)_2CFCFHCFCF_2]_2$  (64) over KF

Temperature	Materials isolated
400°C	(64)
470°C	$(CF_3)_2C=CFCF_2CF_2CFHCFCF(CF_3)_2$ (170 + (64)
500°C	(168) + (169)
520°C	At least 15 products which were not separated

The monoalkene 6H-nonadecafluoro-2,7-dimethyloct-2-ene (170) was identified using the  $^1H$  and  $^{19}F$  nmr data shown in Table 7.8.

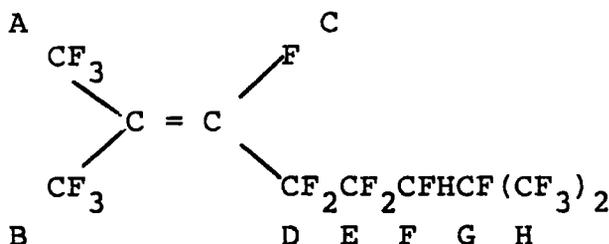

(170)

Notably the diene  $[(CF_3)_2C=CFCF_2]_2$ <sup>155</sup> (171) could not be isolated under these conditions. Therefore, upon removal of a second unit of HF from the monoalkene (170) to produce (171), cyclisation of (171) takes place rapidly.

The monoalkene  $(CF_3)_2C=CFCF_2CF_2CFHCFCF(CF_3)_2$  (170) was stirred with CsF in tetraglyme in an attempt to form the corresponding carbanion  $(CF_3)_2CFCFHCFCF_2CF_2CF_2\bar{C}(CF_3)_2$  Cs<sup>+</sup> (170A). However the  $^{19}F$  nmr spectrum was recorded for the resulting solution and was highly complex. It was concluded

TABLE 7.8  $^1\text{H}$  and  $^{19}\text{F}$  nmr Data for  $(\text{CF}_3)_2\text{C}=\text{CFCF}_2\text{CF}_2\text{CFHCF}(\text{CF}_3)_2$   
(171)

$^{19}\text{F}$  nmr Data:  $\delta$   $\text{CFCl}_3$  0 ppm

Shift/ppm	Coupling	Intensity	Assignment
-58.3	m	3	B $-\text{CF}_3$
-61.3	d, q $J_{\text{AC}}=32\text{Hz}$ $J_{\text{AB}}=10\text{Hz}$	3	A $-\text{CF}_3$
-74.3, -77.3	m	6	H $-\text{CF}_3$ (prochiral)
-96.0	m	1	C $=\text{CF}$
-115.3	t $J_{\text{DE}}=17\text{Hz}$	2	D $-\text{CF}_2$
-122.6	AB $J = 280\text{Hz}$	2	E $-\text{CF}_2$
-187.3	m	1	G $-\text{CF}$
-210.1	m	1	F $-\text{CF}$

$^1\text{H}$  nmr Data :  $\delta$  TMS 0 ppm

-5.6	d $J_{\text{FF}} = 46\text{Hz}$	-	F $-\text{CH}$
------	---------------------------------	---	----------------


that the presence of H destabilizes the anion (17oA) and leads to a series of further reactions.

(iv) Reaction with Potassium Hydroxide

When  $[(\text{CF}_3)_2\text{CFCFHCF}_2]_2$  (64) was stirred with KOH in acetone no reaction occurred until the temperature was raised to  $90^\circ\text{C}$  whereupon tar was produced and only (64) was isolated from the system. Treatment of (64) with dry KOH gave similar results at  $90^\circ\text{-}100^\circ\text{C}$ .

7G Chemistry of 2,4-Dihydrotetradecafluoro-5-methylhexane (72)


The title compound (72) was synthesized using the following route (Chapter Two, B).

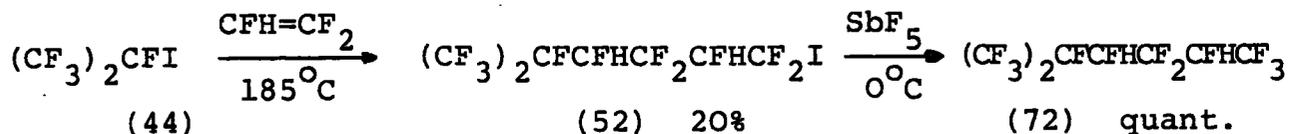

(i) Interpretation of  $^{19}\text{F}$  NMR Spectrum

2,4-Dihydrotetradecafluoro-5-methylhexane (72)

contains two chiral centres:

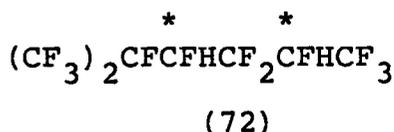

This property gives rise to two diastereoisomers. Each diastereoisomer consists of a further pair of enantiomers which are  $^{19}\text{F}$  nmr equivalent.

The diastereoisomers were separated on a polar column using preparative scale gas chromatography.

The  $^{19}\text{F}$  nmr spectra of 1:1 mixtures of the diastereoisomers were recorded both neat and in solution in acetone. On separating the diastereoisomers the  $^{19}\text{F}$  nmr spectrum of each was again recorded neat and in solution in acetone. Comparison of the spectra obtained made apparent some unusual solvent effects concerning the central  $-\text{CF}_2-$  group of the molecule. These observations are summarized in Table 7.9.


TABLE 7.9 Solvent effects upon  $^{19}\text{F}$  nmr signal of  $-\text{CF}_2-$  group of  $(\text{CF}_3)_2\text{CFCHFCF}_2\text{CFHCF}_3$

System observed	Observation
1:1 Mixture neat	Both $-\text{CF}_2-$ resonances were singlets $\delta$ 121.5 and 122.7 ppm.
1:1 Mixture in Acetone	One AB - $\text{CF}_2-$ resonance $\delta_{\text{AB}}$ -121.0 ppm, $J_{\text{AB}}=177\text{Hz}$ . One singlet $-\text{CF}_2-$ resonance $\delta_{\text{S}}$ -122.4 ppm.
Each Diastereomer (isolated) neat	Both $-\text{CF}_2-$ resonances were singlets <i>ca.</i> $\delta$ -122.0 ppm.
Each Diastereomer (isolated in solution in Acetone)	One AB $-\text{CF}_2-$ resonance $\delta_{\text{AB}}$ -122.0 ppm $J_{\text{AB}}=180\text{Hz}$ . One singlet $-\text{CF}_2-$ resonance $\delta_{\text{S}}$ - 122.5 ppm.

Clearly interaction between the two diastereoisomers cannot give rise to inequivalence of the F atoms since the signals obtained from the neat mixture were both singlets. Therefore this effect must be attributed to the solvation of one of the diastereoisomers by acetone. It is however unusual that this effect should be observed for only one of the diastereoisomers and not both. We have not been able to determine which of the diastereoisomers (72, RR+SS) or (72, SR+RS) is active in this way.

(ii) Pyrolysis over Potassium Fluoride

When  $(\text{CF}_3)_2\text{CFCFHCF}_2\text{CFHCF}_3$  (72) was passed over KF at  $485^\circ\text{C}$ , conversion to the monoalkene 2H-terdecafluoro-5-methylhex-4-ene (172) was achieved.

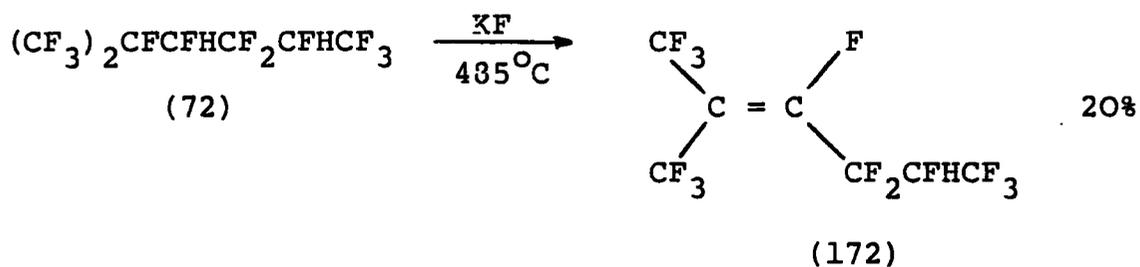

The alkene (172) was identified using mass spectrometry ( $M^+$  332),  $^{19}\text{F}$  nmr spectroscopy ( $\delta$   $\text{CFCl}_3$  0 ppm  $\delta_{\text{F}}$   $\text{C}=\text{CF}$  -96.7 ppm) and infra-red spectrophotometry ( $\nu_{\text{C}=\text{C}}$   $1690\text{ cm}^{-1}$ ).

EXPERIMENTAL

SECTION

## INSTRUMENTATION

Infrared spectra, unless stated, were recorded on a Perkin-Elmer 577 Infrared Spectrophotometer. Solid samples were recorded as KBr discs, liquids as contact films between KBr plates and volatile samples in a cylindrical cell with KBr windows.

$^1\text{H}$  and  $^{19}\text{F}$  n.m.r. spectra were recorded on a Varian EM360L spectrometer operating at 60 and 56.4 MHz respectively at the ambient probe temperature ( $40^\circ\text{C}$ ) and on a Brüker HK90 with Fourier Transform facility at elevated temperatures. Chemical shifts are quoted in ppm relative to TMS and  $\text{CFCl}_3$ . Carbon ( $^{13}\text{C}$ ) spectra were recorded on a Brüker WH-360 operating at 90.6 MHz. Chemical shifts are quoted in ppm relative to TMS.

Mass spectra were recorded on a Varian Associates 77E spectrometer equipped with electron-impact, negative ion ( $\text{NH}_3$  gas) $^{154}$  and chemical ionization ( $^i\text{C}_4\text{H}_8$ ) $^{154}$  facilities together with a capillary column gas chromatograph. Spectra were also recorded on a VG Micromass 12B Spectrometer fitted with a Pye 104 Gas Chromatograph.

Gas liquid chromatographic analyses were carried out on Varian Aerograph Model 920 or Pye Unicam GCD chromatographs using columns packed with diisodecylphthalate (10% and 20%) on chromasorb P (column A), 20% Krytox (perfluoropolyoxypolyene) on chromasorb P (column K) and Silicon elastomer (5%, 10% and 20%) on chromasorb P (column O). Preparative scale gas liquid chromatography was performed on a Varian Aerograph Model 920 using Columns A, K and O.

152

Fractional distillations of product mixtures were carried out using a Fischer-Spaltrohr MMM202 system and other packed columns.

Carbon, hydrogen and nitrogen analyses were obtained using a Perkin-Elmer 240 Elemental Analyzer. Analyses for halogens were performed as described in the literature.<sup>156</sup>

Boiling points and melting points were determined at atmospheric pressure and are uncorrected.

### Reagents

Hexafluoropropene, 1,1-difluoroethene, perfluoroallyl-fluorosulphate (F.A.F.S.), antimony pentafluoride, iodine pentafluoride and bisphenol AF (2) were obtained from the Montedison Company (Montefluos SPA, Milan).

CsF and KF were obtained dry by repeatedly heating under high vacuum ( $10^{-5}$  torr) and grinding in a glove-bag under dry  $N_2$ . Solvents sulpholane, N,N-dimethylformamide and tetraglyme were purified by vacuum distillation and subsequent storage over molecular sieve type 4A.

CHAPTER EIGHT

EXPERIMENTAL FOR CHAPTER TWO -

SYNTHESIS AND EXAMINATION OF

SATURATED MODEL COMPOUNDS

3A. Synthesis of Saturated Model Compounds

(i) Synthesis of Iodofluoroalkanes<sup>47-50,52,62</sup>

Perfluoro-2-iodopropane (44).<sup>108</sup>

A mixture containing hexafluoropropene (120g, 0.80 mole), iodine pentafluoride (35.4g, 0.16 mole) and iodine (80.4g, 0.64 mole), in a sealed stainless steel autoclave (1175 ml capacity) was rocked under autogenous pressure at 150°C for 24 h. On opening the autoclave hexafluoropropene (approx. 1g) was recovered. Further material (228g) transferred from the autoclave using vacuum line techniques was washed with aqueous alkaline sodium thiosulphate and water. Gas chromatography showed one component. Perfluoro-2-iodopropane,  $(CF_3)_2CFI$  (44)<sup>108</sup> (96%) was identified by comparison of the infra red spectrum with that recorded in the literature.<sup>100</sup>

Telomers with 1,1-Difluoroethene<sup>100,101</sup>

A mixture containing perfluoro-2-iodopropane (44) (90.4g, 0.305 mole) and 1,1-difluoroethene (24.0g, 0.375 mole) in a sealed nickel tube (150 ml capacity) was rocked at 185°C for 36 h. under autogenous pressure. On opening the tube after cooling no gaseous products were recovered and a purple liquid (114g) was poured from the tube. Analytical gas chromatography (column O, 120°C) showed the presence of 4 components. Fractional distillation of the mixture using a packed insulated column yielded perfluoro-2-iodopropane (44) (5g, 0.017 mole),

b.pt.  $38^{\circ}\text{C}$ ; 2H,2H-1-iodonona-fluoro-3-methylbutane<sup>100</sup> (48) (73g, 67%), b.pt.  $103^{\circ}\text{C}$  (lit.100,  $105^{\circ}\text{C}$ )  $\delta_{\text{H}}$  (60MHz;  $\text{CCl}_4$ ) -2.8 (2H, t, 2-H);  $\delta_{\text{F}}$  (56.4 MHz;  $\text{CCl}_4$ ) -76.4 (6F, d, 3,4- $\text{CF}_3$ ), -49.6 (2F, m, 1-F), -184.5 (1F, sept, 3-F); m/z 360 ( $\text{M}^+$  8%) and 233 (M-127, 31%); 2H,2H,4H,4H-1-iodoundecafluoro-5-methylhexane,<sup>100</sup>  $(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_2\text{I}$  (62) (26g, 20%); b.pt.  $157^{\circ}\text{C}$ ;  $\delta_{\text{H}}$  (60 MHz;  $\text{CCl}_4$ ) -2.8 to -3.2 (4H, m, 2-H, 4-H);  $\delta_{\text{F}}$  (56.4 MHz;  $\text{CCl}_4$ ) -76.0 (6F, d, 5,6- $\text{CF}_3$ ), -49.2 (2F, m, 1-F), -93.6 (2F, m, 3-F), -185.0 (1F, sept, 5-F); m/z 424 ( $\text{M}^+$ , 1%) and 297 (M-127, 15%).

Preparative scale gas liquid chromatography (column O,  $200^{\circ}\text{C}$ ) on the distillation residue yielded 2,2,4,4,6,6-hexahydro-1-iodoterdecafluoro-7-methyloctane;  $(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_3\text{I}$  (47) (1g, 0.6%);  $\delta_{\text{H}}$  (60 MHz;  $\text{CCl}_4$ ) -2.8 to -3.2 (6H, m, 2-H, 4-H,6-H);  $\delta_{\text{F}}$  (56.4 MHz;  $\text{CCl}_4$ ) -76.2 (6F, d, 7,8- $\text{CF}_3$ ), -49.0 (2F, m, 1-F, -90.3 to -92.0 (4F, m, 3,5-F), -185.0 (1F, sept, 7-F); m/z 488.

A mixture containing perfluoro-2-iodopropane (44) (66.5g, 0.22 mole) and 1,1-difluoroethene (43.0g, 0.66 mole) was sealed in a nickel tube which was then rocked under autogenous pressure at  $220^{\circ}\text{C}$  for 36 hr. On opening the tube a purple liquid (98g) was poured out. Temperature programmed analytical gas chromatography (column O,  $100^{\circ}\text{C}$  to  $250^{\circ}\text{C}$ ) showed 5 components. Fractional distillation yielded (48) (4.3g, 5.4 mole) and (62) (25.0g, 26%). Preparative scale gas liquid chromatography (30% column O,  $250^{\circ}\text{C}$ ) yielded the higher telomers  $(\text{CF}_3)_2\text{CF}-(\text{CH}_2\text{CF}_2)_n\text{I}$ , n=3 (47)<sup>100</sup> (2g) and n=4, 2,2,4,4,6,6,8,8-octahydro-pentadecafluoro-1-iodo-9-methyldecane<sup>100</sup> (1g);  $\delta_{\text{F}}$  (56.4 MHz;  $\text{CCl}_4$ ) -49.0 (2F, m, 1-F); m/z 552.

A mixture containing perfluoroiodoethane (69g, 0.28 mole) 1,1-difluoroethene (16.4g, 0.26 mole) and cumene hydroperoxide (2g) was sealed in a nickel tube which was then rocked under autogenous pressure at 180°C for 24 h. On opening the tube a purple liquid (70g) was poured out and washed with aqueous alkaline sodium thiosulphate and water. Gas liquid chromatography (5% column O, 105°C) showed 5 components. Mass spectrometry of these components showed highest masses 146, 210, 210, 274 and 274 corresponding to  $C_2F_5(C_2H_2F_2)_nI$ ,  $n=0, 1, 1, 2, 2$ . Fractional distillation yielded 2H,2H-1-iodoheptafluorobutane,  $C_2F_5CH_2CF_2I$ <sup>100</sup> (50) (21 g, 24%), b.pt. 88°C; identified by comparison of infra-red spectrum with that of an authentic sample.<sup>100</sup> The other fractions and residue (ca 40g) were not fully characterized.

#### Telomers with Trifluoroethene<sup>100</sup>

A mixture of perfluoro-2-iodopropane (44) (50g, 0.17 mole) and trifluoroethene (13g, 0.16 mole) was sealed in a nickel tube (150 ml capacity) and rocked at 200°C for 24 h under autogenous pressure. On opening the cooled tube no gaseous products were recovered. A purple liquid (60g) was poured from the tube which was observed to consist of 4 major components using analytical gas chromatography (column K, 110°C). Fractional distillation using a Fischer-Spaltrohr column yielded 4 fractions in 95% purity (column K, 110°C) as summarized below (Table 8.1).

A pure sample of each of the 2 middle fractions was isolated using preparative scale gas chromatography (column K, 120°C). Fraction II yielded 2H-1-iododecafluoro-3-methylbutane (50) (ca 1g), b.pt. 101°C; <sup>100</sup>  $\delta_H$  (60 MHz; Neat) -5.1 (1H, d d t, J 42, 10 and 10 Hz, 2-H);  $\delta_F$  (56.4 Mz; Neat) -55.0 (2F, br, 1-F),

TABLE 8.1 Fractions Obtained from the Reaction of  
 $(CF_3)_2CFI$  (44) and  $CF_2=CFH$


B. pt.	No.	Amount Obtained
35-50°C	I	10 g
98-103°C	II	16 g
150-155°C	III	20 g
180-185°C	IV	8 g

-----

-74.0 and -77.7 (6F, br, 2,3- $CF_3$ , prochiral), -213.6 (1F, br, 2-F);  $m/z$  378. Identification of (50) was also facilitated by comparison of infrared spectra with that given in the literature.<sup>100</sup> Fraction III yielded 2H,4H-1-iodododecafluoro-5-methylhexane,  $(CF_3)_2CFCFHC_2CFHC_2I$  (52), b.pt.151°C;  $\delta_H$  (60 MHz; neat) -5.1 (2H, br m, 2,4-H);  $\delta_F$  -54.1 (2 F, br m, 1-F), -73.0 and -76.4 (6 F, br, 5,6- $CF_3$  prochiral), -121.9 (2 F, br, 3-F), -211.9 (2 F, br, 2,4-F);  $m/z$  460.


Relatively small amounts of the regioisomers  $(CF_3)_2CFCF_2CFHI$  and  $(CF_3)_2CFCFHC_2CF_2CFHI$  were identified in the crude product mixture using  $^1H$  nmr spectroscopy  $\delta_H$  ca. -6.1. The fractions I, b.pt. 35-40°C and IV, b.pt. 180-185°C were not fully characterized.

(ii) Coupling Reactions (63,64)



A mixture of  $(CF_3)_2CFCH_2CF_2I$  (48) (40 g, 0.086 mole), acetic anhydride (25 ml) and zinc metal (25 g) was stirred mechanically in a 3-necked glass vessel at 50°C for 4 h.<sup>100</sup>

Volatile products were transferred to a fresh flask, using vacuum line techniques, and stirred with aqueous HCl (100 ml, 0.05M) for 1 h and then washed with water (2 x 50 ml). The fluorocarbon layer was removed and dried ( $\text{MgSO}_4$ ), filtered, and then stored over molecular sieve (type 4A). Analytical gas chromatography showed the product to be (>95% 3H,3H,6H,6H-octadecafluoro-2,7-dimethyloctane,  $[(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2]_2$  (61)<sup>100</sup> (15.0g, 75%); m/z 466. The product was identified by comparison of infra-red spectra with that of an authentic sample.<sup>100</sup>



A mixture of  $(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_2\text{I}$  (62) (33.5g, 79 mmol), acetic anhydride (30 ml) and zinc metal was stirred mechanically at 60°C for 2h. Volatile materials were transferred to a fresh flask using vacuum line techniques, stirred with aqueous HCl (50 ml, 0.05M) and then washed with water (100 ml). The fluorocarbon layer was separated and dried over  $\text{MgSO}_4$ . Analytical gas chromatography showed 1 major and 3 minor components. Distillation of the products removed a forefraction refluxing in the range 80-100°C (13g). The residue was distilled under reduced pressure collecting the fraction b.pt. 130-135°C (3mm Hg). Analytical gas chromatography (column K, 175°C) showed this fraction to be >95% pure and was identified as  $[(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_2]_2$  (63) (9.5g, 40%); variable analysis;  $\delta_{\text{H}}$  -2.9 to -3.1 (br m);  $\delta_{\text{F}}$  -76.2 (12 F, br, 4- $\text{CF}_3$ ), -94.5 (4 F, br, 2-F), -108.5 (4 F, br, 1-F), -184.6 (2 F, br, 3-F); m/z 594. The volatile products were not fully characterized.




A sealed glass ampoule containing  $(\text{CF}_3)_2\text{CFCFHCF}_2\text{I}$ , (50)

(10g, 26 mmol) and mercury (10 ml) was irradiated using a 1 KW ultra-violet lamp at ca. 60°C for 7 d. Volatile material transferred from the glass ampoule using vacuum line techniques was shown to be (>95% purity) by analytical gas chromatography (column A, 80°C) 3,6-dihydroeicosafluoro-2,7-dimethyloctane,  $[(CF_3)_2CFCH_2CF_2]_2$  (64) (5.8g, 89%); (Found: C, 23.1; H, 0.6; F, 75.1.  $C_{10}H_2F_{20}$  requires C, 23.90; H, 0.40; F, 75.70%);  $\delta_H$  -5.1 (d, J 40 Hz, 3,6-H);  $\delta_F$  -74.0 and -77.7 (12 F, br, 2,7-CF<sub>3</sub>, prochiral), -114.8 (4 F, br, 4,5-F), -216.0 (2 F, br, 2,7-F); m/z 483 ( $M^+$  - 19).

A glass ampoule containing  $CF_3CF_2CH_2CF_2I$  (49) (5g, 16 mmol) and mercury (10 ml) was irradiated using a 1 KW ultra-violet lamp at 60°C for 5d. Volatile material transferred from the tube using vacuum line techniques was found by gas chromatography (column O, 120°C) to be one component (>95% purity). The product was 3,3,6,6-tetrahydrotetradecafluorooctane,  $[CF_3CF_2CH_2CF_2]_2$  (57);  $^{100}\delta_H$  -3.0 (m, 3,6-H);  $\delta_F$  -87.1 (6 F, s, 2,7-CF<sub>3</sub>), -114.5 (4 F, br, 4,5-F), -117.8 (4 F, m, 2,7-F); m/z 366. Further identification was provided by comparison of infrared spectra with that given in the literature.<sup>100</sup>

(iii) Fluorination of the Telomer Iodides (70,72,122)



A mixture of the telomer iodides  $(CF_3)_2CF(CH_2CF_2)_nI$  (36g) of approximate molar composition n=1 40%, n=2 30% and n=3 10%, dissolved in  $CF_2ClCFCl_2$  (100 ml), was stirred mechanically in a 3-necked glass vessel. The temperature in the flask was maintained at 0°C using an ice bath while a solution of antimony pentafluoride (40 g, 0.19 mole) in  $CF_2ClCFCl_2$  (50 ml)

was added over a period of 0.5 h. The contents of the flask which became viscous and intensely coloured due to the deposition of iodine, were stirred for a further 0.5 h after the addition was complete. After this time further  $\text{CF}_2\text{ClCFCl}_2$  (50 ml) was added and the resulting mixture filtered to remove solid material. The solid residue was washed with  $\text{CFCl}_2\text{CF}_2\text{Cl}$  (30 ml) and the washings added to the initial filtrate. The resulting solution was then washed with water (250 ml) and neutralised by addition of solid  $\text{NaHCO}_3$  until effervescence ceased. The fluorocarbon layer was separated and  $\text{CFCl}_2\text{CF}_2\text{Cl}$  removed by distillation to leave a pale yellow liquid (16 g). Distillation of this liquid resulted in 3 fractions; I b.pt.  $50-55^\circ\text{C}$ , II b.pt.  $80-85^\circ\text{C}$  and III  $120-130^\circ\text{C}$ . Analytical gas chromatography (column O,  $70-110^\circ\text{C}$ ) showed that the separation was not complete. Therefore the major component of each fraction was isolated using preparative scale gas chromatography (30% column O,  $100^\circ\text{C}$ ). The first component was identified as  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_3$ <sup>100,101</sup> (66);  $m/z$  252 and by comparison of the infrared spectrum that of an authentic sample.<sup>100</sup> The second component was 2H,2H,4H,4H-dodecafluoro-5-methylhexane  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (70), (Found: C, 26.8; H, 1.1; F, 71.7;  $\text{C}_7\text{H}_4\text{F}_{12}$  requires C, 26.58; H, 1.23; F, 72.15%);  $\delta_{\text{H}}$  -3.0 to -3.2 (br m, 2,4-H);  $\delta_{\text{F}}$  -63.0 (3 F, t, J 14Hz, 1-CF<sub>3</sub>) -77.9 (6 F, dt, J t and 7 Hz, 5,6-CF<sub>3</sub>) -90.8 (2 F, br m, 3-F) -185.8 (1 F, br m, 5-F);  $m/z$  297 ( $\text{M}^+$  -19). The third component was 2,2,4,4,6,6-hexahydro-tetradecafluoro-7-methyloctane  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (122);<sup>\*</sup>  $\delta_{\text{H}}$  -3.0 to -3.2 (br m, 2,4,6-H);  $\delta_{\text{F}}$  -64.3 (3 F, t, J 13 Hz), 1-CF<sub>3</sub> -79.3 (6 F, d, J 8 Hz, 7,8-CF<sub>3</sub>) -91.1 (2 F, br.m, 5-F) -92.7 (2 F, br m, 3-F) -187.3 (1 F, br m, 7-F);  $m/z$  371 ( $\text{M}^+$  -19).

\* variable analysis.

When the residue from the distillation was examined using analytical gas chromatography (column O, 180°C) two major components were resolved. These components were isolated using preparative scale gas chromatography (column O, 200°C) and were identified as the n=4 and n=5 telomers  $(CF_3)_2CF(CH_2CF_2)_nF$ ; m/z (n=4) 435 ( $M^+ -19$ ) and (n=5) 599 ( $M^+ -19$ ).



A mixture of  $(CF_3)_2CF(CH_2CF_2)_2I$  (52) (42g, 0.08 mole) and antimony pentafluoride (20g, 0.1 mole) was sealed in a glass ampoule under vacuum at -196°C and allowed to warm up to 0°C using an ice-bath. The mixture was then shaken gently over a period of 0.5 h during which time the contents of the tube turned black due to deposition of iodine. The products were then transferred onto NaF in order to remove antimony pentafluoride and finally transferred from the NaF to a fresh glass vessel, washed with aqueous alkaline  $Na_2S_2O_3$ , water, dried over  $MgSO_4$  and filtered to leave a colourless liquid. The product was examined using analytical gas chromatography and found to be (>95% purity) 2H,4H-tetradecafluoro-5-methylhexane,  $(CF_3)_2CFCHF_2CFCHF_3$  (72) (21g, 75%); (Found: C, 23.6; H, 0.4; F, 75.0;  $C_7H_2F_{14}$  requires C, 23.86; H, 0.57; F, 75.57%);  $\delta_H$  (60 MHz; Neat) -5.4 (M, 2,4-H);  $\delta_F$  -73.9 and 77.5 (6 F, br m, 5,6- $CF_3$ , prochiral), -75.9 (3 F, br m, 1- $CF_3$ ), -121.5 (2 F, br, 3-F), -185.0 (1 F, br, 5-F), -211.2 (2 F, br, 2,4-F); m/z 333 ( $M^+ -19$ ).

83 Examination of the Saturated Model Compounds

## Response to the Curing Agents, General Procedure -

In each experiment a sample of the saturated model was sealed under vacuum in a small glass ampoule (equipped with a "Rotoflo" tap for use with vacuum-lines) with one or a combination of the curing agents. The mixture was then shaken and heated to the temperature indicated. Products were then transferred from the tube by vacuum line techniques and characterized. Solid residues remaining in the glass ampoule were extracted with  $\text{CH}_2\text{Cl}_2$  and examined using  $^{19}\text{F}$  nmr spectroscopy.

(i) Response to  $\text{MgO}$  and  $\text{Ca}(\text{OH})_2$ 

When a mixture of  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (70) (2g, 0.063 mole) and  $\text{MgO}$  (2g, 0.05 mole) was heated to  $177^\circ\text{C}$  for 5 h a colourless liquid was obtained (1.9g) which was examined using analytical gas chromatography (column A,  $80^\circ\text{C}$ ) and found to be (>95% purity) one component with a trace component.  $^{19}\text{F}$  nmr spectroscopy confirmed that the major component was (70) and that the minor component contained the  $(\text{CF}_3)_2\text{C}=\text{CH}-$  group ( $\delta_{\text{F}}$  -61.0 and -63.4 ppm). When the experiment was repeated under identical conditions with  $\text{Ca}(\text{OH})_2$  a similar result was obtained. The residue did not contain fluorinated material.

Treatment of the models  $[(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2]_2$  (61) and  $[(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_2]_2$  (63) under conditions identical to those described above also produced a similar result.

(ii) Response to Bisphenol AF

When a mixture of  $[(CF_3)_2CFCH_2CF_2]_2$  (2g, 0.043 mole) and bisphenol AF (2) (1g, 0.03 mole) was heated to 200°C for 3 hr a colourless liquid was obtained which was identified as pure (61). When the residue was extracted with  $CH_2Cl_2$  and examined using  $^{19}F$  nmr spectroscopy only (2) was detected.

(iii) Response to Phosphonium Salts

When a mixture of the model (61) (1.5g, 0.028 mole) and  $Ph_4P^+Cl^-$  (1g, 0.027 mole) was heated to 190°C for 18 h a colourless liquid was obtained which was identified as pure (61). The residue did not contain fluorinated material. When the experiment was repeated under identical conditions using  $PhCH_2(Ph)_2P^+Cl^-$  there was also no reaction.

(iv) Combinations of the Curing Agents

Table 3.2 summarizes the experimental conditions used. In each experiment which included the inorganic acid-acceptors,  $Ca(OH)_2$  and  $MgO$ , a trace of unsaturation was detected using  $^{19}F$  nmr spectroscopy. In all other experiments no detectable chemical change occurred.

TABLE 3.2 Combinations of the Curing Agents

Saturated Model (2g)	Curing Agents (1 g)	Conditions
(61)	bisphenol AF Ca(OH) <sub>2</sub> MgO	177°C, 5 h
(63)	bisphenol AF Ca(OH) <sub>2</sub> MgO	177°C, 5 h
(61)	bisphenol AF PPh <sub>4</sub> <sup>+</sup> Cl <sup>-</sup>	190°C, 18 h
(63)	bisphenol AF PPh <sub>4</sub> <sup>+</sup> Cl <sup>-</sup>	190°C, 18 h
(61)	bisphenol AF PPh <sub>4</sub> <sup>+</sup> Cl <sup>-</sup> MgO Ca(OH) <sub>2</sub>	177°C, 6 h
(61)	bisphenol AF K <sub>2</sub> CO <sub>3</sub>	177°C, 2 h

8C Attempts to Incorporate Bromine

$[(CF_3)_2CFCH_2CF_2]_2$  (0.53 g, 1.1 mmol) and  $Br_2$  (0.65 g, 4 mmol) were sealed in a glass tube and heated under autogenous pressure to  $300^\circ C$  for 72 h while under the influence of  $\gamma$ -radiation. When the tube was opened a brown liquid (ca. 1 g) was recovered using a vacuum-line technique. Examination of this liquid using  $^{19}F$  and  $^1H$  nmr techniques showed it to be pure (61).

When a mixture of  $[(CF_3)_2CF(CH_2CF_2)]_2$  (63) (0.40 g, 6.7 mmol) and  $Br_2$  (0.60 g, 3.7 mmol) was treated under conditions identical to those described above there was also no reaction.

CHAPTER NINE

EXPERIMENTAL FOR CHAPTER THREE -

SYNTHESIS OF UNSATURATED MODELS

9A. Treatment of  $[(CF_3)_2CFCH_2CF_2]_2$  with Bases (79,80)

Potassium Hydroxide

A mixture of  $[(CF_3)_2CFCH_2CF_2]_2$  (61) (8g, 0.017 mole) and anhydrous KOH (3g, 0.05 mole), sealed in a pyrex Carius tube using vacuum line techniques, was shaken at 20°C for 5 h. On opening the tube a colourless liquid (7 g) was recovered which consisted of one component (gas chromatography, column O, 150°C). The liquid was identified as (61) using infrared and nmr techniques.

A mixture of (61) (8g, 0.017 mole) and anhydrous KOH (5.5g, 0.1 mole), sealed in a pyrex Carius tube was rotated at 30°C for 18 h. On opening the tube a colourless liquid (5.3 g) was recovered using vacuum line techniques. Analytical gas chromatography (carbowax, 105°C) showed one major and one minor component. Mass spectroscopy indicated molecular weights 466 ( $M^+ -19$ ) and 446 ( $M^+ -19$ ) respectively. Gas-phase infrared spectroscopy of the products showed  $\nu_{max}$  1730  $cm^{-1}$  (C=C).  $^{19}F$  nmr spectroscopy was consistent with a mixture of (61) and 3H,6H,6H-heptadecafluoro-8-methyloct-2-ene (80) in 10:1 ratio ( $\delta_F$  -61.0 ppm, 2-CF<sub>3</sub> (z); -67.9 ppm, 1-CF<sub>3</sub> (E)).

$[(CF_3)_2CFCH_2CF_2]_2$  (61) (5g, 0.011 mole) was refluxed over anhydrous KOH (5g) using glass apparatus at 130°C for 2 h. During this time the mixture became black and no material was recovered.

$[(CF_3)_2CFCH_2CF_2]_2$  (61) (3g, 6mmol) was heated to 100°C and swept by a flow of N<sub>2</sub> through a glass tube containing KOH

pellets. The temperature of the glass tube was maintained at 180°C by an oil-bath and the contact time between (61) and KOH was estimated at *c.a.* 1 second. The reaction tube was backed by a second glass tube cooled to -196°C and a drying tube containing H<sub>2</sub>SO<sub>4</sub>. The experiment was continued until all of the starting material had evaporated (2 h). During the experiment the KOH became black and no material condensed in the cold-trap. When the KOH had cooled it was extracted with CH<sub>2</sub>Cl<sub>2</sub> (30 ml). The <sup>19</sup>F nmr spectrum of the CH<sub>2</sub>Cl<sub>2</sub> extract showed no resonances.

Stirring with aqueous KOH (30%) at 20°C resulted in no reaction.

#### Lithium Alkyls - General Procedure

[(CF<sub>3</sub>)<sub>2</sub>CFCH<sub>2</sub>CF<sub>2</sub>]<sub>2</sub> (61) was stirred using a magnetic stirrer in a 50 ml glass flask fitted with a rubber septum and under an atmosphere of dry N<sub>2</sub>. The temperature of the flask was then maintained at -78°C using an acetone/solid CO<sub>2</sub> slush bath. A solution of the lithium alkyl in hexane was then added slowly through the rubber septum using a dry syringe. After the addition the contents of the flask were stirred at -78°C for 1 h and allowed to warm to +20°C by removing the slush bath.

The results using CH<sub>3</sub>Li and <sup>n</sup>C<sub>4</sub>H<sub>9</sub>Li are tabulated below (Table 9.1).

TABLE 9.1 Treatment of (61) with Lithium Alkyls)

Lithium Alkyl (1.55 M in hexane)	Moles (61)	Result
LiCH <sub>3</sub> , 0.03 mol	0.01 mol	) Vigorous re- ) action and ) tarring. No ) products iso- ) lable
Li <sup>n</sup> C <sub>4</sub> H <sub>9</sub> , 0.03 mol	0.01 mol	

Tri-n-butylamine

A mixture of (61) (5g, 0.011 mol) and  $\text{NBu}_3$  (3.5g, 0.024 mol) was stirred using a magnet stirrer in a 50 ml flask fitted with a reflux condenser at  $110^\circ\text{C}$  for 5 h. The products were transferred from the flask using vacuum line techniques and washed with water (10 ml) to leave a pale yellow liquid (3.5 g). Analysis by gas chromatography showed this liquid to be >95% one component. A small sample of this component was isolated using preparative scale gas chromatography (column A,  $130^\circ\text{C}$ ) and identified as 1-(2H-hexafluoro-2-propyl)-3-hydrodecafluoro-2,2-dimethylcyclopentene (79) (3.5g, 74%), (Found: C, 28.0; H, 0.5; F, 71.6;  $\text{C}_{10}\text{H}_2\text{F}_{16}$  requires C, 28.16; H, 0.47; F, 71.37%);  $\nu_{\text{max}}$   $1695\text{ cm}^{-1}$  (C=C);  $\delta_{\text{H}}$  (Neat, capill) -3.9 (1 H, sept, J 7.2 Hz, 2-H), -5.5 (1 H, ddd, J 4.2, 12.3 and 48.0 Hz, 3-H);  $\delta_{\text{F}}$  -63.0 (3F, m, 2- $\text{CF}_3$ ), -64.6 (3F, m, 2- $\text{CF}_3$ ), -68.6 (6 F, d, m, 2- $\text{C}(\text{CF}_3)_2$ ), -111.6 (1 F, sept, J 16 Hz, 5-F), -112.0 (2 F, AB, J 265 Hz, 4-F), -212.0 (1 F, d, J 48.0 Hz, 3-F),  $\delta_{\text{C}}$  -47.4 (1 C, sept, J 33 Hz, 1-CH), -59.5 (1 C, sept, J 36 Hz, 2-C), -86.6 (1 C, ddd, J 13, 34 and 223 Hz, 3-C), -106.6 (1 C, s, 1-C), -117.5 (1 C, t, J 260 Hz, 4-C), -121.9 to -122.9 (1 C, q, J 285 Hz, 2- $(\text{CF}_3)_2$  and 3- $(\text{CF}_3)_2$ ), -159.2 (1 C, dt, J 27 and 309 Hz, 5-C);  $m/z$  426 ( $\text{M}^+$ , 5%) and 275 ( $\text{M}^+$  -151, 17%).

The above reaction was repeated as described above except at the lower temperature of  $100^\circ\text{C}$  for 1 h. The product obtained consisted of three components (gas chromatography; column A,  $100^\circ\text{C}$ ). The three components were isolated using preparative scale gas chromatography (column A,  $130^\circ\text{C}$ )

and identified as (61), (79) and 3H,6H,6H-heptadecafluoro-7-methyloct-2-ene,  $(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CF}_2\text{CH}_2\text{CF}(\text{CF}_3)_2$  (80), (Found: C, 27.15; H, 0.40;  $\text{C}_{10}\text{H}_3\text{F}_{17}$  requires C, 26.60; H, 0.44%;  $\nu_{\text{max}}$  1655  $\text{cm}^{-1}$  (C=C);  $\delta_{\text{H}}$  -6.9 (1 H, t, J 14 Hz, 3-H), -2.9 (2 H, t, J 17.3 Hz, 6-H);  $\delta_{\text{F}}$  -61.0 (3 F, br, 2-CF<sub>3</sub> (z)), -68.0 (3 F, q, J 8Hz, 2-CF<sub>3</sub> (E)), -79.0 (6 F, dt, J 6.8 and 6.8 Hz, 7 and 8-CF<sub>3</sub>), -111.3 (2 F, t, J 14 Hz, 4-F), -113.3 (2 F, br, 5-F), -185.6 (1 F, br, 7-F); m/z 427 ( $\text{M}^+$  -18).

#### 9B. Reactions Involving SbF<sub>5</sub> (71, 75, 81)

A mixture of (61) (5g, 10.7 mmol) and SbF<sub>5</sub> (3.3 g, 15 mmol) was stirred in a 50 ml glass flask using a magnetic stirrer and under an atmosphere of dry N<sub>2</sub>. The temperature of the flask was maintained at 120°C for 2 h using an oil-bath after which time the product was transferred onto dry NaF (10g) using vacuum line techniques. The product remained in contact with NaF for 0.5 h and was then transferred to a fresh flask using vacuum line techniques, washed with water (15 ml) and aq. NaHCO<sub>3</sub> solution (15 ml) and dried over MgSO<sub>4</sub> to yield a colourless liquid (3.9g) identified as 3H,6H-hexadecafluoro-2,7-dimethyloct-2,6-diene,  $(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CF}_2\text{CH}=\text{C}(\text{CF}_3)_2$  (75) (3.9g, 86%); (Found: C, 28.1- H, 0.1- F, 71.7.  $\text{C}_{10}\text{H}_2\text{F}_{16}$  requires C, 28.17; H, 0.47; F, 71.36%);  $\nu_{\text{max}}$  1680  $\text{cm}^{-1}$  (C=C);  $\delta_{\text{H}}$  -6.7 (2 H, t, J 14 Hz, 3,6-H);  $\delta_{\text{F}}$  -60.8 (6 F, m, 2,6-CF<sub>3</sub> (z)), -68.2 (6 F, q, J 3.8 Hz, 1,8-CF<sub>3</sub> (E)), -111.0 (4 F, t, J 15 Hz, 4,5-F);  $\delta_{\text{C}}$  -112.7 (1 C, tt, J 37 and 256 Hz, 4,5-C), -118.9 (2 C, q, J 277 Hz, 2,7-CF<sub>3</sub> (z)), -120.1 (2 C q, J 275 Hz, 1,8-CF<sub>3</sub> (E)), -128.9 (2 C, t, J 26 Hz, 3,6-C), -132.5 (2 C, sept, J 34 Hz, 2,7-C); m/z 426 ( $\text{M}^+$ ).

Elimination of HF from  $(CF_3)_2CFCH_2CF_3$  (66) and  
 $(CF_3)_2CFCH_2CF_2CH_2CF_3$  (70), General Procedure

A mixture of the saturated model and  $SbF_5$  was sealed in a glass ampoule and heated using an oil-bath. Products were transferred onto NaF using vacuum line techniques and then into a fresh flask, washed with water and aq-  $NaHCO_3$  and the fluorocarbon layer separated and dried over  $MgSO_4$ .

A mixture of (66) (6.3g, 27 mmol) and  $SbF_5$  (8.7 g, 40 mmol) was heated to  $120^\circ C$  for 3 h. Analysis of the product by gas chromatography (column A,  $20^\circ C$ ) showed a single component in >95% purity. The product was identified as 2H-nonafluoro-3-methylbut-2-ene,  $(CF_3)_2C=CHCF_3$  (81) (5 g, 80%);  $\delta_H$  -6.7 (1 H, q, J 8.0 Hz, 2-H);  $\delta_F$  -61.0 (3 F, q, J 8.1 Hz, 3- $CF_3$ (z)), -62.0 (3 F, q, J 8.1 Hz, 4- $CF_4$ (E)), -67.6 (3 F, m, 1- $CF_3$ );  $\delta_C$  -127.8 (1 C, sept, J 30 Hz, 3-C), -118.3 -118.0 and -117.0 (3 C, q, K 275 Hz, 1,3,4- $CF_3$ ),  $\delta_C$  for 3-C not observed.

A mixture of (70) (14.8g, 0.05 mol) and  $SbF_5$  (15 g, 0.08 mol) was heated to  $40^\circ C$  for 20 min. Analysis of the product by gas chromatography (column A,  $60^\circ C$ ) showed a single component in >95% purity which was identified as 2H,2H,4H-undecafluoro-5-methylhex-4-ene,  $(CF_3)_2C=CHCF_2CH_2CF_3$  (71) (11g, 74%); (Found: C, 28.1; H, 0.9; F, 71.1.  $C_7H_3F_{11}$  requires: C, 28.38; H, 1.01; F, 70.61%);  $\nu_{max}$   $1674\text{ cm}^{-1}$  (C=C);  $\delta_H$  -2.8 (2 H, m, 2-H); -5.6 (1 H, t, J 13.5 Hz, 4-H);  $\delta_F$  -61.0 (3 F, m, 1- $CF_3$ (z)), -64.0 (3 F, t, J 9.0 Hz, 6- $CF_3$ ), 167.0 (3F, q, J 7.5 Hz, 5- $CF_3$ (E)), -92.0 (2 F, m, 4-F; m/z 277 ( $M^+ -19$ )).

## 9C. Unsaturated Models (37,88) Derived from $\text{CF}_3\text{CF}=\text{CHCF}_3$

### Synthesis of $\text{CF}_3\text{CF}=\text{CFCF}_3$ (83)

A 5 l three-necked flask was charged with sulpholane (1900 ml) and KF (670 g) and stirred mechanically. The temperature inside the flask was maintained at  $200^\circ\text{C}$  using an oil-bath. Hexachlorobuta-1,3-diene (84) (334 g, 1.28 mole) was added dropwise over a period of 3 h and stirred for a further 2 h. The products were collected in liquid air-cooled florentine flasks (2 x 250 ml capacity) using a gentle sweep of dry  $\text{N}_2$ . In all 140 g of material was collected and distilled to yield 2H-heptafluorobut-2-ene,<sup>132,133</sup>  $\text{CF}_3\text{CF}=\text{CHCF}_3$  (83) (95% trans) (122 g, 52%), b.pt.  $6^\circ\text{C}$ . The product (83) was identified using mass spectroscopy (m/z 132) and comparison of infra-red spectra with that of an authentic sample.<sup>129</sup>

### Reactions Involving $\text{CF}_3\text{CF}=\text{CHCF}_3$ (83)

Preparation of  $\text{CF}_3\text{C}(\text{OR})=\text{CHCF}_3$ , General Procedure - A mixture of (83), NaOR (R = Ph,  $\text{CH}_3$ ,  $\text{CH}_3\text{CH}_2$ ) and N,N-dimethylformamide (20 ml) was sealed in a glass tube and shaken at room temperature for 6 h. On opening the tube, (83) was recovered using vacuum line techniques before the products were poured into water (100 ml) and extracted with  $\text{CH}_2\text{Cl}_2$  (2 x 30 ml). Removal of the  $\text{CH}_2\text{Cl}_2$  yielded a mixture of *cis* and *trans*  $\text{CF}_3\text{C}(\text{OR})=\text{CHCF}_3$  in >95% purity (gas chromatography, column O,  $40-100^\circ\text{C}$ ). Variations on this procedure are detailed where applicable. The quantities used and yields obtained are summarized in Table 9.2.

TABLE 9.2 Preparations of  $\text{CF}_3\text{C}(\text{OR})=\text{CHCF}_3$ 

Quantities of Reactants	Ult of Products obtained	Yield <sup>a</sup>
(83) (3.65g, 0.02 mole) NaOCH <sub>3</sub> (1.08g, 0.02 mole)	(83) (0.8g, 4.4 mmol) CF <sub>3</sub> C(OCH <sub>3</sub> )C=CCF <sub>3</sub> (86) <sup>129</sup> (3 g, 0.016 mole)	80%
(83) 5.46g, 0.03 mole) NaOC <sub>2</sub> H <sub>5</sub> (2g, 0.03mole)	(83) (1.2 g, 6.6mmol) CF <sub>3</sub> C(OC <sub>2</sub> H <sub>5</sub> )C=CCF <sub>3</sub> (87), (4 g, 0.02 mole)	65%
(83) (3.64 g, 0.02 mole) NaOPh (2.32g, 0.02 mole)	(83) (1.3g, 7.1 mmol) CF <sub>3</sub> C(OPh)C=CCF <sub>3</sub> (85) <sup>129</sup> (3.1 g, 12 mmol)	61%

-----

The product (86) was obtained by direct transfer under vacuum from the reaction tube.

The products (85) and (86) were identified using mass-spectroscopy (m/z 256 and 194 resp.) and comparison of infrared spectra with those of authentic samples.<sup>129</sup>

Characterization of 2H-3-ethoxyhexafluorobut-2-ene,  
 $\text{CF}_3\text{C}(\text{OC}_2\text{H}_5)=\text{CHCF}_3$  (87) was achieved as follows: (Found:  
 C, 35.52; H, 2.44.  $\text{C}_6\text{H}_6\text{F}_6\text{O}$  requires C, 34.61; H, 2.88%);  
 $\nu_{\text{max}}$  1660  $\text{cm}^{-1}$  (c=C);  $\delta_{\text{H}}$  (capill.) -1.2 (3 H, t, J 7Hz, 3-CH<sub>3</sub>),  
 -3.4 (2 H, q, J 7Hz, 3-CH<sub>2</sub>), -6.3 (1 H, q, J 7.5 Hz, 2-H);  
 $\delta_{\text{F}}$  -59.3 (3 F, d, J 7.5 Hz, 1-F (*trans*)), -72.0 (3 F, s, 4-F  
 (*trans*)) - m/z 206.

A mixture of bisphenol AF (2), (6.72 g, 0.02 mole), (83) (5.7 g, 0.05 mole),  $K_2CO_3$  (5 g) and DMF (30 ml) was sealed in a glass tube and shaken at room temperature for 24 h. On opening the tube (83) (0.6g, 3.3 mmol) was recovered using vacuum line techniques. The products were poured into water (150 ml) and extracted with  $CH_2Cl_2$  (2x20 ml). The extract was dried ( $MgSO_4$ ), filtered and evaporated to leave a colourless oil (10.2g) which was dissolved in n-hexane and eluted down a short column packed with  $Al_2O_3$  to yield 2,2-bis-(4-[3H-hexafluorobut-3-en-2-oxy]phenyl)hexafluoropropane, (88) (9.8g, 74%); (Found: F, 52.40.  $C_{23}H_{10}F_{18}O_2$  requires: F, 51.82%);  $\delta_H$  (d6-acetone) -6.3 (2 H, q, J 7 Hz, 2-H); -7.1 to -7.7 (10 H, AA'XX' coupling, <sup>157</sup> ring-H);  $\delta_F$  -59.7 (6 F, d, J 7Hz, =CHCF<sub>3</sub> (trans)), -63.7 (6 F, s, 1,3-F), -69.6 (6 F, s, =C(OR)CF<sub>3</sub> (trans)); m/z 660.

CHAPTER TENEXPERIMENTAL FOR CHAPTER FOUR -REACTIONS OF UNSATURATED MODEL COMPOUNDS10A. The Hydrolytic Stability of the Model Cross-Links

A mixture of (85) (0.3 g, 1.2 mmol) and aqueous KOH (10 ml, 30% solution) was stirred magnetically in a 25 ml glass flask equipped with a reflux condenser. The temperature of the flask was maintained at 100°C for 3 h using an oil-bath. After cooling the products were extracted with diethyl ether (10 ml), dried (MgSO<sub>4</sub>) and the extract evaporated to leave a colourless liquid (0.2g) identified as (85) by infra red techniques.

When the above procedure was repeated using a mixture of (88) (2g, 3mmol) and aqueous KOH (10 ml, 30% solution) no chemical change took place and (88) (1.5g) was recovered and identified using infra-red and <sup>19</sup>F nmr techniques.

Sealed Tube Experiments with MgO, Ca(OH)<sub>2</sub>. General Procedure

The models (85) and (88) were each separately sealed in glass tubes with a mixture of Ca(OH)<sub>2</sub> and MgO using vacuum line techniques. The tubes were rotated in a stirred oil-bath at 177°C for 3 h. After cooling, the tubes were opened and no volatile material recovered. The products were extracted with CH<sub>2</sub>Cl<sub>2</sub> (10 ml) and the CH<sub>2</sub>Cl<sub>2</sub> evaporated in each case to leave unchanged (85) and (88) respectively. The quantities used and recovered are summarized in Table 9.3.

Material recovered was identified using infra red and <sup>19</sup>F nmr techniques.

TABLE 10.1 Treatment of (85) and (88) with MgO/Ca(OH)<sub>2</sub> Mixture

Amount of Model used	Amount of Model Recovered	Amount of MgO/Ca(OH) <sub>2</sub>
(85) (1 g, 4 mmol)	(85) (0.5 g, 2 mmol)	1 g, 50:50
(88) (2 g, 3 mmol)	(88) (1.5 g, 2.2 mmol)	1 g, 50:50

-----

Sealed Tube Experiments - General Procedure - Mixtures

of (88) with each of water, succinimide, triethylamine and aniline were sealed in nmr sample tubes using vacuum line techniques and heated using a stirred oil-bath. On cooling, <sup>19</sup>F nmr spectra were recorded for each mixture in order to detect chemical changes. The quantities of reagents and conditions are summarized in Table 10.2.

TABLE 10.2 Treatment of (88) with H<sub>2</sub>O, Succinimide, NET<sub>3</sub> and PhNH<sub>2</sub>

Quantities used	Conditions	<sup>19</sup> F nmr Observations
(88) (0.3g, 0.4 mmol) H <sub>2</sub> O (0.6g, 33 mmol)	250°C, 60 h	No change in spectrum from that of (88).
(88) (0.3g, 0.4 mmol) Succinimide, 5% soln. in DMF, (0.6 g)	140°C, 36 h	
(88) (0.3g, 0.4 mmol) NET <sub>3</sub> , 5% soln. in DMF, (0.6g)	140°C 60 h	
(88) (0.3g, 0.4 mmol) PhNH <sub>2</sub> , 5% soln. in DMF, (0.6g)	140°C, 60 h	

10B. Reactivity of Unsaturated Models (90, 91A and 91B)

Experiments Involving  $(CF_3)_2C=CHCF_2CH_2CF_3$  (71)

(71) was sealed separately in glass tubes with each of the mixtures outlined in Table 10.3 using vacuum line techniques. The tubes were then subjected to the conditions summarized by Table 10.3, after which volatile material was recovered using vacuum line techniques and the residue extracted with  $CH_2Cl_2$  (20 ml) and examined using  $^{19}F$  nmr techniques.

TABLE 10.3 Response of (71) to Typical Cure Conditions

Quantity of (71) Used	Composition of Cure-type Mixture	Volatile Material Recovered
3g, 10 mmol	MgO/Ca(OH) <sub>2</sub> , 1g, 50:50, phOH (0.94g, 10 mmol)	(71)
3g, 10 mmol	MgO/Ca(OH) <sub>2</sub> , 1g, 50:50, PhOH (0.94g, 10 mmol), PPh <sub>4</sub> <sup>+</sup> Cl <sup>-</sup> (0.1g, 2.6 mmol)	(71)
3g, 10 mmol	MgO/Ca(OH) <sub>2</sub> , 1g, 50:50, Bisphenol AF (3g, 10 mmol) PPh <sub>4</sub> <sup>+</sup> Cl <sup>-</sup> (0.1g, 2.6 mmol)	(71)

-----

In each case examination of the  $CH_2Cl_2$  extract by  $^{19}F$  nmr techniques indicated (71) as the only fluorinated material present.

A mixture of (71) (2.50g, 8.4 mmol), phenol (0.6g, 6.4 mmol),  $K_2CO_3$  (0.88g, 6.4 mmol) and  $CH_3CN$  (1 ml) was stirred magnetically in a 50 ml flask fitted with a reflux condenser at  $40^\circ C$  for 12 h. The products were then added to water (30 ml) and extracted with diethyl ether (2x10 ml) and evaporated to leave a colourless oil (2.5g). After molecular distillation of this oil, using vacuum line techniques, analytical gas chromatography (capillary column O,  $190^\circ C$ ) showed the presence of two components with similar retention times. Separation of these components by preparative scale gas chromatography was not possible and therefore a sample of the mixture was isolated (30% column O,  $200^\circ C$ ) and identified as 1H,3H,3-phenoxynonafluoro-4,4-dimethylcyclopentene (91A) and 1H,4H,4-phenoxynonafluoro-3,3-dimethylcyclopentene (91B) (50:50 mixture) (2.5g, 85%); variable analysis;  $\nu_{max}$   $1645\text{ cm}^{-1}$  (C=C);  $\delta_H$  -7.7 to -7.0 (1OH, br m, ring-H), -5.7 (2 H, m, 1-H), -3.5 to -3.0 (2 H, m, 3,4-H);  $\delta_F$  -62.7 and -63.7 (6 F, m, 3,4- $CF_3$ ), -67.6 (6 F, m, 3,4- $CF_3$ ); m/z 350.

A mixture of (71) (0.3g, 1 mmol) and KOH (0.2g), sealed in a nmr tube using vacuum line techniques, was heated to  $100^\circ C$  for 12 h, during which time the contents of the tube turned black. When the  $^{19}F$  nmr spectrum was recorded, (71) was identified as the only fluorocarbon present.

#### Experiments Involving $(CF_3)_2C=CHCF_3$ (81)

A mixture of (81) (5.0g, 21.5 mmol), PhOH (2.0g, 21.5 mmol),  $K_2CO_3$  (4.0 g, 28 mmol) and  $CH_3CN$  (10 ml), sealed in a glass tube fitted with a "Rotaflo" tap using vacuum line techniques, was shaken at  $20^\circ C$  for 12 h. The products were then added to water (150 ml), extracted with  $CH_2Cl_2$  (10 ml), dried ( $MgSO_4$ ),

filtered and distilled to leave a colourless liquid (4.5g) which was shown by gas chromatography (column A, 100°C) to consist of one component (>95% purity) identified as 2H,2-phenoxy-3-hydrohexafluoro-3-methylbutane,  $(CF_3)_2CHCH(OPh)CF_3$ , (90) (68%), (Found: C, 40.2; H, 1.85; F, 52.18.  $C_{11}H_7F_9O$  requires C, 40.49; H, 2.15; F, 52.45%);  $\delta_H$  -3.3 (1 H, sept, J 8 Hz, 3-H), -4.9 (1 H, q, J 7 Hz, 2-H), -7.0 (5 H, m, ring-H);  $\delta_F$  -62.4 and -67.6 (6 F, m, 3 prochiral), -76.2 (3 F, m, 1-F); m/z 326.

A mixture of (81) (0.3g, 1.3 mmol) and KOH (0.1g), sealed in a nmr tube using vacuum line techniques, was heated for 12 h. When the  $^{19}F$  nmr spectrum was recorded (81) was identified as the only fluorocarbon present.

A mixture of (81) (0.3g, 1.3 mmol), sulpholane (0.5 ml) and CsF (0.1g), sealed in a nmr tube using vacuum line techniques, was heated to 100°C for 2 h. When the  $^{19}F$  nmr spectrum was recorded (81) was identified as the only fluorocarbon present.

#### Experiments Involving $[(CF_3)_2C=CHCF_2]_2$ (75)

A mixture of (75) (0.3g, 0.7 mmol), tetraglyme (0.5 ml) and CsF (0.1g), sealed in an nmr tube using vacuum line techniques, was heated to 100°C for 2 h. When the  $^{19}F$  nmr spectrum was recorded (79) was identified as the only fluorocarbon present.

A mixture of (75) (2g, 5 mmol), PhOH (1 g, 10 mmol),  $K_2CO_3$  (2g, 10 mmol) and  $CH_3CN$  (2 ml) was stirred magnetically at 30°C for 12 h. The products were added to water (50 ml),

extracted with  $\text{CH}_2\text{Cl}_2$  (20 ml), dried ( $\text{MgSO}_4$ ) and distilled to leave a colourless liquid (1.5g). Capillary column gas chromatography (column O,  $180^\circ\text{C}$ ) showed 4 major components, which were not isolable using preparative scale gas chromatography. Mass spectroscopy showed highest masses of 614, 594, 574 and 554 and all components showed high intensity ( $\text{M}^+ -77$ ) and ( $\text{M}^+ -93$ ) mass peaks.

CHAPTER ELEVEN

EXPERIMENTAL FOR CHAPTER FIVE -  
AN APPROACH TO A NEW FREE-RADICAL  
CROSS-LINKING PROCESS

11A. Synthesis of Crowded ComonomersSynthesis of  $(CF_3)_2CFCHR=CF_2$  (R=H, 99; R=F, 100) - General Procedure

Separate mixtures of  $(CF_3)_2CFCHR=CF_2I$  (R=H(48), F(50)) with KOH pellets, were sealed in glass tubes fitted with "Rotaflo" taps using vacuum line techniques and heated to 90°C for 3 h. Volatile material was then transferred from the tubes and distilled using a short packed column. The quantities used are summarized in Table 11.1.

TABLE 11.1 Synthesis of  $(CF_3)_2CFR=CF_2$  (99,100)

Ult of Iodide	Wt. of KOH	Wt of Alkene	Yield
(48) (30g, 0.08 mol)	(15g, 0.25 mol)	(100) (15g, 0.06 mol)	75%
(50) (45g, 0.12 mol)	(20g, 0.34 mol)	(99) (23g, 0.1 mol)	83%

The alkenes (99) <sup>100,101</sup> and (100) <sup>136</sup> were characterized using analytical data available in the literature.

11B. Synthesis of Polymer Samples

General Procedure - Mixtures of monomer alkenes were sealed in glass tubes using vacuum line techniques and irradiated by a <sup>60</sup>Co γ-ray source at 20°C for 3-7 days. The tubes were then opened and volatile material recovered using high-vacuum (10<sup>-4</sup> torr) at 20°C.

The quantities and proportions of comonomers used are summarized in Table 11.2. The structures of the copolymers have been discussed in detail in Chapter Five, together with  $^{19}\text{F}$  nmr analysis of these products.

TABLE 11.2 Synthesis of Special Copolymers

Comonomers	Quantity Used	Volatile Material Recovered
(i) $\text{CH}_2=\text{CF}_2$	20g, 0.31 mol	None
(ii) $\text{CH}_2=\text{CF}_2$ $\text{CF}_3\text{CF}=\text{CF}_2$	1.8g, 0.03 mol 6.0g, 0.04 mol	$\text{CF}_3\text{CF}=\text{CF}_2$ (4.1g)
(iii) $\text{CH}_2=\text{CF}_2$ (99)	1.3g, 0.02 mol 7.4g, 0.03 mol	(99) (7g)
(iv) $\text{CH}_2=\text{CF}_2$ (100)	7.7g, 0.12 mol 3.2g, 14 mmol	(100) (ca. 2g)
(v) $\text{CH}_2=\text{CF}_2$ (100)	5.0g, 0.08 mol 7.2g, 0.03 mol	(100) (ca. 6g)
(vi) $\text{CH}_2=\text{CF}_2$ (100)	5.7g, 0.09 mol 16.6g, 0.06 mol	(100) (ca. 13g)
(vii) $\text{CH}_2=\text{CF}_2$ $\text{CF}_3\text{CF}=\text{CF}_2$ (99)	2.0g, 0.03 mol 6.0g, 0.04 mol 5.0g, 0.02 mol	$\text{CF}_3\text{CF}=\text{CF}_2/99$ Mixture (9 g)



### 11C. Vacuum Pyrolysis of $\text{CH}_2=\text{CF}_2/(\text{CF}_3)_2\text{CFCF}=\text{CF}_2$ Copolymers

General Procedure - Samples of the copolymers were heated under high vacuum in a 100 ml glass flask backed by a cold trap ( $-196^\circ\text{C}$ ). When no more volatile material could be condensed

into the cold-trap, it was removed and a molecular distillation bucket fitted to the 100 ml flask. On raising the temperature further material was collected in the molecular distillation bucket.

The polymer samples are referenced below using Table 11.2.

Sample (iv) (3.0g) was heated to 90°C for 1 h during which time a bright orange colouration appeared in the cold-trap. After further heating to 120°C for 1 h a colourless liquid (<0.1g) was collected in the cold-trap and identified as perfluoro-2,3-dimethylbutane (103) (lit.100) by infra-red and  $^{19}\text{F}$  nmr techniques.<sup>100</sup> The molecular distillation bucket was fitted and the sample heated to 180°C for 1 h. The sample was observed to melt and become discoloured. After heating to 220°C for 1 h a trace of involatile material was condensed into the molecular distillation bucket. The  $^{19}\text{F}$  nmr spectrum recorded on this material was very complex and the  $^1\text{H}$  nmr spectrum showed the presence of  $-\text{CH}_2-$  groups ( $\delta_{\text{H}}$  -3.1 ppm). After each stage of heating a small portion of the copolymer residue was dissolved in DMAC and the  $^{19}\text{F}$  nmr spectrum recorded. The proportion of units derived from (100) remaining in the copolymer was calculated using the intensity of the resonance of the pendant  $-\text{CF}_3$  groups. The results are shown in Table 11.3.

TABLE 11.3 % of Comonomer Units Derived from (100) Remaining in the Copolymer (iv) at Each Stage after Vacuum Pyrolysis

Conditions	% Incorporation
Initial	7.0
120°C, 1 h	5.8
180°C, 1 h	3.8

-----

Sample (vi) (5.0g) was heated to 160°C for 2h. A colourless liquid (0.3g) was obtained using molecular distillation apparatus, dissolved in  $\text{CF}_2\text{ClCFCl}_2$  (0.3 ml) and found to contain *ca.* 140 products by analytical gas chromatography (capill. column 0, 150°C), of mass range 200-800. The  $^1\text{H}$  nmr spectrum recorded on this solution showed the presence of  $-\text{CH}_2-$  groups ( $\delta_{\text{H}}$  -3.0 ppm), (see Figure 5.1, Chapter Five).

#### 11D. Differential Scanning Calorimetry Studies - General Procedure

Two samples of each copolymer (*ca.* 0.02g) studied were heated slowly under argon from 20°C to temperatures above 300°C. Six thermograms, obtained using differential scanning calorimetry, are represented qualitatively by Figure 11.1 with reference to Table 11.2.

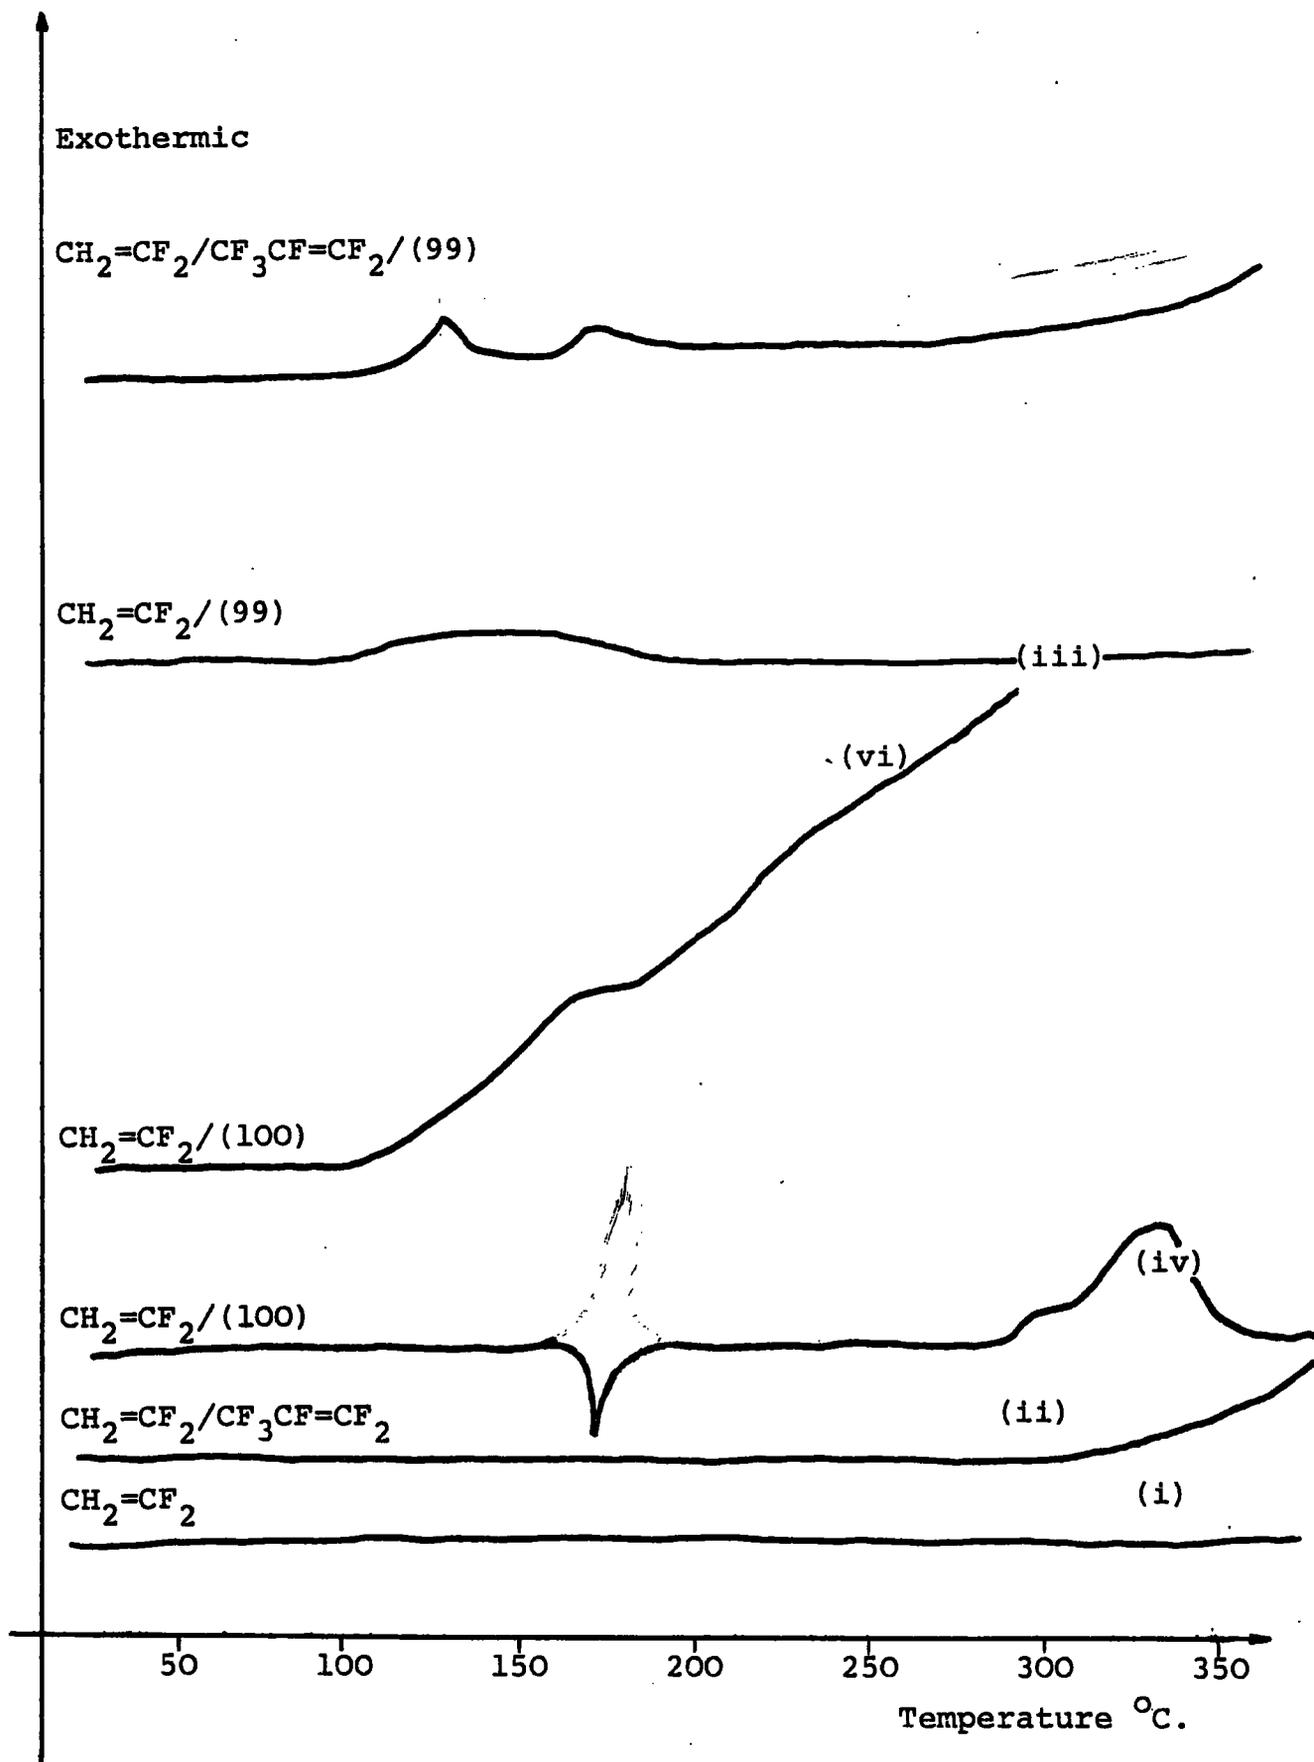


FIGURE 11.1 Differential Thermograms for Copolymers Incorporating Crowded Comonomers

### 11E. Perfluoroallylfluorosulphate/Diethyl Ether Experiment

A mixture of perfluoroallylfluorosulphate (104) (19.8g, 86 mmol) and diethyl ether (20g, 0.27 mole), sealed in a glass ampoule using vacuum line techniques was irradiated by  $\gamma$ -rays at 20°C for 4 d. A second tube containing (104) (20g, 87 mmol) was also irradiated under the same conditions as a control. On opening the first tube a colourless liquid (38g) was obtained and shown by analytical gas chromatography (column O, 100°C) to consist of 3 main components. A small sample of each main component was isolated (>90% purity) by preparative scale gas chromatography and partially characterized as  $\text{FSO}_2\text{OCF}_2\text{CHFCF}_2\text{OSO}_2\text{F}$  (107);  $\delta_{\text{H}} -4.0$  (1 H, 2-H) -  $\delta_{\text{H}} +8.0$  (2 F, 1-SO<sub>3</sub>F);  $m/z$  330 -  $\text{C}_2\text{H}_5\text{OCF}_2\text{CF}=\text{CF}_2$  (108);  $\nu_{\text{max}}$  1695  $\text{cm}^{-1}$  (C=C);  $m/z$  176;  $\text{FSO}_2\text{OCF}_2\text{CF}(\text{C}_2\text{H}_5)\text{CF}_2\text{OSO}_2\text{F}$  (109);  $\delta_{\text{F}} + 8.0$  (2 F, 1,3-SO<sub>3</sub>F), -185.0 (1 F, 2-F);  $m/z$  358. On opening the control tube no chemical change was observed.

CHAPTER TWELVE

EXPERIMENTAL FOR CHAPTER SIX -

NOVEL CHEMISTRY INVOLVING ANTIMONY PENTAFLUORIDE

12A. Cyclisation Reactions (109,111)

A mixture of  $(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CH}_2\text{CF}_3$  (71) (2g, 67 mmol) and  $\text{SbF}_5$  (2 g, 100 mmol) in a 50 ml round bottomed flask was stirred magnetically at  $100^\circ\text{C}$  for 2 h. Volatile material (1.8 g) was then transferred from the flask using vacuum-line techniques, washed with water (10 ml) and shown by analytical gas chromatography (column A,  $75^\circ\text{C}$ ) to consist of one major component (>95% purity). A small sample was then isolated by preparative scale gas chromatography (column A,  $100^\circ\text{C}$ ) and characterized as 1H-2,4-bistrifluoromethyl-4H-tetrafluorocyclopentene (109) (1.8g, 97%). (Found: C, 30.1; H, 0.4.  $\text{C}_7\text{H}_2\text{F}_{10}$  requires C, 30.43; H, 0.72%);  $\nu_{\text{max}}$   $1690\text{ cm}^{-1}$  (C=C);  $\delta_{\text{H}}$  -3.2 (1 H, tq, J 4 and 8 Hz, 1-H); -6.4 (1 H, br, 4-H);  $\delta_{\text{F}}$  -67.0 (3 F, br, 4-CF<sub>3</sub>), -67.5 (3 F, br, 2-CF<sub>3</sub>), -100.0 (2 F, AB, J 282 Hz) and -100.5 (2 F, AB J 269 Hz) (3 and 5-CF<sub>2</sub>);  $\delta_{\text{C}}$  -57.1 (br m, 4-C), -122.1 (q, J 250 Hz) and -125.0 (q, J 279 Hz) (2 and 4-CF<sub>3</sub>), -120.6 and -120.7 (2 C, t, J 257 Hz, 3 and 5-C), -137.4 (t, J 31 Hz, 1-C), -138 (br m, 2-C) - m/z 276 ( $\text{M}^+$ , 36%) and 257 ( $\text{M}^+$  -19, 79%).

A mixture of  $(\text{CF}_3\text{CF}_2\text{CH}_2\text{CF}_2)_2$  (57) (4 g, 11 mmol) and  $\text{SbF}_5$  (5 g, 25 mmol), sealed in a glass ampoule using vacuum line techniques, was stirred magnetically at  $110^\circ\text{C}$  for 2 h. Volatile material was transferred onto NaF (2.0 g) and then, after 30 min, to a fresh flask to yield a colourless liquid (3g) shown by analytical gas chromatography (column A,  $120^\circ\text{C}$ )

to consist of one component (>95% purity) characterized as 1H-2-trifluoromethyl-3H,3-pentafluoroethyltetrafluorocyclopentene (111) (2.5g, 70%), (Found: C, 29.5; H, 0.6; F, 69.5  $C_8H_2F_{12}$  requires C, 29.45; H, 0.61; F, 69.91%;  $\delta_H$  -3.8 (1 H, t, J 20 Hz, 3-H), -6.6 (1 H, br, 1-H);  $\delta_F$  -69.0 (3 F, d, J 60 Hz, 2-CF<sub>3</sub>), -85.0 (3 F, d, J 20 Hz, 3-CF<sub>2</sub>CF<sub>3</sub>), -115.0 (2 F, AB, J 245 Hz, 4-F), -115.6 (2 F, br, 3-CF<sub>2</sub>CF<sub>3</sub>); -117.0 (2 F, AB, J 273 Hz, 5-F);  $\delta_C$  -51.7 (m, 3-C), -114.0, -119.0, -122.0 (3 C, br m, 4,5-C and 3-CF<sub>2</sub>CF<sub>3</sub>), -119.5 (q, J 272 Hz) and -120.6 (q, J 280 Hz) (2-CF<sub>3</sub> and 3-CF<sub>2</sub>CF<sub>3</sub>), -134.4 (t, J 17 Hz, 1-C), -138.1 (q, J 39 Hz, 2-C); m/z 326 (M<sup>+</sup>, 2%) and 207 (M<sup>+</sup> -119, 11%).

#### Isomerisation of (CF<sub>3</sub>)<sub>2</sub>CFCH=CF<sub>2</sub> (99)

A mixture of (99) (0.5 g, 2.1 mmol) and SbF<sub>5</sub> (0.6, 3 mmol) was sealed in an nmr tube and shaken at 20°C for 1 h. When <sup>19</sup>F and <sup>1</sup>H nmr spectra were recorded (CF<sub>3</sub>)<sub>2</sub>C=CHCF<sub>3</sub> (81) was identified as the only product;  $\delta_F$  -61.0 (3 F), -62.0 (3 F) and -67.6 (3 F);  $\delta_H$  -6.7 (1 H, q, J 8.0 Hz).

#### 12B. Attempts at Related Reactions (115, 116)

##### Synthesis of C<sub>8</sub>F<sub>17</sub>CH<sub>2</sub>CF<sub>3</sub> (116)

A mixture of 1-iodoperfluorooctane (114) (120 g, 0.2 mole) and 1,1-difluoroethene (9.9 g, 0.15 mole), in a sealed nickel tube (150 ml capacity) was rocked under autogenous pressure at 185°C for 36 h. On opening the tube the solid products (122 g) were removed by shaking with CH<sub>2</sub>Cl<sub>2</sub> (100 ml) and distillation at room temperature. Distillation at 18 mm Hg afforded a fraction boiling at 75°C which was (114) (23 g) and

one at 110°C to yield 1-iodo-2,2-dihydrnonadecafluorodecane,  $C_8F_{17}CH_2CF_2I$  (115) (66g, 54%), (Found: C, 18.0; H, 0.20; F, 58.3; I, 20.25.  $C_{10}H_2F_{19}I$  requires C, 19.60; H, 0.33; F, 59.18; I, 20.89%);  $\delta_H$  -3.0 (2 H, tt, J 15 and 15 Hz, 2-H);  $\delta_F$  -38.3 (2 F, m, 1-F), -80.5 (3 F, t, J 16 Hz, 10-F); 113.3 (2 F, br, 9-F), -123 (10 F, br, 4,5,6,7,8-F), -127.1 (2 F, br, 3-F); m/z 610 ( $M^+$ , 5%) and 483 ( $M^+ -127$ , 44%).

A solution of (115), (55g, 85 mmol) in  $CF_2ClCFCl_2$  (50 ml) was stirred mechanically in a 1 l round bottomed 3-necked flask equipped with a reflux condenser and a supply of dry  $N_2$ . A solution of  $SbF_5$  (25g, 0.12 mole) in  $CF_2ClCFCl_2$  (50 ml) was added with caution over a period of 1 h and the temperature in the flask maintained at 0-5°C using an ice-bath. After stirring for a further 30 min the products were added to water (300 ml) and then washed with aqueous  $Na_2HCO_3$  (300 ml). The fluorocarbon layer was separated, filtered and distilled at room temperature to obtain a pale yellow liquid (38g) which was shown to consist of one component (>95% purity) by analytical gas chromatography (column O, 150°C). Distillation under hard vacuum yielded 2H,2H-eicosafuorodecane,  $C_8F_{17}CH_2CF_3$  (116) (32g, 75%) (Found: C, 23.4; H, 0.2; F, 75.3.  $C_{10}H_2F_{20}$  requires C, 23.90; H, 0.40; F, 75.70%);  $\delta_H$  -3.1 (2 H, tq, J 15 and 15 Hz, 2-H);  $\delta_F$  -62.0 (3 F, t, J 17 Hz, 1-F), -78.5 (3 F, t, J 20 Hz, 10-F), -113.0 (2 F, br, 9-F), -123.0 (10 F, br, 4,5,6,7,8-F), -128.5 (2 F, br, 3-F); m/z 483 ( $M^+ -19$ , 17%).

#### Attempted Cyclisation of (116)

A mixture of (116) (38g, 76 mmol) and  $SbF_5$  (32.8g, 0.15 mol), sealed in a glass ampoule, was stirred magnetically under autogenous pressure at 190°C for 12 h, during which time the

the contents of the tube turned bright orange/red. Volatile material (20 g) was then transferred to a fresh tube using vacuum line techniques, by which it was found to have a very high vapour pressure.  $\text{SiF}_4$  was identified as a component using gas phase infra-red techniques;  $\nu_{\text{max}}$  1029 and  $388 \text{ cm}^{-1}$ ,<sup>158</sup> and vented cautiously from the tube. The products were then washed with water (2x30 ml) and shown by analytical gas chromatography (column K,  $80^\circ\text{C}$ ) to consist of three main components (ca. 80%) and less volatile material (ca. 20%).  $^1\text{H}$  nmr studies on the products showed no resonances. A sample of each of the three main components was isolated (>95% purity) using preparative scale gas chromatography (column A,  $50^\circ\text{C}$ ) identified as  $\text{C}_n\text{F}_{2n}$  ( $n=8-10$ ) using the data summarized in Table 12.1

TABLE 12.1 Volatile Products from Reaction between (116) and  $\text{SbF}_5$

n	$^{19}\text{F}$ nmr Data	Neg. Ion m/z
8	-82.5 (6 F, t, J 18 Hz) -113 to -127 (10 F, complex)	400
9	-83.0 (6 F, t, J 18 Hz) -113 to -127 (12 F, complex)	450
10	-83.0 (6 F, t, J 18 Hz) -113 to -127 (14 F, complex)	500

-----

Other Reactions Attempted - General Procedure

The reactant mixtures summarized in Table 12.2 were each sealed with  $\text{SbF}_5$  in glass ampoules and subjected to the conditions stated. Volatile material was then transferred

into an nmr tube and sealed using vacuum line techniques and products identified using nmr spectroscopy. Variations on this procedure are detailed where applicable.

TABLE 12.2 Attempted Inter-Molecular Reactions involving Antimony Pentafluoride

Reactants	Conditions	Observations
(118) (3.0g, 10 mmol) (119) (2.0g, 10 mmol) SbF <sub>5</sub> (2.0g, 9 mmol)	150°C, 12 h	No Reaction
(109) (5.8g, 14.2 mmol) (119) (3.5g, 10 mmol) SbF <sub>5</sub> (3.7g, 16 mmol)	190°C, 12 h	
(81) (3.0g, 12.9 mmol) (119) (3.5g, 18 mmol) SbF <sub>5</sub> (6.8g, 31.5 mmol)	150°C, 12 h	
(118) (0.3g, 1 mmol) SbF <sub>5</sub> (0.3g, 1.5 mmol)	Sealed in nmr tube, -50°C to + 20°C	
Toluene (5g, 54 mmol) (118) (3g, 10 mmol) SbF <sub>5</sub> (3g, 14 mmol)	Soln. of (118) in SbF <sub>5</sub> added dropwise to toluene at -78°C	

12C. Elimination Reactions and the Formation of Stable Carbocations (127, 128, 129, 133)

Synthesis of Cations (127) and (128)

Separate mixtures of  $(CF_3)_2CF(CH_2CF_2)_nF$ ,  $n=3$  (122) (0.3g, 0.8 mmol) and  $n=4$  (123) (0.3g, 0.7 mmol), with  $SbF_5$  (1.0g, 5.0 mmol) were sealed in nmr tubes using vacuum line techniques.  $^1H$  and  $^{19}F$  nmr spectra were recorded at  $40^\circ C$  and the stable cations (127) and (128) characterized using the data which is summarized fully in Table 6.3.

Quenching of the Cation (127) with MeOH

A mixture of (122), (1.0g, 2.7 mmol) and  $SbF_5$  (3g, 14 mmol) stirred magnetically in a 50 ml round-bottomed flask under an atmosphere of dry  $N_2$ , was cooled to  $-78^\circ C$  using an acetone dry-ice bath and MeOH (3g, 0.1 mol) added slowly over a period of 30 min. Stirring was then continued for a further 1 h when the products were allowed to warm to  $20^\circ C$ , poured into water (200 ml), extracted with  $CH_2Cl_2$  (2x30 ml), washed with water (100 ml), dried ( $MgSO_4$ ) and distilled at room temperature to obtain a yellow oil (0.8g). Molecular distillation at high vacuum followed by chromatography on silica gel with diethyl ether-light petroleum (b.p.  $60-80^\circ C$ ) (1:3) yielded 3,3,5,7,7-pentahydro-4-methoxydecafluoro-2-methyloct-4-enone,

$(CF_3)_2CFCH_2C(OCH_3)=CHCOCH_2CF_3$  (129) (0.5g, 53%);  $\nu_{max}$  1600 and  $1700\text{ cm}^{-1}$  ( $\alpha,\beta$ -unsaturated ketone);  $\delta_H$  -3.2 (2 H, q, J 10.6 Hz, 7-H), -3.6 (3H, s, 4-OMe), -3.7 (2 H, d, J 22 Hz, 3-H), -5.6 (1 H, s, 5-H);  $\delta_F$  -65.0 (3 F, t, J 10.6 Hz, 8-F), -78.5 (6 F, d, J 7 Hz, 2- $CF_3$ ), -182.8 (1 F, m, 2-F); m/z 350 ( $M^+$ , 8%). and 111 ( $M^+$  -239, 29%).

\* variable analysis.

### Reaction of the Cation (127) with $\text{SbF}_5$

A mixture of (122) (5.1g, 13.4 mmol) and  $\text{SbF}_5$  (9.0g, 41 mmol) was stirred magnetically in a 50 ml round-bottomed flask at 20°C under an atmosphere of dry  $\text{N}_2$ . A small sample was removed after 5 min and a  $^{19}\text{F}$  nmr spectrum recorded which showed the presence of the cation (127). The temperature in the flask was then maintained at 110°C for 30 min using an oil-bath after which time the temperature was lowered to 0°C and water (50 ml) added with caution. The fluorocarbon layer was washed with weak aqueous  $\text{NaHCO}_3$  (200 ml) to leave a yellow liquid (2.55g) shown by analytical gas chromatography (capill. column O, 80°C), to consist of one main component (>90% purity). A sample of this component was isolated (>95% purity) using preparative scale gas chromatography and characterized as 2,5-bistrifluoromethyl-3H,7H-undecafluorooct-2-ene,

$(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CF}(\text{CF}_3)\text{CF}_2\text{CH}_2\text{CF}_3$  (133) (approx. 40%);  $\nu_{\text{max}}$  1680  $\text{cm}^{-1}$  (C=C); variable analysis;  $\delta_{\text{H}}$  -3.0 (2 H, m, 7-H), -6.8 (1 H, t, J 14 Hz, 3-H);  $\delta_{\text{F}}$  -61.0 (3 F, br, 2- $\text{CF}_3$  (z)), -62.5 (3 F, br, 8-F), -68.3 (3 F, br, 2- $\text{CF}_3$  (E)), -78.2 (3 F, br, 5- $\text{CF}_3$ ), -110.9 (2 F, br, 6-F), -120.1 (2 F, br, 4-F), -185.5 (1 F, br, 5-F); m/z 427 ( $\text{M}^+$  -19, 6%) and 163 ( $\text{M}^+$  -283, 32%).

### Isolation of Polyenes from the Cation (128)

A mixture of  $(\text{CF}_3)_2\text{CF}(\text{CH}_2\text{CF}_2)_4\text{F}$  (123) (2.8g, 6.3 mmol) and  $\text{SbF}_5$  (7 g, 33 mmol) was stirred magnetically in a 50 ml round-bottomed flask at 20°C for 30 min. A small sample was removed and a  $^{19}\text{F}$  nmr spectrum recorded which showed the presence of the cation (128). The mixture was then transferred dropwise into a 500 ml round-bottomed flask containing  $\text{NaF}$  (20g) maintained at 0-5°C by an ice-bath. After 1 h a mole-



## 12D. Dehydrohalogenation of Polymers by $\text{SbF}_5$

General Procedure - Samples of the polymers summarized in Table 12.4 were dissolved in the specified solvent, filtered and cast into thin films by slow evaporation of the solvent using vacuum line techniques. After continued removal of the solvent under high vacuum ( $10^{-5}$  torr) the films were exposed to  $\text{SbF}_5$  vapour. The treated films were then handled in a dry glove-box in order to prepare samples for  $^1\text{H}$  nmr and infra-red analyses.

TABLE 12.4 Treatment of Polymers with  $\text{SbF}_5$

Polymer	Solvent	Observation	Analytical Data from Treated Film
$(\text{CH}_2=\text{CF}_2/\text{CF}_3\text{CF}=\text{CF}_2)$	-	Instantaneous intense colouration	i.r. $1600-1650\text{ cm}^{-1}$ (C=C)
$(\text{CH}_2\text{CHCl})_n$	Acetone	"	i.r. $1700\text{ cm}^{-1}$ (C=C) $^1\text{H}$ nmr $\delta_{\text{H}}$ -6.3 ppm
$(\text{CH}_2\text{CF}_2)_n$	DMF	"	i.r. $1600-1700\text{ cm}^{-1}$ (C=C)
$(\text{CHF}\text{CF}_2)_n$	DMAC	Became dark only after prolonged contact at $60^\circ\text{C}$	i.r. $1600-1700\text{ cm}^{-1}$ (C=C)

CHAPTER THIRTEEN

EXPERIMENTAL FOR CHAPTER SEVEN -

THE GENERAL CHEMISTRY OF THE MODEL COMPOUNDS

13A. Reactions Involving 1-(2H-hexafluoro-2-propyl)-3-hydro-decafluoro-2,2-dimethylcyclopentene (79) (145-148)

Reaction of (79) with Methoxide

Freshly cut sodium (0.1g, 5 mmol) was added to dry MeOH (5 ml) and stirred at 20°C for 1 h under dry N<sub>2</sub>. (79) (2g, 4 mmol) was then added over a period of 10 min with further stirring. After washing with water (2 x 10 ml) a fluoro-carbon layer was separated, distilled under hard vacuum to obtain a colourless liquid (1.4g) and shown by gas chromatography (column O, 150°C) to consist of 2 main components. A sample of each component was isolated (>95% purity) using preparative scale gas chromatography (column O, 150°C) and identified as (79) and 1-(2-methoxytetrafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (146); (Found: C, 31.8; H, 0.8; F, 63.6. C<sub>11</sub>H<sub>4</sub>F<sub>14</sub>O requires C, 31.58, H, 0.96; F, 63.64%);  $\nu_{\max}$  1650-1700 cm<sup>-1</sup> (conjugated diene);  $\delta_{\text{H}}$  -3.8 (3 H, s, 2-OCH<sub>3</sub>), -5.4 (1 H, dd, J 15 and 48 Hz, 3-H),  $\delta_{\text{F}}$  -57.8 (3 F, m, vinyl-CF<sub>3</sub>), -65.3 and -70.0 (6 F, br, 2-CF<sub>3</sub>), -71.0 (1 F, d, J 12.5 Hz, acyclic vinyl-F), -111.9 (2 F, AB, J 261 Hz, 4-F), -119.8 (1 F, d, J 12.5 Hz, 5-F), -210.9 (1 F, m, 3-F); m/z 418 (M<sup>+</sup>, 100%) and 315 (M<sup>+</sup> -103, 29.8%).

Pyrolysis over Potassium Fluoride

(79) (2 g, 4.7 mmol) in the vapour phase was passed through a glass tube packed with KF heated to 300°C by a furnace, and backed by a cold trap (-196°C), using vacuum line techniques. A colourless liquid (1.8g) was obtained

and shown by gas chromatography (column A, 95°C) to consist of 2 main components. A sample of each component was isolated (>95% purity) using preparative scale gas chromatography and identified as (79) and 1-(pentafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (145); (Found: C, 29.3; requires C, 29.56%);  $\nu_{\max}$  1700-1750  $\text{cm}^{-1}$  (conjugated diene);  $\delta_{\text{H}}$  -5.0 (1 H, ddd, J 5, 12 and 48 Hz);  $\delta_{\text{F}}$  -60.0 (3 F, br, vinyl-CF<sub>3</sub>), -66.7 and -71.0 (6 F, br, 2-(CF<sub>3</sub>)<sub>2</sub>), -68.3 (2 F, m, Acyclic Vinyl-F), -113.2 (2 F, AB, K 261 Hz, 4-F), -117.2 (1 F, t, J 14.0 Hz, 5-F), -211.6 (1 F, m, 3-F); m/z 406 (M<sup>+</sup>, 20%) and 249 (M<sup>+</sup> -157, 21%).

#### Reaction of (145) with Caesium Fluoride

(145) (1.0 g, 2.5 mmol) was added dropwise to a stirred suspension of CsF (0.5g) in tetraglyme (2 ml). After stirring for a further 10 min a small sample was removed, the <sup>19</sup>F nmr spectrum recorded, and the stable carbanion (148) identified using the data summarized in Chapter Seven, Table 7.1. Bromine (ca. 0.5 g, 3.3 mmol) was then added to the stirred solution. After stirring for a further 1 h. water (5 ml) was added and a fluorocarbon layer isolated which was shown by gas chromatography (column A, 125°C) to consist of two main components identified as a mixture of (79) and 1-(2-bromohexafluoro-2-propyl)-3-hydrodecafluoro-2,2-dimethylcyclopentene (148); m/z 487 (M<sup>+</sup> -19) and 425 (M<sup>+</sup> -81, 9%).

13B. Reactions involving 3,6-Dihydrohexadecafluoro-2,7-dimethylocta-2,6-diene (75) and 2H-nonafluoro-3-methylbut-2-ene (81) (149,150,152-155)

Free-Radical Additions - General Procedure

Binary mixtures of (75) with  $[\text{CH}_3(\text{CH}_2)_n]_2\text{O}$  ( $n=0,1$ ) and methanol, sealed in glass ampoules using vacuum line techniques, were irradiated with  $\gamma$ -rays under the conditions summarized in Table 13.1

TABLE 13.1 Free-Radicals Additions to (75) and (81)

Substrate	Addend	Conditions ( $\gamma$ -ray)
(3.0g, 7 mmol)	$(\text{C}_2\text{H}_5)_2\text{O}$ (0.5g, 7 mmol)	) 20°C, 3 d
(75) (1.9g, 4.5 mmol)	MeOH (0.3g, 10 mmol)	
(1.3g, 3.1 mmol)	$(\text{CH}_3)_2\text{O}$ (0.3g, 6 mmol)	
Hexachlorobuta-1,3-diene,		
(151) (7.3g, 28 mmol)	$(\text{C}_2\text{H}_5)_2$ (2.1g, 28 mmol)	20°C, 8 d

Diethyl ether/(75)

On opening the tube a colourless liquid (3.0 g) was distilled from polymeric residue (0.5g) using vacuum line techniques. Gas chromatography (carbowax, 140°C) on the volatile material showed the presence of two main components one of which had a short retention time equal to that of diethyl ether. A sample of the less volatile component was isolated (>95% purity) using preparative scale gas chromatography (column Z, 180°C) and identified as 2,7-dimethyl-3,6-bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluorooxepane (149)

(Found: C, 33.7; H, 2.1; F, 61.3.  $\text{C}_{14}\text{H}_{12}\text{F}_{16}\text{O}$  requires C, 33.6; H, 2.4; F, 60.8%);  $\nu_{\text{max}}$  (C=C) absent;  $\delta_{\text{H}}$  -3.9 (2 H, sept, J 8 Hz, 3,6- $\text{CH}(\text{CF}_3)_2$ ), -3.3 (2 H, m, 2,7-H), -1.3 to

-1.7 (6 H, s, 2,7-Me), -1.6 (2 H, m, 3,6-H);  $\delta_F$  -60.7 and -63.7 to -67.3 (12 F, m, 3,6-CH(CF<sub>3</sub>)<sub>2</sub>), -120.5 (2 F, s) and -123.1 (2 F, AB, J 242 Hz), (4,4,5,5-F); m/z (CI) 501 (M<sup>+</sup>, 33%) and (EI) 249 (M<sup>+</sup> -151, 8%).

#### Methanol/(75)

On opening the tube, water (5 ml) was added and a white solid precipitate (1.0 g) separated. Recrystallisation to constant melting point from CH<sub>2</sub>Cl<sub>2</sub> yielded 3-hydroxymethylhexafluoro-2,7-dimethyloct-6-ene (152) (0.5 g, 24%), m.p. 73.5°C (Found: C, 29.5; H, 1.1. C<sub>11</sub>H<sub>6</sub>F<sub>16</sub>O requires C, 28.82; H, 1.31%);  $\nu_{\max}$  1680 cm<sup>-1</sup>;  $\delta_H$  -5.9 (2 H, s, 3-CH<sub>2</sub>), -3.2 (1 H, m, 3-H);  $\delta_F$  -61.0 (3 F, br, 7-CF<sub>3</sub> (z)), -65.3 to -67.3 (3 F, br, 8-F(E)) and (6 F, br, 1,2-CF<sub>3</sub> (prochiral)). -124.3 (4 F, br, 4,5-CF<sub>2</sub>); m/z (CI) 459 (M<sup>+</sup>, 9%).

#### Dimethyl Ether/(75)

On opening the tube, a colourless liquid (1.3g) was obtained using vacuum line techniques and shown by gas chromatography (column O, 65°C) to consist of 2 major components, one of which had a very short retention time. A sample of the less volatile component was isolated (>95% purity) using preparative scale gas chromatography (column O, 90°C) and identified as 3,6-bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluorooxepane (150); variable analysis;  $\nu_{\max}$  (C=C) absent;  $\delta_H$  -4.0 to -3.3 (broad);  $\delta_F$  -60.0 to -63.8 (12 F, br, 3,6-CH(CF<sub>3</sub>)<sub>2</sub>), -112.4 (2 F, AB, J 271 Hz) and 122.2 (2 F, AB, J 262 Hz) (4,5-CF<sub>2</sub>); m/z (CI) 473 (M<sup>+</sup>, 2%).

Diethyl Ether/Hexachlorobuta-1,3-diene

On opening the tube a small sample was withdrawn and the  $^1\text{H}$  nmr spectrum recorded showed diethyl ether (>99% purity) as the only hydrocarbon present.

Addition of Diazomethane - General Procedure

Diazomethane was prepared using the method of Boer and Backer<sup>152</sup>. Separate solutions of (75) and (81), stirred in 50 ml round-bottomed flasks and cooled to  $0^\circ\text{C}$ , were treated with a solution of  $\text{CH}_2\text{N}_2$  in diethyl ether until the yellow colouration of  $\text{CH}_2\text{N}_2$  persisted. On warming to  $20^\circ\text{C}$  the ether was removed by distillation at room temperature to obtain the crude products which were purified by vacuum transfer.

 $\text{CH}_2\text{N}_2$ /(75)

Compound (75) (1.0g, 2.2 mmol) and diazomethane yielded a white solid (1.1g), recrystallized from  $\text{CH}_2\text{Cl}_2$  and identified as 1,2-di(5,5-bistrifluoromethyl-4,5-dihydro-3H-4-pyrazolo)-tetrafluoroethane (153) (80%), (Found: C, 28.4; H, 0.8; N, 11.2; F, 59.9.  $\text{C}_{12}\text{H}_6\text{N}_4\text{F}_{16}$  requires C, 28.24; H, 1.18; N, 10.98; F, 59.61%);  $\nu_{\text{max}}$  (C=N), (N-H) absent;  $\delta_{\text{H}}$  -3.2 (2 H, ddd, J 9, 9 and 9 Hz, 4-H), -4.4 to -5.3 (4 H, AB d, J 18 and 9 Hz, 3-H);  $\delta_{\text{F}}$  -65.0 and -69.0 (6 F, m, 5- $\text{CF}_3$ ), -109.7 (4 F, AB, J 290 Hz, 1,2-F); m/z (CI) 511 ( $\text{M}^+$ , 73%) and 483 ( $\text{M}^+ -28$ , 16%).

 $\text{CH}_2\text{N}_2$ /(81)

Compound (81) (5.0 g, 22 mmol) and diazomethane yielded a colourless liquid (5.0 g) shown by gas chromatography (column A,  $50^\circ\text{C}$ ) to consist of 2 components with very similar retention

times identified as 4,5,5-tris(trifluoromethyl)-4,5-dihydro-3H-pyrazole (154); variable analysis;  $\delta_{\text{H}}$  -4.8 (2 H, AB, J 20 Hz, 3-H), -5.0 (1 H, m, 4-H);  $\delta_{\text{F}}$  -60.7 (3 F, m, 4-CF<sub>3</sub>), -71.9 and -72.9 (6 F, m, 5,5-CF<sub>3</sub>); m/z 274 (M<sup>+</sup>, 55%) and 266 (M<sup>+</sup> -28, 21%); and 4,5,5-tris(trifluoromethyl)-4,5-dihydro-1H-pyrazole (155); variable analysis;  $\delta_{\text{H}}$  -7.8 (1 H, br, N-H), -6.6 (1 H, br, 3-H), -5.0 (1 H, m, 4-H);  $\delta_{\text{F}}$  -60.7 (3 F, m, 4-CF<sub>3</sub>), -71.9 and -72.9 (6 F, m, 5,5-CF<sub>3</sub>); m/z 274 (M<sup>+</sup>, 65%) and 164 (M<sup>+</sup> -110, 18%).

### 13C. One Electron Transfer Reactions<sup>156,157</sup>

#### Reduction of (70) by Tri-n-butylamine

A mixture of (70) (1.5g, 4.7 mmol) and tri-n-butylamine (2.0g, 14 mmol), sealed in a small glass ampoule using vacuum line techniques was irradiated using a 1 KW high pressure ultra-violet lamp for 3 d. The temperature in the region of the tube was ca. 60°C. On opening the tube a colourless liquid (1.0g) was distilled out and shown by gas chromatography (column A, 95°C) to consist of 2 main components, one of which had a retention time identical to that of (70). A sample of the second component was isolated (>95% purity) using preparative scale gas chromatography (column A, 120°C) and identified as 2,3,3,4,4-pentahydro undecafluoro-2-methylhexane (156) (Found: C, 28.1; H, 1.6; F, 69.6. C<sub>7</sub>H<sub>5</sub>F<sub>11</sub> requires C, 28.19; H, 1.68; F, 70.13%);  $\nu_{\text{max}}$  (C=C) absent;  $\delta_{\text{H}}$  -3.0 (1 H, sept, J 8 Hz), -2.5 to 1.9 (4 H, m, 3,5-H);  $\delta_{\text{F}}$  -62.5 (3 F, dt, J 9 and 9 Hz, 6-F), -69.2 (6 F, m, 2-CF<sub>3</sub>); m/z 298 (M<sup>+</sup>) and 133 (M<sup>+</sup> -165, 100%).

### Reaction of (62) with Tri-n-butylamine

A mixture of (62) (5.0g, 11.8 mmol) and tri-n-butylamine (3.4 g, 23.6 mmol) was stirred magnetically in a 50 ml round-bottomed flask, equipped with a reflux condenser and drying tube ( $\text{CaCl}_2$ ), at  $120^\circ\text{C}$  for 12 h. Volatile material (3.6g) was then transferred from the flask using vacuum line techniques and shown by gas chromatography (column A,  $80^\circ\text{C}$ ) to consist of four main components. Separation of the mixture by preparative scale gas chromatography (column A,  $100^\circ\text{C}$ ) yielded (95% purity)  $(\text{CF}_3)_2\text{C}=\text{CHCF}_2\text{CH}_2\text{CF}_3$  (71) (0.2g),  $(\text{CF}_3)_2\text{CFCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (70) (1.0g),  $(\text{CF}_3)_2\text{CHCH}_2\text{CF}_2\text{CH}_2\text{CF}_3$  (156) (0.3g) and 2,3,5,5-tetrahydrodecafluoro-2-methylhex-3-ene (*trans*) (157) (1.1g, 33%); variable analysis;  $\nu_{\text{max}}$   $1650\text{ cm}^{-1}$  (C=C);  $\delta_{\text{H}}$  -4.9 (1 H, dd, J 10 and 30 Hz, 3-H) - -3.9 (1 H, d.sept, J 8 and 10 Hz, 2-H), -2.9 (2 H, dq, J 10 and 10 Hz, 5-H);  $\delta_{\text{F}}$  -67.0 (3 F, dt, J 6 and 10 Hz, 6-F), -70.0 (6 F, dd, J 3 and 8 Hz, 2- $\text{CF}_3$ ), -100.0 (1 F, br, 4-F); m/z 278 ( $\text{M}^+$ , 16%) and 127 ( $\text{M}^+ -151$ , 11%).

### 13D. Reactions involving Perfluoro-2-methylbut-2-ene(161) 161,165

#### Synthesis of (161)

A mixture of (100) (5.0g, 20 mmol), CsF (0.5g) and sulpholane (10 ml), sealed in a glass ampoule using vacuum line techniques, was heated to  $100^\circ\text{C}$  for 2 h with occasional shaking. After cooling to  $20^\circ\text{C}$  the tube was opened and a colourless liquid (4.5g) transferred to a fresh flask using vacuum line techniques. Gas chromatography (column A,  $20^\circ\text{C}$ ) showed this liquid to consist of one component (>95% purity)

identified as perfluoro-2-methylbut-2-ene (161) (4.5 g, 90%), b.pt. 29°C; variable analysis;  $\nu_{\max}$  1690  $\text{cm}^{-1}$  (C=C, weak)  $\delta_{\text{F}}$  -60.4 (3 F, qd, J 10 and 4 Hz, 2-CF<sub>3</sub> (Z)), -61.7 (3 F, dq, J 30 and 10 Hz, 3-CF<sub>3</sub> (Z)), -69.0 (3 F, q, J 10 Hz, 2-CF<sub>3</sub> (E)), -100.3 (1 F, qqq, J 4, 10 and 30 Hz, 3-F); m/z 250 (M<sup>+</sup>).

#### Reaction of (161) with MeOH

A mixture of (161) (1.8g, 7.2 mmol) and methanol (0.7g, 21.6 mmol), sealed in a glass ampoule using vacuum line techniques, was shaken at 20°C for 6 h. On opening the tube a colourless liquid (2.5g) was removed using a pipette and shown by gas chromatography (column K, 50°C) to consist of three main components, one of which had a retention time identical to that of methanol. The remaining two components were isolated as a mixture using preparative scale gas chromatography (column K, 80°C) and identified as a 1:1 mixture of 2-methoxy-nonafluoro-3-methylbut-2-ene (162);  $\delta_{\text{H}}$  -4.0 (3 H, s, 2-OMe);  $\delta_{\text{F}}$  -60.0 - 64.0 (9 F, br m, 2,3-CF<sub>3</sub>); m/z 262; and 2H-3-methoxy-decafluoro-2-methylbutane (163);  $\delta_{\text{H}}$  -3.7 (3 H, s, 3-OMe), -3.6 (1 H, sept, J 7 Hz, 2-H);  $\delta_{\text{F}}$  -60.0 and -64.7 (6 F, br, 2-CF<sub>3</sub> (prochiral)), -77.5 (3 F, d, J 8 Hz, 3-CF<sub>3</sub>), -130.6 (1 F, q, J 8 Hz, 3-F); m/z 282 (M<sup>+</sup>).

#### Reaction of (161) with CH<sub>2</sub>N<sub>2</sub>

A solution of (161) (1.8g, 7.2 mmol) in diethyl ether (2 ml), stirred in a 50 ml round-bottomed flask cooled to 0°C, was treated with a solution of diazomethane in diethyl ether until the yellow colouration of CH<sub>2</sub>N<sub>2</sub> persisted. On warming to 20°C the ether was removed by distillation at room temperature to obtain a colourless liquid (1.5 g) shown by gas

chromatography (column A, 50°C) to consist of one main component (>95% purity) and identified as 4,5,5-tris(trifluoromethyl)-4-fluoro-4,5-dihydro-1H-pyrazole (164); variable analysis;  $\nu_{\max}$  1600  $\text{cm}^{-1}$  (C=N);  $\delta_{\text{H}}$  -6.8 (1 H, br, C-H), -7.5 (1H, br, N-H) -  $\delta_{\text{F}}$  -68.3 to -71.0 (6 F, br m, 5,5-CF<sub>3</sub>), -75.2 (3 F, dd, J 14 and 14 Hz, 4-CF<sub>3</sub>), -163.7 (1 F, m, 4-F); m/z (CI) 292 (M<sup>+</sup>, 17%), 204 (M<sup>+</sup> -88, 14%) and 165 (M<sup>+</sup> -127, 1%).

#### Reaction of (161) with CsF

The alkene (161) (1.0g, 4 mmol) was added dropwise to a stirred suspension of CsF (0.5g) in tetraglyme (2 ml). After stirring for a further 1 h a small sample was removed, the <sup>19</sup>F nmr spectrum recorded, and the stable carbanion (161) identified using the chemical shift data summarized in Chapter Seven, Table 7.4.

#### 13E. Reactions of Models derived from 1-Iodo-2-Hydrodecafluoro-3-methylbutane (50) (168-170,172)

##### Reaction of (64) with Tri-n-butylamine

A mixture of (64) (1.0 g, 2 mmol) and tri-n-butylamine (0.8g, 5.6 mmol), stirred in a 10 ml round-bottomed flask equipped with a reflux condenser, was heated to 125°C for 12 h. Volatile material (1.5g) was then recovered using vacuum line techniques and shown by gas chromatography (column F, 130°C) to consist of two main components in approximately equal ratio. The two components were then isolated (>95% purity) using preparative scale gas chromatography (Column F, 130°C) and identified as perfluoro-2-(prop-2-yl)-3,3-dimethylcyclopentene (168);  $\nu_{\max}$  1695  $\text{cm}^{-1}$  (C=C);  $\delta_{\text{F}}$  -65.7 (6 F, br, 3-CF<sub>3</sub>), -75.7 (6 F, dq,

J 24 and 5 Hz, 2-C(CF<sub>3</sub>)<sub>2</sub>), -107.3 (1 F, m, 5-F), 122.3 (4 F, br m, 3,4-F), -181.2 (1 F, sept sept, J 5 and 24 Hz, 2-CF); m/z (neg. ion) 462 (M<sup>-</sup>, 11%) and 293 (M<sup>-</sup> -169, 12%); and perfluoro-3-(prop-2-yl)-4,4-dimethylcyclopentene (169); δ<sub>F</sub> -74.6 (6 F, br, 4-CF<sub>3</sub>), -75.0 and -77.8 (6 F, br, 3-C(CF<sub>3</sub>)<sub>2</sub> (prochiral)), -118.6 (2 F, br, 5-F), -123.3 (2F, br, 1,2-F), 188.3 (2 F, br, 3-F and 2-CF); m/z (neg.ion) 462 (M<sup>-</sup>, 33%) and 262 (M<sup>-</sup> -200, 100%).

#### Reaction of (64) with CsF

A mixture of (64) (0.3 g, 0.6 mmol), CsF (0.1 g) and sulpholane (0.3 ml), sealed in an nmr tube using vacuum line techniques, was heated to 140°C for 3 h. The <sup>19</sup>F nmr spectrum was then recorded and (168) identified as a single product using the chemical shift data summarized above.

#### Pyrolysis of (64) over Potassium Fluoride - General Procedure

(64), in the vapour phase, was passed through a tube containing KF using vacuum line techniques. Product material was condensed into a cold trap (-196°C), allowed to warm to room temperature and separated into component products using preparative scale gas chromatography (column A, 70°C). The quantities and conditions used are summarized in Table 13.2.

TABLE 13.2 Pyrolysis of (64) over Potassium Fluoride

Starting Material	Temperature	Products Isolated
(64) (1.5g, 3 mmol)	400°C	(64)
(64) (10g, 20 mmol)	470°C	(170) + (64)
(64) (4g, 8 mmol)	500°C	(168) + (169)
(64) (2g, 4 mmol)	520°C	Complex Mixture not separable

6H-Nonadecafluoro-2,7-dimethyloct-2-ene

$(CF_3)_2C=CFCF_2CF_2CFHCF(CF_3)_2$  (170); variable analysis;  
 $\nu_{max}$  1680  $cm^{-1}$  (C=C);  $\delta_H$  -5.5 (1 H, d, J 46 Hz, 6-H);  $\delta_F$  -58.3 (3 F, m, 2- $CF_3$  (Z)), -61.3 (3 F, dq, J 32 and 12 Hz, 2- $CF_3$  (E)), -74.3 and -77.3 (6 F, br, 7- $CF_3$  (prochiral)), -96.0 (1 F, m, 3-F), -115.3 (2 F, m, 4-F), -122.6 (2 F, AB, J 248 Hz, 5-F), -187.3 (1 F, br, 7-F), -211.1 (1 F, br, 6-F); m/z 463 ( $M^+$  -19, 1%).

Pyrolysis of (72) over Potassium Fluoride

Using the general procedure described above (72) (8g, 23 mmol) yielded a colourless liquid (6.0g) which was shown by gas chromatography (column A, 60°C) to consist of 2 main components one of which had a retention time identical to that of (72). A sample of the second component was isolated (>95% purity) using preparative scale gas chromatography (column A, 60°C) and identified as 2H-terdecafluoro-5-methyl-hex-4-ene (172) (Found: C, 25.4; H, 0.1; F, 74.1.  $C_7HF_{13}$  requires C, 25.30; H, 0.30; F, 74.40%);  $\nu_{max}$  1690  $cm^{-1}$  (C=C);  $\delta_H$  -5.3 (1 H, d, J 45 Hz);  $\delta_F$  -58.7 (3 F, m, 5- $CF_3$  (Z)), -60.2 (3 F, dq, J 28 and 11 Hz, 5- $CF_3$  (E)), -76.6 (3 F, br, 1-F), -96.7 (1 F, m, 4-F), -114.8 (2 F, AB, J 254 Hz, 3-F), -216.6 (1 F, d, J 45 Hz, 2-F); m/z 332 ( $M^+$ , 9%).

APPENDIX ONEN.M.R. Spectra

1. 2H,2H,4H,4H-dodecafluoro-5-methylhexane (70)
2. 2,2,4,4,6,6-Hexahydrotetradecafluoro-7-methyloctane (122)
3. 2,3,3,5,5-Pentahydro undecafluoro-2-methyl hexane (156)
4. 1-Iodo-2,2-dihydrnonadecafluorodecane (115)
5. 2H,2H-eicosafuorodecane (116)
6. 3,5-Dihydroeicosafuoro-2,7-dimethyloctane (64)
7. 2H,4H-tetradecafluoro-5-methylhexane (72)
8. 2H,2H,4H-undecafluoro-5-methylhex-4-ene (71)
9. 3H,6H,6H-heptadecafluoro-7-methyloct-2-ene (80)
10. 3H,6H-hexadecafluoro-2,7-dimethyloct-2,6-diene (75)
11. 6H-nonadecafluoro-2,7-dimethyloct-2-ene (170)
12. 2H-terdecafluoro-5-methylhex-4-ene (172)
13. 2,3,5,5-Tetrahydrodecafluoro-2-methylhex-3-ene (157)
14. 2,5-Bis(trifluoromethyl)-3H,7H,7H-undecafluorooct-2-ene (133)
15. 2-Methoxynonafluoro-3-methylbut-2-ene (162)
16. 3-Hydroxymethylhexadecafluoro-2,7-dimethyloct-6-ene (152)
17. 2H-3-ethoxyhexafluorobut-2-ene (87)
18. 2H,2-phenoxy-3-hydrohexafluoro-3-methylbutane (90)
19. 1H,3H,3-phoxynonafluoro-4,4-dimethylcyclopentene (91A)
20. 1H,4H,4-phoxynonafluoro-3,3-dimethylcyclopentene (91B)
21. 1-(2H-hexafluoro-2-propyl)-3-hydrodecafluoro-2,2-dimethylcyclopentene (79)
22. 1-(Pentafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (146)
23. 1-(2-Methoxytetrafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (146)
24. 1H-2,4-bis(trifluoromethyl)-4H-tetrafluorocyclopentene (109)
25. 1H-2-trifluoromethyl-3H,3-pentafluoroethyltetrafluorocyclopentene (111)

26. Perfluoro-2-(prop-2-yl)-3,3-dimethylcyclopentene (168)
27. Perfluoro-3-(prop-2-yl)-4,4-dimethylcyclopentene (169)
28. 4,5,5-Tris(trifluoromethyl)-4,5-dihydro-3H-pyrazole (154)
29. 4,5,5-Tris(trifluoromethyl)-4,5-dihydro-1H-pyrazole (155)
30. 1,2-Di(5,5-bis(trifluoromethyl)-4,5-dihydro-3H-4-pyrazolo)tetrafluoroethane (153)
31. 4,5,5-Tris(trifluoromethyl)-4-fluoro-4,5-dihydro-1H-pyrazole (164)
32. Stable Carbocation (127)
33. Stable Carbocation (128)
34. 3,3,5,7,7-Pentahydro-4-methoxydecafluoro-2-methyloct-4-enone (129)
35. 2,7-Dimethyl-3,6-bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluorooxepane (149)
36. 3,6-Bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluorooxepane (150)
37. Perfluoro-2-methylbut-2-ene (161)
38. 2H-3-methoxydecafluoro-2-methylbutane (163)
39. 2,2-Bis-(4-[2H-hexafluorobut-2-enoxy]phenyl)hexafluoropropane (88)

The following abbreviations are used in this appendix:

S, singlet; D, doublet; T, triplet; Q, quartet; Sept, septet; M, complex multiplet.

Unless otherwise stated the spectra were recorded at 40°C in CDCl<sub>3</sub>, or CCl<sub>4</sub>.

CFCl<sub>3</sub>, TMS and TMS were used as reference for <sup>19</sup>F, <sup>1</sup>H and <sup>13</sup>C spectra respectively.

For <sup>1</sup>H spectra downfield chemical shifts are quoted as positive whilst for <sup>19</sup>F spectra, upfield shifts are quoted as positive. For <sup>13</sup>C spectra "downfield" shifts are quoted as positive where downfield is the direction of increasing the absolute values.

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
<b>1. <u>2H,2H,4H,4H-dodecafluoro-5-methylhexane (70)</u></b>			
<sup>19</sup> F Spectrum: (capill. neat)			
63.0	T (J = 14)	3	f-CF <sub>3</sub>
77.9	D (J = 7) of T (J = 7)	6	a-CF <sub>3</sub>
90.8	M	2	d-CF <sub>2</sub>
185.8	M	1	b-CF
<sup>1</sup> H Spectrum: (capill. neat)			
3.0 to 3.2	M	4	c,e-CH <sub>2</sub>
<b>2. <u>2,2,4,4,6,6-Hexahydrotetradecafluoro-7-methyloctane (122)</u></b>			
<sup>19</sup> F Spectrum: (capill. neat)			
64.3	T (J = 13)	3	h-CF <sub>3</sub>
79.3	D (J = 8)	6	a-CF <sub>3</sub>
91.1	M	2	d-CF <sub>2</sub>
92.7	M	2	f-CF <sub>2</sub>
187.3	M	1	b-CF
<sup>1</sup> H Spectrum: (capill. neat)			
3.0 to 3.2	M	6	c,e,g -CH <sub>2</sub>
a	b c d e f	a b c d e f g h	a b c d e f
(CF <sub>3</sub> ) <sub>2</sub> CFCH <sub>2</sub> CF <sub>2</sub> CH <sub>2</sub> CF <sub>3</sub>	(CF <sub>3</sub> ) <sub>2</sub> CFCH <sub>2</sub> CF <sub>2</sub> CH <sub>2</sub> CF <sub>2</sub> CH <sub>2</sub> CF <sub>3</sub>	(CF <sub>3</sub> ) <sub>2</sub> CHCH <sub>2</sub> CF <sub>2</sub> CH <sub>2</sub> CF <sub>3</sub>	(156)
(70)	(122)		
<b>3. <u>2,3,3,5,5-Pentahydroundecafluoro-2-methylhexane (156)</u></b>			
<sup>19</sup> F Spectrum: (capill. neat)			
62.5	D (J = 9) of T (J = 9)	3	f-CF <sub>3</sub>
69.2	M	6	a-CF <sub>3</sub>
98.5	M	2	d-CF <sub>2</sub>
<sup>1</sup> H Spectrum:			
3.0	Sept (J = 8)	1	b-CH
1.9 to 2.5	M	4	c,3-CH <sub>2</sub>

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
4. <u>1-Iodo-2,2-dihydrnonadecafluorodecane</u> (115)			
<sup>19</sup> F Spectrum:			
38.3	M	2	f-CF <sub>2</sub>
80.5	T (J = 16)	3	a-CF <sub>3</sub>
113.3	M	2	b-CF <sub>2</sub>
123.0	M	10	c-CF <sub>2</sub>
127.1	M	2	d-CF <sub>2</sub>
<sup>1</sup> H Spectrum:			
3.0	T (J = 15) of T (J = 15)	2	e-CH <sub>2</sub>
5. <u>2H,2H-eicosafuorodecane</u> (116)			
<sup>19</sup> F Spectrum:			
62.0	T (J = 17)	3	f-CF <sub>3</sub>
78.5	T (J = 20)	3	a-CF <sub>3</sub>
113.0	M	2	b-CF <sub>2</sub>
123.0	M	10	c-CF <sub>2</sub>
128.5	M	2	d-CF
<sup>1</sup> H Spectrum:			
3.1	T (J = 15) of Q (J = 15)	2	e-CH <sub>2</sub>
a b c d e f	a b c d e f	a b c d	
CF <sub>3</sub> CF <sub>2</sub> (CF <sub>2</sub> ) <sub>5</sub> CF <sub>2</sub> CH <sub>2</sub> CF <sub>2</sub> I	CF <sub>3</sub> CF <sub>2</sub> (CF <sub>2</sub> ) <sub>5</sub> CF <sub>2</sub> CH <sub>2</sub> CF <sub>3</sub>	[(CF <sub>3</sub> ) <sub>2</sub> CF <sub>2</sub> CFHCF <sub>2</sub> ] <sub>2</sub>	
(115)	(116)	(64)	
6. <u>3,6-Dihydroeicosafuoro-2,7-dimethyloctane</u> (64)			
<sup>19</sup> F Spectrum:			
74.0	M	6 )	a-CF <sub>3</sub>
77.7	M	6 )	
114.8	M	4	d-CF <sub>2</sub>
186.0	M	2	b-CF
216.0	M	2	c-CF
<sup>1</sup> H Spectrum:			
5.1	D (J = 40)	-	c-CH

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
<b>7. <u>2H,4H-tetradecafluoro-5-methylhexane</u> (72) (neat, diastereomer mixture)</b>			
$^{19}\text{F}$ Spectrum:			
73.9	M	3 )	a-CF <sub>3</sub>
77.5	M	3 )	
75.9	M	3	f-CF <sub>3</sub>
121.5	M	2	d-CF <sub>2</sub>
185.0	M	1	b-CF
211.2	M	1	c-CF
$^1\text{H}$ Spectrum:			
5.4	M		c, 2-CH
<b>8. <u>2H,2H,4H-undecafluoro-5-methylhex-4-ene</u> (71)</b>			
$^{19}\text{F}$ Spectrum:			
61.0	M	3	a-CF <sub>3</sub> (z)
64.0	T (J = 9)	3	e-CF <sub>3</sub>
67.0	Q (J = 7.5)	3	a-CF <sub>3</sub> (E)
92.0	M	2	c-CF <sub>2</sub>
$^1\text{H}$ Spectrum:			
2.8	M	2	d-CH <sub>2</sub>
6.6	T (J = 13.5)	1	b-CH
a b c d e f	a b c d e	a b c d e f g	
(CF <sub>3</sub> ) <sub>2</sub> CFCHCF <sub>2</sub> CFHCF <sub>3</sub>	(CF <sub>3</sub> ) <sub>2</sub> C=CHCF <sub>2</sub> CH <sub>2</sub> CF <sub>3</sub>	(CF <sub>3</sub> ) <sub>2</sub> C=CHCF <sub>2</sub> CF <sub>2</sub> CH <sub>2</sub> CF(CF <sub>3</sub> ) <sub>2</sub>	
(72)	(71)	(80)	
<b>9. <u>3H,6H,6H-heptadecafluoro-8-methyloct-2-ene</u> (80)</b>			
$^{19}\text{F}$ Spectrum:			
61.0	M	3	a-CF <sub>3</sub> (z)
68.0	Q (J = 8)	3	a-CF <sub>3</sub> (E)
79.0	D (J=6.8) of T(J=6.8)	6	g-CF <sub>3</sub>
111.3	T (J = 14)	2	c-CF <sub>2</sub>
113.3	M	2	d-CF <sub>2</sub>
185.6	M	7	f-CF
$^1\text{H}$ Spectrum:			
2.9	T (J = 17)	2	e-CH <sub>2</sub>
6.8	T (J = 14)	1	b-CH

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
10.	<u>3H,6H-hexadecafluoro-2,7-dimethyloct-2,6-diene</u> (75)		
<sup>19</sup> F Spectrum:			
60.8	M	6	a-CF <sub>3</sub> (z)
68.2	Q (J = 9)	6	a-CF <sub>3</sub> (E)
111.0		4	d-CF <sub>2</sub>
<sup>1</sup> H Spectrum:			
6.7	T (J = 14)	-	c-CH
<sup>13</sup> C Spectrum:			
112.7	T(J=256) of T(J=37)	-	d-C
118.9	Q(J=277)	-	a-C (z)
120.1	Q(J=275)	-	a-C (E)
128.9	T(J=26)	-	c-C
132.5	Sept (J=34)	-	b-C
	a    b c d	a    b c d e f g	
	[(CF <sub>3</sub> ) <sub>2</sub> C=CHCF <sub>2</sub> ] <sub>2</sub>	(CF <sub>3</sub> ) <sub>2</sub> C=CFCF <sub>2</sub> CF <sub>2</sub> CFHCF(CF <sub>3</sub> ) <sub>2</sub>	
	(35)	(170)	
11.	<u>6H-nonadecafluoro-2,7-dimethyloct-2-ene</u> (170)		
<sup>19</sup> F Spectrum:			
58.3	M	3	a-CF <sub>3</sub> (z)
61.3	D(J=32) of Q(J=12)	3	a-CF <sub>3</sub> (E)
74.3	M	3 )	g-CF <sub>3</sub>
77.3	M	3 )	
96.0	M	1	b-CF
115.3	M	2	c-CF <sub>2</sub>
122.6	AB (J = 248)	2	d-CF <sub>2</sub>
187.3	M	1	f-CF
211.1	M	1	e-CF
<sup>1</sup> H Spectrum:			
5.5	D (J = 46)		e-CH





Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------




18. 2H-2-phenoxy-3-hydrohexafluoro-3-methylbutane (90)

$^{19}\text{F}$  Spectrum:

62.4	M	3 )	a-CF <sub>3</sub>
67.6	M	3 )	
76.2	M	3	d-CF <sub>3</sub>

$^1\text{H}$  Spectrum:

3.3	Sept (J = 8)	1	b-CH
4.9	Q (J = 7)	1	c-CH
7.0	M	5	ring-H

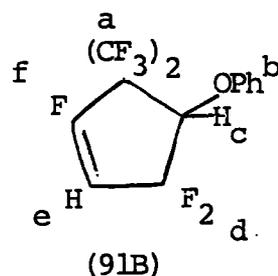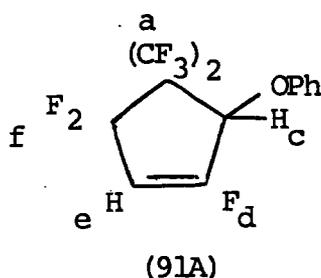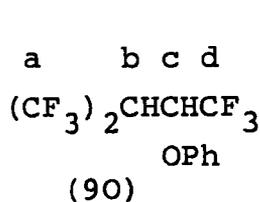

19 and 20. Mixture (50:50) of 1H,3H-3-phenoxy-4,4-dimethylcyclopentene (91A) and 1H,4H-4-phenoxy-3,3-dimethylcyclopentene (91B)

$^{19}\text{F}$  Spectrum:

62.7	M	3 )	a-CF <sub>3</sub>
63.7	M	3 )	
67.6	M	6 )	
115 to 120	M	3	d, f-CF

$^1\text{H}$  Spectrum

3.0 to 3.5	M	1	c-CH
5.7	M	1	e-CH
7.0 to 7.7	M	5	ring-H

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------

21. 1-(2H-hexafluoro-2-propyl)-3H-decafluoro-2,2-dimethyl-cyclopentene (79)

$^{19}\text{F}$  Spectrum:

63.0 to 64.6	M	6	a-CF <sub>3</sub>
68.6	D	6	c-CF <sub>3</sub>
111.6	Sept (J = 16)	1	d-CF
112.0	AB (J = 265)	2	e-CF <sub>2</sub>
212.0	D (J = 48)	1	f-CF

$^1\text{H}$  Spectrum:

3.9	Sept (J = 7)	1	b-CH
5.5	D(J=4) of D(J=12) of D(J=48)	1	f-CH



22. 1-(Pentafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethyl-cyclopentene (145)

$^{19}\text{F}$  Spectrum:

6.0	M	3	b-CF <sub>3</sub>
66.7 and 71.0	M	6	a-CF <sub>3</sub>
68.3	M	2	c-CF <sub>2</sub>
113.2	AB (J = 261)	2	e-CF <sub>2</sub>
117.2	T (J = 14)	1	d-CF
211.6	M	1	f-CF

$^1\text{H}$  Spectrum:

5.0	D(J=5) of D(J=12) of D(J=48)	1	f-CH
-----	------------------------------	---	------

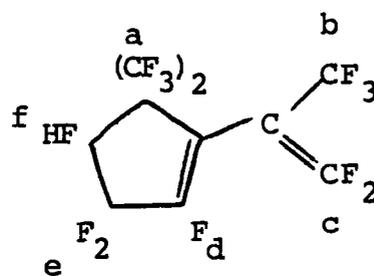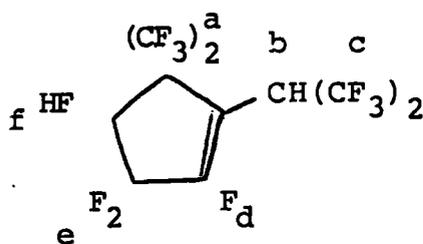

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------

23. 1-(2-Methoxytetrafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (146)

<sup>19</sup>F Spectrum:

57.8	M	3	b-CF <sub>3</sub>
65.3 and 70.0	M	6	a-CF <sub>3</sub>
71.0	D (J = 12.5)	1	d-CF
111.9	AB (J = 261)	2	f-CF <sub>2</sub>
119.8	D (J = 12.5)	1	e-CF
210.9	M	1	g-CF

<sup>1</sup>H Spectrum:

3.8	S	3	c-OCH <sub>3</sub>
5.4	D(J=48) of D(J=15)	1	g-CH

24. 1H-2,4-bis(trifluoromethyl)-4Htetrafluorocyclopentene(109)

<sup>19</sup>F Spectrum:



67.0	M	3 )	a, e-CF <sub>3</sub>
67.5	M	3 )	
100.0	AB (J = 260)	2 )	c, g-CF <sub>2</sub>
100.5	AB (J = 282)	2 )	

<sup>1</sup>H Spectrum:

3.2	T (J = 8) of Q (J = 4)	1	b-CH
6.4	M	1	f-CH

<sup>13</sup>C Spectrum:

57.1	M	1	b-C
120.6 and 120.7	T(J = 257)	2	c, g-CF <sub>2</sub>
122.1	Q(J = 250)	1 )	a, e-CF <sub>3</sub>
125.0	Q(J = 279)	1 )	
137.4	T(J = 31)	1	f-CH
138.0	M	1	d-C

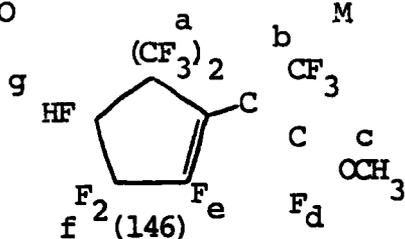

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------

25. 1H-2-trifluoromethyl-3H,3-pentafluoroethyltetrafluorocyclopentene (111)

$^{19}\text{F}$  Spectrum:




69.0	D (J = 20)	3	h-CF <sub>3</sub>
85.0	D (J = 20)	3	b-CF <sub>3</sub>
115.0	AB (J = 245)	2	d-CF <sub>2</sub>
115.6	M	2	a-CF <sub>2</sub>
117.0	AB (J = 273)	2	e-CF <sub>2</sub>

$^1\text{H}$  Spectrum:

3.8	T (J = 20)	1	c-CH
6.6	M	1	f-CH

$^{13}\text{C}$  Spectrum:

51.7	M	1	c-C
114.0	M	) 3	c,d,e-CF <sub>2</sub>
122.0	M	)	
119.5	Q (J = 272)	1	b,h-CF <sub>3</sub>
120.6	Q (J = 280)	1	
134.4	T (J = 17)	1	f-CH
138.1	Q (J = 39)	1	g-C

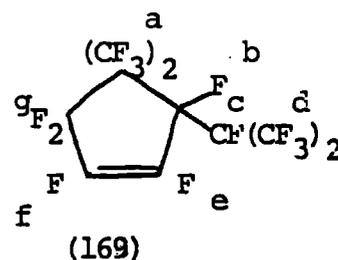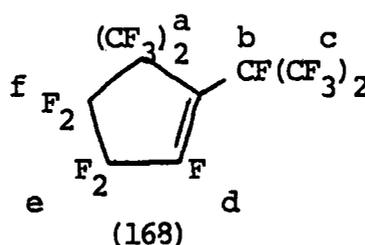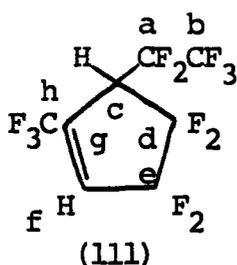

26. Perfluoro-2-(prop-2-yl)-3,3-dimethylcyclopentene (168)

$^{19}\text{F}$  Spectrum:

65.7	M	6	a-CF <sub>3</sub>
75.7	D(J = 24) of Q(J = 5)	6	c-CF <sub>3</sub>
107.3	M	1	d-CF
122.3	M	2	f-CF <sub>2</sub>
181.3	M	1	b-CF

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------

27. Perfluoro-3-(prop-2-yl)-4,4-dimethylcyclopentene (169)

$^{19}\text{F}$  Spectrum:

74.6	M	6	a-CF <sub>3</sub>
75.0 and 77.8	M	6	d-CF <sub>3</sub>
118.6	M	2	g-CF <sub>2</sub>
123.3	M	2	3,f-CF
188.3	M	1	c-CF

28. 4,5,5-Tris(trifluoromethyl)-4,5-dihydro-3H-pyrazole (154)

$^{19}\text{F}$  Spectrum:

60.7	M	3	b-CF <sub>3</sub>
71.9 and 72.9	M	6	a-CF <sub>3</sub>

$^1\text{H}$  Spectrum:

4.8	AB (J = 20)	1	b-CH
5.0	M	1	b-CH


29. 4,5,5-Tris(trifluoromethyl)-4,5-dihydro-1H-pyrazole (155)

$^{19}\text{F}$  Spectrum:


60.7	M	3	b-CF <sub>3</sub>
71.9 and 72.9	M	6	a-CF <sub>3</sub>

$^1\text{H}$  Spectrum:


5.0	M	1	b-CH
6.6	M	1	c-CH
7.8	M	1	d-NH

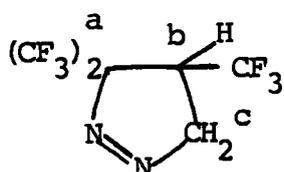

(154)

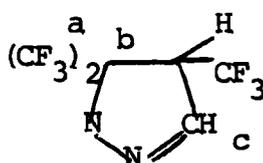

(155)

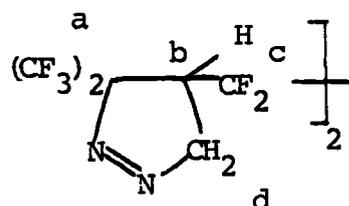

(153)

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------

30. 1,2-Di(5,5-bis(trifluoromethyl)-4,5-dihydro-3H-4-pyrazolo)tetrafluoroethane (153)

<sup>19</sup>F Spectrum:

65.0	M	)	a-CF <sub>3</sub>
69.0	M	)	
109.7	AB (J = 280)	4	c-CF <sub>2</sub>

<sup>1</sup>H Spectrum:

3.2	D(J=9) of D(J=9) of D(J=9)	2	b-CH
4.4 to 5.3	AB (J = 18) of D(J = 9)	4	d-CH <sub>2</sub>


31. 4,5,5-Tris(trifluoromethyl)-4-fluoro-4,5-dihydro-1H-pyrazole (164)

<sup>19</sup>F Spectrum:

68.3 to 71.0	M	6	a-CF <sub>3</sub>
75.2	D (J=14) of D(J = 14)	3	c-CF <sub>3</sub>
163.7	M	1	b-CF

<sup>1</sup>H Spectrum:

6.8	br	1	d-CH
7.5	br	1	e-NH

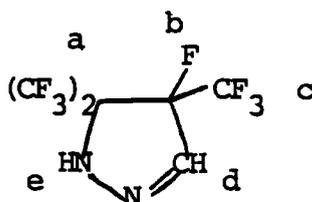

(164)

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------

32. Stable Carbocation (127) (Soln. in  $\text{SbF}_5$ )

$^{19}\text{F}$  Spectrum:

-68.1	)	2	d, f-CF
61.4	)	3	h-CF <sub>3</sub>
76.9	)	6	a-CF <sub>3</sub>
180.9	)	1	b-CF

$^1\text{H}$  Spectrum:

4.5 to 5.0	)	4	c, g-CH <sub>2</sub>
8.2	)	1	e-CH


33. Stable Carbocation (128) (Soln. in  $\text{SbF}_5$ )

$^{19}\text{F}$  Spectrum:


-7.0 to 0.0	)	3	d, f, h-CF
62.4	)	3	-CF <sub>3</sub>
76.9	)	6	a-CF <sub>3</sub>
181.0	)	1	b-CF

$^1\text{H}$  Spectrum:


4.0 to 4.5	)	4	c, i-CH <sub>2</sub>
6.5 to 7.0	)	2	e, g-CH



(127)



(128)

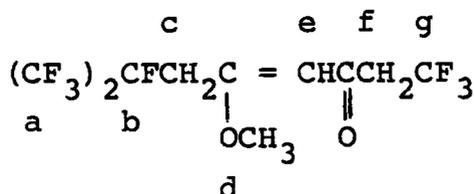

(129)

Shift (p.p.m.)	Fine Structure Coupling Constants (Hz)	Relative Intensity	Assignment
-------------------	---	-----------------------	------------

34. 3,3,5,7,7-Pentahydro-4-methoxydecafluoro-2-methyloct-4-enone (129)

$^{19}\text{F}$  Spectrum:

65.0	T (J = 10.6)	3	g-CF <sub>3</sub>
78.5	D (J = 7.0)	6	a-CF <sub>3</sub>
182.5	M	1	b-CF

$^1\text{H}$  Spectrum:

3.2	Q (J = 10.6)	2	f-CH <sub>2</sub>
3.6	S	3	d-OCH <sub>3</sub>
3.7	D (J = 22.0)	2	c-CH <sub>2</sub>
5.6	S	1	e-CH

35. 2,7-Dimethyl-3,6-bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluorooxepane (149)

$^{19}\text{F}$  Spectrum:

60.7	M	) 12	b-CF <sub>3</sub>
63.7 to 67.3	M		
120.5	S	2	) a-CF <sub>2</sub>
123.1	AB (J = 242)	2	)

$^1\text{H}$  Spectrum:

1.3 to 1.7	S	6	d-CH <sub>3</sub>
1.6	M	2	b-CH
3.3	M	2	c-CH
3.9	Sept (J = 8)	2	e-CH


36. 3,6-Bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluoro-oxepane (150)

$^{19}\text{F}$  Spectrum:


60.0 to 60.8	M	12
112.4	AB (J = 271)	2
122.2	AB (J = 262)	2

$^1\text{H}$  Spectrum:


3.3 to 4.0	br M	-
------------	------	---

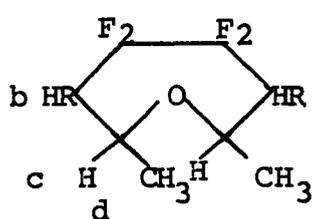

(149)

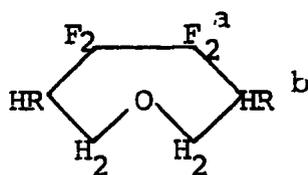

(150)

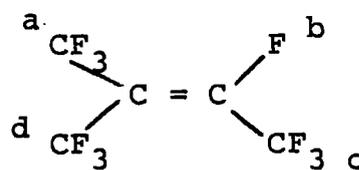

(161)

(R = -CH(CF<sub>3</sub>)<sub>2</sub>)












APPENDIX TWOInfra Red Spectra

1. 1-(2H-hexafluoro-2-propyl)-3H-decafluoro-2,2-dimethylcyclopentene (79)
2. 1-(Pentafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (145)
3. 1-(2-Methoxytetrafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (146)
4. Perfluoro-2-(prop-2-yl)-3,3-dimethylcyclopentene (168)
5. Perfluoro-3-(prop-2-yl)-4,4-dimethylcyclopentene (169)
6. 1H-2-trifluoromethyl-3H,3-pentafluoroethyltetrafluorocyclopentene (111)
7. 1H-2,4-bis(trifluoromethyl)-4H-tetrafluorocyclopentene (109)
8. 1H,3H,3-phenoxyonafluoro-4,4-dimethylcyclopentene (91A) and 1H,4H,4-phenoxyonafluoro-3,3-dimethylcyclopentene (91B) (Mixture)
9. 2H,2-phenoxy-3H-hexafluoro-3-methylbutane (90)
10. 2H-3-methoxydecafluoro-2-methylbutane (163) and 2-Methoxyonafluoro-3-methylbut-2-ene (162 (Mixture))
11. 2,3,5,5-Tetrahydrodecafluoro-2-methylhex-3-ene (157)
12. 3H,6H,6H-heptadecafluoro-7-methyloct-2-ene (80)
13. 2H,2H,4H-undecafluoro-5-methylhex-4-ene (71)
14. 2H-terdecafluoro-5-methylhex-4-ene (172)
15. 2,5-Bis(trifluoromethyl)-3H,7H,7H-undecafluorooct-2-ene (133)
16. 3H,6H-hexadecafluoro-2,7-dimethyloct-2,6-diene (75)
17. 3-Hydroxymethylhexadecafluoro-2,7-dimethyloct-6-ene (152)
18. 1-Iodo-2H,2H-nonadecafluorodecane (115)
19. 2H,2H-eicosafluorodecane (116)
20. 2H,2H-octafluorobutane (119)
21. 2,3,3,5,5-Pentahydroundecafluoro-2-methylhexane (156)
22. 2H,4H-tetradecafluoro-5-methylhexane (72)
23. 3H,6H-eicosafluoro-2,7-dimethyloctane (64)

24. 2,2-Bis-(4-[2H-hexafluorobut-2-enoxy]phenyl)hexafluoropropane (88)
25. 2,2-Bis(4-methoxyphenyl)hexafluoropropane (88A)
26. 2,2-Bis(4-[pentafluoropyridino]phenyl)hexafluoropropane (88B)
27. 4,5,5-Tris(trifluoromethyl)-4,5-dihydro-1H-pyrazole (155)
28. 4,5,5-Tris(trifluoromethyl)-4-fluoro-4,5-dihydro-1H-pyrazole (164)
29. 1,2-Di(5,5-bis(trifluoromethyl)-4,5-dihydro-3H,4-pyrazolo)-tetrafluoroethane (153)
30. 3,6-Bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluoro-oxepane (150)
31. 2,7-Dimethyl-3,6-bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluoro-oxepane (149)
32. 3,3,5,7,7-Pentahydro-4-methoxydecafluoro-2-methyloct-4-enone (129)


25 MICRONS 3.0 4.0 5.0 6.0 7.0 8.0 10 12 14 16 20 25 40

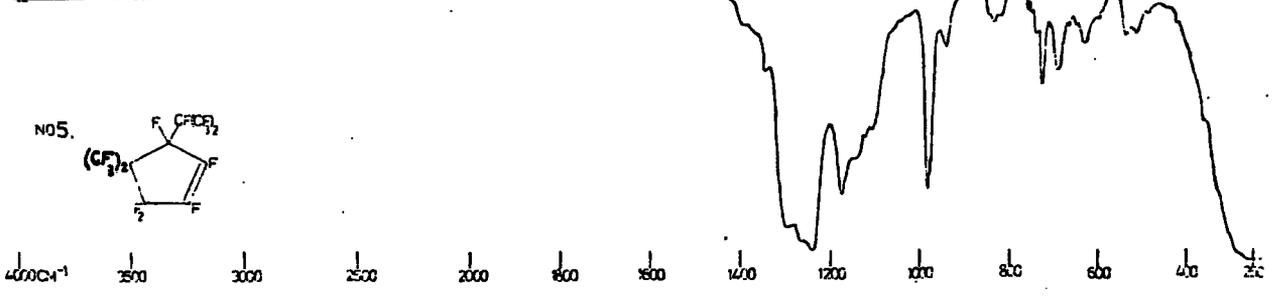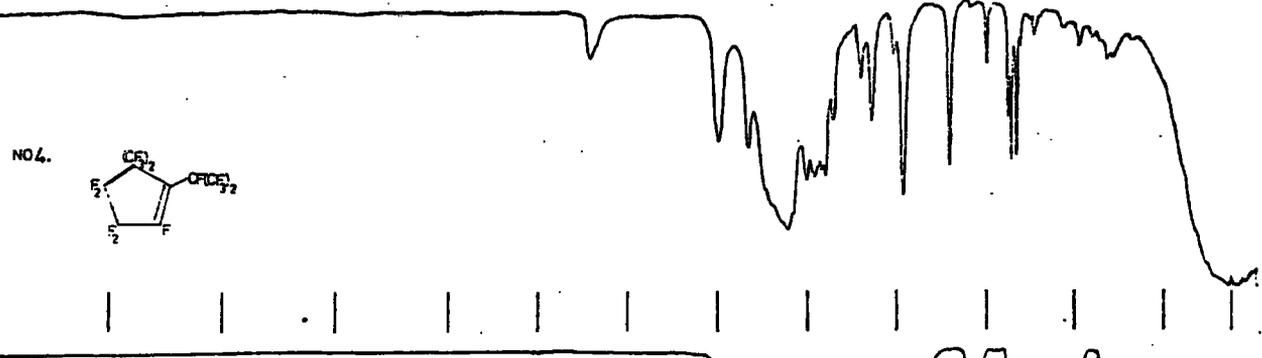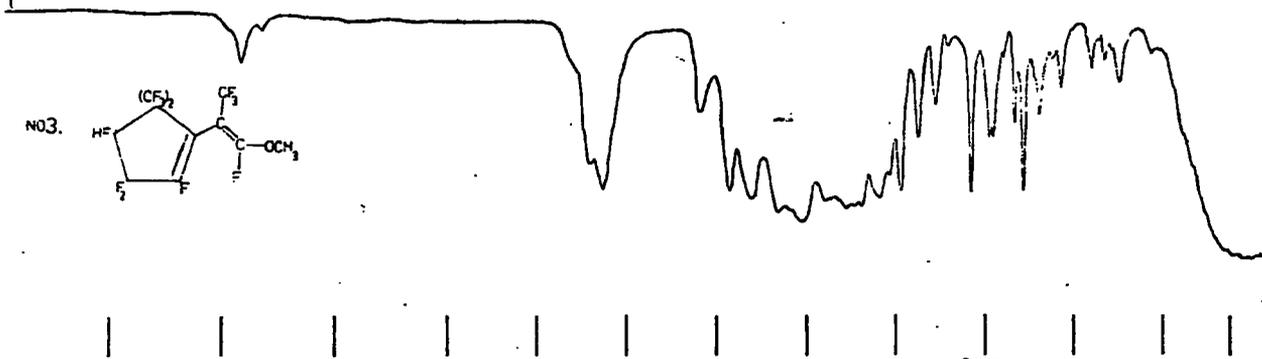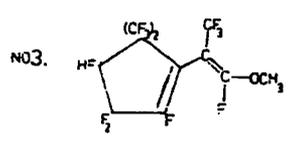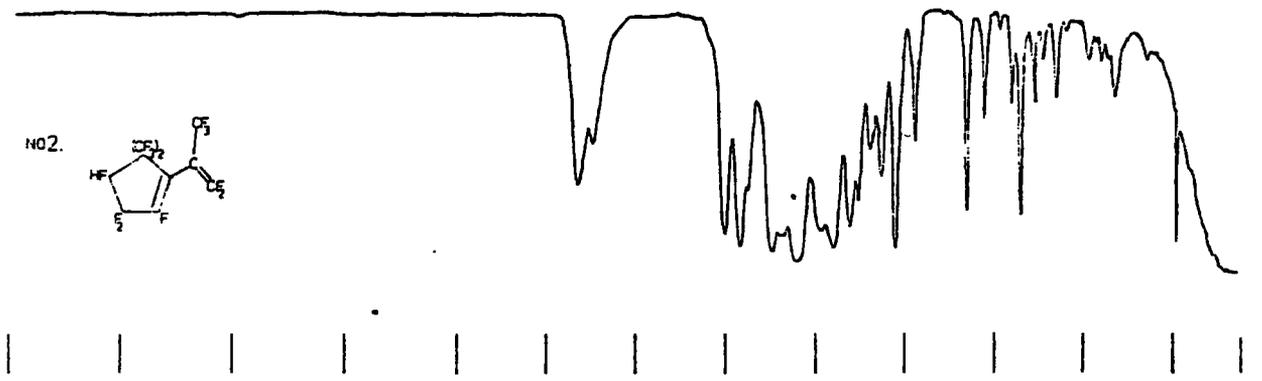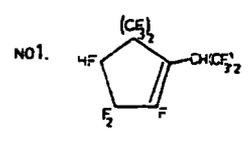



4000 CM⁻¹ 3500 3000 2500 2000 1600 1400 1200 1000 800 600 400 250

2.5 3.0 4.0 5.0 6.0 7.0 8.0 10 12 14 16 20 25 40  
MICRONS



NO 6.




NO 7.

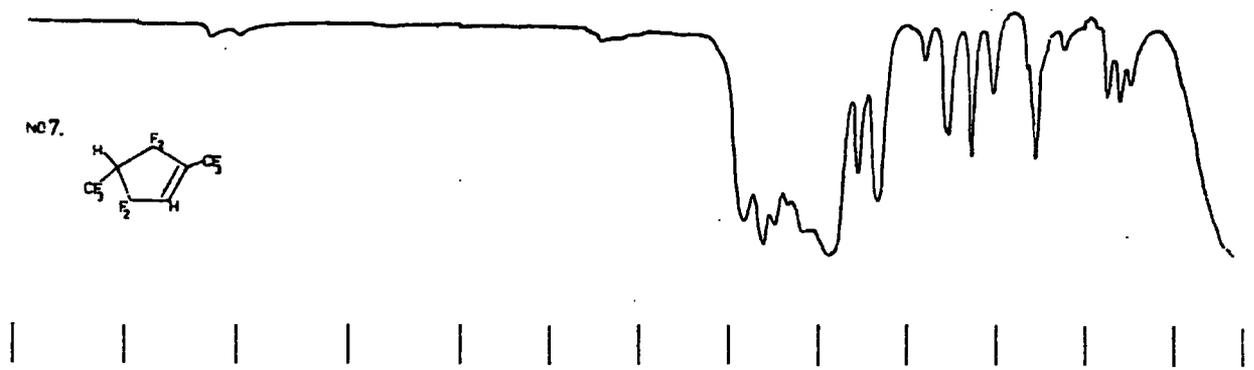


NO 8.

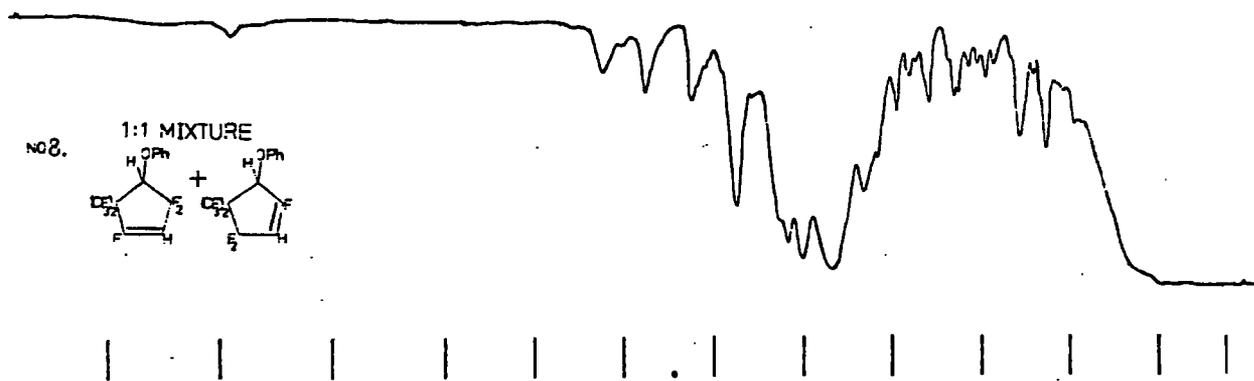


NO 9.

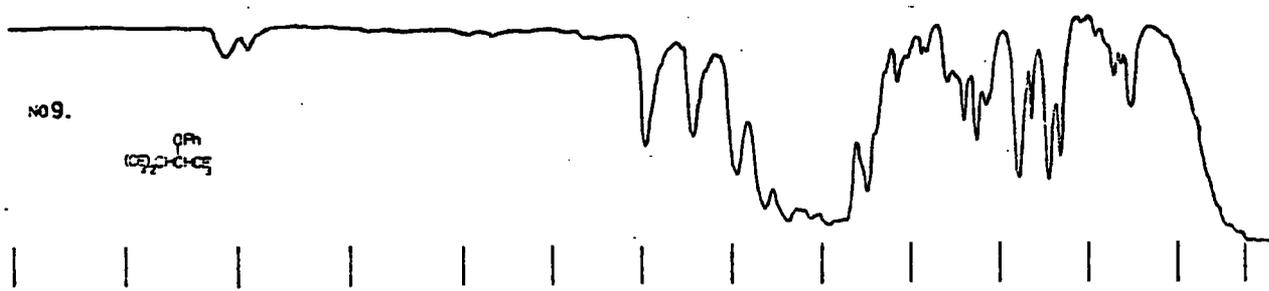


NO 10.




4000cm<sup>-1</sup> 3500 3000 2500 2000 1800 1600 1400 1200 1000 800 600 400 250

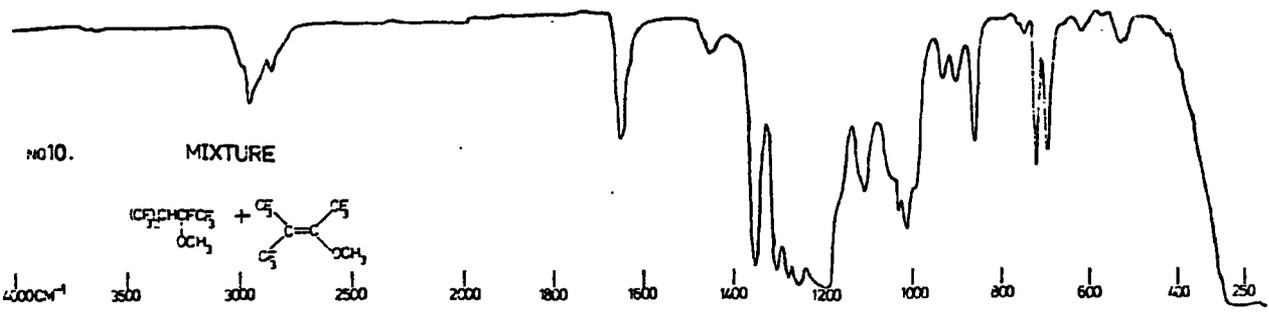

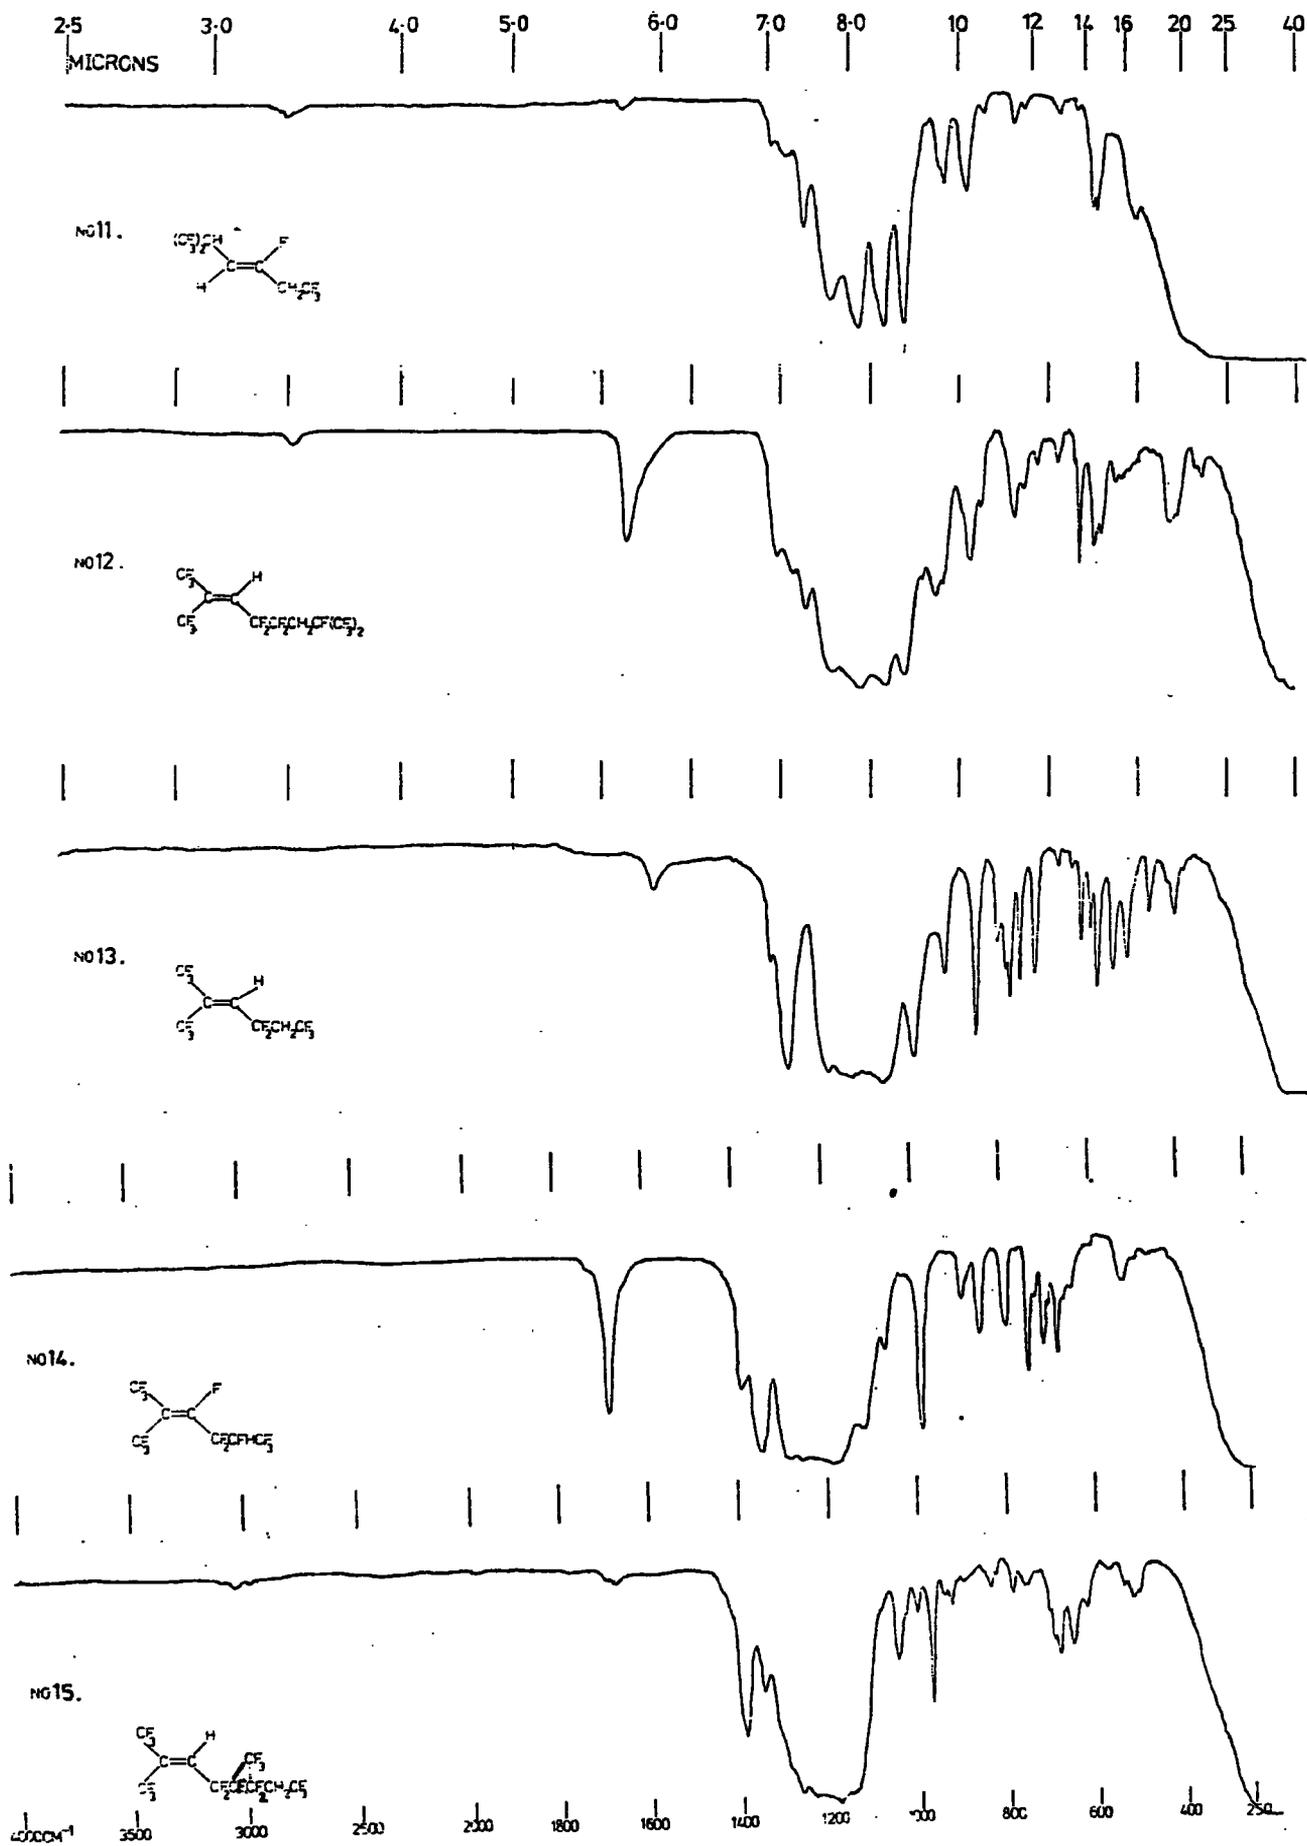





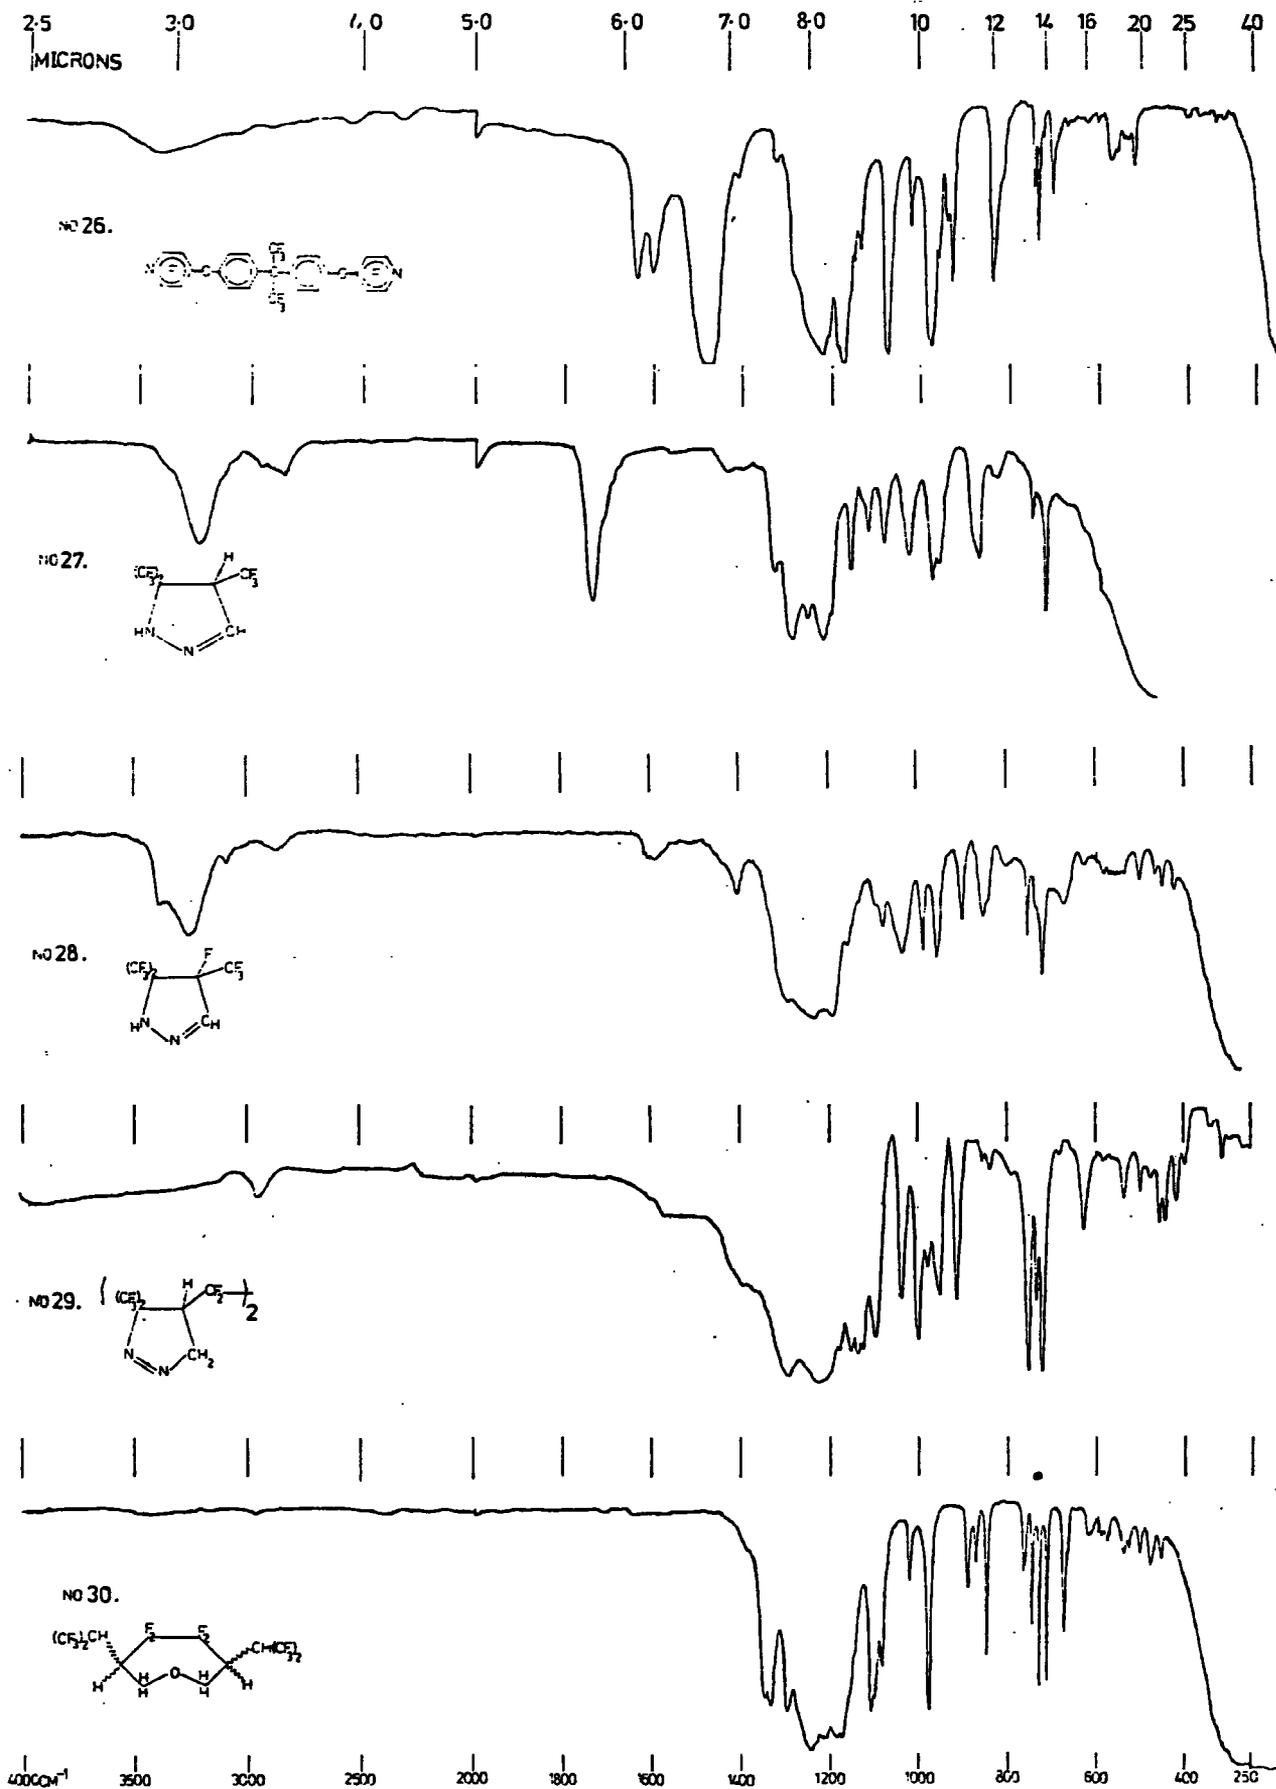



APPENDIX THREEMass Spectra

The following abbreviations are used in this appendix:


NEG - Negative Ion  $^{41}O$  ( $NH_3$  or  $^{13}C_4H_{10}$ )

EI - Electron Impact


CI - Chemical Ionization

1. EI/1-(2H-hexafluoro-2-propyl)-3H-decafluoro-2,2-dimethylcyclopentene (79)
2. EI/1-(Pentafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (145)
3. EI/1-(2-Bromohexafluoro-2-propyl)-3H-decafluoro-2,2-dimethylcyclopentene (148)
4. EI/1-(2-Methoxytetrafluoroprop-2-enyl)-3H-decafluoro-2,2-dimethylcyclopentene (146)
5. NEG/Perfluoro-2-(prop-2-yl)-3,3-dimethylcyclopentene (168)
6. NEG/Perfluoro-3-(prop-2-yl)-4,4-dimethylcyclopentene (169)
7. EI/1H-2-trifluoromethyl-3H,3-pentafluoroethyltetrafluorocyclopentene (111)
8. NEG/ (111)
9. EI/1H-2,4-bis(trifluoromethyl)-4H-tetrafluorocyclopentene (109)
10. CI/1H,3H,3-phenoxyonafluoro-4,4-dimethylcyclopentene(91A) and 1H,4H,4-phenoxyonafluoro-3,3-dimethylcyclopentene (91B) (Mixture)
11. EI/2H,2-phenoxy-3H-hexafluoro-3-methylbutane (90)
12. CI/2-Methoxynonafluoro-3-methylbut-2-ene (162)
13. CI/2H-3-methoxydecafluoro-2-methylbutane (163)
14. EI/2,3,5,5-Tetrahydrodecafluoro-2-methylhex-3-ene (157)
15. CI/3H,6H,6H-heptadecafluoro-7-methyloct-2-ene (80)
16. EI/2H,2H,4H-undecafluoro-5-methylhex-4-ene (71)
17. EI/2H-terdecafluoro-5-methylhex-4-ene (172)
18. EI/6H-nonadecafluoro-2,7-dimethyloct-2-ene (170)
19. EI/2,5-Bis(trifluoromethyl)-3H,7H,7H-undecafluorooct-2-ene(133)
20. EI/3H,6H-hexadecafluoro-2,7-dimethyloct-2,6-diene (75)
21. NEG/ (75)

22. CI/3-Hydroxymethylhexadecafluoro-2,7-dimethyloct-6-ene (152)
23. NEG/ (152)
24. EI/1-Iodo-2H,2H-nonadecafluorodecane (115)
25. EI/eH,2H-eicosafluorodecane (116)
26. EI/2,3,3,5,5-Pentahydroundecafluoro-2-methylhexane (156)
27. EI/2H,4H-tetradecafluoro-5-methylhexane (72)
28. NEG/3H,6H-eicosafluoro-2,7-dimethyloctane (64)
29. EI/2,2-Bis-(4-[2H-hexafluorobut-2-enoxy]phenyl)hexafluoropropane (88)
30. NEG/ (88)
31. EI/2,2-Bis-(4-methoxyphenyl)hexafluoropropane (88A)
32. EI/2,2-Bis-(4-[pentafluoropyridino]phenyl)hexafluoropropane (88B)
33. EI/4,5,5-Tris(trifluoromethyl)-4,5-dihydro-1H-pyrazole (155)
34. CI/4,5,5-Tris(trifluoromethyl)-4-fluoro-4,5-dihydro-1H-pyrazole (164)
35. NEG/ (164)
36. CI/1,2-Di(5,5-bis(trifluoromethyl)-4,5-dihydro-3H,4-pyrazolo)tetrafluoroethane (153)
37. NEG/ (153)
38. CI/3,6-Bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluoro-oxepane (150)
39. NEG/ (150)
40. CI/2,7-Dimethyl-3,6-bis(2H-hexafluoro-2-propyl)-4,4,5,5-tetrafluoro-oxepane (149)
41. NEG/ (149)
42. EI/3,3,5,7,7-Pentahydro-4-methoxydecafluoro-2-methyloct-4-enone (129)
43. CI/ (129)

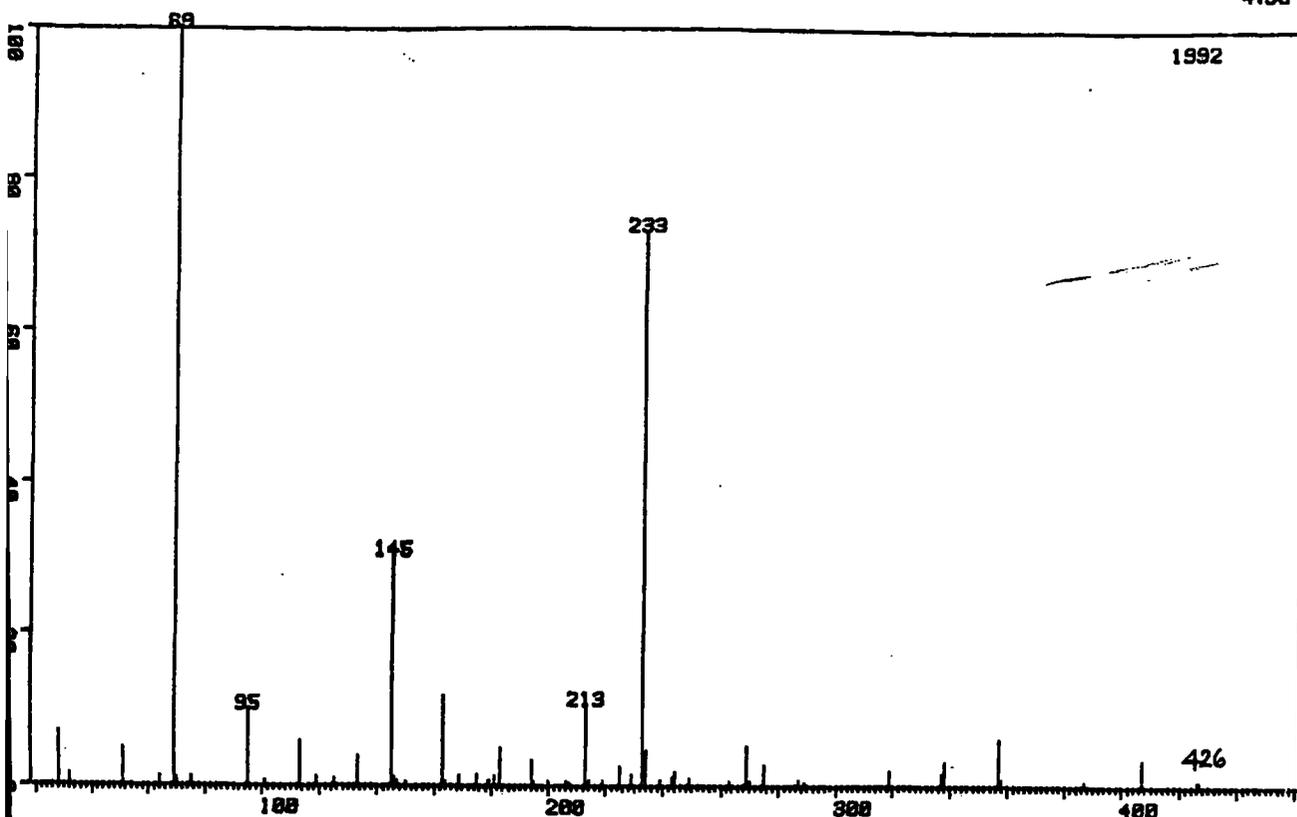
MJS271 28  
CAL: CALMS13-FEB-84  
4:56

PEAK NO.	MASS	ZHT. BASE	PEAK NO.	MASS	ZHT. BASE	PEAK NO.	MASS	ZHT. BASE
1	28.12	5.10	30	155.97	0.83*	59	242.89	0.44*
2	30.91	0.49	31	156.97	0.37	60	248.89	4.47*
3	32.00	0.88	32	162.96	2.44*	61	249.87	1.76*
4	43.11	0.59	33	167.96	0.61*	62	250.96	0.27
5	49.87	0.27	34	168.94	0.81*	63	255.00	0.39*
6	50.94	23.30	35	174.97	2.12*	64	256.97	0.27
7	52.03	0.42*	36	180.90	3.54*	65	266.83	1.10*
8	58.08	0.29	37	181.93	0.32	66	268.89	28.64*
9	68.95	100.00*	38	186.09	0.37*	67	269.86	4.03*
0	69.13	2.32*	39	186.91	2.42*	68	274.97	16.87*
1	69.86	1.90	40	187.94	0.42*	69	275.71	4.91*
2	75.04	0.68*	41	198.88	1.64*	70	287.03	4.62*
3	81.96	0.61*	42	199.90	3.49*	71	288.09	0.71
4	93.03	0.24	43	200.95	0.44*	72	293.02	0.24
5	95.02	0.78	44	204.93	1.12*	73	299.01	1.10*
6	100.94	0.39*	45	205.95	2.44	74	300.10	0.29*
7	106.04	0.46*	46	206.97	0.46*	75	307.07	0.76
8	112.01	0.22*	47	213.00	0.29	76	318.76	8.11*
9	113.00	7.89*	48	213.69	0.27*	77	319.72	4.18*
0	114.00	0.32*	49	217.94	1.95*	78	337.08	8.25*
1	118.94	2.34*	50	219.92	2.49*	79	338.08	19.02*
2	124.99	0.46	51	219.94	0.24	80	338.98	2.91
3	130.89	1.20*	52	223.93	0.39*	81	357.00	42.52*
4	131.97	0.34*	53	224.91	13.55*	82	358.06	4.42
5	136.98	1.44	54	225.94	0.95	83	387.03	1.78
6	142.95	0.42	55	230.92	1.03	84	387.93	0.27
7	144.98	0.32	56	231.95	0.27*	85	406.96	17.97*
8	149.91	1.15*	57	236.91	0.76*	86	407.89	2.71
			58	237.90	0.46*	87	424.08	5.01*

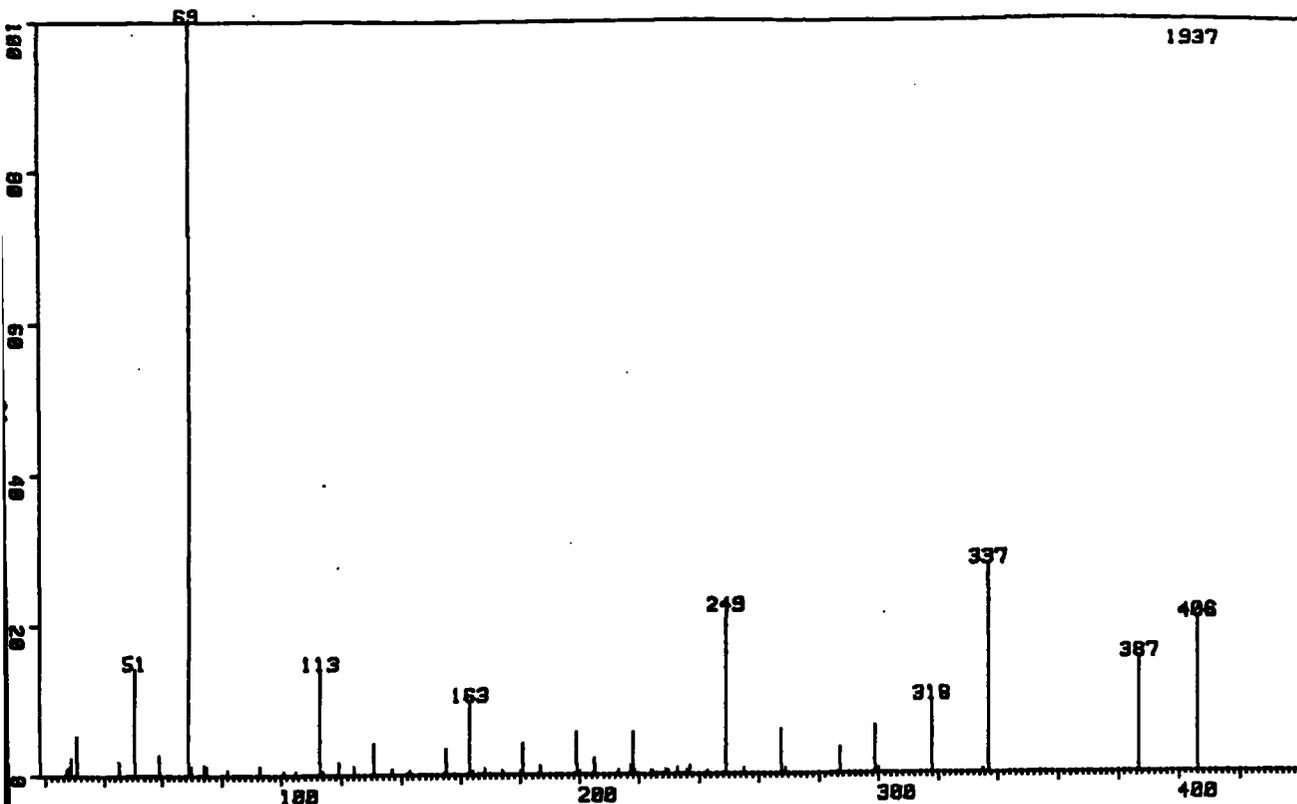MJS238 15  
CAL:CALM2525-SEP-84  
2:45


PEAK NO.	MASS	ZHT. BASE.	PEAK NO.	MASS	ZHT. BASE.
1	27.17	0.93	36	217.93	5.52
2	28.06	1.24	37	218.91	0.52
3	28.96	2.43	38	223.94	0.62
4	30.85	5.21	39	224.97	0.46
5	45.15	1.86	40	228.90	0.67
6	50.94	14.20	41	229.96	0.52
7	59.01	2.68	42	232.93	0.98
8	68.96	100.00	43	235.89	0.62
9	69.91	1.34	44	236.95	1.19
10	74.14	1.39	45	242.92	0.46
11	75.05	1.24	46	248.96	21.73
12	81.97	0.72	47	254.95	0.88
13	93.00	1.19	48	267.37	5.89
14	100.91	0.57	49	268.93	0.77
15	104.99	0.62	50	286.93	3.41
16	112.96	14.04	51	298.75	6.30
17	113.99	0.46	52	299.90	0.72
18	118.92	1.76	53	317.83	9.65
19	124.00	1.19	54	335.15	0.46
20	130.92	4.08	55	337.06	27.88
21	136.97	0.83	56	386.93	15.28
22	142.94	0.52	57	406.00	20.55
23	154.98	3.36			
24	162.97	9.65			
25	164.00	0.52			
26	167.96	0.83			
27	174.01	0.57			
28	179.93	0.57			
29	180.93	4.08			
30	186.97	1.19			
31	198.91	5.63			
32	199.96	0.52			

2

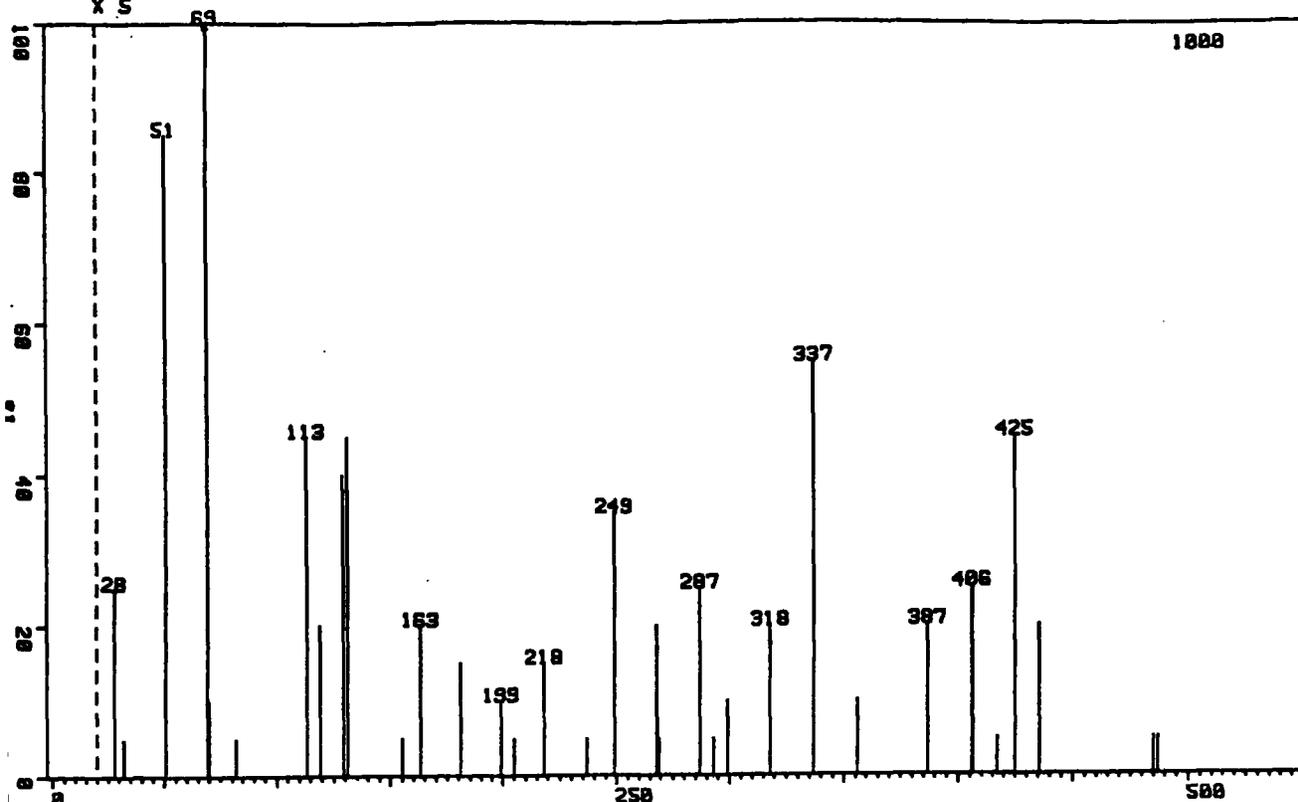MJS29 0  
CALILIB  
X 520-AUG-85  
8:8


3

MASS	%HT. BASE	MASS	%HT. BASE	MASS	%HT. BASE
44.10	0.85	175.08	0.34	297.02	0.32
45.15	0.37	178.98	0.51	298.06	0.51
49.87	0.24	181.01	3.37	299.05	2.03
50.94	16.78	182.04	0.32	300.04	0.32
68.98	100.00	186.07	0.27	303.00	0.37
69.47	0.22	187.07	0.95	305.04	0.63
69.91	1.61	193.06	0.29	306.06	0.34
75.06	0.76	199.02	2.30	317.87	3.59
78.88	0.29	200.01	0.39	325.13	0.37
80.84	0.56	205.06	1.20	337.11	10.70
82.01	0.95	206.09	0.29	339.04	0.39
85.05	0.27	213.05	0.39	342.97	0.27
93.05	0.66	217.07	0.81	346.94	0.76
95.11	0.37	219.05	2.98	348.95	0.88
99.97	0.37	219.02	0.66	352.94	0.37
101.02	0.49	224.05	0.66	356.02	1.83
105.07	0.24	225.08	0.71	366.02	0.27
110.93	0.66	229.05	0.63	367.00	0.39
113.06	9.21	231.03	0.42	368.03	0.32
114.10	0.29	236.03	0.42	375.07	0.37
119.01	3.69	237.06	1.15	385.04	0.51
124.07	0.61	243.08	0.68	387.03	3.98
128.95	8.47	248.97	7.16	396.93	0.56
130.95	8.99	250.00	0.83	398.94	0.66
132.06	0.44	255.06	0.56	405.88	5.30
137.08	0.51	267.58	4.32	416.74	1.20
143.09	0.42	269.01	1.39	419.05	0.32
145.09	0.34	275.06	0.83	425.17	9.13
149.09	0.22	281.00	0.27	436.05	3.76
155.08	1.34	286.91	4.66	485.02	0.88
163.07	4.40	288.07	0.49	486.94	0.90

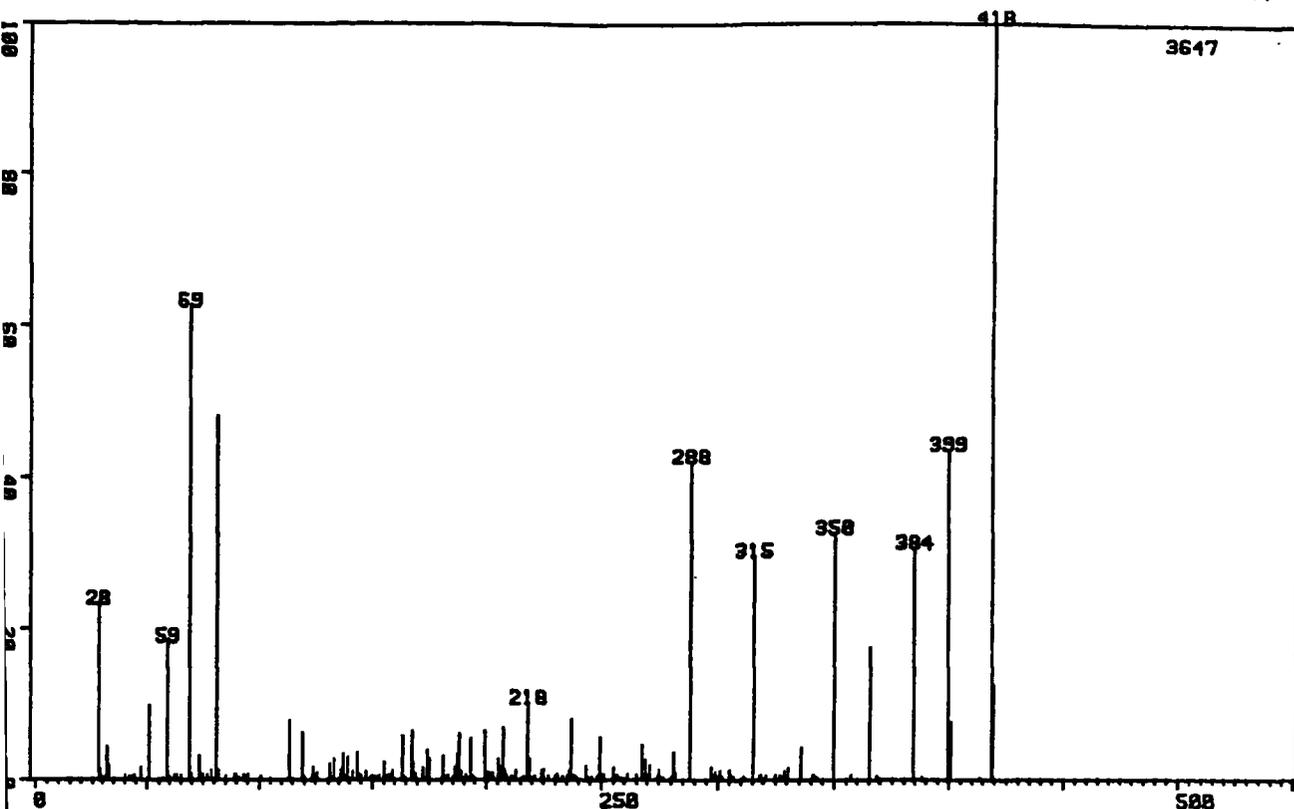MS210X 28  
CAL: CALM1721-SEP-84  
5:4


PEAK NO.	MASS	%HT. BASE	PEAK NO.	MASS	%HT. BASE
112	233.10	0.44	147	300.09	0.30
113	235.11	0.47	148	301.17	1.32
114	236.10	1.15	149	302.10	0.41
115	237.09	8.20	150	305.07	1.32
116	238.08	0.85	151	306.10	0.63
117	239.06	0.41	152	307.12	0.33
118	243.09	1.89	153	311.06	0.44
119	244.12	0.27	154	312.01	0.27
120	245.11	0.30	155	315.22	29.78
121	246.14	0.38	156	318.01	0.44
122	248.13	0.44	157	319.06	0.58
123	249.08	5.68	158	321.05	0.58
124	250.08	0.77	159	325.05	0.58
125	251.12	0.80	160	326.99	0.58
126	255.08	1.54	161	327.97	0.30
127	256.11	0.47	162	328.99	1.18
128	257.09	0.71	163	330.67	1.62
129	258.43	0.25	164	335.87	4.36
130	261.19	0.82	165	341.19	0.77
131	265.07	0.66	166	342.19	0.33
132	267.57	4.61	167	343.11	0.25
133	269.04	2.69	168	349.71	32.77
134	270.04	0.74	169	357.24	0.52
135	271.06	1.97	170	365.30	17.63
136	274.07	0.41	171	368.15	0.38
137	275.09	1.40	172	384.33	30.68
138	276.11	0.33	173	388.22	0.36
139	277.12	0.36	174	399.16	43.62
140	280.11	0.36	175	400.69	7.70
141	281.12	3.67	176	413.46	0.27
142	282.15	1.01	177	418.12	100.00
143	287.83	42.20	178	419.30	12.67

4

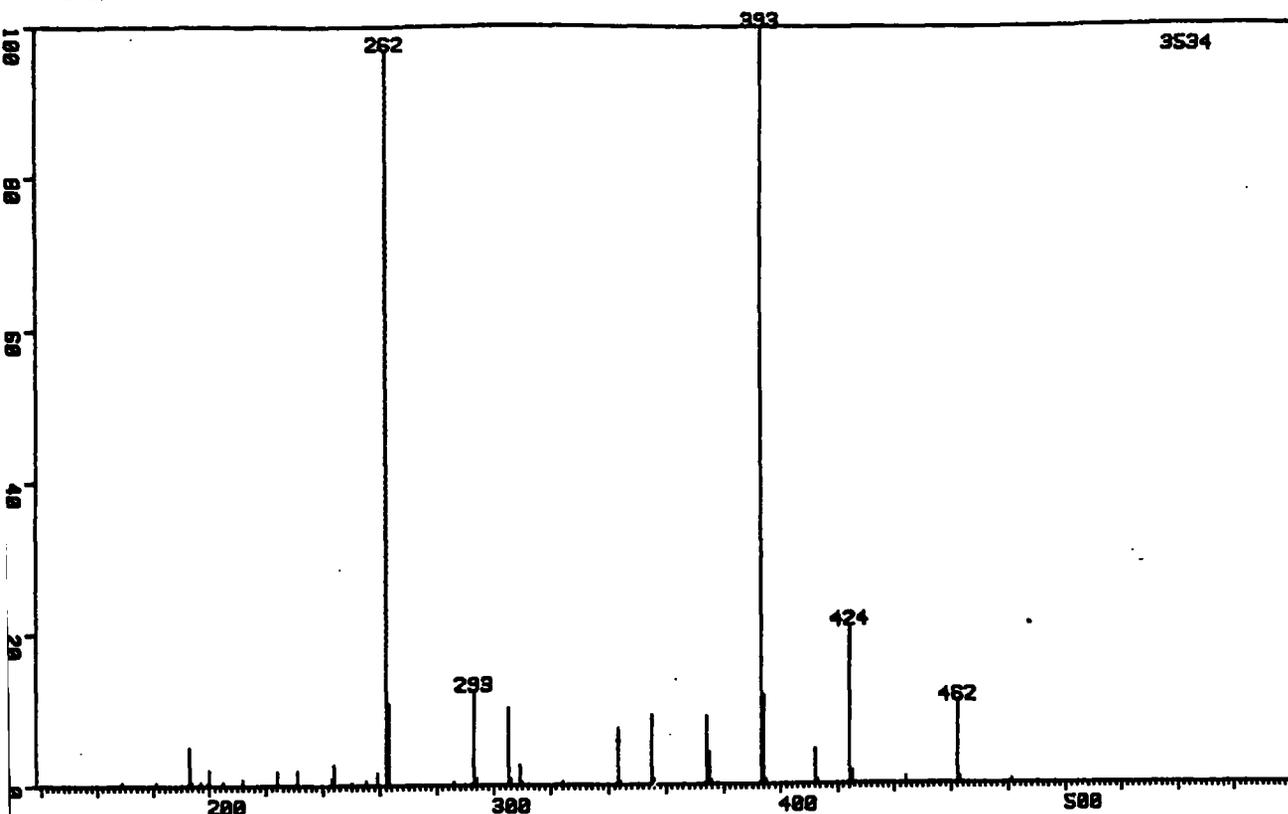MS992N 39  
CAL: CALN1624-MAY-85  
1:59

5

MASS	ZHT. BASE	MASS	ZHT. BASE
196.97	0.40	412.07	4.58
199.96	2.01	413.03	0.59
205.04	0.40	424.06	20.97
212.02	0.82	425.09	1.75
224.04	1.87	444.07	0.88
231.00	1.95	462.10	10.84
243.04	0.88	463.13	0.85
244.06	2.66		
250.05	0.31		
255.09	0.54		
259.01	1.61		
262.02	96.86		
263.05	10.72		
286.06	0.37		
293.05	12.37		
294.05	0.93		
305.04	10.13		
306.04	0.88		
309.03	2.57		
310.00	0.31		
324.09	0.37		
343.10	7.50		
344.10	0.42		
355.10	9.20		
356.07	0.76		
374.10	8.97		
375.06	4.24		
376.07	0.57		
393.04	100.00		
394.07	11.74		
395.06	0.65		

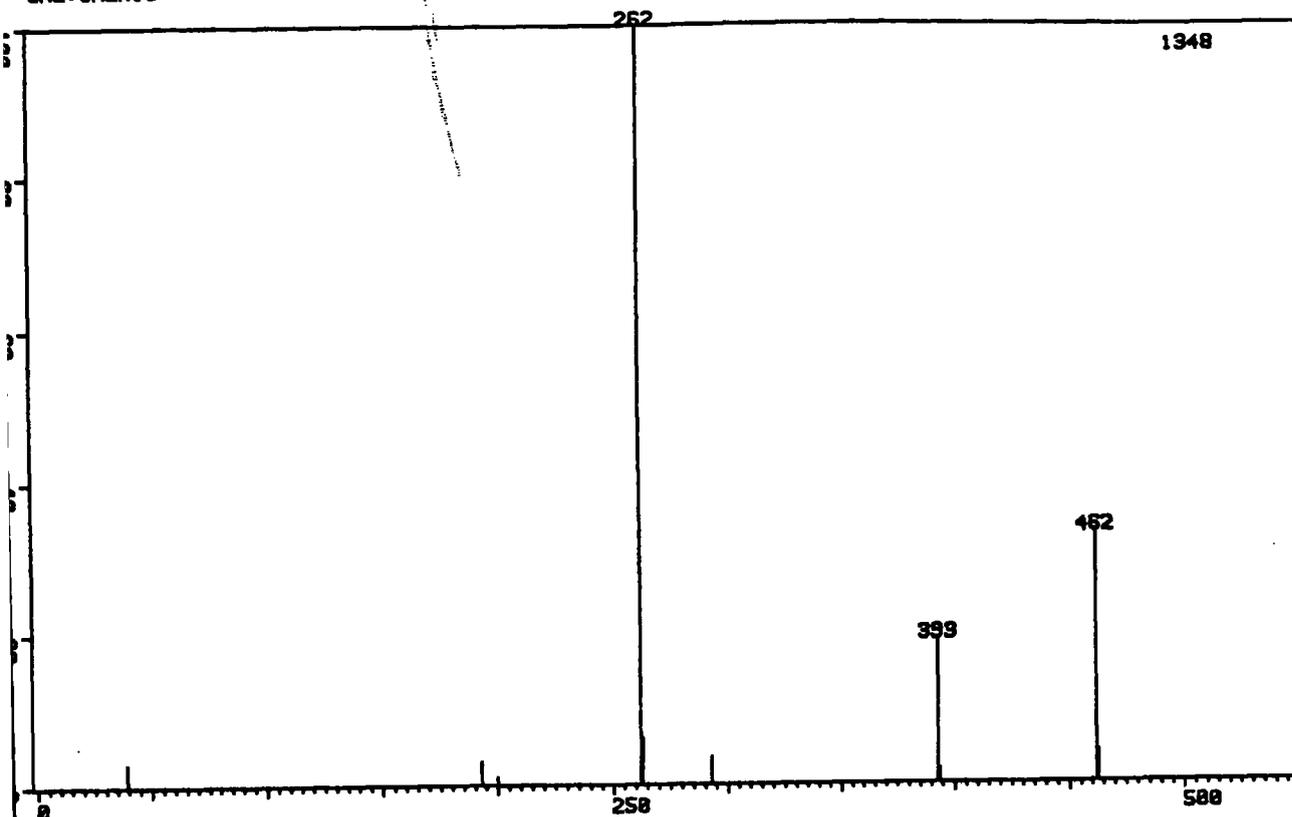
MS79NX 52  
CALICALN1602-JUL-85  
2:38

6

MASS	%HT. BASE
39.00	3.04
193.02	3.19
199.96	1.11
261.97	100.00
263.00	6.16
293.00	3.71
392.98	19.07
394.01	1.85
461.97	33.16
462.96	4.08

MS234X 4  
CAL: CALTS

21-SEP-84  
8:41

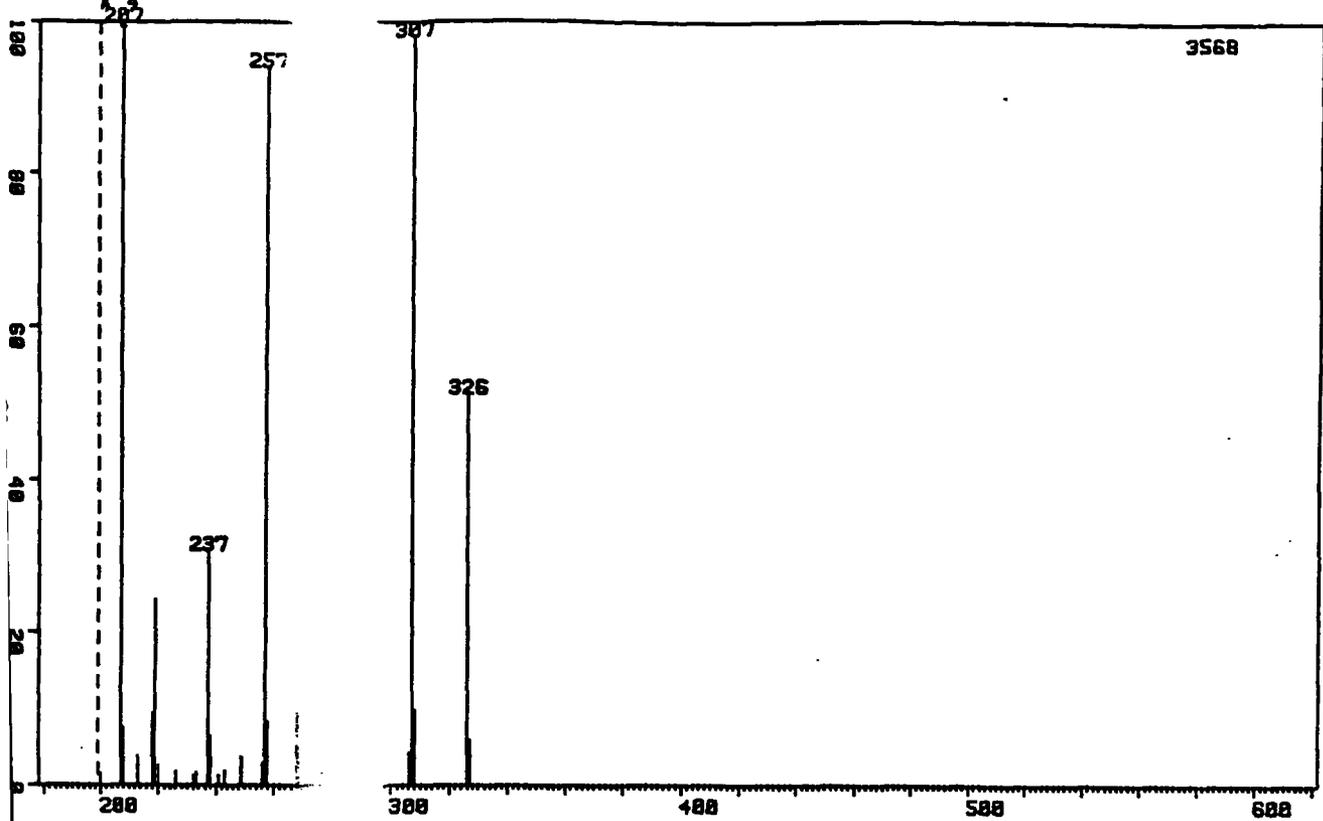


7

PEAK NO.	MASS	ZHT. BASE	PEAK NO.	MASS	ZHT. BASE
60	149.97	1.11	60	149.97	1.59
61	157.03	0.52	61	157.03	8.71
62	158.02	0.66	62	158.02	0.66
63	168.00	1.21	63	168.00	1.87
64	168.98	2.39	64	168.98	4.53
65	183.01	100.00	65	183.01	1.42
66	187.02	1.28	66	187.02	1.63
67	188.01	1.90	67	188.01	1.80
68	207.02	20.71	68	207.02	11.07
69	208.00	1.11	69	208.00	1.11
70	218.99	0.80	70	218.99	4.39
71	237.01	2.32	71	237.01	1.00
72	257.03	2.63	72	257.03	5.95
73	258.02	0.45	73	258.02	0.93
74	286.99	2.21	74	286.99	0.80
75	307.02	8.02	75	307.02	2.84
76	326.01	0.59	76	326.01	1.59
93	93.02	4.50			
94	94.04	1.45			
95	95.06	6.60			
98	98.97	5.19			
99	99.92	3.53			
06	06.04	1.28			
07	07.03	0.66			
13	13.02	10.13			
14	14.03	0.38			
17	17.02	1.42			
18	18.00	0.93			
18	18.97	18.64			
19	19.94	0.73			
24	24.02	1.24			

MJS234 6  
CAL: CALN18  
X 18

TR: 5

21-SEP-84  
8:58

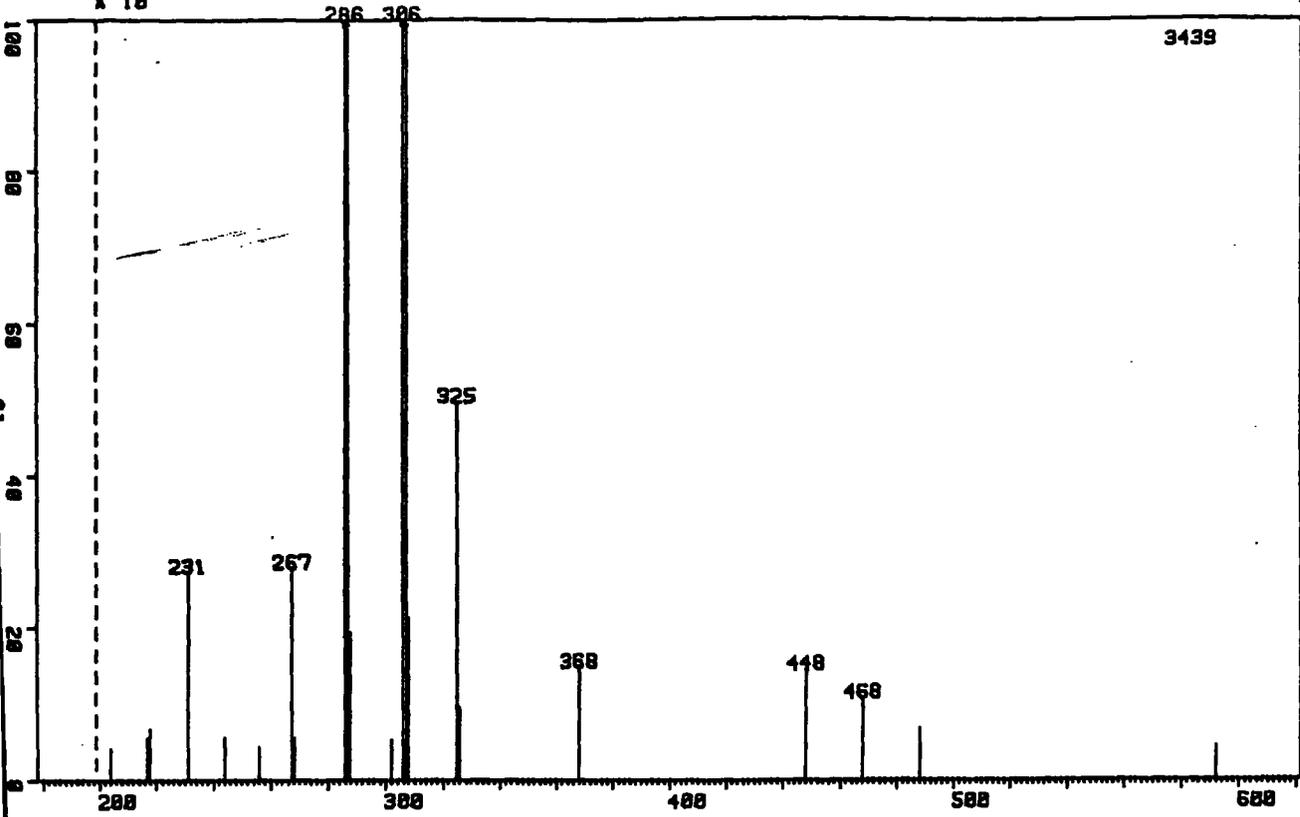


8

MASS	ZHT. BASE
167.09	0.73
184.06	0.85
187.05	0.56
188.02	0.50
193.01	100.00
194.01	8.43
203.94	0.50
216.97	0.68
217.95	0.41
231.10	2.85
244.09	0.56
267.47	3.14
268.63	0.41
286.09	97.91
287.09	36.97
288.09	2.09
306.05	97.30
307.09	46.87
308.07	2.29
317.06	0.35
325.09	4.91
326.11	0.56
333.09	0.62
368.06	1.82
448.11	1.38
468.19	1.18
488.07	0.79
592.08	0.56

MJS48 30  
CAL: CALM25

02-NOV-84  
4:27

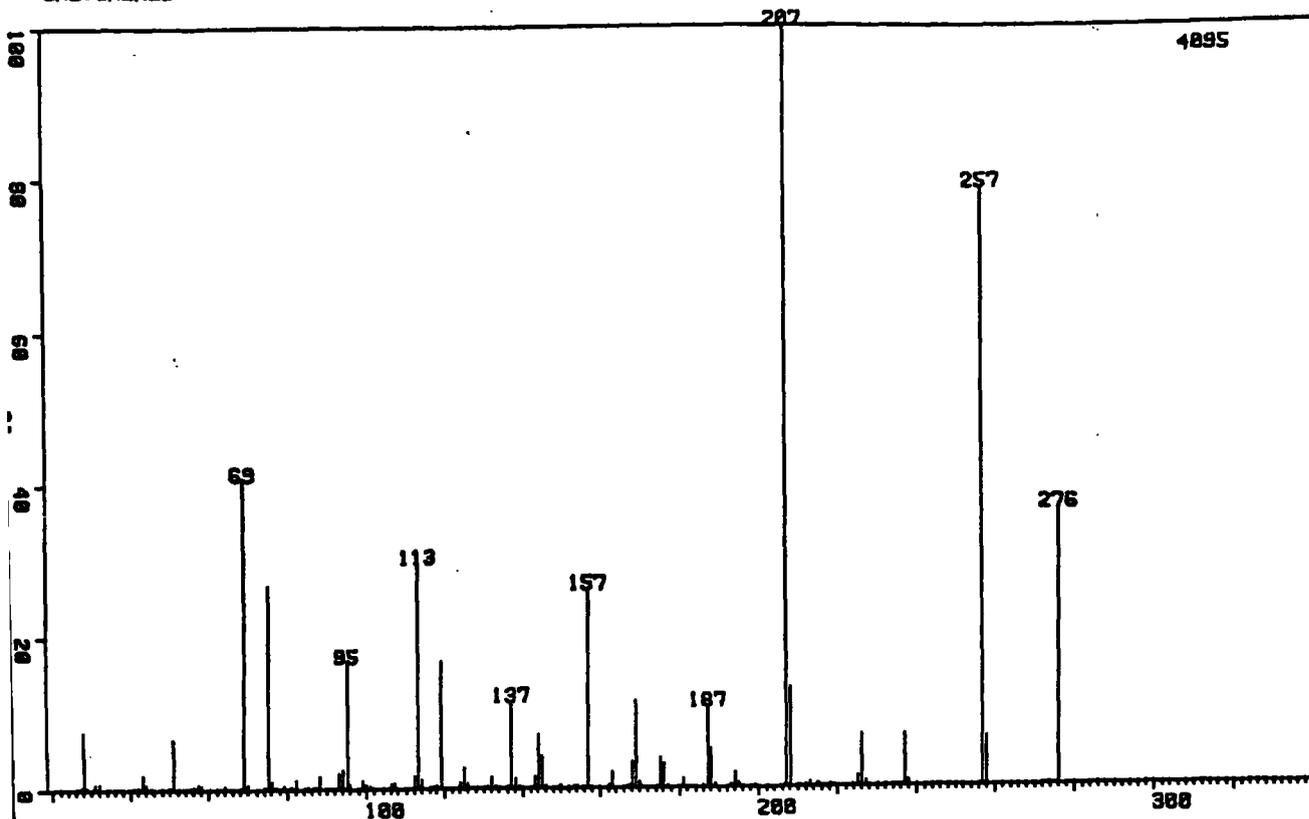


9

MASS	%HT. BASE	MASS	%HT. BASE	MASS	%HT. BASE
31.95	0.85	112.05	1.73	170.06	0.93
40.97	0.24	112.43	0.24	175.10	3.88
42.03	0.27	113.07	29.67	176.08	3.20
43.09	1.88	113.57	0.22	177.05	0.32
44.10	0.73	114.09	1.17	181.00	1.15
45.14	0.22	117.05	0.22	186.04	0.24
49.88	0.29	118.09	0.32	187.03	10.67
50.95	6.57	119.07	16.65	187.88	5.13
55.16	0.27	124.06	0.85	189.10	0.46
56.13	0.39	125.09	2.64	193.12	0.37
57.10	0.76	126.08	0.73	194.10	1.95
58.07	0.61	131.04	0.27	195.09	0.61
64.10	0.46	132.07	1.47	199.03	0.32
68.67	0.22	133.09	0.32	202.50	0.22
68.99	40.71	136.09	0.22	206.97	100.00
69.94	0.51	136.61	0.20	208.07	13.14
74.09	0.22	137.07	11.36	209.91	0.22
75.10	26.67	138.07	1.34	210.63	0.22
76.10	1.00	139.05	0.22	212.04	0.27
77.09	0.24	143.07	1.44	213.09	0.56
79.00	0.37	144.07	7.06	215.09	0.44
81.01	0.29	145.10	4.25	217.04	0.27
82.03	1.17	146.10	0.27	218.13	0.37
85.06	0.29	150.02	0.37	219.04	0.27
87.07	0.27	153.11	0.22	225.07	1.39
88.04	1.56	153.99	0.22	226.10	6.81
93.06	2.05	154.23	0.24	227.13	0.66
94.07	2.54	156.94	26.01	237.06	6.81
95.10	16.61	162.06	0.39	238.05	0.78
96.10	0.66	163.09	2.12	256.95	78.68
99.01	1.07	167.05	0.24	276.13	36.48


MS662C 139  
CAL: CAL T23  
X 4

24-MAY-85  
6:57

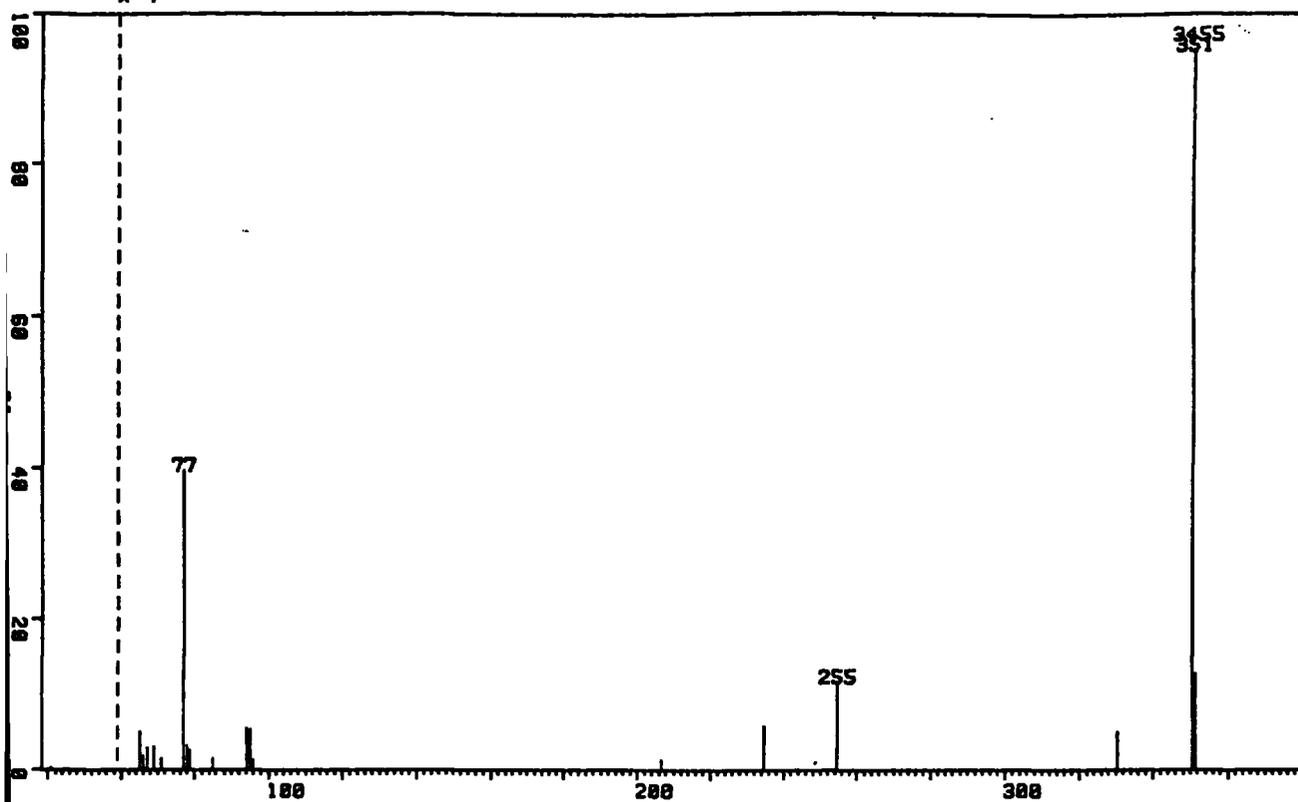

10


MASS	%HT. BASE
65.02	1.13
66.03	0.43
67.01	0.67
68.93	0.69
70.94	0.35
76.97	8.91
77.94	0.75
78.92	0.61
85.04	0.35
93.95	1.24
94.96	1.22
95.95	0.32
206.70	0.32
234.69	1.33
254.65	2.60
330.55	1.13
350.51	21.39
351.54	2.87

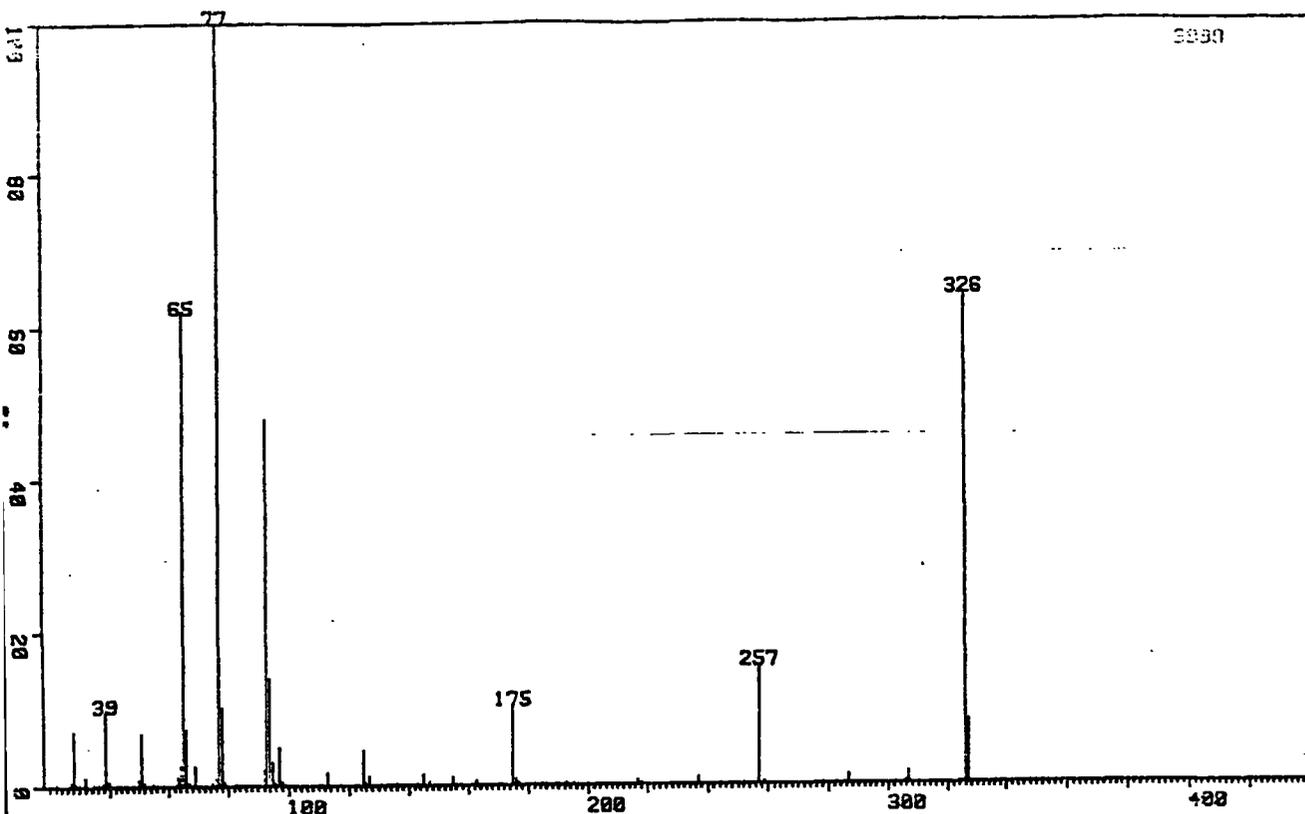26-JUN-85  
11:16MS106X 68  
CAL:CALM39

MASS	ZHT.	MASS	ZHT.
	BASE		BASE
28.13	7.18	122.92	0.23
28.99	0.28	124.96	4.55
32.01	1.20	125.95	0.43
38.08	0.38	126.96	1.28
39.00	9.60	135.96	0.23
39.89	0.60	142.93	0.28
49.89	1.05	144.93	1.45
50.96	6.93	146.94	0.48
52.04	0.48	154.93	1.13
55.11	0.30	162.84	0.48
63.06	1.25	170.80	0.25
64.10	2.65	174.91	10.38
65.09	61.79	175.92	0.93
66.08	7.40	176.90	0.23
67.08	0.38	192.84	0.28
68.93	2.63	216.85	0.65
75.05	0.58	236.85	0.98
76.07	1.08	256.96	15.43
77.05	100.00	258.81	0.33
77.46	0.25	286.80	1.15
77.61	0.23	305.81	0.33
77.69	0.23	306.83	1.58
78.03	10.35	325.79	64.07
78.98	0.50	326.99	8.28
83.03	0.28		
91.98	2.20		
92.99	47.94		
94.01	14.03		
95.01	3.13		
96.01	0.35		
97.00	5.05		

MJS34X 63  
CAL: CALT38  
X 8

30-SEP-85  
3:28

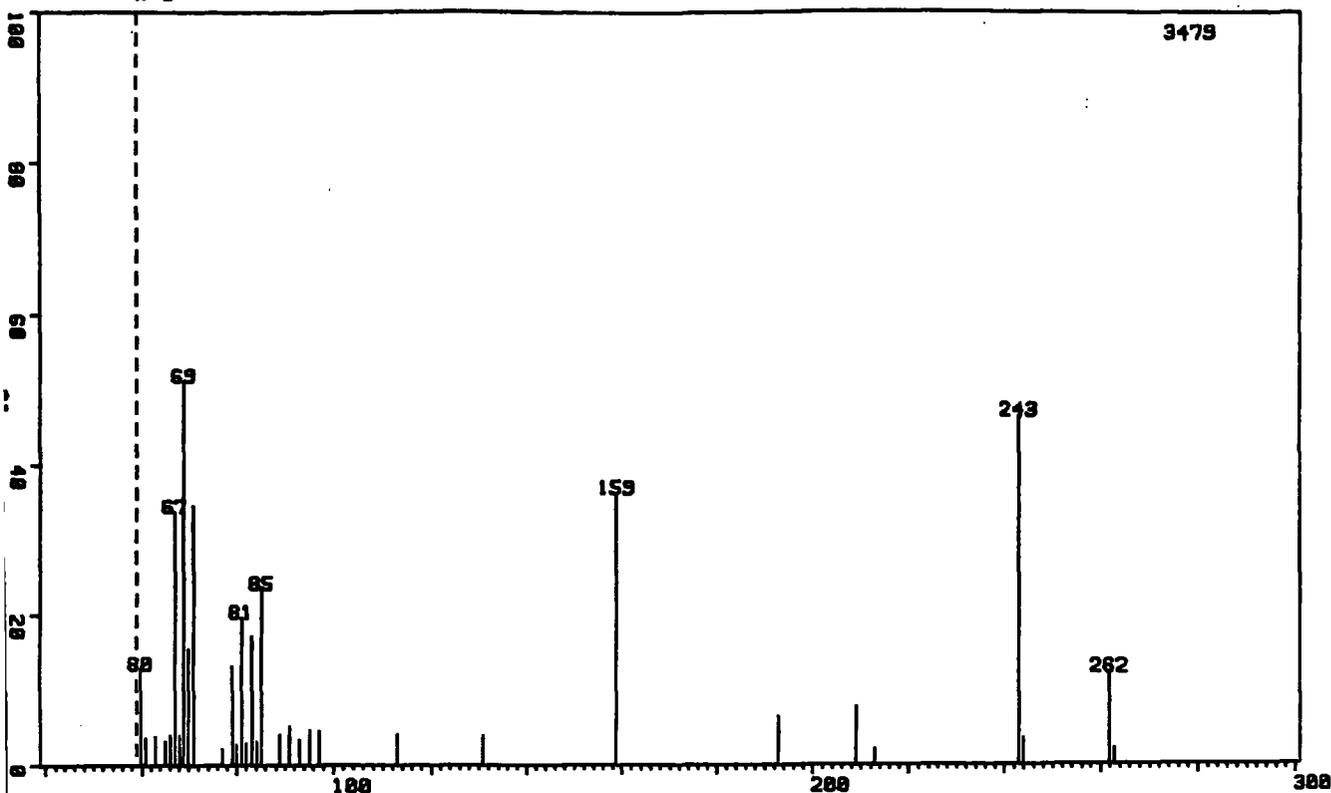


MASS	%HT. BASE
67.02	4.51
67.99	0.55
68.88	0.32
68.95	6.81
69.89	2.07
70.97	4.63
77.01	0.29
78.95	1.75
79.90	0.37
80.94	2.62
82.00	0.40
83.03	2.30
84.06	0.43
85.07	3.13
88.94	0.55
90.86	0.69
90.96	0.60
93.03	0.46
95.07	0.63
97.06	0.60
112.93	0.55
130.87	0.52
158.83	4.83
192.88	0.86
208.84	1.03
212.92	0.29
242.88	6.18
243.89	0.49
261.83	1.64
262.85	0.29

12

MJS34X 64  
CAL: CALT38  
X 8

30-SEP-85  
3:23

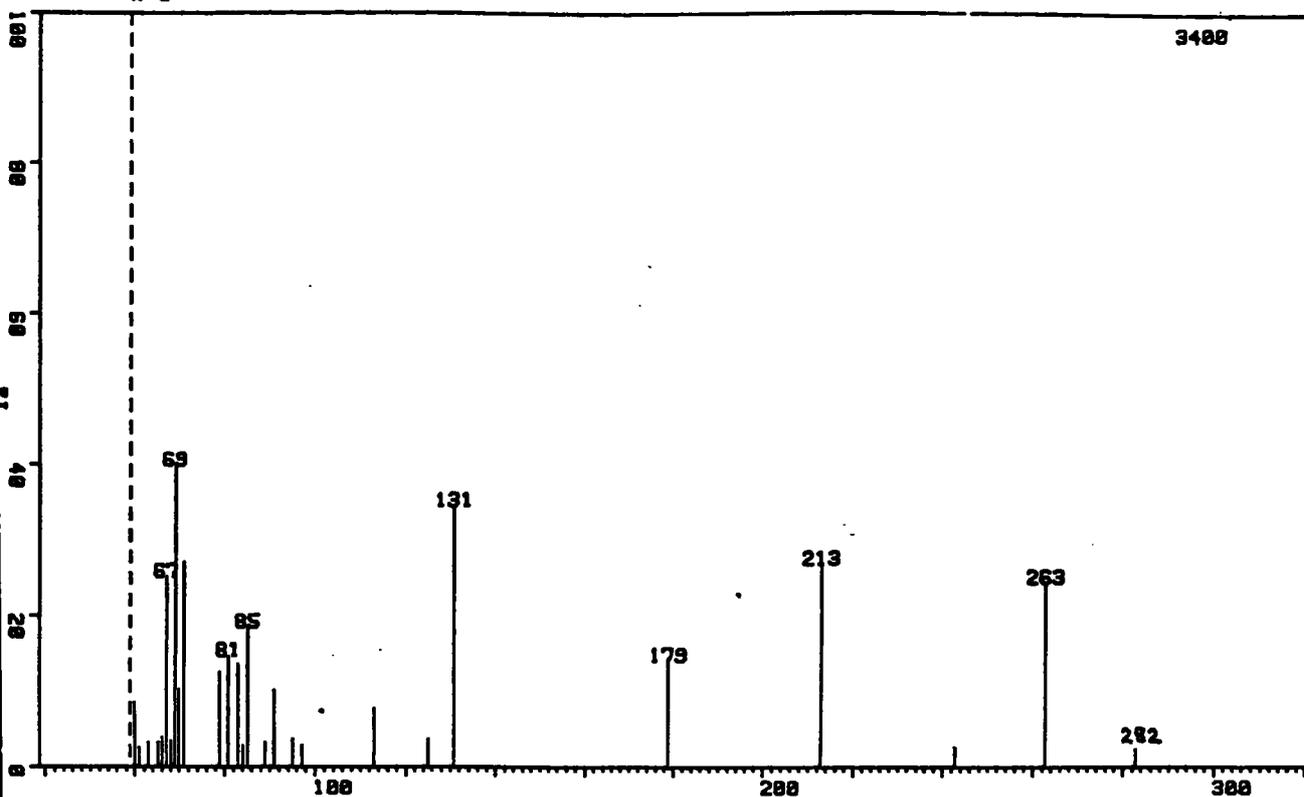


MASS	%HT. BASE
60.92	0.35
62.98	0.44
65.03	0.44
66.03	0.53
67.01	3.35
67.98	0.47
68.88	0.35
68.94	5.32
69.89	1.38
70.97	3.62
78.94	1.68
80.91	1.97
83.02	1.82
84.05	0.38
85.07	2.47
88.94	0.44
90.85	1.35
90.95	0.56
95.07	0.50
97.06	0.38
112.92	1.03
124.95	0.50
130.85	4.62
178.82	1.88
212.84	3.59
242.83	0.35
262.82	3.26
282.82	0.32

13

MJS 0  
CAL: LTB


25-OCT-85  
8.8

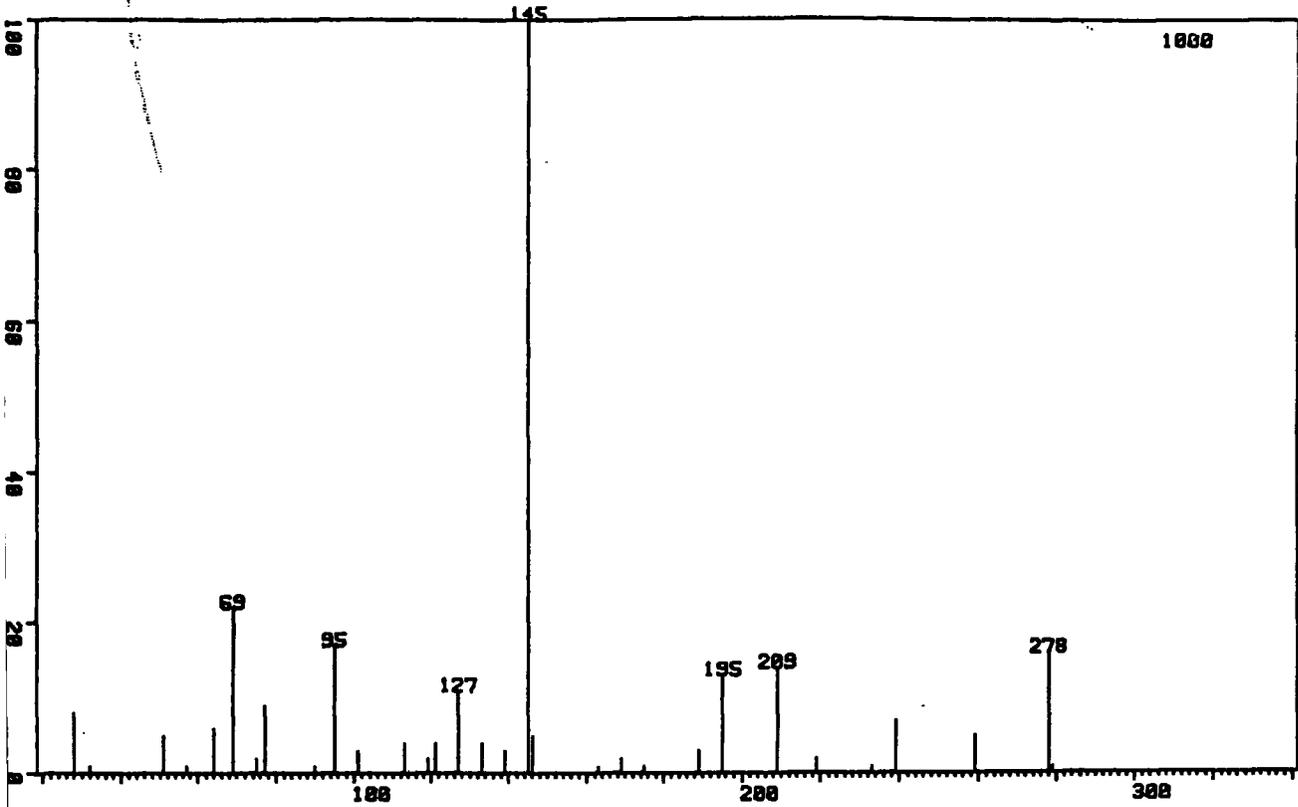

MASS	%HT. .BASE
------	---------------

14

28.00	8.00*
32.00	1.00*
51.00	5.00*
57.00	1.00*
64.00	6.00*
69.00	22.00*
75.00	2.00*
77.00	9.00*
90.00	1.00*
95.00	17.00*
101.00	3.00*
113.00	4.00*
119.00	2.00*
121.00	4.00*
127.00	11.00*
133.00	4.00*
139.00	3.00*
145.00	100.00*
146.00	5.00*
163.00	1.00*
169.00	2.00*
175.00	1.00*
189.00	3.00*
195.00	13.00*
209.00	14.00*
219.00	2.00*
233.00	1.00*
239.00	7.00*
259.00	5.00*
278.00	16.00*
279.00	1.00*

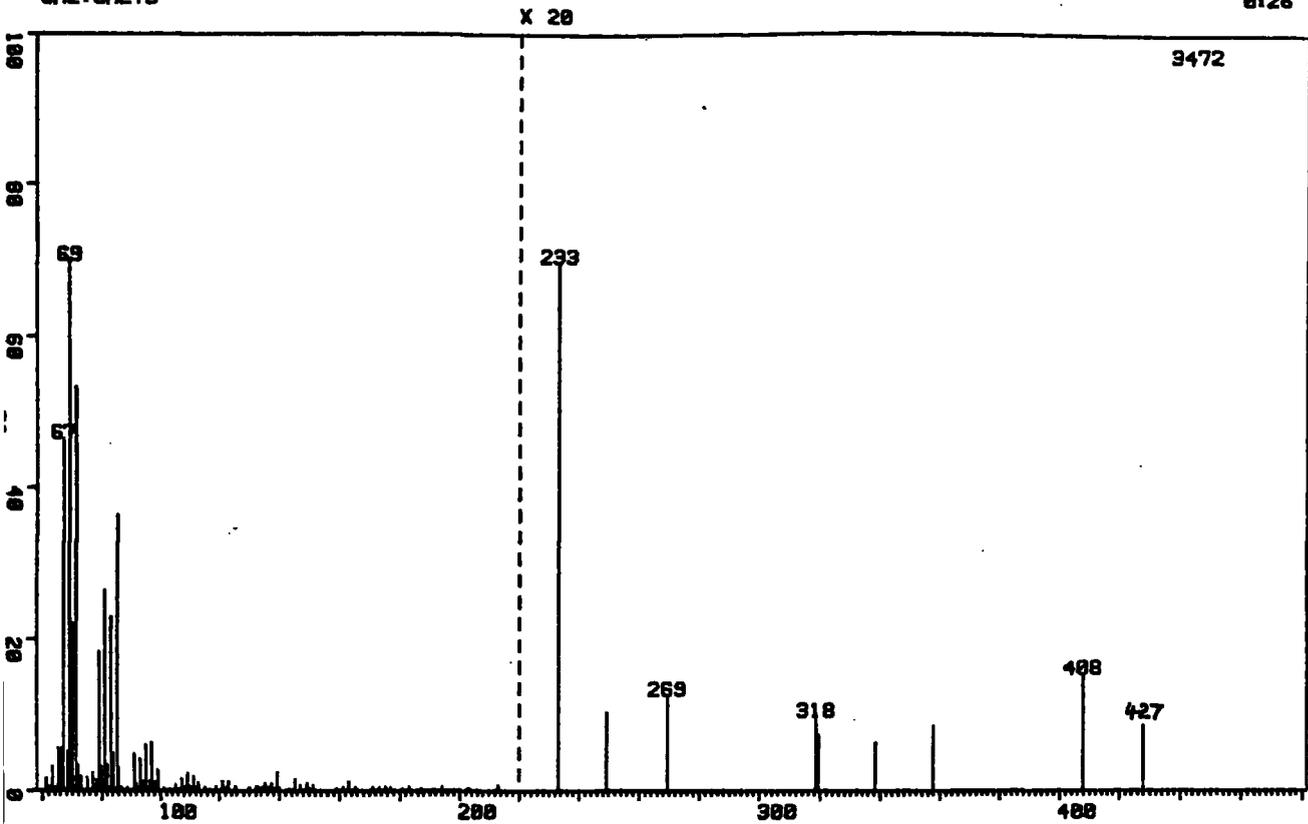
MJS6X 2  
CAL:CALT311-OCT-85  
8:26

MASS	%HT. BASE	MASS	%HT. BASE
67.15	46.63	143.10	0.29
68.13	5.27	145.02	1.53
69.10	70.02	147.11	0.78
70.07	22.09	149.05	1.04
71.14	53.43	150.07	0.40
72.16	3.49	151.10	0.78
73.11	1.93	159.07	0.32
75.13	1.81	161.11	0.52
77.06	2.45	162.97	1.15
78.03	1.44	163.13	0.78
78.99	18.32	165.12	0.43
79.98	3.25	171.03	0.43
81.04	26.47	173.12	0.43
82.09	3.49	175.15	0.55
83.13	22.90	177.11	0.49
84.13	5.04	180.93	0.32
85.11	36.38	183.09	0.52
86.08	3.14	187.10	0.35
86.97	0.40	191.15	0.26
87.02	0.58	194.02	0.63
88.94	0.43	203.19	0.37
90.98	4.87	213.11	0.66
92.03	1.01	233.14	3.49
93.06	4.26	249.13	0.52
94.07	1.30	269.19	0.63
95.08	6.08	318.30	0.49
96.10	1.41	319.30	0.37
97.09	6.39	338.38	0.32
98.07	1.35	357.59	0.43
99.04	2.74	407.68	0.78
101.06	0.43	427.77	0.43

15


MJS291 20  
CAL: CALMS

17-FEB-84  
9:33

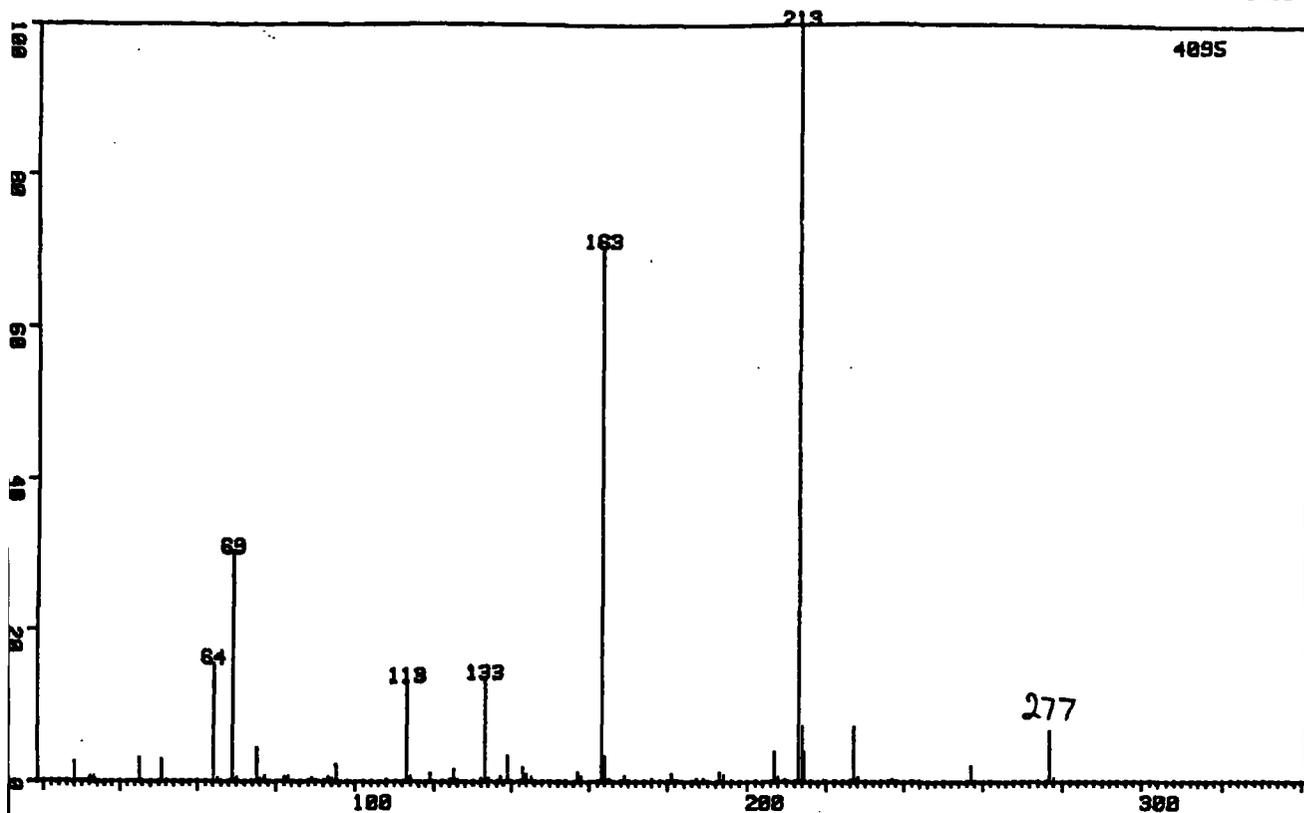


16

MASS	ZHT. BASE
28.07	28.80
31.96	5.79
33.07	1.88
45.14	4.49
50.96	5.35
64.11	19.54
68.95	33.14
75.06	8.97
95.04	3.62
113.03	19.39
125.07	1.88
133.04	12.59
138.99	4.78
143.02	2.03
157.06	1.45
163.02	58.47
164.06	2.75
207.08	3.33
213.03	100.00
214.08	6.51
227.07	5.07
257.04	2.17
277.09	4.92

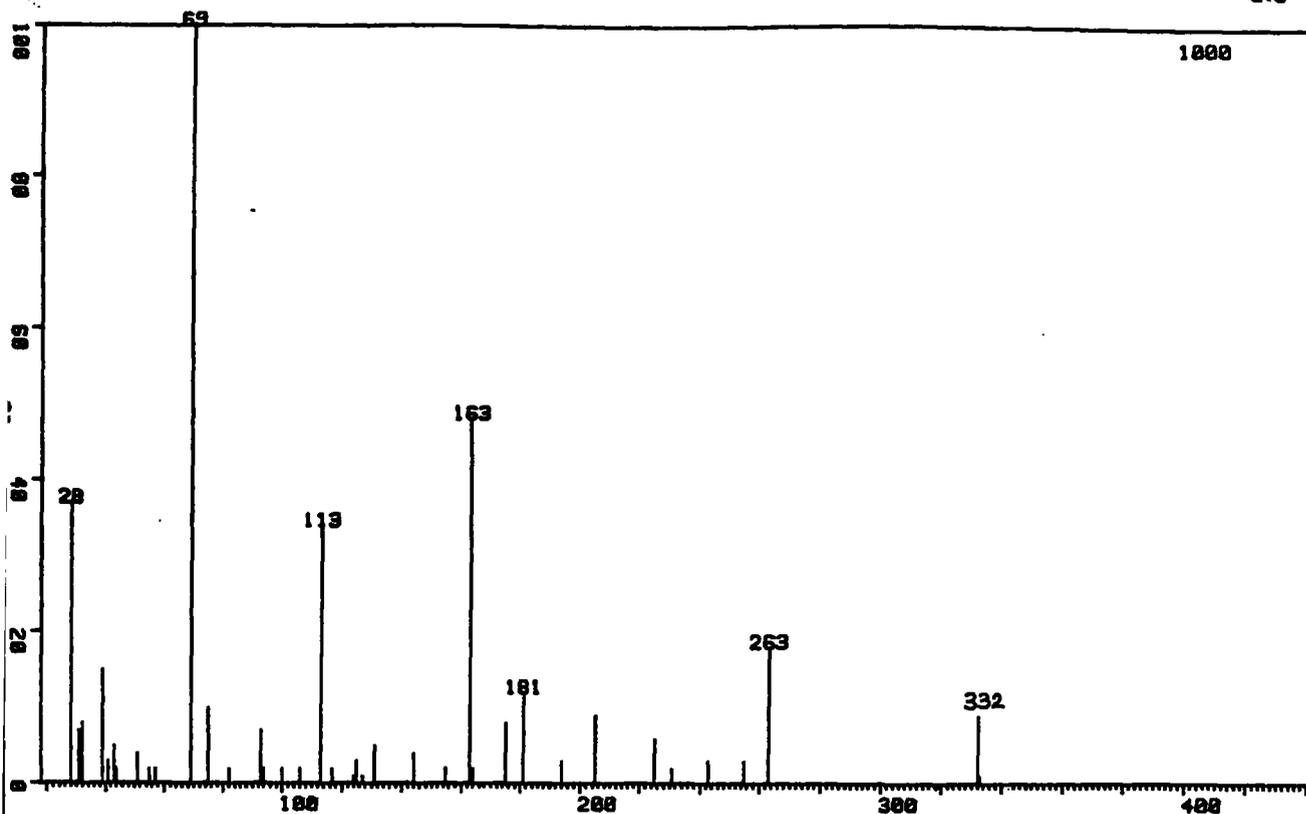MJS101 0  
CAL:LTB30-SEP-85  
0.0

17

MASS	%HT. BASE	MASS	%HT. BASE	MASS	%HT. BASE
30.88	7.03	75.08	10.10*	162.91	48.21*
31.99	7.98	76.08	0.42*	163.94	2.09*
37.12	0.64	77.09	0.31	168.90	0.31*
38.98	1.09	78.98	0.28	173.93	0.33
39.82	15.18	80.96	0.39	174.93	8.29*
39.89	0.36	81.04	0.36	175.94	0.50*
40.97	2.59	82.03	1.48*	180.85	12.14
42.06	0.81	83.13	0.81*	181.93	0.67*
43.12	4.46*	84.11	0.36	185.96	0.33
44.10	2.26	85.13	0.53	192.93	1.31
45.16	0.36	85.99	0.33	193.95	2.76
49.88	0.98	86.98	0.70*	204.91	8.68
50.95	4.05*	90.96	0.50*	205.92	0.78
53.10	0.28	92.96	6.56	211.90	0.36
55.10	0.56*	93.99	2.34*	212.92	1.00
55.15	1.81*	97.06	0.42	224.92	5.64*
56.10	1.20*	97.94	0.25	225.92	0.36*
56.15	0.78*	98.91	0.56*	230.87	2.34
57.14	2.37	99.85	1.70	242.90	3.04
58.07	0.28*	105.04	0.75	243.92	1.03
60.96	0.28*	106.01	2.23*	254.92	2.62*
62.01	0.31	111.95	0.92	262.90	17.94*
63.06	0.45*	112.97	33.59*	263.95	1.03*
65.13	0.42	114.00	1.06*	273.89	1.37*
66.13	0.36*	116.97	2.32	274.95	0.42*
67.12	0.45	118.91	1.40	292.88	0.56
68.03	0.39*	119.00	0.45	293.93	0.25
68.97	100.00*	123.96	1.31	311.89	0.31
69.04	1.31*	124.97	2.96*	312.92	0.47
69.91	1.23	130.90	4.85	331.87	8.90*
69.98	0.78	135.96	1.03	332.90	0.78*

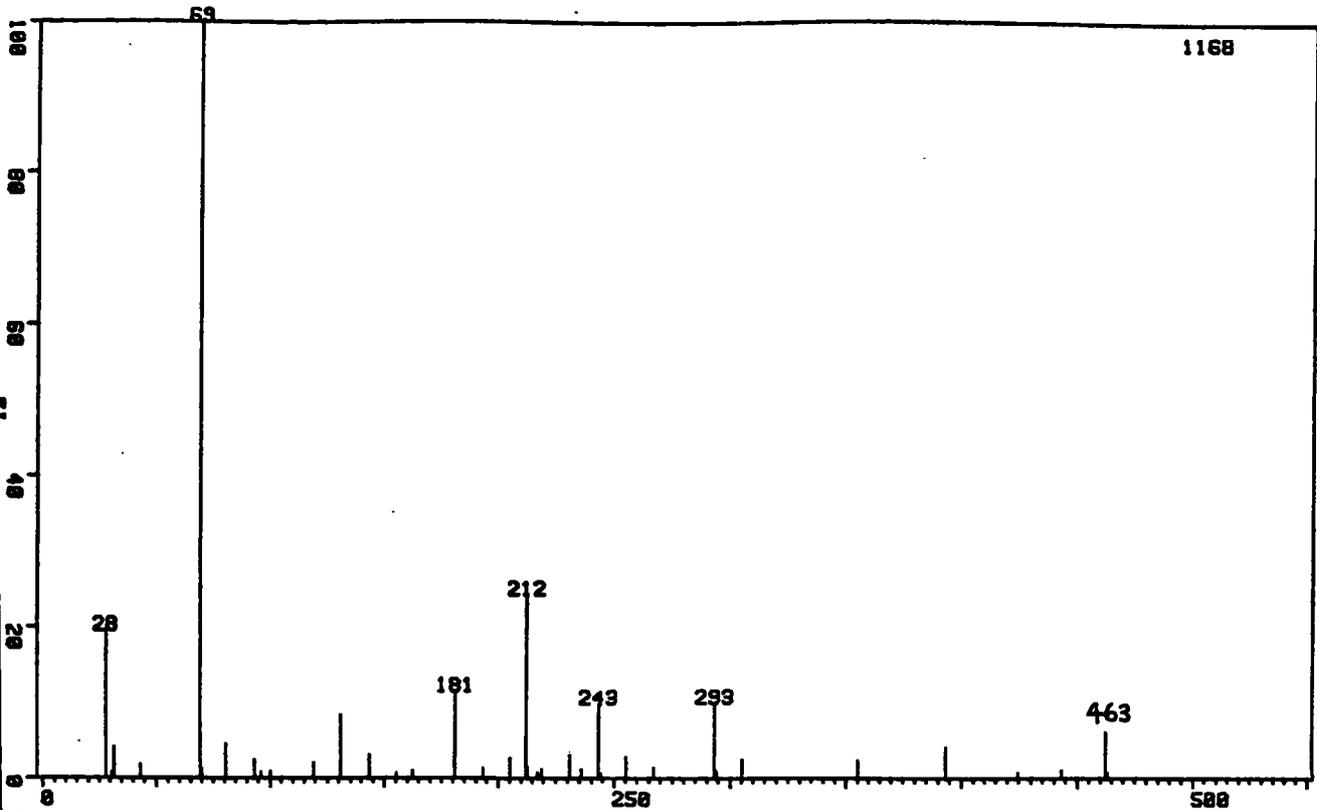MS31 14  
CAL: CALM2727-AUG-85  
2:27


MASS	%IT.	MASS	%IT.
	BASE		BASE
27.97	19.61	355.14	2.40
30.78	0.86	393.20	4.11
31.92	4.20	424.12	0.86
43.15	1.80	443.22	1.11
69.04	100.00	462.19	6.16
69.99	1.28	463.19	0.86
80.84	4.54		
93.10	2.48		
96.21	0.86		
100.03	0.94		
119.12	2.14		
131.14	8.30		
143.16	3.08		
155.15	0.77		
162.08	1.03		
181.08	11.56		
193.14	1.37		
205.16	2.65		
212.10	24.32		
213.14	1.63		
217.09	0.86		
219.05	1.28		
231.07	3.17		
236.12	1.28		
243.11	9.93		
244.13	0.77		
255.06	2.83		
267.08	1.46		
293.10	10.02		
294.12	0.94		
305.07	2.57		

18

MJS89X 22  
CAL:CAL18


03-JUN-85

113

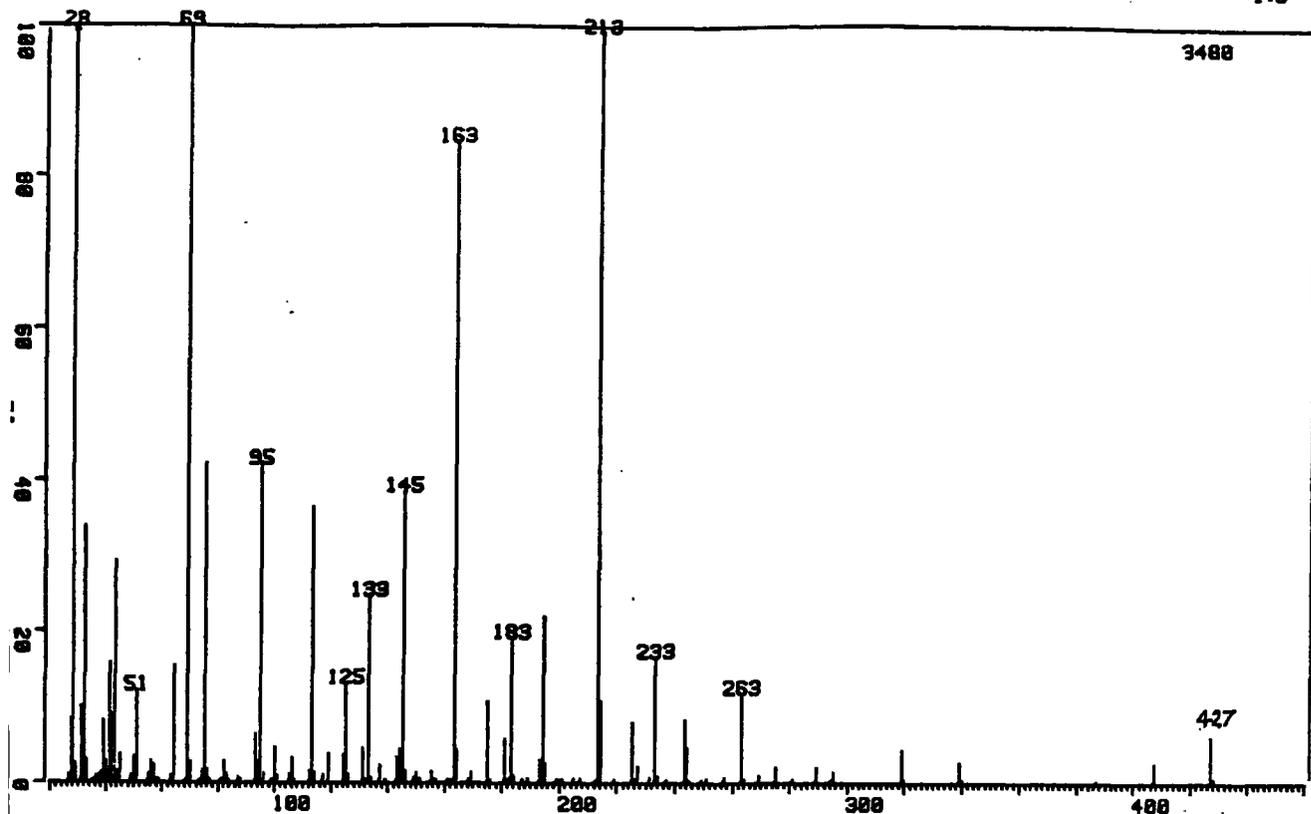


MASS	ZHT. BASE	MASS	ZHT. BASE	MASS	ZHT. BASE
68.97	97.15	133.03	24.12	213.00	96.48
69.04	0.39	134.05	0.78	214.03	10.58
69.91	2.82	137.03	2.32	218.99	0.39
73.09	0.34	139.01	0.45	225.01	7.84
74.06	1.62	143.01	3.32	226.02	0.50
75.07	41.09	144.03	4.44	227.03	2.18
76.08	1.84	145.03	37.52	230.96	0.78
77.07	0.39	146.04	1.70	233.01	16.28
80.98	0.47	149.01	0.75	234.02	0.98
82.01	2.82	149.96	1.42	237.01	0.39
83.05	1.17	151.00	0.56	242.99	8.15
84.02	0.47	155.03	1.48	244.02	4.72
87.05	0.89	156.04	0.50	245.02	0.36
88.03	0.50	157.04	0.45	248.99	0.36
93.03	6.25	160.99	0.42	250.99	0.50
94.06	2.76	162.01	0.36	257.01	0.81
95.07	40.95	163.02	82.16	263.02	11.59
96.07	1.20	164.03	4.24	264.02	0.53
98.98	0.45	168.02	0.42	268.99	0.98
99.93	4.63	168.99	1.45	275.00	2.04
100.98	1.03	175.02	10.50	280.97	0.36
105.07	1.12	176.04	0.45	289.00	2.04
106.04	3.24	180.98	5.75	294.00	0.34
107.05	0.36	182.00	0.45	295.00	1.42
112.00	1.62	183.03	18.73	318.99	4.27
113.03	35.51	184.06	1.06	319.97	0.50
114.05	1.45	187.02	0.47	339.00	2.65
117.03	1.06	189.00	0.64	340.00	0.36
118.97	3.77	193.01	2.99	386.97	0.34
124.04	3.66	194.02	21.41	406.97	2.60
125.04	12.84	195.02	2.62	426.95	6.03

19

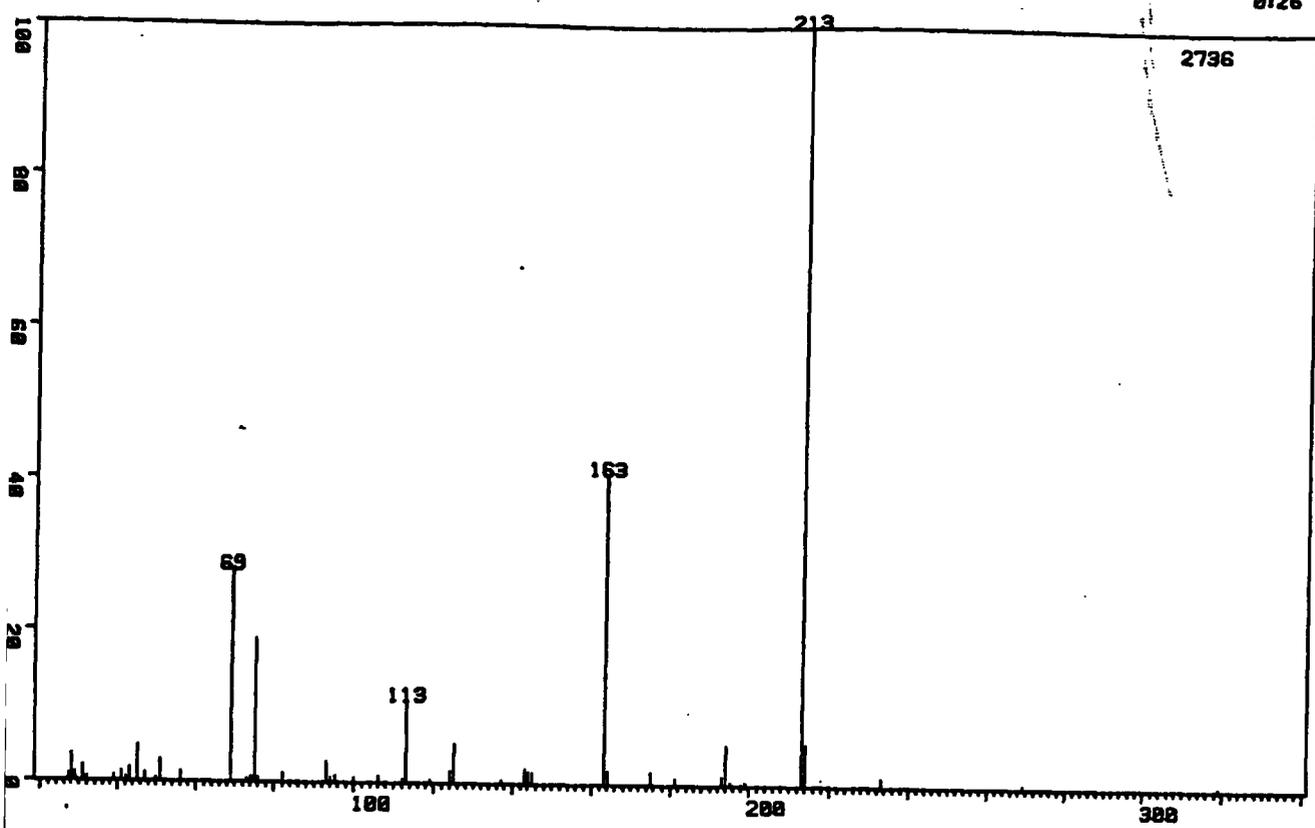


20.

MASS	ZHT. BASE	MASS	ZHT. BASE
27.29	0.99	137.11	0.48
28.17	3.62	143.12	2.12
29.05	1.21	144.11	1.64
30.93	2.01	145.10	1.61
32.03	0.69	163.10	40.94
39.01	0.73	164.12	1.90
41.00	1.35	175.10	1.72
42.09	0.69	181.07	0.95
43.12	1.13	193.10	1.24
43.16	1.90	194.09	5.30
45.18	4.75	195.10	0.48
47.13	1.17	199.04	0.55
49.90	0.48	213.12	100.00
50.98	2.89	214.10	5.52
56.13	1.43	233.12	1.21
69.02	28.03	269.12	0.51
73.18	0.40	319.17	0.37
74.13	0.69		
75.12	18.97		
76.09	0.69		
82.04	1.21		
93.09	2.78		
94.11	0.77		
95.10	0.95		
99.97	0.69		
106.09	0.99		
112.06	0.51		
113.08	10.62		
119.02	0.40		
124.08	1.75		
125.10	5.26		

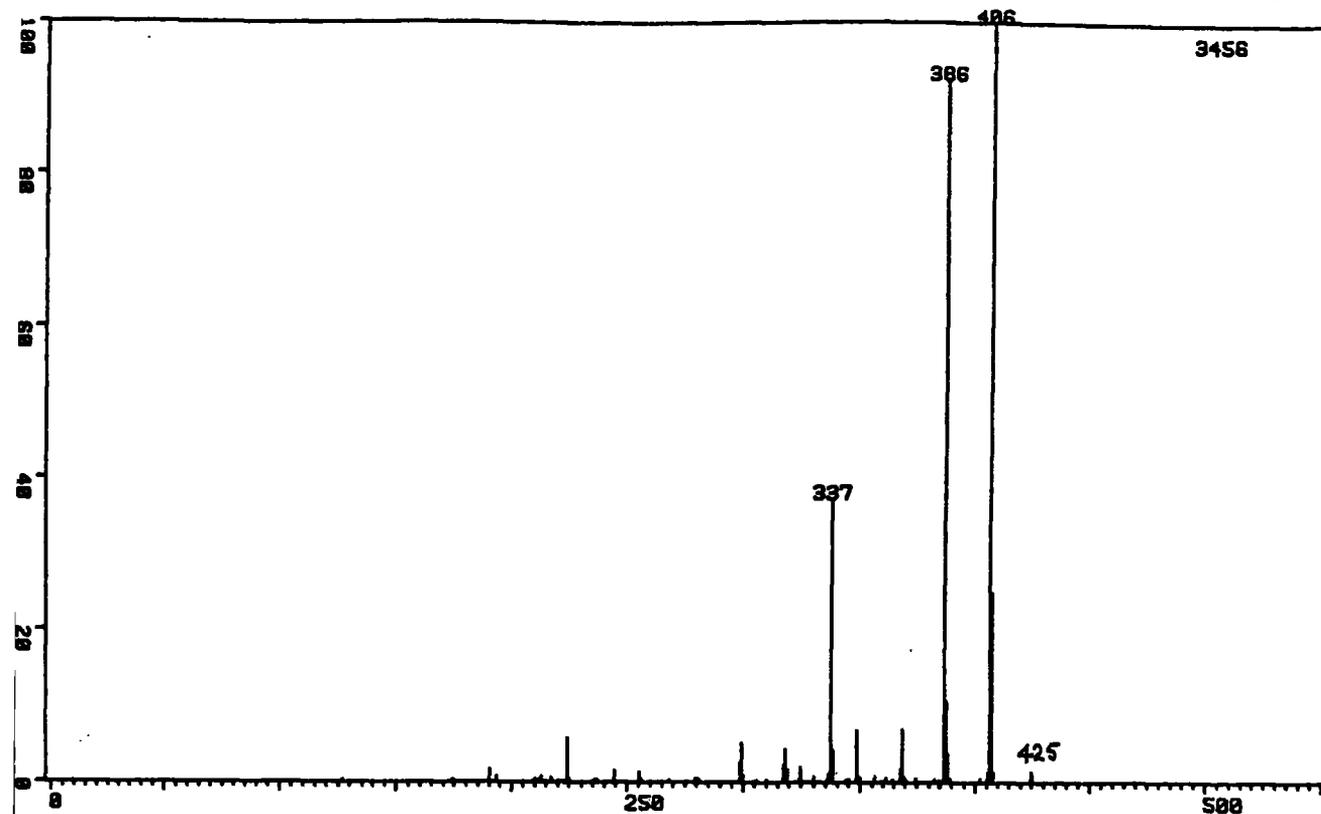MJS10X 4  
CAL: CALN411-OCT-85  
0:44


MASS	%HT. BASE	MASS	%HT. BASE
174.19	0.38	325.19	0.29
190.15	1.71	330.20	0.78
193.18	0.78	336.19	1.10
210.08	0.49	337.21	37.41
212.11	0.38	338.16	4.22
213.15	0.78	344.21	0.32
217.12	0.41	345.24	0.38
224.13	5.84	348.19	6.83
225.10	0.49	349.18	0.81
236.14	0.32	350.19	0.61
237.11	0.32	356.25	0.81
244.11	1.56	361.23	0.52
255.16	1.36	364.19	0.32
256.17	0.41	367.20	1.65
268.15	0.32	368.17	7.03
279.15	0.61	369.19	0.78
280.16	0.61	370.23	0.38
281.17	0.35	374.22	0.52
298.18	2.58	382.27	0.38
299.18	5.21	384.27	0.32
300.18	0.95	386.26	92.36
306.20	0.26	387.24	10.65
310.16	0.32	388.22	3.79
317.16	2.23	389.21	0.38
318.16	4.37	402.20	0.58
319.19	1.71	405.23	1.42
324.20	1.97	406.25	100.00
		407.25	25.00
		408.25	1.36
		424.27	1.48
		425.27	0.93

21

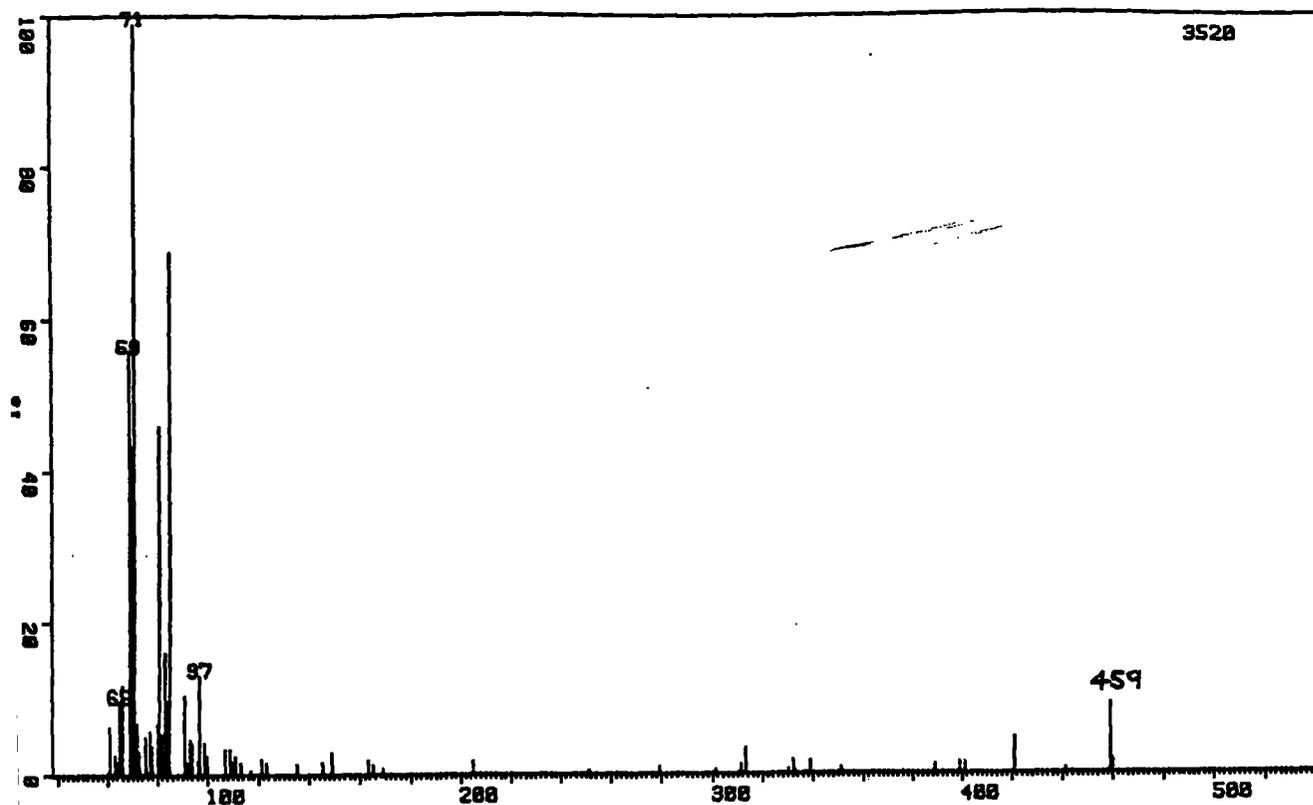2151X 3  
CAL: CALT124-AUG-84  
8:32


MASS	%HT. BASE	MASS	%HT. BASE
60.95	6.25	112.94	1.51
63.02	2.59	113.08	1.56
64.06	1.73	117.02	0.54
65.08	9.52	121.01	2.02
66.08	11.79	123.07	1.59
68.94	2.22	135.08	1.36
69.00	55.77	144.98	1.56
69.95	43.30	148.94	2.81
71.02	98.92	149.05	2.16
72.07	7.02	162.96	0.60
73.04	1.59	163.12	1.90
73.08	3.18	165.10	1.25
75.12	5.00	168.90	0.91
77.02	5.88	205.02	1.65
78.00	3.84	250.98	0.48
79.92	6.68	279.09	0.99
80.98	45.99	300.95	0.60
82.02	5.43	310.98	1.19
83.05	16.02	312.99	3.38
84.08	9.74	329.98	0.68
85.10	68.92	331.99	1.79
90.94	10.45	332.93	0.43
91.98	1.56	339.01	1.56
92.96	2.53	350.98	0.82
93.01	4.74	388.99	1.16
94.03	4.18	398.96	1.48
96.05	1.87	401.01	1.45
97.05	13.04	421.02	4.69
98.95	1.19	441.03	0.60
99.00	4.29	459.08	9.09
99.98	2.56	460.09	1.79

22

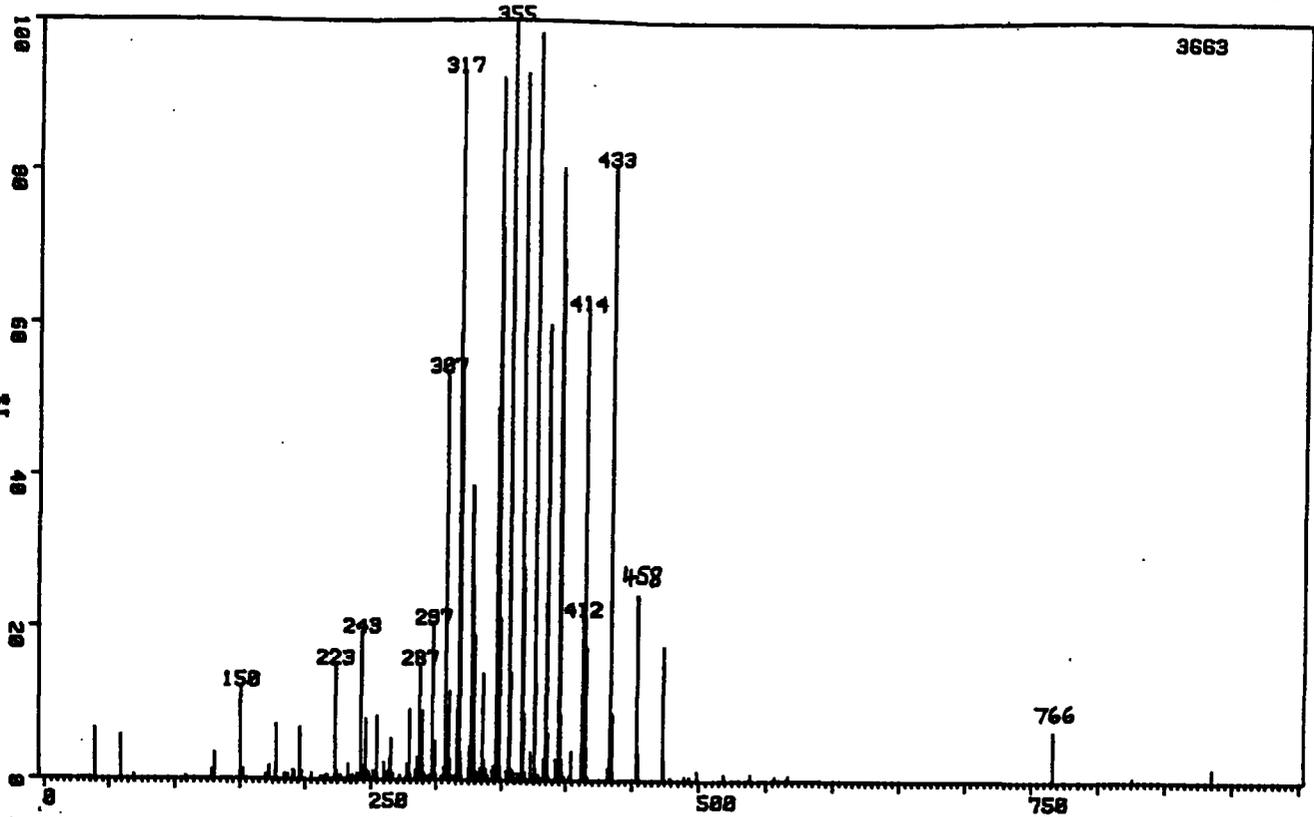


23

MASS	%HT.	MASS	%HT.	MASS	%HT.
	BASE		BASE		BASE
305.93	1.50	356.35	14.06	396.87	2.89
306.92	53.70	357.36	1.64	397.83	1.12
307.91	8.87	358.31	1.34	398.88	0.44
308.89	2.48	359.32	1.23	402.84	0.55
309.88	11.68	360.35	0.25	403.77	3.82
310.90	2.70	362.29	0.96	411.66	21.84
312.87	0.38	363.26	1.04	413.65	62.00
313.83	0.33	365.28	92.90	414.68	17.44
314.79	0.57	366.25	27.96	415.71	4.37
315.81	9.17	367.29	9.01	416.66	0.52
316.76	93.26	368.26	1.09	431.49	1.64
317.78	54.14	372.20	3.69	432.48	0.68
318.74	3.69	373.19	0.93	433.47	80.94
319.70	0.60	375.10	98.20	434.46	8.82
324.69	1.50	375.82	0.38	435.54	1.23
325.68	4.45	376.10	12.67	453.22	24.41
326.73	38.66	377.09	1.61	454.26	3.58
327.65	25.55	378.01	0.30	455.22	0.46
328.64	19.19	379.08	0.79	472.97	17.69
329.63	4.45	382.06	0.35	473.96	2.68
330.63	1.23	383.01	2.73	478.92	0.38
331.59	0.60	384.04	23.26	488.89	0.55
345.33	48.92	385.07	59.84	492.80	0.44
346.45	92.30	386.03	6.12	498.60	1.20
347.43	72.48	387.06	0.60	518.53	0.87
348.49	21.38	391.94	2.81	538.26	0.87
349.47	1.88	392.98	1.91	556.95	0.44
353.44	1.23	393.95	80.37	566.81	0.68
355.34	100.00	394.92	68.33	766.81	6.61
355.94	0.38	395.89	8.65	825.94	0.49
				885.00	1.75

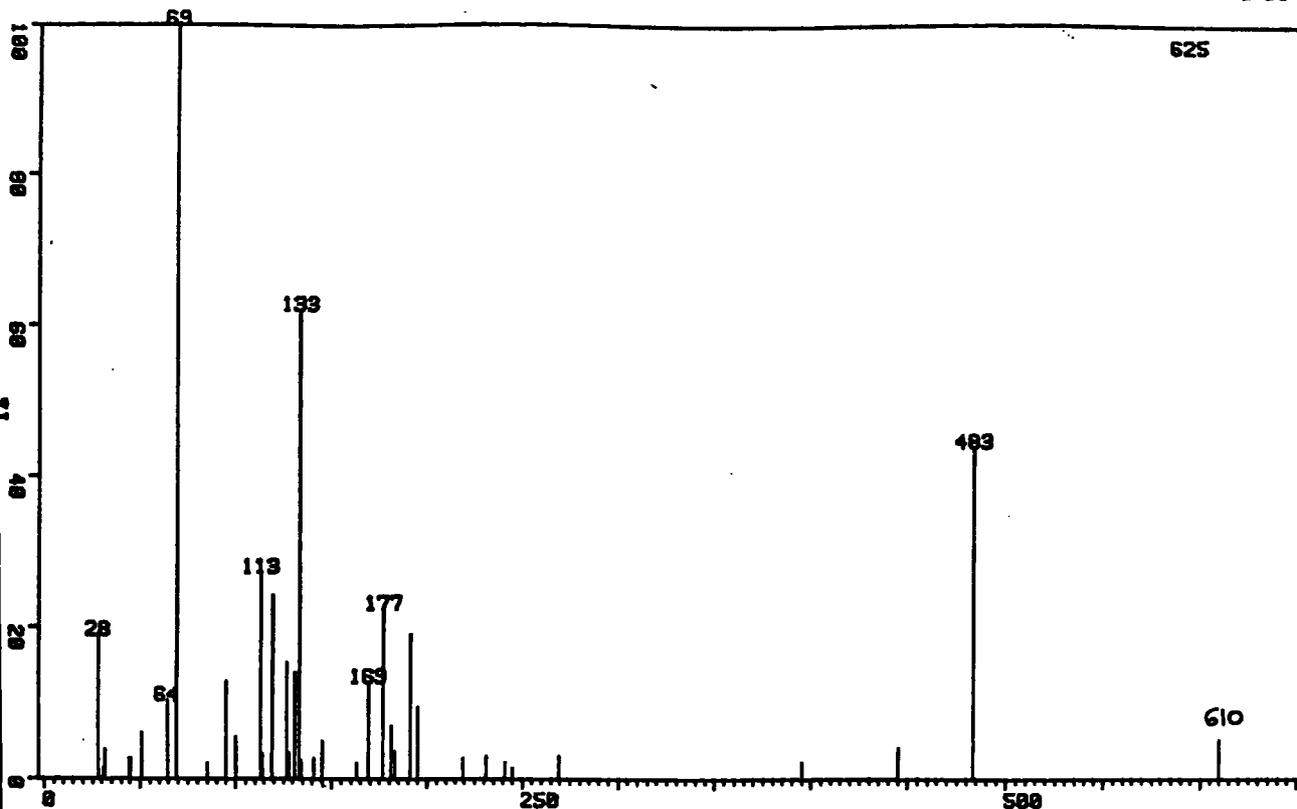MJS91X 33  
CAL: CALM109-MAY-85  
5:33


MASS	ZHT.	MASS	ZHT.
	BASE		BASE
28.06	19.04	245.12	1.44
30.83	1.44	269.08	3.04
31.94	3.84	395.15	2.24
44.11	2.72	445.18	4.16
45.14	2.72	483.24	44.00
50.96	6.08	610.28	5.28
64.11	10.40		
68.96	100.00		
85.01	2.08		
95.07	12.96		
99.96	5.60		
113.07	27.36		
114.07	3.36		
119.00	24.32		
126.98	15.36		
127.97	3.52		
131.04	14.08		
133.08	62.08		
134.11	2.56		
140.94	2.72		
145.09	4.96		
163.06	2.08		
169.02	12.80		
176.99	22.56		
181.07	7.04		
183.12	3.68		
190.97	19.20		
195.08	9.44		
219.04	2.72		
231.10	3.04		
241.03	2.24		

24

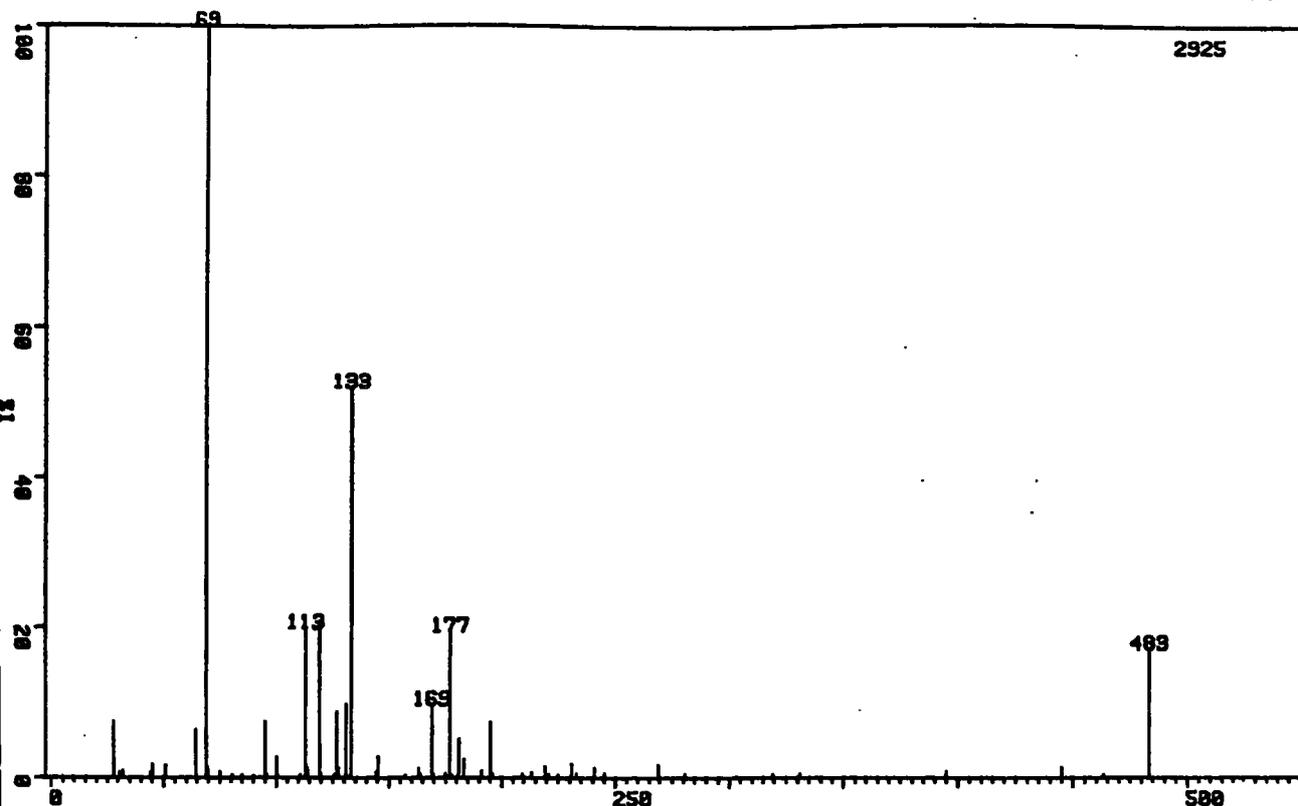MJS91X 29  
CAL: CALM109-MAY-85  
4:54


0 25

MASS	%HT. BASE	MASS	%HT. BASE
45.15	1.81	169.97	0.55
50.96	1.71	175.06	0.58
64.11	6.39	176.96	19.52
68.96	100.00	177.99	0.38
69.47	0.31	181.03	5.16
69.91	1.33	183.09	2.50
75.06	0.75	190.96	0.92
80.92	0.31	195.07	7.38
84.98	0.41	196.06	0.51
89.91	0.34	208.98	0.62
95.07	7.49	213.10	0.75
96.07	0.38	219.04	1.54
99.94	2.70	220.97	0.51
100.98	0.27	225.12	0.34
111.00	0.48	231.05	1.88
113.05	20.00	233.11	0.62
114.07	1.33	240.95	1.40
119.00	20.41	245.08	0.62
119.97	0.62	269.07	1.78
126.08	0.38	281.07	0.58
126.98	8.72	302.98	0.27
127.97	1.33	319.02	0.38
131.02	9.74	331.09	0.44
131.63	0.34	395.11	0.92
133.11	51.97	445.07	1.44
144.07	0.72	463.15	0.44
145.07	2.84	483.17	17.16
157.02	0.31		
163.04	1.33		
164.07	0.44		
169.00	9.74		

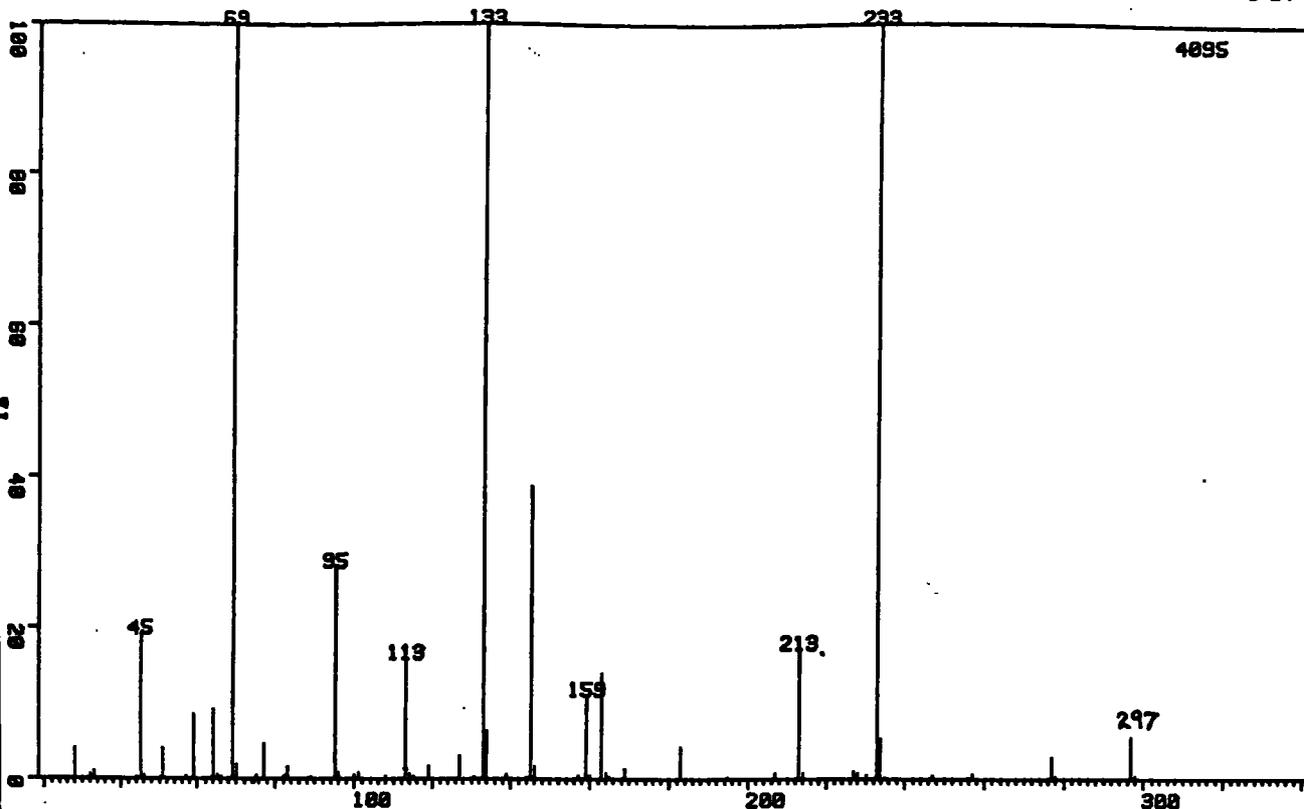MSS1X 45  
CAL: CALM1801-SEP-85  
6.87

0 26

MASS	%HT. BASE	MASS	%HT. BASE
28.06	4.05	130.85	0.24
31.94	0.68	132.93	100.00
33.06	1.05	133.75	6.40
44.09	0.24	138.98	0.66
45.12	19.17	144.02	0.22
46.11	0.37	145.00	38.68
50.92	4.00	145.99	1.68
57.07	0.34	156.99	0.42
58.97	8.45	158.94	11.06
64.06	9.18	159.91	0.56
65.08	0.56	162.93	13.94
66.12	0.29	163.96	0.90
68.94	100.00	164.94	0.32
69.24	0.24	168.92	1.39
69.31	0.24	182.95	4.22
69.88	1.93	194.93	0.27
75.09	0.49	206.88	0.81
77.06	4.64	212.88	17.17
81.99	0.46	213.93	0.85
83.02	1.64	226.93	1.00
88.97	0.27	227.91	0.85
95.03	28.01	230.23	0.54
96.03	0.90	232.82	100.00
99.90	0.56	233.77	5.42
100.93	0.90	234.90	0.24
107.99	0.34	246.97	0.39
112.98	15.92	256.93	0.73
114.00	0.78	276.91	2.91
115.01	0.32	277.88	0.34
118.93	1.68	296.83	5.54
126.98	3.00	297.91	0.44

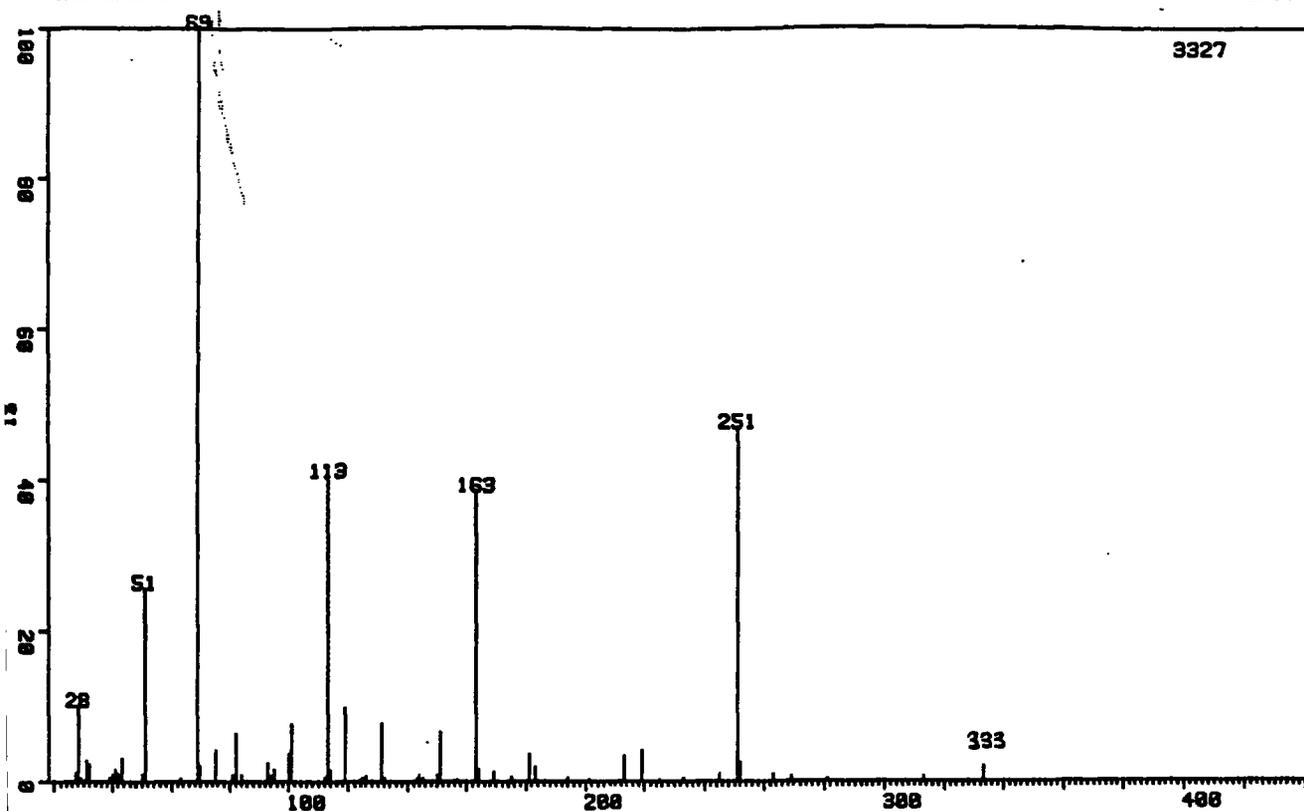
MS30X 4  
CAL: CALT316-OCT-85  
8:44

MASS	%HT. BASE	MASS	%HT. BASE
27.29	1.11	126.06	0.78
28.17	10.01	130.98	7.78
29.05	0.48	132.03	0.45
30.93	2.80	143.05	0.45
32.03	2.34	144.08	0.99
39.00	0.51	145.09	0.57
39.84	0.93	150.00	0.90
40.98	1.65	151.05	6.64
42.07	1.11	157.08	0.30
43.11	0.87	163.08	38.44
43.14	3.13	164.10	1.71
49.89	1.02	169.05	1.32
50.96	25.70	175.10	0.63
63.08	0.45	181.04	3.70
69.00	100.00	183.09	1.98
69.94	2.19	194.08	0.39
75.12	4.27	201.06	0.39
81.00	0.93	213.10	3.40
82.04	6.49	219.05	4.09
84.18	0.99	225.09	0.33
93.03	2.43	233.12	0.54
94.06	0.90	245.09	1.02
95.07	1.59	251.07	46.86
99.94	3.73	252.09	2.58
100.98	7.69	263.09	0.99
112.01	0.48	269.08	0.78
113.04	40.37	281.07	0.42
114.06	1.56	313.16	0.66
118.98	9.80	333.14	2.04
124.05	0.33		
125.05	0.54		

27


MS30X 7  
CAL: CALN4

16-OCT-85  
1:15

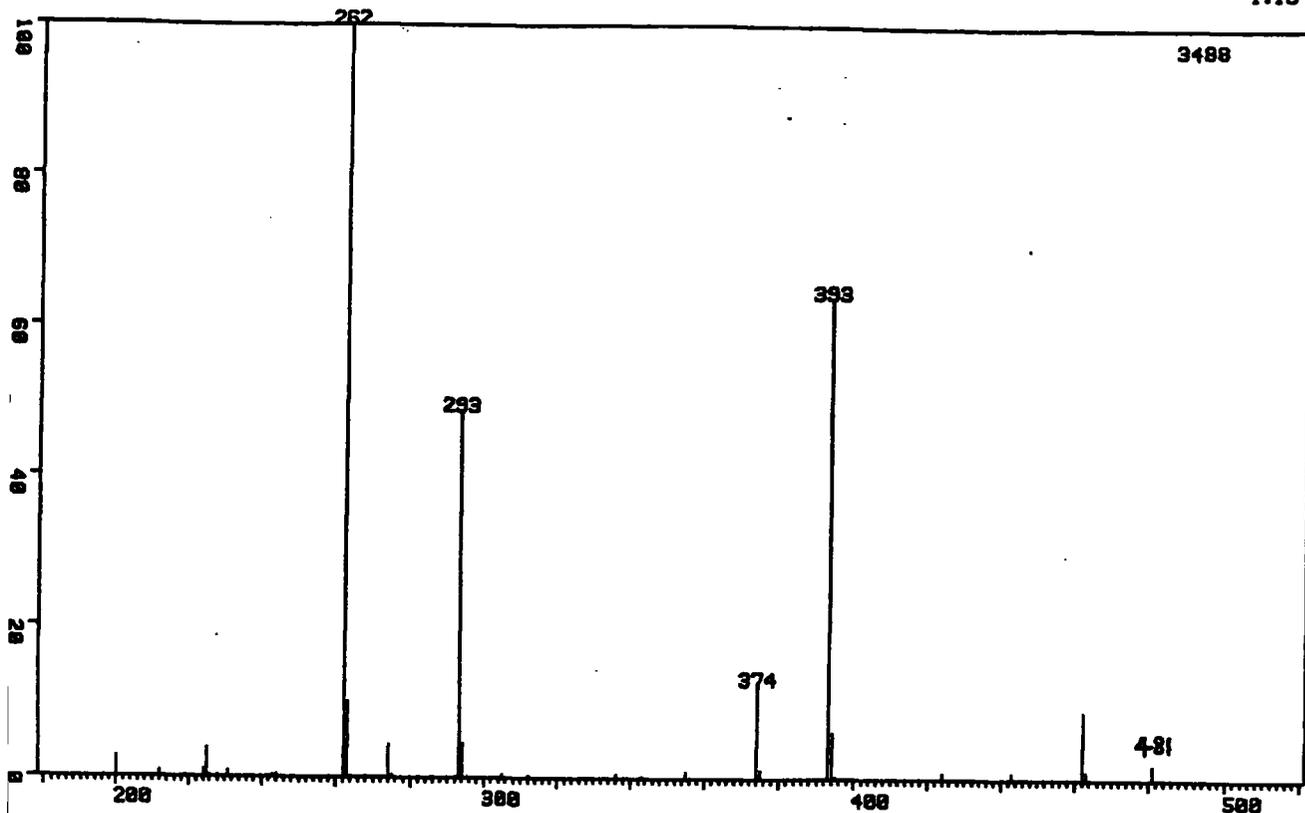

28

MASS	ZHT.	MASS	ZHT.
	BASE		BASE
39.00	1.26	395.06	0.29
58.93	0.46	424.10	0.92
174.03	0.32	443.04	0.89
193.01	14.54	462.06	8.89
194.03	1.20	463.04	1.03
199.96	2.72	481.04	1.92
211.99	0.80		
218.98	0.26		
224.01	1.03		
225.03	3.84		
226.03	0.34		
228.00	0.32		
230.99	0.86		
242.99	0.29		
244.03	0.37		
262.03	100.00		
263.03	10.12		
264.05	0.32		
274.05	4.33		
275.05	0.40		
293.04	48.77		
294.06	4.59		
305.06	0.52		
312.05	0.37		
336.06	0.52		
343.04	0.32		
355.07	0.95		
374.06	12.47		
375.07	1.23		
393.05	63.96		
394.07	6.16		

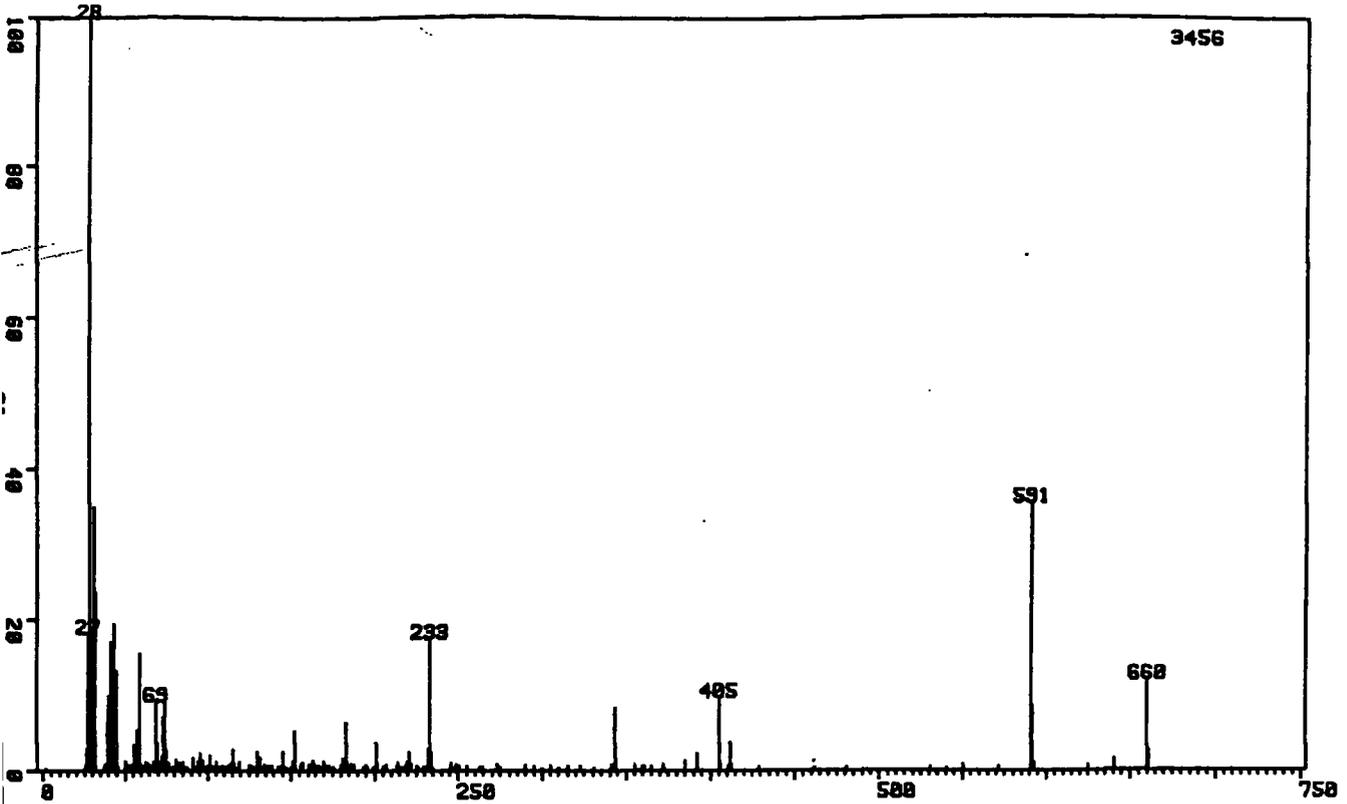


29

MASS	ZHT. BASE	MASS	ZHT. BASE	MASS	ZHT. BASE
43.09	15.13	206.93	0.81	342.94	8.36
43.12	19.50	212.92	0.67	343.93	1.56
44.09	1.50	213.97	1.13	354.91	0.93
44.14	1.74	215.01	0.41	358.88	0.49
45.15	13.28	216.02	0.49	360.89	0.67
46.14	0.75	216.95	0.41	364.89	0.61
49.88	1.33	218.91	0.87	371.93	0.95
50.94	0.95	219.90	1.27	372.93	0.32
52.01	0.44	220.91	2.43	384.88	1.36
53.07	0.90	221.93	1.01	391.94	2.24
54.11	0.61	224.91	0.69	392.92	0.46
55.09	0.46	225.93	0.41	404.91	9.81
55.13	3.56	228.92	0.43	405.87	1.19
56.13	2.00	229.89	0.43	410.90	0.72
57.06	0.43	230.90	0.49	411.95	3.85
57.08	0.41	231.91	2.89	412.98	0.98
57.11	5.47	232.93	17.56	428.91	0.46
58.03	0.69	233.96	2.46	461.91	0.38
58.07	0.64	234.91	0.55	480.82	0.43
58.99	15.60	235.90	0.26	530.71	0.49
59.85	0.98	244.91	0.67	540.77	0.35
59.91	0.41	245.95	1.13	550.73	0.90
61.95	0.75	246.96	0.43	571.79	0.61
61.99	0.52	248.91	0.81	590.76	35.62
63.04	1.19	249.90	0.67	591.84	8.65
64.07	1.01	250.92	0.72	592.90	1.13
65.09	0.72	254.90	0.64	624.80	0.72
66.09	0.32	262.88	0.43	640.80	1.53
67.08	1.22	264.91	0.52	641.90	0.35
68.05	0.84	272.90	0.87	659.85	12.09
68.94	9.29	273.95	0.61	660.89	2.75
69.01	3.76				


MJS13X 4  
CAL: CALN1

04-OCT-85  
8:43

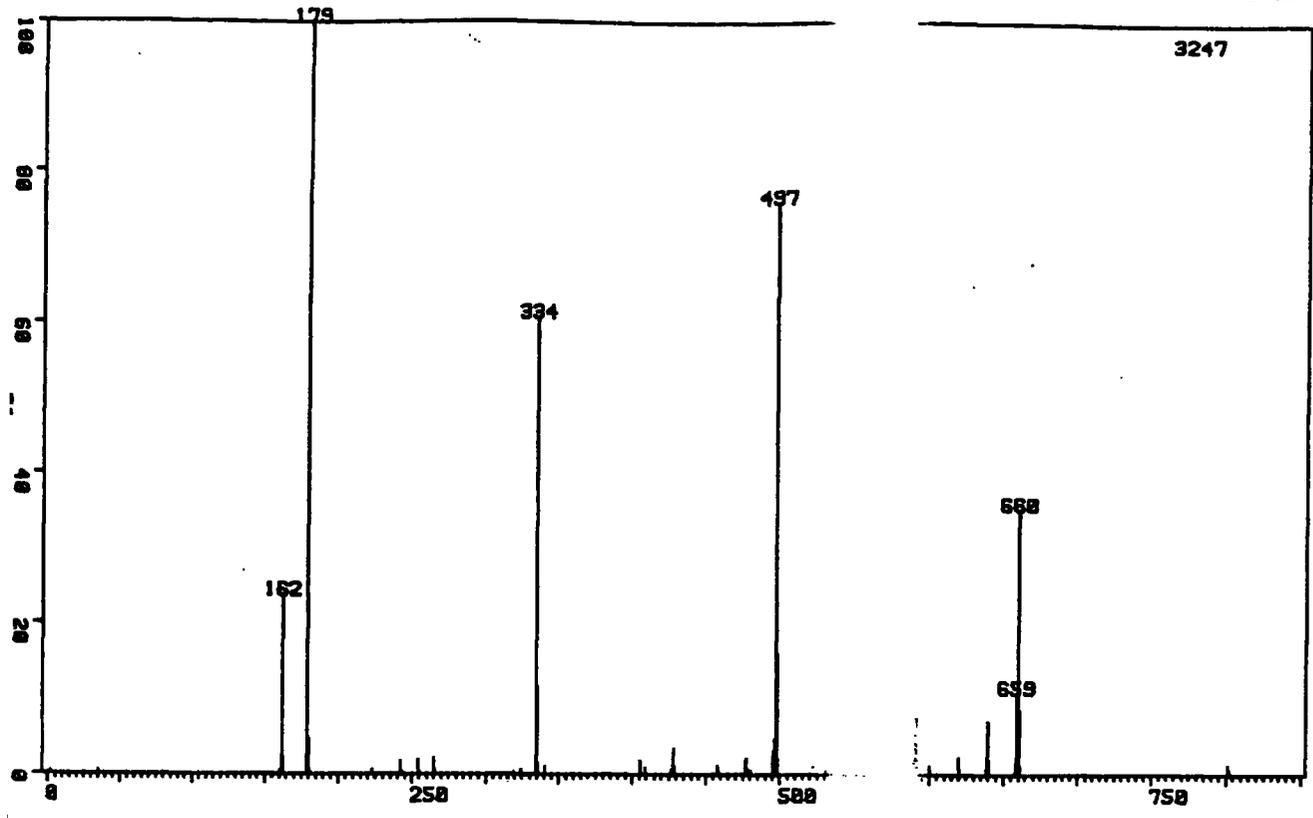


30

MASS	ZHT. BASE	MASS
159.97	0.46	476.82
162.01	23.78	477.86
163.03	2.19	478.86
178.97	100.00	479.82
179.95	4.65	480.88
180.96	0.43	494.86
222.99	0.59	495.85
241.98	1.76	496.84
242.99	0.34	497.88
253.98	1.94	498.87
254.99	0.43	530.77
265.01	2.13	550.79
266.03	0.71	570.77
318.94	0.31	571.81
323.91	0.65	588.77
324.90	0.62	590.74
333.97	60.61	591.76
334.97	11.58	599.71
335.96	1.45	600.75
340.86	1.05	619.76
404.88	1.88	620.78
405.85	0.43	638.73
408.87	0.95	639.76
426.91	0.46	640.73
427.89	3.45	657.75
428.90	1.08	658.69
457.87	1.17	659.69
458.87	0.49	660.70
		661.72
		801.61
		802.61

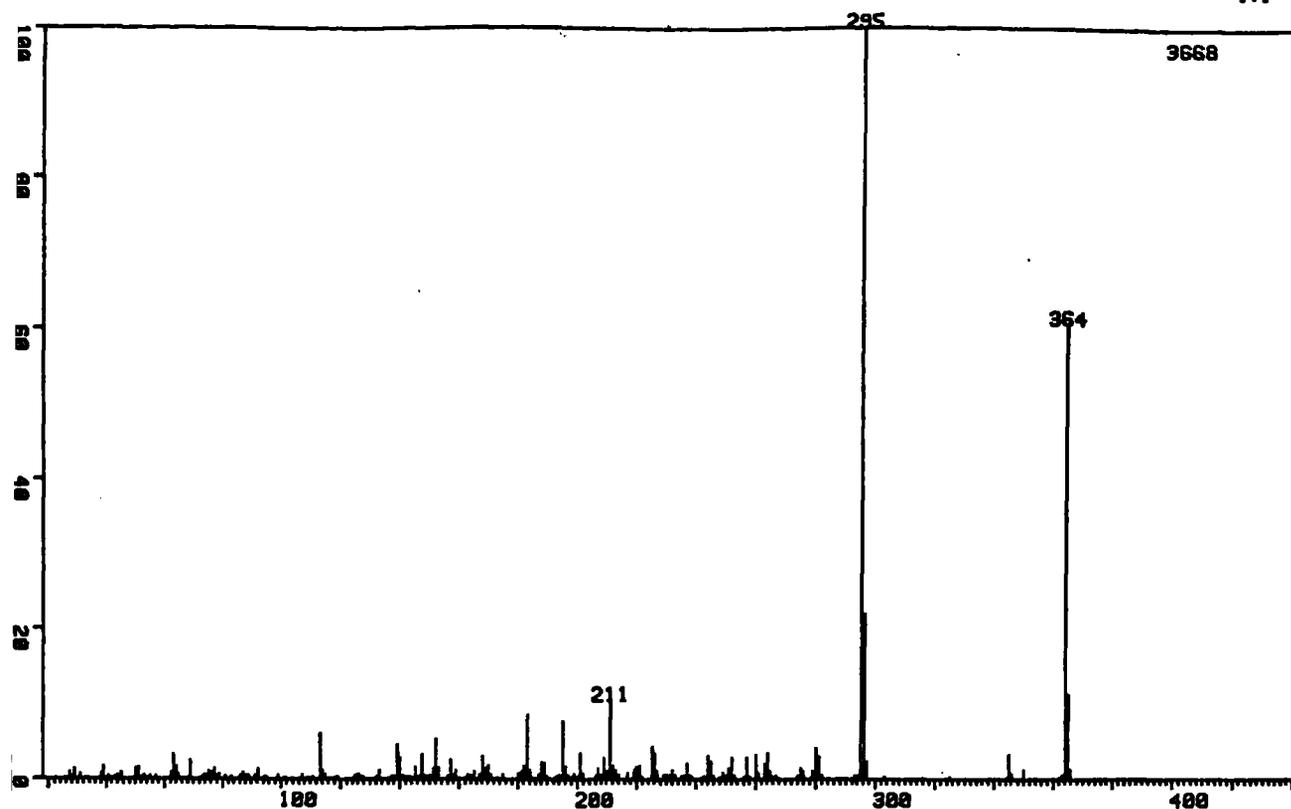MJS12X 6  
CAL: CAL T304-OCT-85  
1:1


MASS	ZHT. BASE	MASS	ZHT. BASE
209.03	2.89	256.08	0.25
210.02	1.09	257.03	2.86
211.03	10.52	258.03	0.38
212.06	1.91	260.02	3.27
213.05	1.25	261.03	0.93
214.07	0.60	263.06	2.10
217.04	0.87	264.08	3.44
219.01	1.15	265.04	1.09
220.00	1.72	266.06	0.30
221.02	1.88	267.05	0.44
222.04	0.41	274.08	0.46
225.11	4.39	275.08	1.44
226.08	3.49	276.08	1.09
227.07	1.20	279.03	1.06
229.00	0.57	280.03	4.14
230.00	0.68	281.04	3.05
231.02	0.63	282.05	0.57
232.03	1.28	293.09	0.57
233.04	0.71	294.08	0.52
235.05	0.44	295.09	100.00
236.04	0.55	296.11	22.03
237.03	2.18	297.07	2.40
238.02	0.63	303.02	0.41
239.01	0.41	325.06	0.35
242.03	0.27	345.09	3.35
243.04	0.44	346.08	0.74
244.05	3.19	350.04	1.34
245.07	2.45	363.08	0.52
246.08	0.52	364.09	60.61
248.01	0.35	365.10	11.34
249.02	1.01	366.08	1.39

31

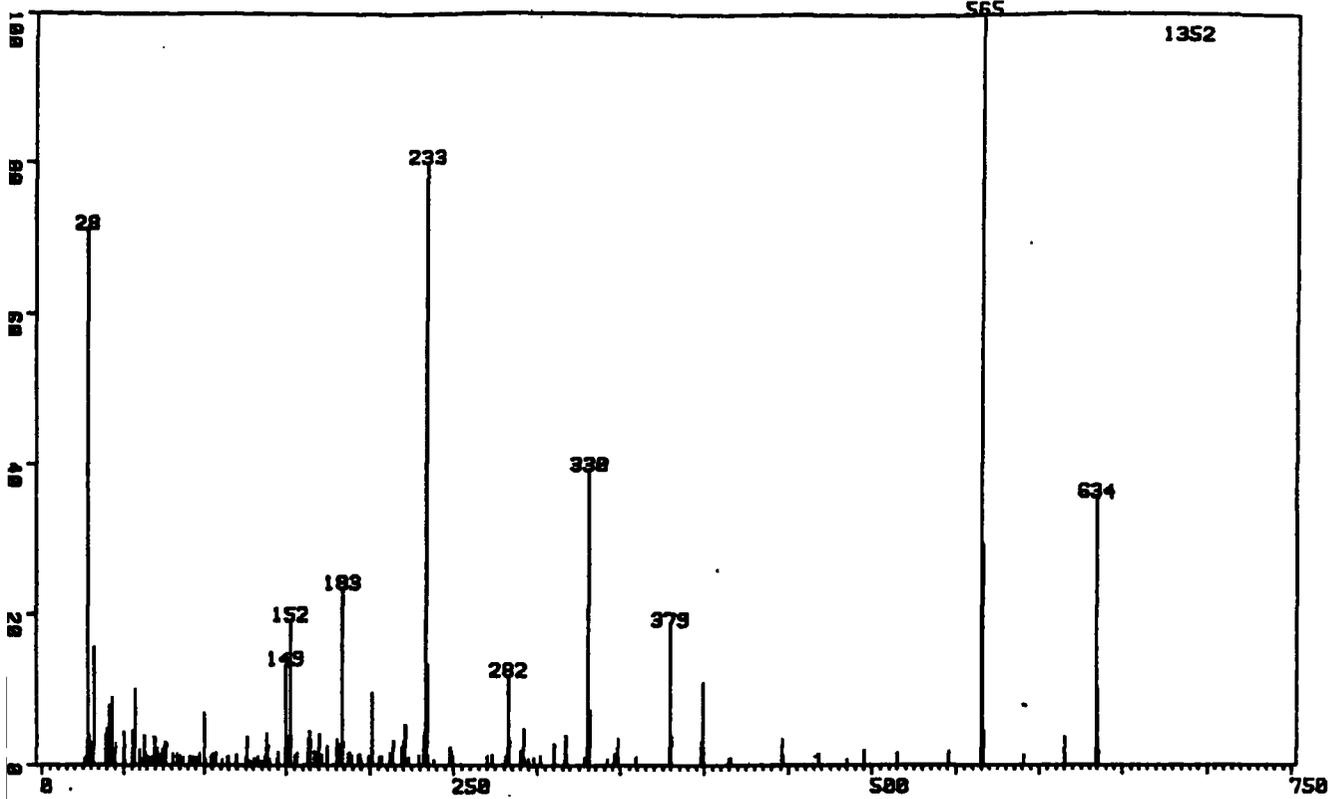MJS11X 4  
CAL:CALT2003-OCT-85  
0:44

MASS	ZHT.	MASS	ZHT.
	BASE		BASE
211.93	1.70	327.93	1.04
212.95	1.33	328.90	1.04
213.96	3.25	329.95	39.35
218.92	2.37	330.94	7.32
219.91	3.18	341.91	0.81
220.92	5.40	345.96	1.55
222.95	1.04	347.93	3.55
228.91	1.33	348.92	1.11
231.91	4.22	358.94	1.11
232.94	80.03	378.88	18.64
233.94	13.31	379.91	3.92
234.93	1.33	397.93	3.18
237.89	0.74	398.91	10.95
247.90	2.29	399.93	2.29
248.91	1.85	414.94	0.89
249.90	1.18	415.93	0.96
269.91	1.26	446.00	3.48
272.91	1.41	446.97	1.33
280.93	1.18	467.84	1.55
281.91	1.41	484.89	0.74
282.40	11.83	494.89	1.92
282.92	3.33	514.90	1.70
289.90	2.00	545.91	1.85
291.89	4.81	564.83	100.00
292.94	0.96	565.90	29.29
295.00	0.81	566.89	4.51
297.97	0.96	590.92	1.41
301.98	1.33	614.86	3.77
309.94	2.74	615.89	1.48
316.92	4.07	633.87	35.65
317.94	1.33	634.87	10.28
		635.93	2.00

32

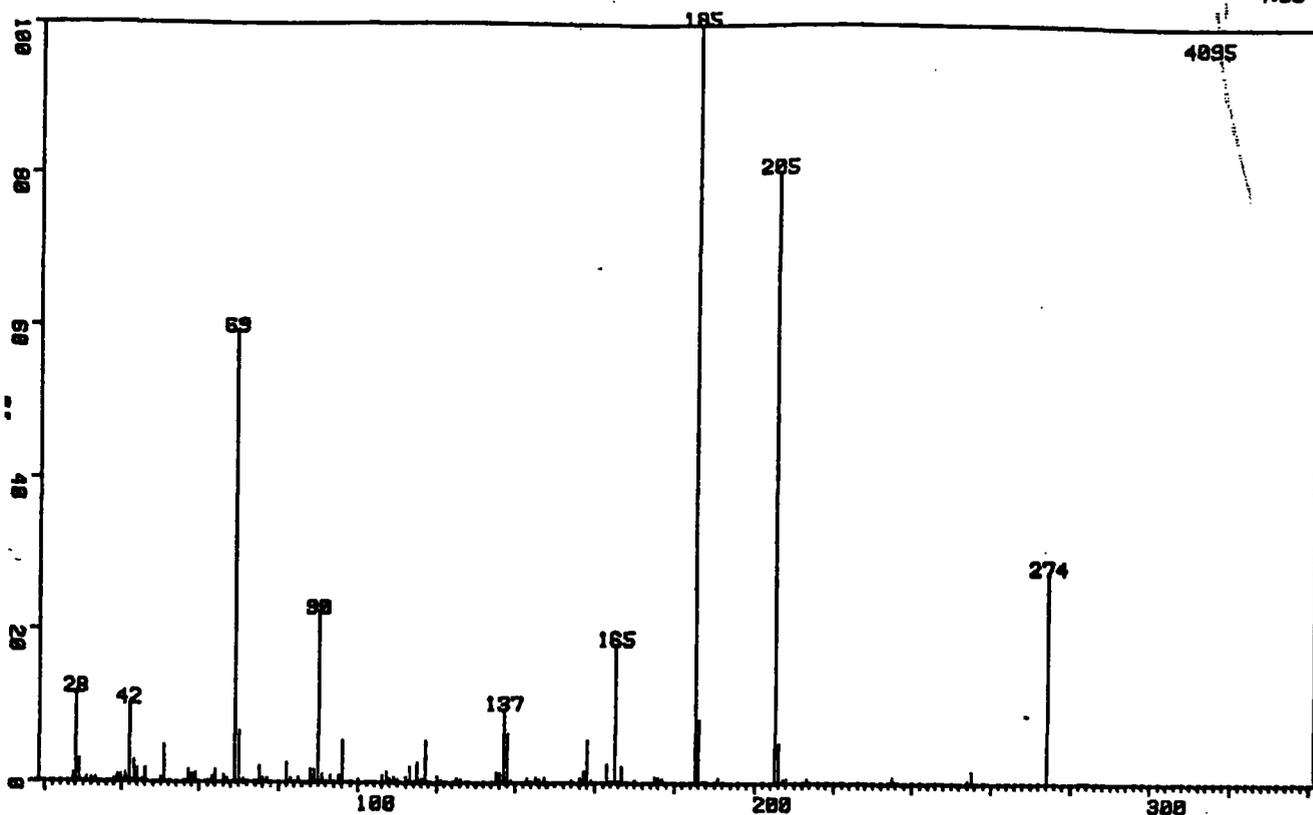


33

MASS	ZHT.	MASS	ZHT.
	BASE		BASE
33.06	0.51	117.09	5.47
38.04	0.32	119.98	0.88
38.96	1.03	121.03	0.34
39.85	0.95	125.09	0.46
40.93	1.34	126.10	0.39
42.02	10.38	135.11	1.42
43.08	2.91	136.09	1.37
44.09	1.86	137.04	9.67
45.12	0.24	138.02	6.59
46.12	1.83	139.02	0.42
49.87	0.61	143.03	0.51
50.94	4.86	145.06	0.78
57.08	1.71	165.07	18.10
58.06	1.10	166.82	2.08
58.98	1.20	170.05	0.32
63.07	0.76	175.12	0.93
64.10	1.64	176.09	0.85
66.11	0.90	177.09	0.56
67.08	0.54	185.08	100.00
68.95	59.07	185.98	8.42
69.90	6.79	187.08	0.27
71.00	0.27	191.04	0.56
75.07	2.15	205.11	80.37
76.07	0.54	205.98	5.20
77.06	0.46	207.09	0.42
81.98	2.54	208.06	0.63
83.02	0.46	213.08	0.51
85.02	0.71	235.12	0.85
88.01	1.71	254.09	0.42
88.97	1.56	255.08	1.51
89.93	22.20	274.14	27.67


MJS35X 11  
CAL: CALT1  
X 3

23-AUG-85  
1:41

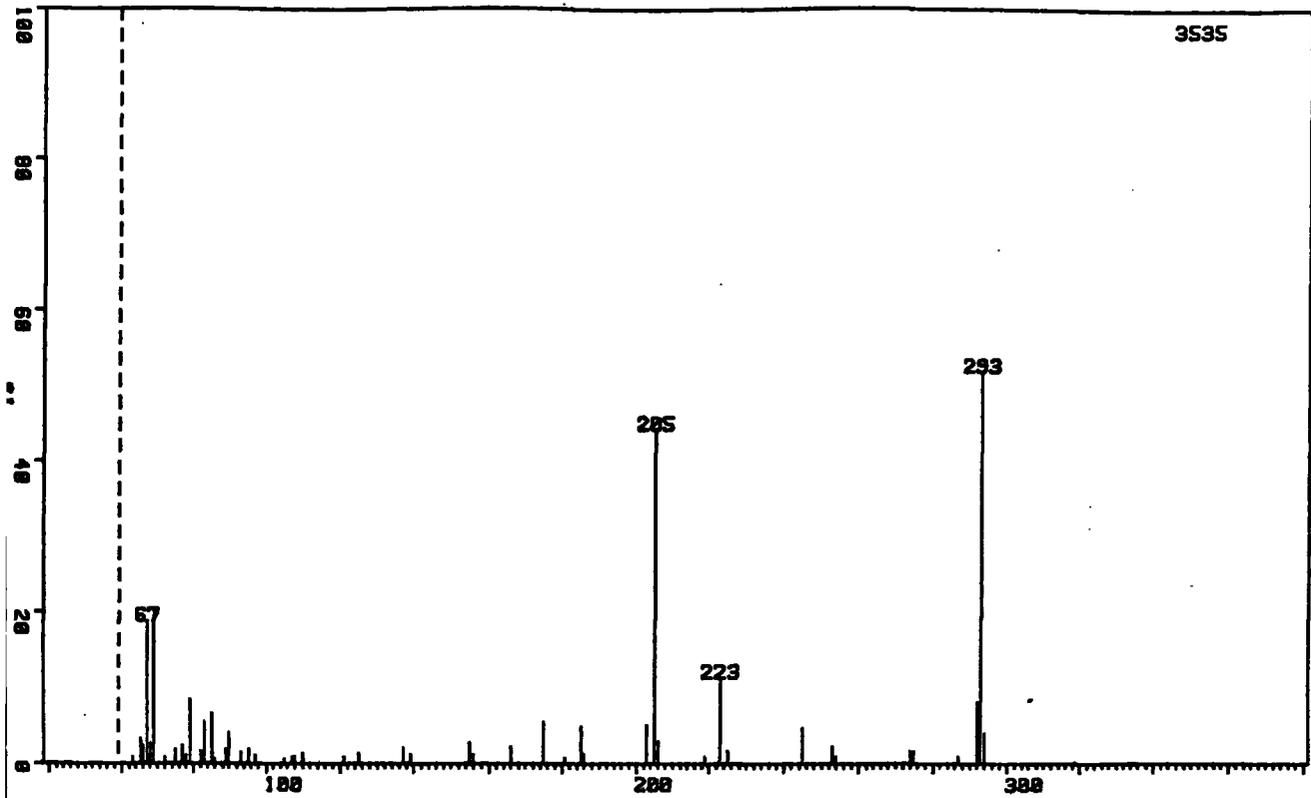


MASS	ZHT.	MASS	ZHT.
	BASE		BASE
26.34	5.04	68.02	0.92
28.17	12.92	68.97	6.77
29.03	100.00	72.03	0.31
29.44	0.22	75.01	0.64
29.48	0.22	77.01	0.81
29.86	2.56	78.00	0.39
37.09	3.09	78.96	2.81
38.04	12.42	82.02	0.56
38.87	0.25	136.92	0.70
38.90	0.33	138.98	0.42
39.17	0.72	154.90	0.92
39.85	65.23	155.91	0.42
42.02	90.23	165.89	0.75
42.76	0.22	174.89	1.84
43.08	92.18	180.85	0.28
44.14	13.89	184.98	1.64
45.13	1.56	185.92	0.45
48.93	0.36	202.83	1.70
49.84	2.26	204.93	14.53
53.04	24.47	205.94	1.03
54.08	5.60	218.91	0.31
55.10	64.00	222.88	3.76
56.10	98.41	224.94	0.58
56.76	0.25	244.94	1.56
57.07	90.87	252.86	0.75
58.04	95.63	253.92	0.33
58.98	3.26	273.86	0.58
63.02	0.31	274.93	0.56
65.06	1.11	286.92	0.33
66.05	0.81	291.87	2.70
67.04	6.21	292.92	17.01

34

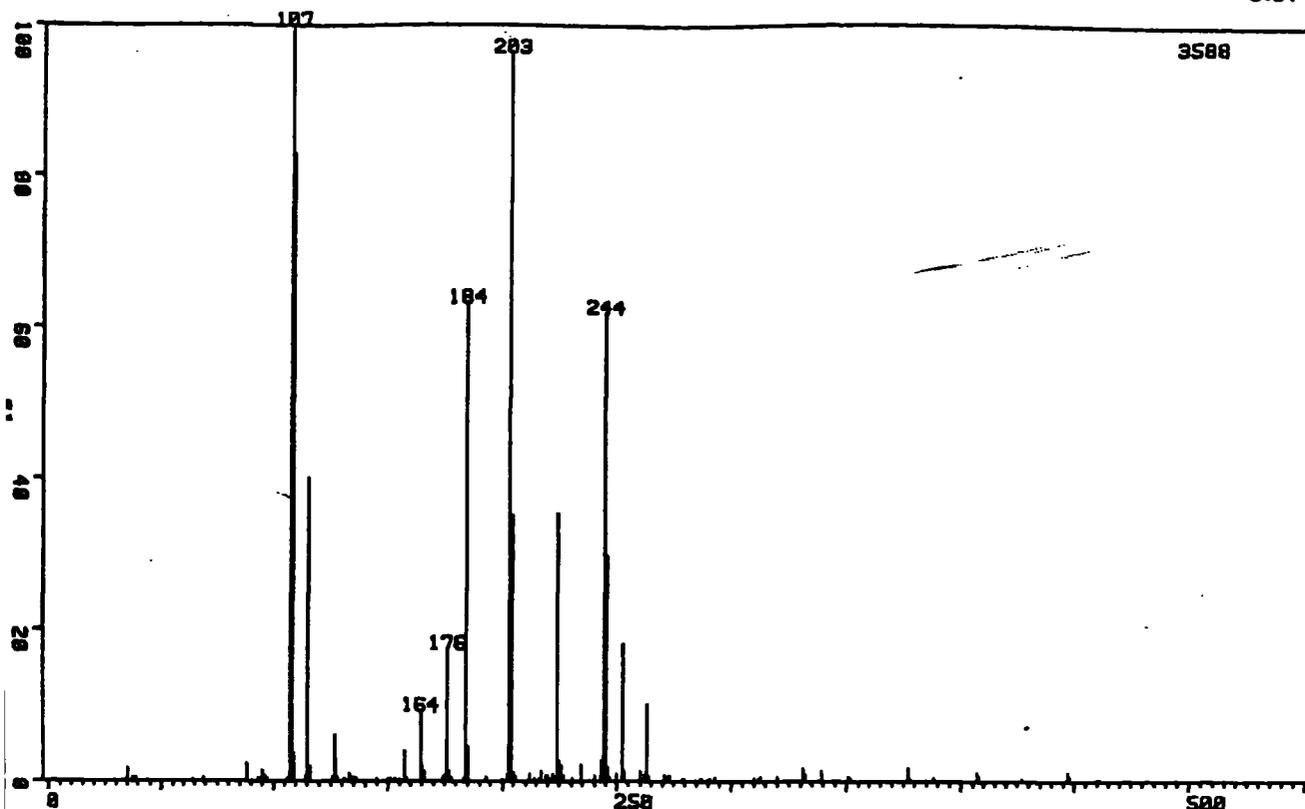MJS35 6  
CAL: CALN1622-OCT-85  
8:57


MASS	%HT. BASE	MASS	%HT. BASE	MASS	%HT. BASE
106.10	0.31	183.07	0.33	253.08	1.48
107.08	100.00	184.08	63.24	260.02	1.31
108.07	82.94	185.08	4.65	261.07	0.28
109.05	3.85	186.09	0.28	262.06	0.86
114.11	0.67	193.07	0.47	263.08	10.26
115.13	40.19	200.02	0.28	264.10	0.72
116.13	2.03	202.06	0.86	271.05	0.86
126.13	0.50	203.07	96.32	272.09	0.53
127.03	6.19	204.08	35.23	273.09	0.81
127.13	2.93	214.07	0.39	279.07	0.36
128.07	0.59	216.10	0.31	287.08	0.36
131.04	0.31	217.10	1.39	291.06	0.36
133.10	1.14	219.05	0.92	293.07	0.56
134.08	0.39	220.05	0.84	310.07	0.47
135.09	0.50	221.06	0.31	312.07	0.33
136.06	0.45	222.06	1.03	313.09	0.59
145.07	0.39	223.08	0.50	320.08	0.50
150.00	0.31	224.07	35.42	331.08	1.76
151.05	0.36	225.07	2.73	332.08	1.03
153.08	0.36	226.08	2.20	339.09	1.39
155.08	0.31	227.08	0.81	351.11	0.67
157.07	4.07	231.05	0.39	352.10	0.36
158.07	0.45	234.08	2.17	377.09	1.84
164.09	9.42	240.01	0.89	378.07	0.31
165.08	2.20	243.05	2.81	388.09	0.47
166.08	1.39	244.07	61.85	407.15	1.20
174.07	0.59	245.08	29.88	408.08	0.81
175.08	0.92	246.07	2.03	427.10	0.36
176.07	17.61	247.06	0.64	447.10	1.25
177.06	1.48	250.04	1.03	448.10	0.64
178.05	0.53	252.05	18.17	461.13	0.31

35

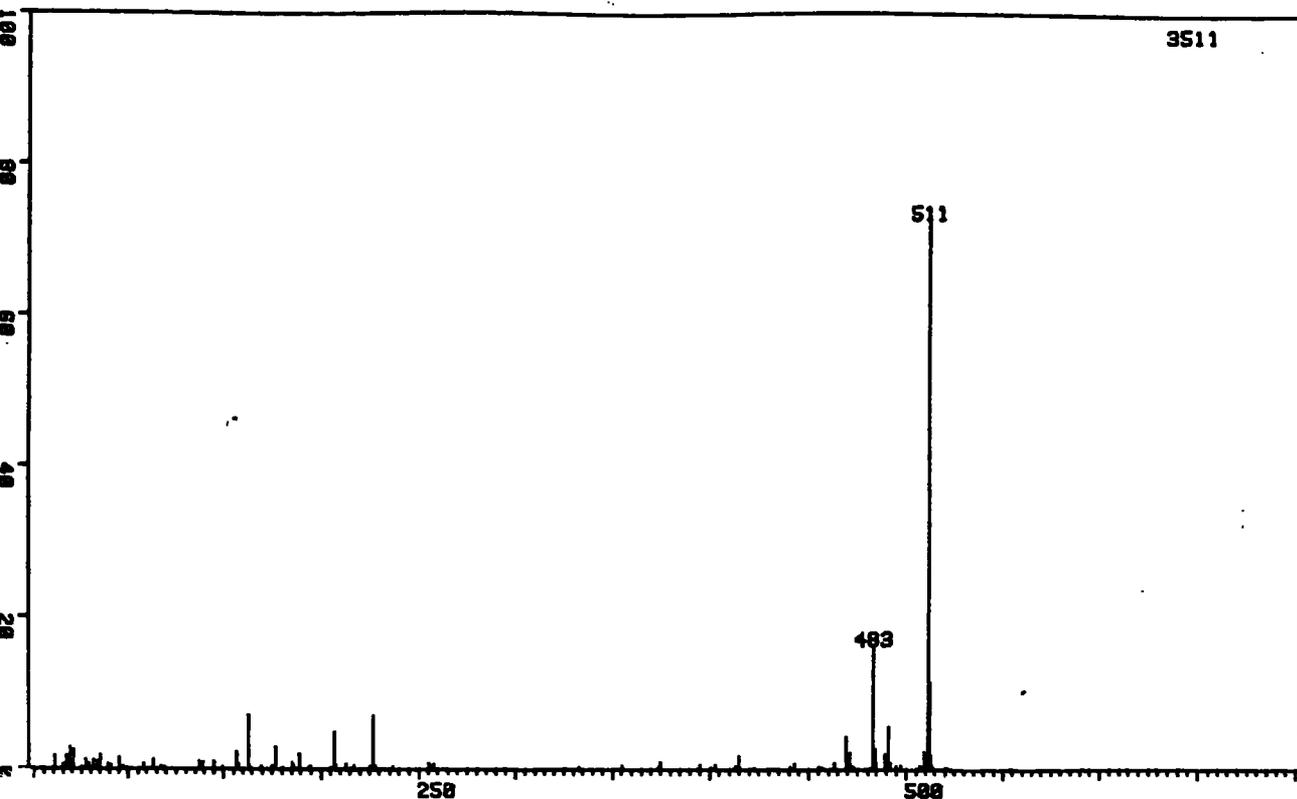
MJS27X 4  
CAL: CALTS11-OCT-85  
8:43

36


MASS	ZHT. BASE	MASS	ZHT. BASE
112.92	1.28	400.89	0.31
116.95	0.37	402.90	0.71
118.88	0.34	412.89	0.51
136.91	1.08	414.93	1.85
138.89	0.97	415.96	0.26
144.95	1.05	422.90	0.31
145.06	0.26	440.91	0.34
148.92	0.31	442.91	0.83
154.93	2.34	454.95	0.43
157.91	0.66	456.98	0.34
162.90	7.15	462.88	0.94
163.92	0.34	468.89	4.39
168.88	0.48	469.89	0.91
174.91	0.40	470.95	2.34
176.92	2.93	471.94	0.54
180.84	0.31	472.98	0.40
184.90	1.00	481.98	0.23
185.95	0.71	482.95	16.38
186.92	0.28	483.97	2.76
188.86	2.02	484.99	1.05
193.92	0.37	488.93	2.11
194.93	0.37	489.94	0.48
204.94	0.34	490.97	5.67
206.89	4.96	491.96	0.94
207.93	0.60	494.96	0.48
212.91	0.77	496.98	0.60
216.93	0.48	506.90	0.51
224.92	0.37	508.92	2.39
226.93	7.12	509.93	0.88
227.93	0.54	510.90	72.60
236.94	0.37	511.88	11.51

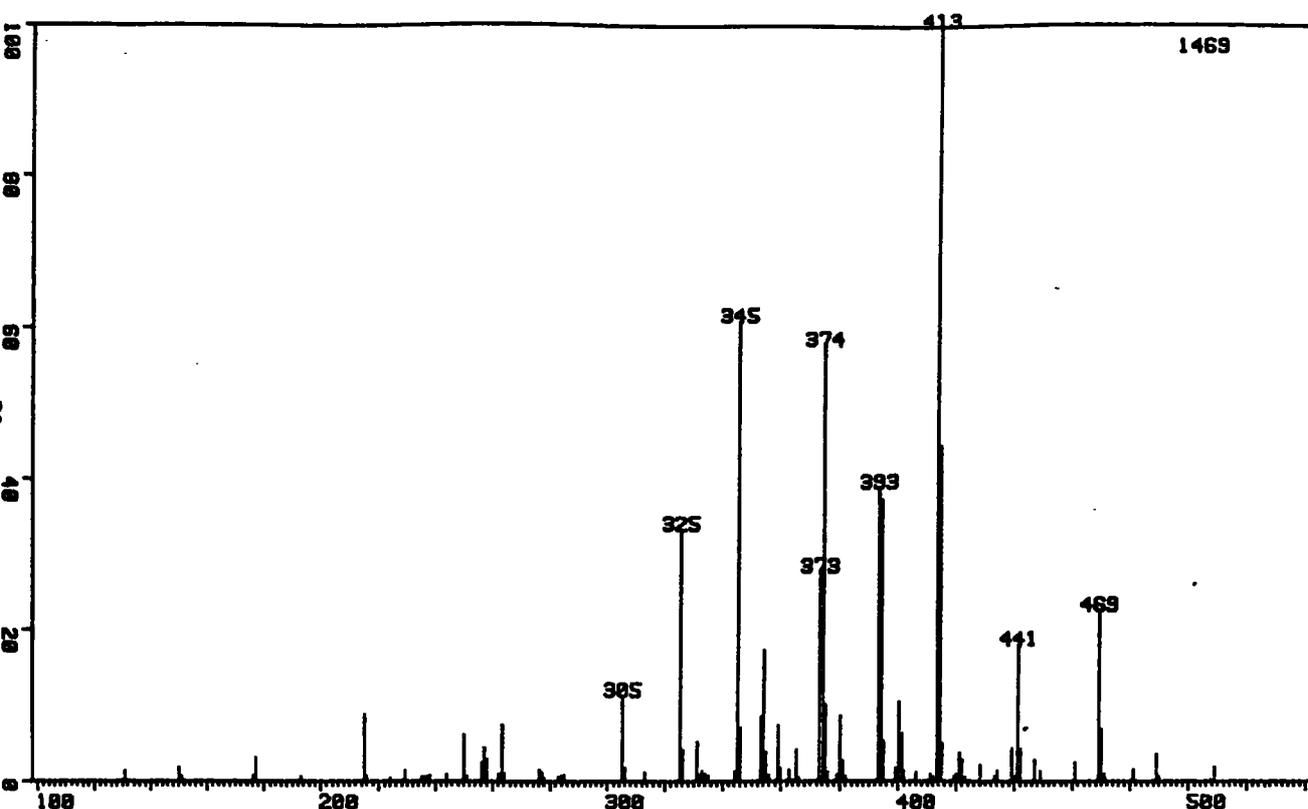MJS27X 12  
CAL: CALN411-OCT-85  
1:55

MASS	ZHT. BASE	MASS	ZHT. BASE	MASS	ZHT. BASE
37 150.00	1.84	325.10	33.49	400.01	10.55
151.02	0.68	326.07	4.22	401.06	6.33
176.06	0.75	331.04	5.31	402.06	1.43
177.07	3.20	332.07	0.88	406.06	1.23
193.07	0.68	333.09	1.50	411.09	0.95
215.08	8.92	334.08	1.09	412.04	0.61
216.10	0.75	335.08	0.88	413.08	100.00
224.06	0.68	344.09	1.36	414.08	44.38
229.09	1.50	345.08	61.06	415.11	5.11
235.11	0.61	346.08	7.22	419.07	0.75
236.06	0.68	353.08	8.65	420.03	1.02
237.07	0.61	354.07	17.49	421.04	3.81
238.05	0.82	355.05	3.95	422.06	2.86
244.05	0.95	356.07	1.02	423.08	0.61
250.02	6.19	359.03	7.49	428.03	2.18
251.05	0.75	360.02	1.84	433.07	0.75
256.09	2.52	363.06	1.57	434.11	1.43
257.10	4.56	365.09	4.15	439.04	4.42
258.08	3.00	366.07	0.61	440.05	0.75
262.08	1.02	373.08	27.84	441.07	18.18
263.10	7.56	374.09	58.00	442.05	4.29
264.09	1.09	375.10	10.28	447.07	2.93
276.11	1.57	376.07	1.29	449.07	1.36
277.06	1.23	379.09	0.88	461.08	2.52
278.07	0.54	380.07	8.65	469.04	22.74
283.06	0.61	381.06	2.72	470.06	7.01
284.07	0.75	382.09	0.75	471.06	1.02
285.08	0.82	393.09	38.87	481.05	1.57
305.06	11.37	394.11	37.30	489.09	3.61
306.09	1.84	395.06	5.38	490.07	0.75
313.06	1.16	399.02	1.84	509.06	1.97

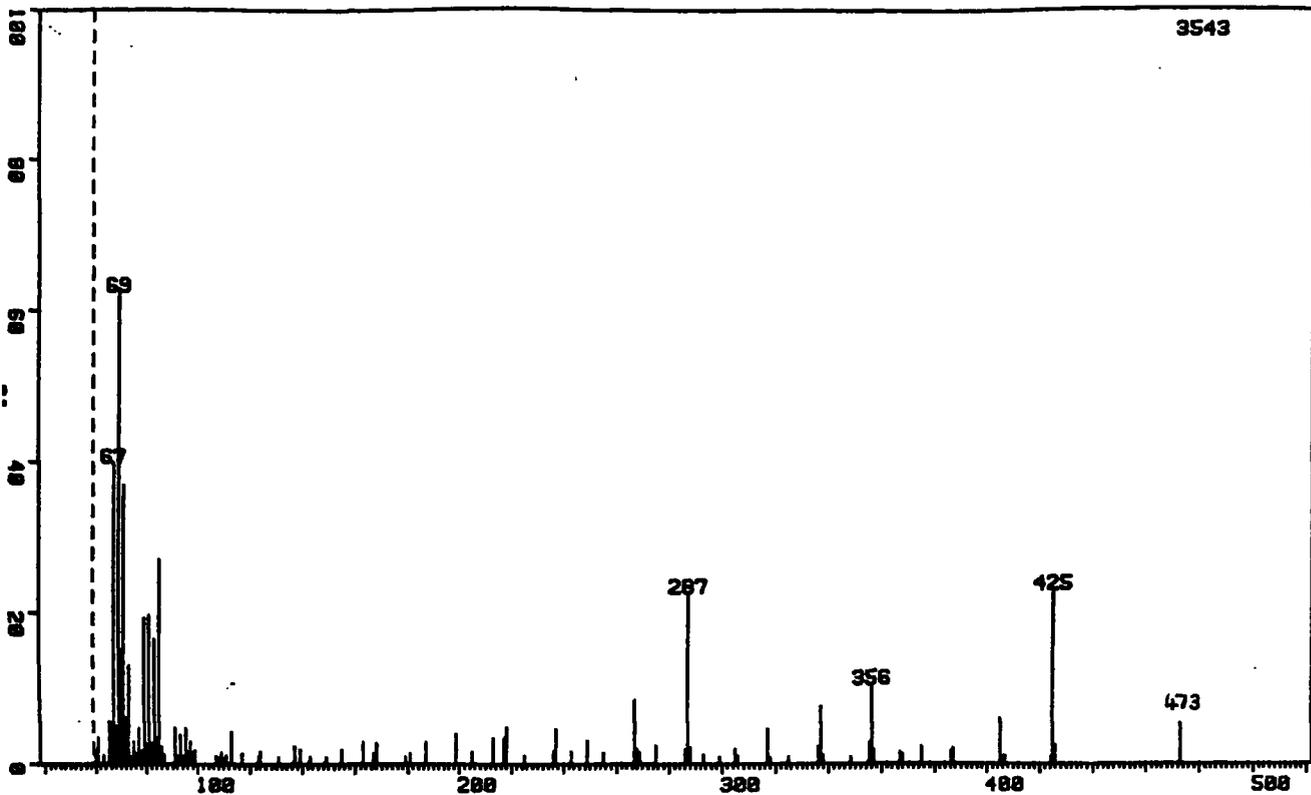
MS36X 4  
CAL:CALP15  
X 316-OCT-85  
8:41

MASS	ZHT. BASE	MASS	ZHT. BASE	MASS	ZHT. BASE
60.94	1.21	110.97	0.42	268.94	0.54
62.99	0.42	112.92	1.44	274.94	0.82
65.05	1.89	116.91	0.48	285.92	0.65
66.05	1.86	123.03	0.34	286.93	7.59
67.04	13.35	123.93	0.59	287.94	0.76
68.00	1.72	130.85	0.31	292.92	0.42
68.95	20.86	136.90	0.79	298.94	0.34
69.91	5.08	137.02	0.34	304.94	0.68
70.97	12.33	138.98	0.65	305.96	0.37
72.01	2.12	142.88	0.31	316.90	1.55
73.03	4.35	148.96	0.31	317.93	0.31
74.06	0.37	154.89	0.65	324.94	0.34
75.00	0.51	162.91	0.99	335.87	0.76
75.07	1.04	166.90	0.48	336.93	2.54
76.04	0.48	167.89	0.93	337.92	0.42
77.01	1.61	178.89	0.34	347.94	0.31
77.99	0.62	180.85	0.48	354.93	0.93
78.95	6.46	186.90	0.99	355.92	3.53
79.90	0.93	198.89	1.35	356.93	0.65
80.98	6.58	204.96	0.54	366.91	0.51
82.02	1.02	212.93	1.16	367.92	0.45
83.07	5.53	216.92	1.13	374.95	0.76
84.09	1.21	217.93	1.64	385.92	0.56
85.11	9.03	224.94	0.40	386.91	0.71
86.07	0.85	235.93	0.56	404.86	2.00
87.03	0.48	236.92	1.55	405.94	0.37
90.93	1.64	242.90	0.56	406.94	0.40
91.98	0.40	248.93	1.04	423.95	0.31
92.98	1.33	254.92	0.54	424.92	7.71
94.02	0.40	266.91	2.85	425.93	0.85
95.04	1.61	267.90	0.71	472.94	1.81

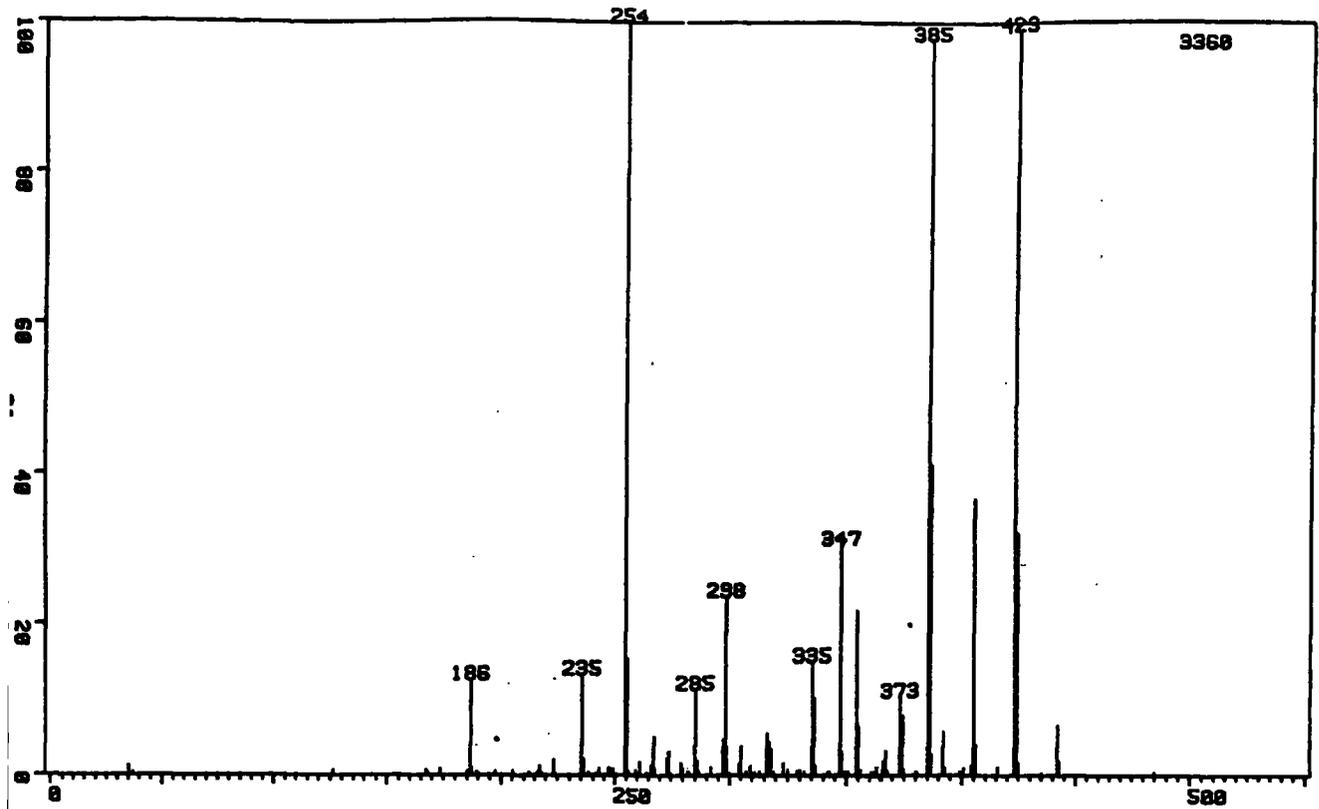


39

MASS	ZHT.	MASS	ZHT.	MASS	ZHT.
	BASE		BASE		BASE
205.39	0.60	285.99	2.05	350.88	0.62
212.34	0.42	287.00	0.45	353.89	21.90
216.35	0.45	291.95	1.10	354.94	6.64
217.34	1.28	296.95	4.73	355.95	0.74
218.32	0.42	297.97	23.87	360.86	0.51
223.33	2.14	298.96	3.90	361.98	0.39
235.27	13.42	299.93	0.33	362.92	1.19
236.22	2.20	303.94	1.52	365.93	1.93
238.13	0.39	304.96	3.93	366.91	3.30
242.12	0.36	306.95	0.51	367.92	0.51
243.13	0.98	308.91	1.34	372.90	10.54
247.08	1.04	310.90	0.45	373.93	8.07
248.07	0.83	312.93	0.45	374.94	0.77
249.07	0.80	315.88	5.60	379.90	0.51
254.06	100.00	316.94	4.55	380.93	0.39
255.06	15.45	317.94	3.51	384.92	97.74
256.07	0.62	318.94	0.45	385.91	41.28
259.01	0.68	322.92	1.64	386.91	2.89
261.02	1.73	324.92	0.80	391.90	5.80
264.05	0.36	328.87	0.62	392.89	1.07
266.04	1.31	329.90	0.74	398.94	0.57
267.04	5.21	331.90	0.57	400.89	0.98
268.03	0.92	334.95	15.24	403.94	1.31
273.02	2.26	335.94	10.30	404.95	36.64
274.02	3.24	336.94	1.28	405.96	4.08
275.03	0.36	341.92	0.51	415.90	1.07
279.00	1.67	342.91	0.57	422.89	99.05
279.98	0.86	346.92	30.83	423.94	32.02
281.97	0.62	347.91	3.24	424.91	1.73
282.98	0.39	348.90	0.45	434.90	0.36
284.98	11.52	349.90	0.45	441.86	6.64

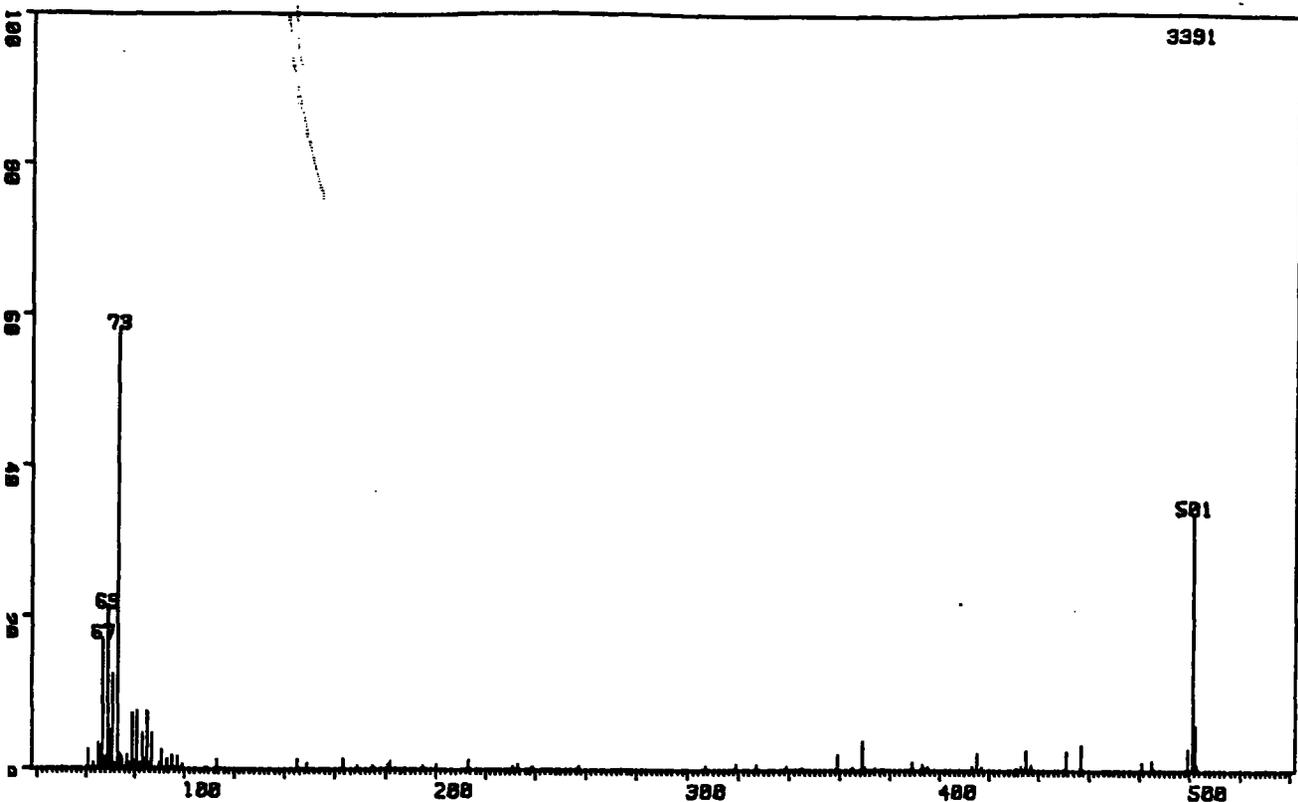

40

MASS	ZHT. BASE	MASS	ZHT. BASE	MASS	ZHT. BASE
60.93	2.45	79.90	1.03	256.98	0.44
63.01	0.86	80.96	7.64	306.99	0.59
65.06	3.33	82.01	0.80	318.96	0.86
66.07	2.83	83.05	4.75	326.98	0.77
67.06	17.10	84.08	1.27	338.99	0.47
68.03	1.47	85.08	7.52	345.00	0.32
68.93	2.77	86.09	0.74	359.00	2.12
69.00	21.14	87.05	4.69	365.04	0.41
69.95	5.10	89.88	0.65	368.95	3.83
71.01	12.44	90.96	2.36	369.97	0.44
72.05	0.74	93.00	0.80	374.09	0.35
73.07	58.04	93.06	1.30	376.99	0.29
74.09	2.12	95.02	1.03	388.96	1.09
75.04	0.53	95.09	1.65	392.98	0.88
75.11	1.50	97.09	1.53	394.96	0.47
77.01	1.86	99.05	0.62	413.04	0.56
77.99	0.77	108.95	0.32	415.00	2.27
78.96	7.28	112.97	1.30	417.00	0.44
		145.01	1.33	430.97	0.38
		148.97	0.91	433.03	0.71
		162.98	1.39	435.00	2.60
		168.97	0.47	437.02	0.80
		175.00	0.53	451.02	2.51
		180.94	0.65	457.01	3.30
		182.04	1.09	481.03	1.12
		195.01	0.56	485.05	1.42
		199.98	0.71	485.98	0.29
		212.97	1.24	499.05	2.98
		230.96	0.44	501.07	33.97
		232.99	0.80	502.09	6.05
		238.98	0.44	503.06	0.80

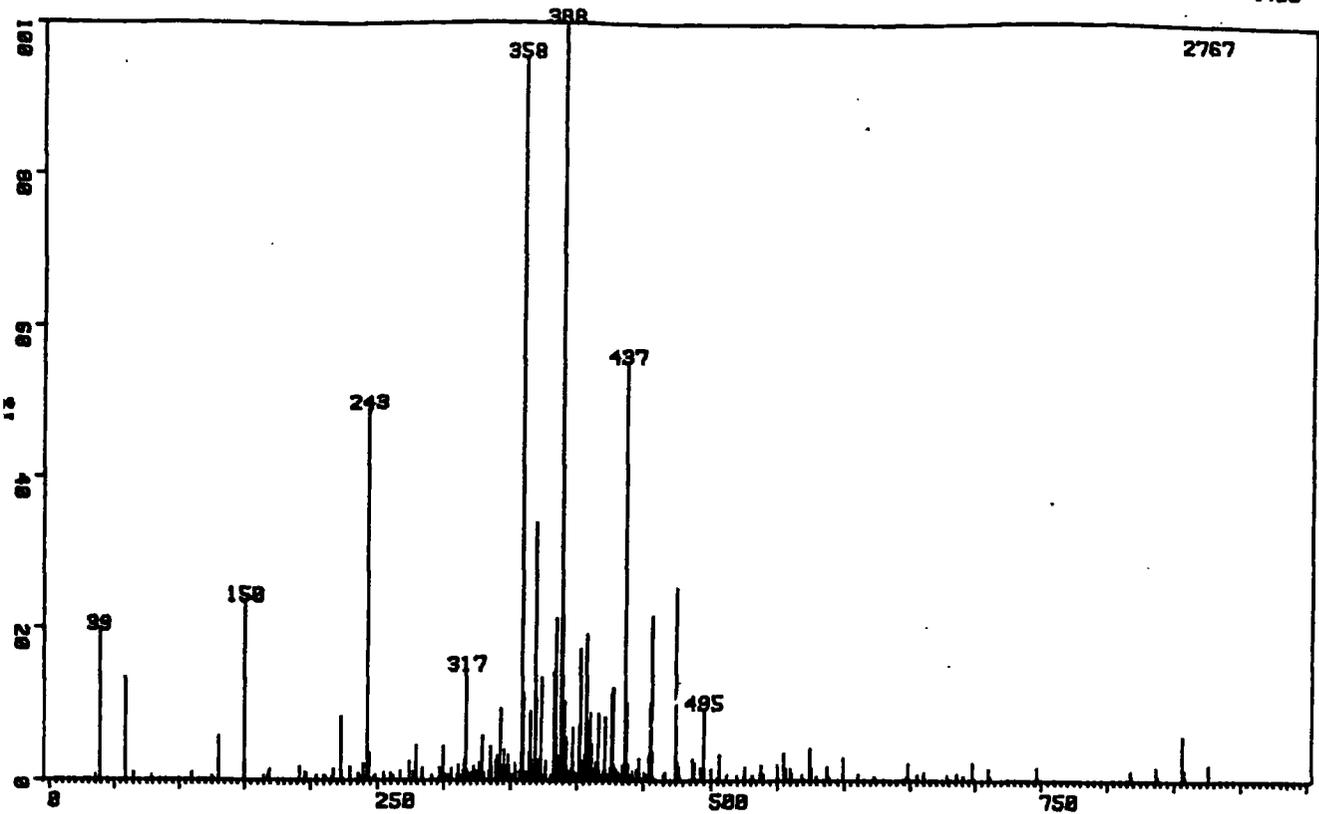MJS217 11  
CAL: CALT226-JUL-84  
1139


MASS	ZHT.	MASS	ZHT.	MASS	ZHT.
	BASE		BASE		BASE

41

357.43	1.26	454.26	3.29	554.95	3.51
358.38	95.41	455.30	10.16	556.00	1.12
359.32	11.49	456.26	21.65	557.05	1.52
360.35	4.12	457.30	3.83	560.00	1.48
361.32	1.12	458.26	0.65	561.91	0.90
383.09	14.20	465.17	0.69	568.83	0.83
384.04	21.21	467.10	1.12	574.67	4.26
385.07	5.75	474.05	25.44	575.65	1.59
386.10	2.28	475.04	7.08	579.56	0.51
387.06	3.18	476.04	2.49	587.55	1.84
388.09	100.00	476.94	1.84	588.55	0.69
389.04	21.83	477.93	0.65	599.32	2.96
390.00	3.32	486.85	2.86	611.04	0.90
390.97	10.37	487.87	0.83	622.98	0.47
392.01	5.42	488.79	2.35	647.68	0.47
392.98	5.75	492.80	1.73	648.54	2.28
401.77	7.16	493.74	0.72	655.50	0.72
402.77	17.35	494.86	9.43	660.38	1.05
403.77	2.57	495.79	1.55	678.33	0.69
406.77	7.48	500.58	1.45	686.23	0.90
407.77	19.08	505.67	0.36	691.05	0.47
408.77	7.70	506.63	3.47	698.02	2.35
426.61	11.31	507.59	0.98	709.87	1.63
427.58	12.03	512.55	0.83	711.76	0.47
436.53	55.19	519.41	0.76	747.18	1.73
437.52	10.12	525.34	0.51	817.23	1.26
438.51	1.55	526.34	1.84	836.98	1.70
439.42	2.10	531.22	0.76	837.93	0.76
440.42	0.61	532.35	0.69	856.77	5.96
442.44	1.26	537.24	1.01	857.74	1.37
445.38	1.37	538.26	2.02	876.33	2.20
446.38	0.83				


MJS113 9  
CAL: CALT1

23-JUL-85  
1:25

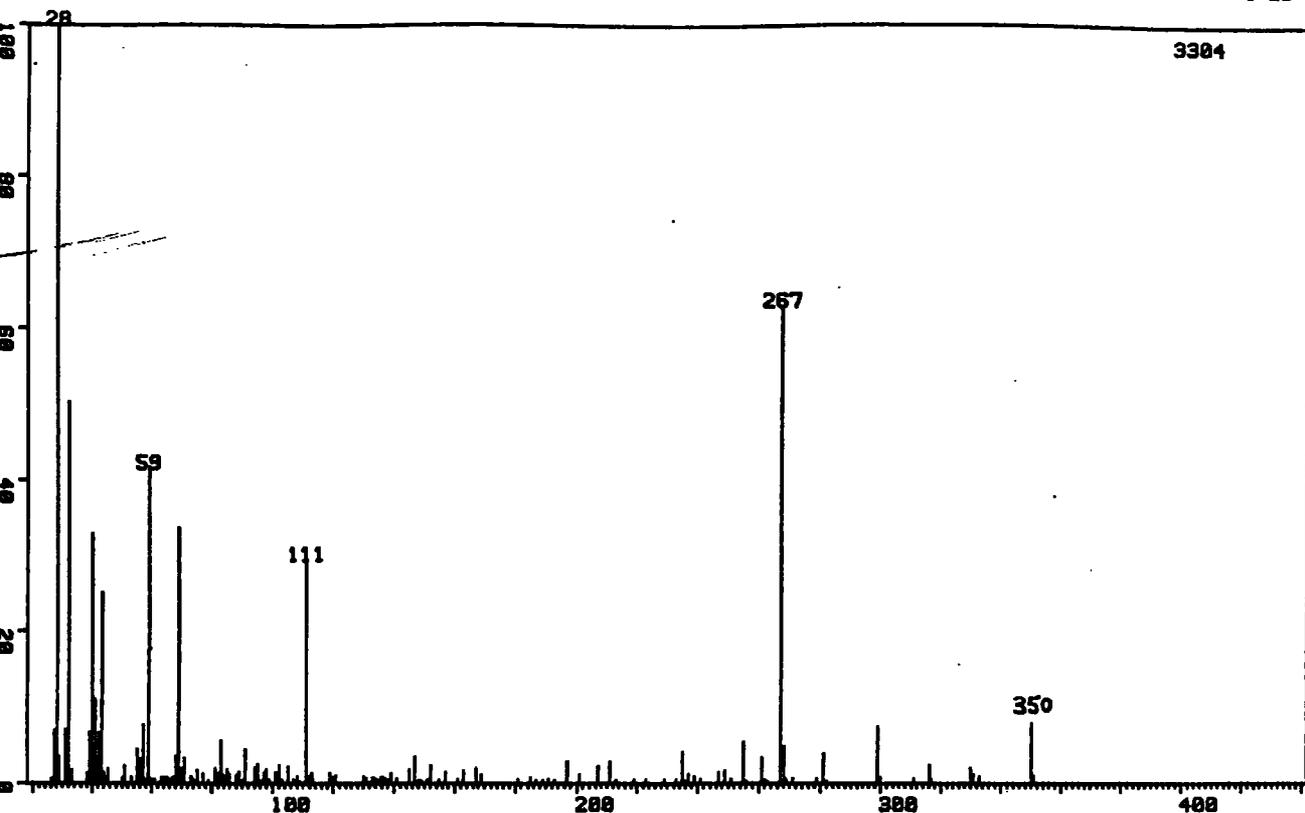

42

MASS	ZHT. BASE	MASS	ZHT. BASE	MASS	ZHT. BASE
44.11	0.48	100.93	1.48	234.92	4.15
44.17	0.82	101.97	2.45	235.91	0.42
45.15	2.00	103.00	0.45	236.91	1.30
49.88	0.73	105.04	2.27	238.90	1.06
50.94	2.30	106.97	0.51	240.92	0.61
53.05	0.45	107.95	1.06	246.94	1.54
53.09	0.88	108.99	0.27	248.92	1.76
55.10	2.12	110.89	29.36	250.93	0.61
55.14	4.51	111.03	0.88	254.92	5.48
56.14	3.30	111.95	1.06	255.93	0.42
57.07	2.24	112.07	0.58	260.93	3.48
57.12	7.75	112.96	1.42	261.95	0.48
58.05	0.39	118.91	1.39	262.94	0.33
58.08	0.64	118.98	1.42	266.92	62.92
58.97	41.53	119.94	0.88	267.91	4.96
59.90	0.70	120.91	1.12	268.90	0.64
60.95	0.64	129.88	1.00	270.89	0.67
63.05	0.85	130.94	0.73	278.91	0.70
64.07	0.85	132.98	0.79	280.92	4.00
65.10	0.94	134.08	0.54	281.95	0.33
66.07	0.58	134.98	0.39	298.88	7.45
66.11	0.54	135.99	0.94	299.90	0.88
67.03	0.91	136.97	0.76	310.90	0.70
67.06	0.85	137.95	0.39	315.92	2.42
68.00	3.66	138.93	1.42	316.92	0.51
68.93	33.72	140.91	0.70	329.90	2.06
69.86	0.79	144.98	1.88	330.94	1.24
69.97	2.03	146.97	3.57	332.93	1.00
71.04	3.36	147.96	0.39	349.91	8.05
73.08	1.06	148.93	0.33	350.92	1.09
		150.94	0.54		

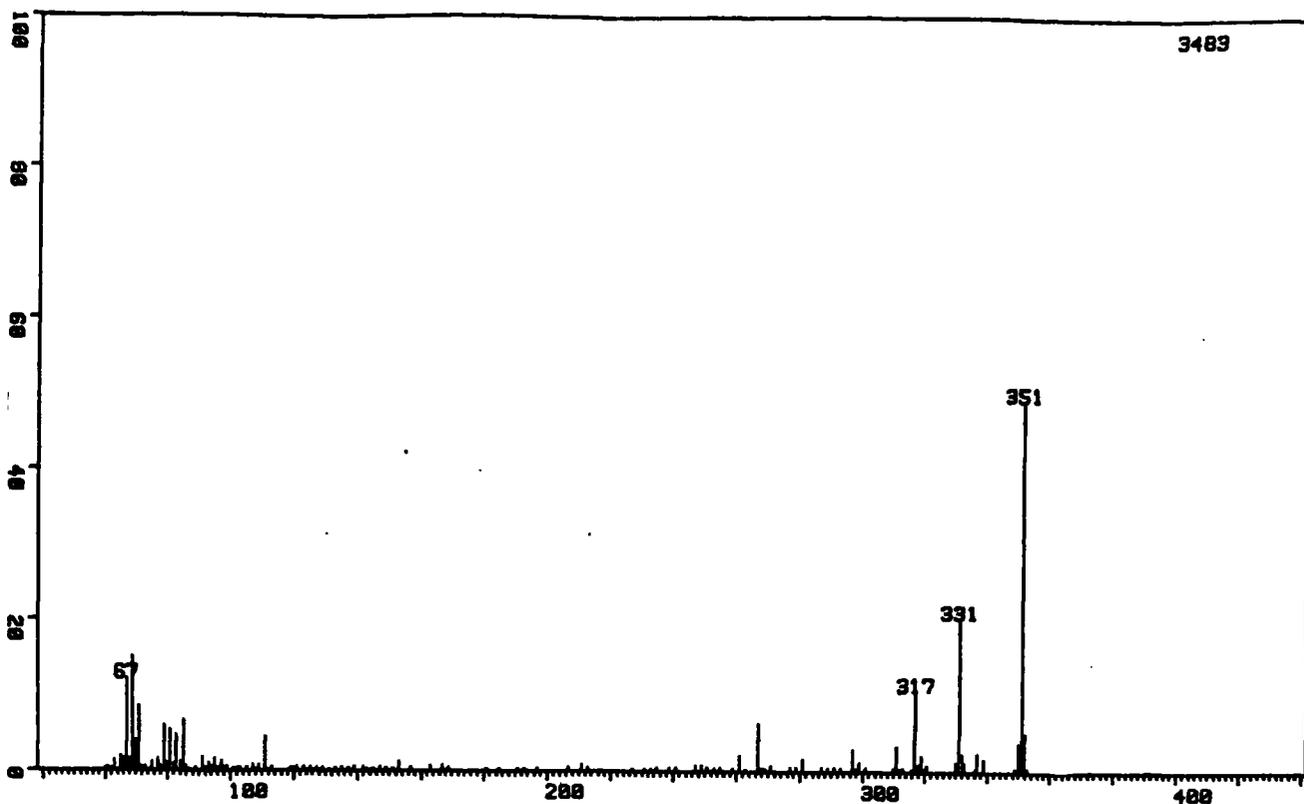MJS113 3  
CAL:CAL126-JUL-85  
8:33

MASS	ZHT. BASE	MASS	ZHT. BASE	MASS	ZHT. BASE
60.91	0.55	180.85	0.34	286.81	0.66
61.94	0.32	184.85	0.32	288.80	0.55
62.99	1.49	190.81	0.32	290.79	0.57
65.03	2.07	192.83	0.26	292.83	0.43
66.03	1.75	196.85	0.43	296.78	2.96
67.01	12.35	206.83	0.57	297.81	0.37
67.98	1.64	210.81	0.86	298.77	1.23
68.93	15.13	212.89	0.49	300.80	0.55
69.88	4.08	226.88	0.32	309.75	0.40
70.97	8.58	230.83	0.32	310.76	3.36
		232.86	0.32	311.79	0.40
		234.85	0.52	312.79	0.46
128.90	0.32	238.86	0.43	315.75	0.32
130.92	0.26	240.87	0.52	316.78	10.74
132.93	0.37	246.87	0.89	317.78	1.00
135.00	0.49	248.86	0.92	318.77	2.15
137.00	0.40	250.82	0.55	319.75	0.37
138.92	0.66	252.84	0.49	320.76	0.89
141.77	0.43	254.85	0.60	329.73	1.41
142.92	0.34	258.82	0.40	330.75	20.47
144.90	0.32	260.83	2.15	331.78	2.38
146.89	0.60	262.84	0.32	332.77	1.41
148.89	0.34	266.83	6.40	335.78	0.32
148.96	0.34	267.83	0.63	336.74	2.53
150.95	0.29	268.82	0.40	338.73	1.75
152.88	1.23	270.79	0.80	348.72	0.60
156.90	0.40	276.82	0.66	349.72	3.88
162.94	0.78	278.80	0.66	350.73	49.33
166.89	0.80	280.83	1.69	351.75	5.28
168.88	0.40				

43

COLLOQUIA AND CONFERENCES

COLLOQUIA AND CONFERENCES

The Board of Studies in Chemistry requires that each postgraduate research thesis contains an appendix listing:

- (A) all research colloquia, research seminars and lectures arranged by the Department of Chemistry during the period of the author's residence as a postgraduate student;
- (B) all research conferences attended and papers presented by the author during the period when research for the thesis was carried out;
- (C) details of the postgraduate induction course.

RESEARCH COLLOQUIA, SEMINARS AND LECTURES

A. Lectures and Seminars organised by the Department of Chemistry during the period 1982-1985

- 13.10.82 \* Dr. W.J. Feast (Durham)  
"Approaches to the Synthesis of Conjugated Polymers"
- 14.10.82 Prof. H. Suhr (Tubingen, FRG)  
"Preparative Chemistry in Nonequilibrium Plasmas"
- 27.10.82 Dr. C.E. Housecroft (Oxford High School/Notre Dame)  
"Bonding capabilities of butterfly-shaped Fe<sub>4</sub> units. Implications for C-H bond activation in hydrocarbon complexes"
- 28.10.82 \* Prof. M.F. Lappert, FRS (Sussex)  
"Approaches to Asymmetric Synthesis and Catalysis using electron-rich olefins and some of their metal complexes"
- 15.11.82 \* Dr G. Bertrand (Toulouse, France)  
"Curtius Rearrangement in Organometallic Series: A route for new hybridised species"
- 24.11.82 Prof. F.R. Hartley (R.M.C.S., Shrivenham)  
"Supported Metal-Complex Hydroformulation Catalysts"
- 24.11.82 \* Prof. G.G. Roberts (Applied Physics, Durham)  
"Langmuir-Blodgett films: Solid state polymerisation of diacetylenes"
- 8.12.82 Dr. G. Wooley (Trent)  
"Bonds in transition metal-cluster compounds"
12. 1.83 Dr. D.C. Sherrington (Strathclyde)  
"Polymer-supported phase transfer catalysts"
9. 2.83 Dr. P. Moore (Warwick)  
"Mechanistic studies in solution by stopped flow F.T.-NMR and high pressure NMR line broadening"
21. 2.83 Dr. R. Lynden-Bell (Cambridge)  
"Molecular motion in the cubic phase of NaCN"
2. 3.83 \* Dr. D. Bloor (Queen Mary College, London)  
"The solid-state chemistry of diacetylene monomers and polymers"
8. 3.83 Prof. D.C. Bradley, FRS (Queen Mary College, London)  
"Recent Developments in Organo-Imido-Transition Metal Chemistry"
9. 3.83 Dr. D.M.J. Lilley (Dundee)  
"DNA, Sequence, Symmetry, Structure and Supercoiling"

11. 3.83 \* Prof. H.G. Viehe (Louvain, Belgium)  
"Oxidations on Sulphur" and  
"Fluorine substitutions in radicals"  
(The W.K.R. Musgrave Lecture)
16. 3.83 Dr. I. Gosney (Edinburgh)  
"New extrusion reactions: Organic synthesis  
in a hot-tube"
25. 3.83 Prof. F.G. Baglin (Nevada, USA)  
"Interaction induced Raman Spectroscopy in  
Supracritical ethane"
21. 4.83 Prof. J. Passmore (New Brunswick, Canada)  
"Novel selenium-iodine cations"
4. 5.83 Prof. P.H. Plesch (Keele)  
"Binary ionisation equilibria between two ions  
and two molecules. What Ostwald never thought of"
10. 5.83 \* Prof. W. Burger (Munich, FRG)  
"New reaction pathways from trifluoromethyl-  
substituted heterodienes to partially fluorinated  
heterocyclic compounds"
11. 5.83 \* Dr. N. Isaacs (Reading)  
"The application of high pressures to the theory  
and practice of organic chemistry"
13. 5.83 Dr. R. de Koch (Michigan/Amsterdam)  
"Electronic structural calculations in organo-  
metallic cobalt cluster molecules. Implications  
for metal surfaces"
13. 5.83 Dr. T.B. Marder (UCLA/Bristol)  
"The Chemistry of Metal-carbon and metal-metal  
multiple bonds"
16. 5.83 Prof. R.J. Lagow (Texas, USA)  
"The chemistry of polylithium organic compounds.  
An unusual class of matter"
18. 5.83 Dr. D.M. Adams (Leicester)  
"Spectroscopy at very high pressures."
25. 5.83 Dr. J.M. Vernon (York)  
"New heterocyclic chemistry involving lead  
tetraacetate"
15. 6.83 Dr. A. Pietrzykowski (Warsaw/Strathclyde)  
"Synthesis, structure and properties of Aluminoxanes"
22. 6.83 Dr. D.W.H. Rankin (Edinburgh)  
"Floppy molecules - the influence of phase on  
structure"
5. 7.83 \* Prof. J. Miller (Camfinas, Brazil)  
"Reactivity in nucleophilic substitution reactions"

- 5.10.83 Prof. J.P. Maier (Basel, Switzerland)  
"Recent approaches to spectroscopic characterization of cations"
- 12.10.83 \* Dr. C.W. McLeland (Port Elizabeth, Australia)  
"Cyclization of aryl alcohols through the intermediacy of alkoxy radicals and aryl radical cations"
- 19.10.83 Dr. N.W. Alcock (Warwick)  
"Aryl tellurium (IV) compounds, patterns of primary and secondary bonding"
- 26.10.83 \* Dr. R.H. Friend (Cavendish, Cambridge)  
"Electronic properties of conjugated polymers"
- 30.11.83 Prof. I.M.G. Cowie (Stirling)  
"Molecular interpretation of non-relaxation processes in polymer glasses"
- 2.12.83 \* Dr. G.M. Brooke (Durham)  
"The fate of the ortho-fluorine in 3,3-sigmatropic reactions involving polyfluoro-aryl and -hetero-aryl systems"
- 14.12.83 Prof. R.J. Donovan (Edinburgh)  
"Chemical and physical processes involving the ion-pair states of the halogen molecules"
10. 1.84 Prof. R. Hester (York)  
"Nanosecond Laser Spectroscopy of Reaction Intermediates"
18. 1.84 Prof. R.K. Harris (UEA)  
"Multi-nuclear solid state magnetic resonance"
8. 2.84 Dr. B.T. Heaton (Kent)  
"Multi-nuclear NMR studies"
15. 2.84 Dr. R.M. Paton (Edinburgh)  
"heterocyclic Syntheses using Nitrile Sulphides"
7. 3.84 Dr. R.T. Walker (Birmingham)  
"Synthesis and Biological Properties of some 5-substituted Uracil Derivatives; yet another example of serendipity in Anti-viral Chemotherapy"
21. 3.84 Dr. P. Sherwood (Newcastle)  
"X-ray photoelectron spectroscopic studies of electrode and other surfaces"
21. 3.84 Dr. G. Beaman (Durham/Kratos)  
"EXAFS: General Principles and Applications"
23. 3.84 Dr. A. Ceulemans (Leuven)  
"The Development of Field-Type models of the Bonding in Molecular Clusters"
2. 4.84 \* Prof. K. O'Driscoll (Waterloo)  
"Chain Ending reactions in Free Radical Polymerisation"

3. 4.84 Prof. C.H. Rochester (Dundee)  
"Infrared Studies of Adsorption at the Solid-Liquid Interface"
25. 4.84 Dr. R.M. Acheson (Biochemistry, Oxford)  
"Some Heterocyclic Detective Stories"
27. 4.84 Dr. T. Albright (Houston, U.S.A.)  
"Sigmatropic Rearrangements in Organometallic Chemistry"
14. 5.84 \* Prof. W.R. Dolbier (Florida, USA)  
"Cycloaddition Reactions of Fluorinated Allenes"
16. 5.84 Dr. P.J. Garratt (UCL)  
"Synthesis with Dilithiated Vicinal Diesters and Carboximides"
22. 5.84 Prof. F.C. de Schryver (Leuven)  
"The use of Luminescence in the study of micellar aggregates" and  
"Configurational and Conformational control in excited state complex formation"
23. 5.84 Prof. M. Tada (Waseda, Japan)  
"Photochemistry of Dicyanopyrazine Derivatives"
31. 5.84 Dr. A. Haaland (Oslo)  
"Electron Diffraction Studies of some organometallic compounds"
11. 6.84 \* Dr. J.B. Street (IBM, California)  
"Conducting Polymers derived from Pyrroles"
19. 9.84 \* Dr. C. Brown, (IBM, California)  
"New Superbase reactions with organic compounds"
21. 9.84 \* Dr. H.W. Gibson (Signal UOP, Illinois)  
"Isomerization of Polyacetylene"
- 19.10.84 \* Dr. A. Germain (Languedoc, Montpellier)  
"Anodic Oxidation of Perfluoro Organic Compounds in Perfluoroalkane Sulphonic Acids"
- 24.10.84 \* Prof. R.K. Harris (Durham)  
"N.M.R. of Solid Polymers"
- 28.10.84 Dr. R. Snaith (Strathclyde)  
"Exploring Lithium Chemistry: Novel Structures, Bonding and Reagents"
- 7.11.84 Prof. W.W. Porterfield (Hampden-Sydney College, USA)  
"There is no Borane Chemistry (only Geometry)"
- 7.11.84 \* Dr. H.S. Munro (Durham)  
"New Information from ESCA Data"
- 21.11.84 Mr. N. Everall (Durham)  
"Picosecond Pulsed Laser Raman Spectroscopy"

- 27.11.84 \* Dr. W.J. Feast (Durham)  
"A Plain Man's Guide to Polymeric Organic Metals"
- 28.11.84 Dr. T.A. Stephenson (Edinburgh)  
"Some recent studies in Platinum Metal Chemistry"
- 12.12.84 Dr. K.B. Dillon (Durham)  
"<sup>31</sup>P N.M.R. Studies of some Anionic Phosphorus Complexes"
11. 1.85 Emeritus Prof. H. Suschitzky (Salford)  
"Fruitful Fissions of Benzofuroxanes and Isobenzimidazoles (umpolung of o-phenylenediamine)"
13. 2.85 Dr. G.W.J. Flett (Oxford)  
"Synthesis of some Alkaloids from Carbohydrates"
19. 2.85 \* Dr. D.J. Mincher (Durham)  
"Stereoselective Synthesis of some novel Anthra-cyclinones related to the anti-cancer drug Adriamycin and to the Steffimycin Antibiotics"
27. 2.85 \* Dr. R.E. Mulvey (Durham)  
"Some unusual Lithium Complexes"
6. 3.85 Dr. P.J. Kocienski (Leeds)  
"Some Synthetic Applications of Silicon-Mediated Annulation Reactions"
7. 3.85 Dr. P.J. Rodgers (I.C.I. plc. Agricultural Division, Billingham)  
"Industrial Polymers from Bacteria"
12. 3.85 Prof. K.J. Packer (B.P. Ltd./East Anglia)  
"N.M.R. Investigations of the Structure of Solid Polymers"
14. 3.85 \* Prof. A.R. Katritzky F.R.S. (Florida)  
"Some Adventures in Heterocyclic Chemistry"
20. 3.85 Dr. M. Poliakoff (Nottingham)  
"New Methods for detecting Organometallic Intermediates in Solution"
28. 3.85 Prof. H. Ringsdorf (Mainz)  
"Polymeric Liposomes as Models for Biomembranes and Cells?"
24. 4.85 Dr. M.C. Grossel (Bedford College, London)  
"Hydroxypyridone dyes -Bleachable one-dimensional Metals?"
25. 4.85 Major S.A. Shackelford (U.S. Air Force)  
"In Situ Mechanistic Studies on Condensed Phase Thermochemical Reaction Processes: Deuterium Isotope Effects in HMX Decomposition, Explosives and Combustion"
1. 5.85 Dr. D. Parker (I.C.I. plc, Petrochemical and Plastics Division, Wilton)  
"Applications of Radioisotopes in Industrial Research"

7. 5.85 Prof. G.E. Coates (formerly of University of Wyoming, U.S.A.)  
"Chemical Education in England and America: Successes and Deficiencies"
8. 5.85 Prof. D. Tuck (Windsor, Ontario)  
"Lower Oxidation State Chemistry of Indium"
8. 5.85 \* Prof. G. Williams (U.C.W. Aberystwyth)  
"Liquid Crystalline Polymers"
9. 5.85 \* Prof. R.K. Harris (Durham)  
"Chemistry in a Spin: Nuclear Magnetic Resonance"
14. 5.85 Prof. J. Passmore (New Brunswick, U.S.A.)  
"The Synthesis and Characterisation of some Novel Selenium-Iodine Cations, aided by  $^{77}\text{Se}$  N.M.R. Spectroscopy"
15. 5.85 Dr. J.E. Packer (Auckland, New Zealand)  
"Studies of Free Radical Reactions in aqueous solution using Ionising Radiation"
17. 5.85 Prof. I.D. Brown (McMaster University, Canada)  
"Bond Valence as a Model for Inorganic Chemistry"
21. 5.85 Dr. D.L.H. Williams (Durham)  
"Chemistry in Colour"
22. 5.85 \* Dr. M. Hudlicky (Blacksburg, U.S.A.)  
"Preferential Elimination of Hydrogen Fluoride from Vicinal Bromofluorocompounds"
22. 5.85 \* Dr. R. Grimmett (Otago, New Zealand)  
"Some Aspects of Nucleophilic Substitution in Imidazoles"
4. 6.85 Dr. P.S. Belton (Food Research Institute, Norwich)  
"Analytical Photoacoustic Spectroscopy"
13. 6.85 Dr. D. Woolins (Imperial College, London)  
"Metal - Sulphur - Nitrogen Complexes"
14. 6.85 \* Prof. Z. Rappoport (Hebrew University, Jerusalem)  
"The Rich Mechanistic World of Nucleophilic Cyclic Substitution"
19. 6.85 Dr. T.N. Mitchell (Dortmund)  
"Some Synthetic and NMR - Spectroscopic Studies of Organotin Compounds"
26. 6.85 Prof. G. Shaw (Bradford)  
"Synthetic Studies on Imidazole Nucleosides and the Antibiotic Coformycin"
12. 7.85 \* Dr. K. Laali (Hydrocarbon Research Institute, University of Southern California)  
"Recent Developments in Superacid Chemistry and Mechanistic Considerations in Electrophilic Aromatic Substitutions; a Progress Report"

B. Lectures Organised by Durham University Chemical Society during the period 1982-1985

- 14.10.82 \*Mr. F. Shenton (County Analyst, Durham)  
"There is death in the pot"
- 28.10.82 Prof. M.P. Lappert, F.R.S. (Sussex)  
"The Chemistry of Some Unusual Subvalent Compounds of the Main Group IV and V Elements"
- 4.11.82 Dr. D.H. Williams (Cambridge)  
"Studies on the Structures and Modes of Action of Antibiotics"
- 11.11.82 Dr. J. Cramp (I.C.I. plc)  
"Lasers in Industry"  
(Joint Lecture with the Society of Chemical Industry)
- 25.11.82 Dr. D.H. Richards, P.E.R.M.E. (Ministry of Defence)  
"Terminally Functional Polymers - their Synthesis and Uses"
27. 1.83 \*Prof. D.W.A. Sharp (Glasgow)  
"Some Redox Reactions in Fluorine Chemistry"
3. 2.83 Dr. R. Manning (Dept. Zoology, Durham)  
"Molecular Mechanisms of Hormone Action"
10. 2.83 Sir G. Allen, F.R.S. (Unilever Ltd.)  
"U.K. Research"
17. 2.83 Prof. A.G. MacDiarmid (Pennsylvania)  
"Metallic Covalent Polymers (SN)<sub>x</sub> and (CH)<sub>x</sub> and their Derivatives" (R.S.C. Centenary Lecture)
3. 4.83 \*Prof. A.C.T. North (Leeds)  
"The Use of a Computer Display System in Studying Molecular Structures and Interactions"
- 20.10.83 \*Prof. R.B. Cundall (Salford)  
"Explosives"
- 3.11.83 \*Dr. G. Richards (Oxford)  
"Quantum Pharmacology"
- 10.11.83 \*Prof. J.H. Ridd (U.C.L.)  
"Ipso-Attack in Electrophilic Aromatic Substitution"
- 17.11.83 \*Dr. J. Harrison (Sterling Organic)  
"Applied Chemistry and the Pharmaceutical Industry"  
(Joint Lecture with the Society of Chemical Industry)
- 24.11.83 \*Prof. D.A. King (Liverpool)  
"Chemistry in 2-Dimensions"
- 1.12.83 \*Dr. J.D. Coyle (The Open University)  
"The Problem with Sunshine"
26. 1.84 \*Prof. T.L. Blundell (Birkbeck College, London)  
"Biological Recognition: Interactions of Macromolecular surfaces"

2. 2.84 \*Prof. M.B.H. Jonathan (Southampton)  
"Photoelectron Spectroscopy - A Radical Approach"
12. 6.84 \*Prof. D. Phillips (The Royal Institution)  
"Luminescence and Photochemistry - A Light Entertainment"
23. 2.84 \*Prof. F.G.A. Stone F.R.S. (Bristol)  
"The Use of Carbene and Carbyne Groups to Synthesise Metal Clusters"  
(The Waddington Memorial Lecture)
1. 3.84 \*Prof. A.J. Leadbetter (Rutherford Appleton Labs.)  
"Liquid Crystals"
3. 3.84 \*Prof. D. Chapman (Royal Free Hospital School of Medicine, London)  
"Phospholipids and Biomembranes, Basic Science and Future Technique"
28. 3.84 \*Prof. H. Schmidbaur (Munich, F.R.G.)  
"Ylides in Coordination Sphere of Metal: Synthetic, Structural and Theoretical Aspects"  
(R.S.C. Centenary Lecture)
- 13.10.84 Dr. N. Logan (Nottingham)  
" $N_2O_4$  and Rocket Fuels"
- 23.10.84 \*Dr. W.J. Feast (Durham)  
"Syntheses of Conjugated Polymers. How and Why?"
- 3.11.84 Prof. B.J. Aylett (Queen Mary College London)  
"Silicon - Dead Common or Refined?"
- 15.11.84 Prof. B.T. Golding (Newcastle-upon-Tyne)  
"The Vitamin B<sub>12</sub> Mystery"
- 22.11.84 \*Prof. D.T. Clark (I.C.I. New Science Group)  
"Structure, Bonding, Reactivity and Synthesis as Revealed by ESCA"  
(R.S.C. Tilden Lecture)
- 29.11.84 Prof. C.J.M. Stirling (University College of North Wales)  
"Molecules taking the Strain"
- 6.12.84 \*Prof. R.D. Chambers (Durham)  
"The Unusual World of Fluorine"
24. 1.85 Dr. A.K. Covington (Newcastle-upon-Tyne)  
"Chemistry with Chips"
31. 1.85 Dr. M.L.H. Green (Oxford)  
"Naked Atoms and Negligee Ligands"
7. 2.85 Prof. A. Ledwith (Pilkington Bros.)  
"Glass as a High Technology Material"  
(Joint Lecture with the Society of Chemical Industry)
14. 2.85 Dr. J.A. Salthouse (Manchester)  
"Son et Lumiere"

21. 2.85 Prof. P.M. Maitlis, F.R.S. (Sheffield)  
"What Use is Rho $\delta$ ium?"

7. 3.85 Dr. P.W. Atkins (Oxford)  
"Magnetic Reactions"

(C) Research Conferences attended

Graduate Symposium, Durham, April 1983

17th Sheffield Symposium on "Modern Aspects of Stereochemistry",  
Sheffield, 21 December 1983

Graduate Symposium, Durham, April 1984

International Symposium on "Chemistry of Carbanions",  
University of Durham, 16-20 July 1984

Graduate Symposium, Durham, April 1985

(D) First Year Induction Course, October 1982

This course consists of a series of one hour lectures  
on the services available in the department.

1. Departmental organisation
2. Safety matters
3. Electrical appliances and infrared spectroscopy
4. Chromatography and Microanalysis
5. Atomic absorptiometry and inorganic analysis
6. Library facilities
7. Mass spectrometry
8. Nuclear magnetic resonance spectroscopy
9. Glassblowing technique.

REFERENCES

REFERENCES

1. A.A. Woolf, J. Fluorine.Chem., 1934, 25, 41-5
2. "The Strengths of Chemical Bonds" (2nd Ed.), T.L.Cottrell, Butterworths Scientific Publications, London, 1958.
3. "Preparation, Properties and Industrial Applications of Organofluorine Compounds", M. le Blanc *et al*, ed.R.E.Banks, Ellis Horwood: Chichester, 1982.
4. "Organic Fluorine Chemistry", W.A. Sheppard and C.M. Shorts, Inc., New York, 1969, ch.p.
5. "Organofluorine Chemicals and their Industrial Applications" R.F. Anderson and J.O. Punderson, ed. R.E. Banks, Ellis Horwood: Chichester, 1982.
6. "Preparation, Properties and Industrial Applications of Organofluorine Compounds", S. Smith, ed. R.E. Banks, Ellis Horwood: Chichester, 1979.
7. D.J. Burton, J.Fluorine.Chem., 1934, 25, 21-5.
8. D. Cook *et al*, Rubbercon 81, Int.Rubber Conf. 1981, 1 D5.1-D5. (Chem.Abs., 95: 116764t)
9. F. Swarts, Central blat, 1903, 1, 3.
10. T. Midgley, Jr., and A.L. Henne, Ind.Eng.Chem., 1930,22,542.
11. H.S. Booth *et al*, Ind.Eng.Chem., 1932, 24, 328.
12. H.S. Booth, *et al*, J.Amer.Chem.Soc., 1933, 55, 2231.
13. A.L. Henne and E.C. Ladd, J.Amer.Chem.Soc., 1936, 58, 402.
14. E.G. Locke, W.R. Brode and A.L.Henne, J.Amer.Chem.Soc. 1934, 56, 1726.
15. Farbwerke Hoechst, Netherlands Patent 302,391; June 24, 1964.
16. Farbenfabriken Bayer, British Patent 681,067; October 15,1952.
17. H. Madai, East German Patent 12,182, October 6, 1956.
18. L.B. Smith, C.B. Miller, U.S.Patent 2,753,379, April 14,1953.
19. F.B. Downing *et al*, U.S.Patent 2,480,560, August 30, 1949.
20. F.B. Skiles, U.S. Patent 2,674,631, April 6, 1954.
21. J.C. Hillyer and J.F.Wilson, U.S.Patent 2,471,525, ~~May~~ 31,1949.
22. A.L.Henne and C.J. Fox, J.Amer.Chem.Soc., 1954, 76, 479.
23. H. Gilman and R.G. Jones, J.Amer.Chem.Soc., 1943, 65, 2037.
24. D.A.Nelson, U.S.Patent 2,758,138, 1956, (Chem,Abs 51: 3654)

25. J.D. La Zerte *et al*, J.Amer.Chem.Soc., 1953, 75, 4525.
26. A. Fontana, Monte Fluos SPA, Personal Communication.
27. R.D.Chambers, Durham University Chem.Dept., Personal Commun.
28. "Fluorine in Organic Chemistry", R.D. Chambers, Wiley New York, 1973, Ch.2.
29. F.W. Stacey and J.F. Harris, Org.Reactions, 1983, 13, 150.
30. C. Walling and E.S. Huyser, Org.Reactions, 1963, 13, 91.
31. H. Singh and J.M. Tedder, J.Chem.Soc., 1966, 612.
32. J.M. Tedder and J.C. Walton, Prog.Reaction Kinetics, 1967 4, 53.
33. "Radicals", D.C. Nonhebel, J.M. Tedder and J.C. Walton, Cambridge University Press, 1979.
34. H.S. Eleuterio, U.S.Patent 2,958,685, 1960, (Chem.Abs., 55: 6041).
35. C.W. Wilson and E.R. Santee, J.Polym.Sci., 1965, 8, 97.
36. R.E. Naylor and S.W. Lasoski, J.Polym.Sci., 1960, 1, 44.
37. A.J. Lovinger and R.E. Cais, Macromolecules, 1984, 17, 1939.
38. R.E. Cais *et al*, Macromolecules, 1984, 17, 1932.
39. R.C. Ferguson, J.Amer.Chem.Soc., 1960, 32, 2416.
40. R.E. Florin *et al*, J.Research NBS, 1954, 53, 121.
41. C.W. Brown and E.R. Howels, Nature, 1954, 174, 549.
42. H.G. Bryce, J.Fluorine Chem., 1964, 5, 295.
43. R.E. Banks and R.N. Haszeldine, J.Oil.Chem.Assn., 1959, 42, 591.
44. J.N. Cox, B.A. Wright and W.W. Wright, J.Appl.Polym.Sci., 1964, 8, 2935.
45. J.H. Brown, Prog.Rubber.Technol., 1976, 39, 31.
46. A.Apotheker and P.J. Krusic, Ger.Offen., 2,612,360, (ca 85: 193894f).
47. W.S.Durrell *et al*, J.Polym.Sci., Part A, 1965, 3, 4065.
48. A.D. Gustav *et al*, British Patent 1,145,445, (ca 70:1070-906)
49. W.W. Smeigel, Die.Angewandte Makro.Chem., 1979, 76/77, 39.
50. "Encyclopedia of Polymer Science and Technology", R.P. Bruiger, Wiley, New York, 1970, 7, 204.

51. "Encyclopedia of Polymer Science and Technology", F.S.Cohen and P. Kraft, Wiley, New York, 1970, 14, 522.
52. S.M. Ognitz and C.J. Stutz, European Rubber Journal, June 1980.
53. T.M.Vial, Rubber.Chem.Tech., 1971, 44, 344.
54. C.P. Meyer, Chem.and Eng.News, 1978, 56, 20.
55. W.H. Sharkey, J.Macromol.Sci., Chem., 1967, 11, 291.
56. W.H. Sharkey, Adv.Polym.Sci., 1975, 17, 74.
57. "S-Triazines and Derivatives", E.M. Smolin and L.Rappaport, Interscience, New York, 1959, pp.215.
58. E. Dorfman *et al*, Rubber Chem.and Tech., 1966, 2, 1175.
59. G.A. Grindahl, W.X. Bajzer and O.E. Pierce, J.Org.Chem., 1967, 32, 603.
60. J.A. Young and R.L. Dressler, J.Org.Chem., 1967, 32, 2237.
61. H.C. Brown, J.Polym.Sci., 1960, 9, 44.
62. H.C. Brown and P.D. Schuman, J.Org.Chem., 1963, 28, 1122.
63. D.A. Barr and R.W. Haszeldine, J.Chem.Soc., 1955, 1881 and 1960, 1151.
64. D.A. Barr and R.W. Haszeldine, Nature, 1955, 175, 991.
65. J.B. Rose, U.S. Patent 3,065,214: 1962.
66. D.A. Barr *et al*, Proc.Chem.Soc., 1959, 230.
67. G.E. Griften and R.W. Haszeldine, Proc.Chem.Soc., 1959, 369.
68. J.B. Rose, British Patent 789,254, 1958.
69. "Fluoropolymers", K.L. Paciorek, ed. L.A. Wall, Wiley Interscience, New York, 1972, Ch.10.
70. A.L. Moran, D.B. Pattison, Rubber Age, 1971, 37, 103.
71. K.L. Paciorek, L.C. Mitchell and C.T. Lenk, J.Polym.Sci., 1960, 45, 405.
72. J.B. Finlay, A. Hallenbeck and J.D. MacLachlan, J.Elastomers Plast., 1978, 10, 3.
73. G. Kojima and H. Wachi, Rubber Chem.Tech., 1984, 51, 940.
74. G.A. Sankina *et al*, Kauch.Rezina, 1984, 9, 16.
75. K.L. Paciorek *et al*, J.Polym.Sci., 1962, 60, 141.
76. B.A. Merkl and P. Davis, Technical Report, ASD-TDE 62-30, Part II, Wright-Patterson Air Force Base, OHIO.

77. J.F. Smith and G.T. Perkins, J.Appl.Polym.Sci., 1961, 5, 460.
78. A. Voet, Macromol.Reviews, 1980, 15, 327.
79. M.J. Bro, J.Appl.Polym.Sci., 1959, 1, 310.
80. J.F. Smith, Rubber World, 1960, 142, 102.
81. J.D. Park, H.V. Holler and J.R. Locher, J.Org.Chem., 1960, 25, 990.
82. G.E. Decker, R.W. Wise and D. Guerry, Rubber Chem.Tech., 1963, 36, 451.
83. "Fluorine in Organic Chemistry", R.D. Chambers, John Wiley and Sons, 1973.
84. S. Andreo, J.Amer.Chem.Soc., 1964, 86, 2003.
85. W.D. Good *et al*, J.Phys.Chem., 1964, 63, 1133.
86. Jpn. Kokai Tokyo Koho KP 58,111,848.
87. G.H.Kalb *et al*, ACS Adv.Chemistry Series, 1973, 129, 13.
88. G.H. Kalb, R.W. Quartes and R.S. Graff, Appl.Polym. Symposia, 1973, 22, 127.
89. E.E. Schneider, J.Chem.Phys., 1955, 23, 978.
90. G. Kojima and Y. Tabata, J.Macromol.Sci.Chem., 1971, A5, 1087.
91. K. Makunchi, A. Masaharu and A. Toshihiko, J.Polym.Sci., Polym. Chem.Ed., 1976, 14, 617.
92. R.G. Spain *et al*, WADC Technical Report 55-492, Part VI.
93. K.L. Paciorek *et al*, J.Org.Chem., 1962, 27, 266.
94. K.L. Paciorek *et al*, J.Org.Chem., 1962, 27, 1015.
95. J.D. Park *et al*, J.Org.Chem. 1960, 25, 990.
96. P.J. Krusic and J.K. Kochi, J.Amer.Chem.Soc., 1971, 93, 846.
97. P. Meakin and P.J. Krusic, J.Amer.Chem.Soc., 1973, 95, 8185.
98. B.E. Smart *et al*, J.Amer.Chem.Soc., 1975, 96, 7385.
99. R.D. Chambers *et al*, Tetr.Lett., 1963, 619.
100. J. Hutchinson, Ph.D. Thesis, Durham University, 1961.
101. R.D. Chambers *et al*, Tetrahedron, 1964, 20, 497.
102. R.D. Chambers *et al*, Tetr.Lett., 1963, 619.
103. C.G. Krespan, Contribution 725, Central Research Dept., E.I. Du Pont de Nemours and Co. Ltd., Delaware.

104. Daikin Kogyo Co. Ltd., Jpn.Kokai Tokkyo Koho JP 58,192,838.
105. Jpn.Kokai Tokkyo Koho JP.60,123,333.
106. P. Tarrant, J.Fluorine Chem., 1984, 25, 41.
107. R.D. Chambers *et al* Perkin Trans.I, 1976, 2106.
108. R.D. Chambers *et al*, J.Chem.Soc., 1961, 733, 3779.
109. M. Hauptschein, M. Braid and F.E. Lawlor, J.Amer.Chem.Soc., 1958, 80, 846.
110. M. Hauptschein, M.Braid and F.E. Lawlor, J.Amer.Chem.Soc., 1957, 79, 2549.
111. R.N. Haszeldine, J.Chem.Soc., 1952, 4423.
112. M. Hauptschein, M. Braid and F.E. Lawlor, J.Amer.Chem.Soc., 1957, 79, 6248.
113. R.N. Haszeldine and E.G. Walaschewski, J.Chem.Soc., 1953, 75, 3607.
114. A.L. Henne, J.Amer.Chem.Soc., 1953, 75, 5750.
115. A.L. Henne, W. Postelneck, J.Amer.Chem. Soc., 1955, 77, 2334.
116. M. Hauptschein and J. Oesterling, J.Amer.Chem.Soc., 1960, 82, 2868.
117. R.N. Haszeldine *et al*, J.Chem.Soc., 1955, 3005.
118. R.N. Haszeldine, J.Chem.Soc., 1953, 3761.
119. H.C. Brown and A.B. Ash, J.Amer.Chem.Soc., 1955, 77, 4019.
120. D.E. Copp and J.M. Tedder, Int.J.Chem.Kinet., 1981, 103, 6937.
121. R.N. Haszeldine, J.Chem.Soc., 1953, 3761.
122. A.F. Benning and J.D. Park, U.S. Patent 2,490,764, 1949.
123. J.C. Amphlett and E. Whittle, Trans.Farad.Soc., 1968, 64, 2130.
124. R.D. Chambers, A.A. Lindley and P.D. Philpot, Israel.J. Chem., 1978, 17, 150.
125. "Annual Reports on NMR Spectroscopy", ed. G.A. Webb, Academic Press, 1980, Vol.10B.
126. J.L. Hahnfield and D.J. Burton, Tetr.Lett., 1975, 773.
127. W.H. Sharkey, Fluorine Chem.Revs., 1968, 2, 1.
128. N. Yoneda *et al*, Chem.Lett., 1983, 7, 1135.

129. D.B. Speight, Ph.D. Thesis, Durham University, 1974.
130. "Elimination Reactions", D.V. Banthorpe, Elsevier Publishing Coy., 1963.
131. "The Chemistry of the Carbon-Halogen Bond", R.A. More O'Ferrall, ed. S. Patai, Ch.9.
132. J.T. Maynard, J.Org.Chem., 1963, 28, 112.
133. R.D. Chambers and A.J. Palmer, Tetrahedron, 1969, 25, 4217.
134. See 124.
135. See 125.
136. R.N. Haszeldine, U.S. Patent 3,069,479: 1962.
37. R.D. Chambers, A. Fontana and M. Salisbury, Unpublished Results.
138. C.I. Gochenour and G.D. Kyker, U.S. Patent 2,436,357, Feb. 17, 1948.
139. H. Burger, R. Koplín and G. Pawelke, J.Fluorine Chem., 1984, 24, 457.
140. V.A. Petrov *et al*, Izv.Akad.Nauk SSSR, Ser. Khim., 1984, 2811. (ca 102:1486082).
141. M.V. Galakhov *et al*, Izv.Akad.Nauk SSSR, Ser.Khim., 1985, 306 (ca 103:22071w)
142. A. Fletcher, Ph.D. Thesis, Durham University, 1973.
143. G.A. Olah, R.D. Chambers and M.B. Comisarow, J.Amer. Chem.Soc., 1967, 89, 1268.
144. R.D. Chambers, R.S. Matthews and A. Parkin (nee Fletcher), J.Chem.Soc., Chem.Comm., 1973, 509.
145. "High Resolution Nuclear Magnetic Resonance Spectroscopy", J.W. Emsley, J. Feeney, L.H. Sutcliffe, Pergamon Press, 1966, Vol.2.
146. J. Feast, Chem.Ind., 1985, 263.
147. A.J. Dias and T.J. McCarthy, J.Polym.Sci., Polym.Chem.Ed. 1985, 23, 1057.
148. A.E. Bayliff, M.R. Bryce, R.D. Chambers and R.S. Matthews, J.Chem.Soc., Chem.Comm., 1975, 1018.
149. M. Seabury, Unpublished Results.
150. W.R. Dolbie and C.R. Burkholder, J.Org.Chem., 1984, 49, 1518.
151. M.B. Bryce, J.R. Kirk and R.D. Chambers, J.Chem.Soc., Perkin Trans.I, 1982, 673.

152. T.J. de Boer and H.J. Backer, Org.Synth., 1954, 34, 96.
153. S.A. Markarian and H. Fischer, J.Chem.Soc., Chem.Comm., 1979, 1055.
154. "Mass Spectroscopy for Chemists and Biochemists", M.E.Rose and R.A.W. Johnstone, Cambridge University Press, 1982.
155. R.N. Haszeldine *et al*, J.Chem.Soc., Perkin Trans.I, 1976, 1170.
156. R.E. Banks, F. Cuthbertson and W.K.R. Musgrave, Anal. Chem.Acta., 1955, 13, 442.
157. "Spectrometric Identification of Organic Compounds", J.Wiley and Sons, New York, 3rd Ed., 1974.
158. D.A. Long and E.L. Thomas, Trans.Faraday Soc., 1963, 69, 1026.

